

Thermal Conductivity of the Elements

C. Y. Ho, R. W. Powell, and P. E. Liley

Thermophysical Properties Research Center, Purdue University, West Lafayette, Indiana 47906

This is the abridged version of a comprehensive volume on the thermal conductivity of the elements. It contains recommended reference values resulting from critical evaluation, analysis, and synthesis of all the available data. It also gives estimated values for those elements for which no thermal conductivity data are available. Thus, the work provides recommended or estimated thermal conductivity values for all the elements over the full temperature ranges where experimental data are available or reliable extrapolations or estimations can be made. The results on each element are presented in both graphical and tabular forms. Summary graphs arranged by group in the periodic table are also given.

Key words: Conductivity; critically evaluated data; data compilation; elements; reference data; thermal conductivity; transport properties.

Contents

	Page		Page
1. Introduction.....	281	Figure 6. Thermal Conductivity of Elements of Groups IV A and IV B.....	292
2. General Procedures for the Evaluation, Correlation, and Estimation of Thermal Conductivity.....	281	Figure 7. Thermal Conductivity of Elements of Groups V A and V B.....	293
2.1 Theoretical background.....	281	Figure 8. Thermal Conductivity of Elements of Groups VI A and VI B.....	294
2.2 Data Evaluation.....	286	Figure 9. Thermal Conductivity of Elements of Groups VII A and VII B.....	295
2.3 Summary Graphs.....	287	Figure 10. Thermal Conductivity of Elements of Group VIII.....	296
3. Specific Considerations Concerning the Body of Data.....	302	Figure 11a. Thermal Conductivity of Elements of the Rare Earth Group.....	297
4. Acknowledgments.....	419	Figure 11b. Thermal Conductivity of Elements of the Rare Earth Group.....	298
5. References.....	420	Figure 12. Thermal Conductivity of Elements of the Actinide Group.....	299
		Figure 13. Thermal Conductivity of Graphites..	300
		Figure 14. Thermal Conductivity of the Elements at 300 K.....	301

List of Tables and Figures

Table 1. Constants for Low-Temperature Thermal Conductivity Calculations Using Equations (7) and (8).....	284
Table 2. Conversion Factors for Units of Thermal Conductivity.....	303
Figure 1. Reduced Thermal Conductivity as a Function of Reduced Temperature for Twenty-two Metals at Cryogenic Temperatures.....	283
Figure 2. Thermal Conductivity of Elements of Group 0.....	288
Figure 3. Thermal Conductivity of Elements of Groups I A and I B.....	289
Figure 4. Thermal Conductivity of Elements of Groups II A and II B.....	290
Figure 5. Thermal Conductivity of Elements of Groups III A and III B.....	291

Thermal Conductivity of the Elements

Aluminum.....	305
Antimony.....	306
Argon.....	307
Arsenic.....	309
Barium.....	310
Beryllium.....	311
Bismuth.....	312
Boron.....	313
Bromine.....	314
Cadmium.....	315
Calcium.....	316
Carbon.....	317
Carbon (Amorphous).....	317

	Page		Page
Carbon—Continued		Platinum.....	379
Diamond.....	318	Plutonium.....	380
Graphite.....	319	Potassium.....	381
Acheson Graphite.....	319	Praseodymium.....	382
AGOT Graphite.....	320	Promethium.....	383
ATJ Graphite.....	321	Radium.....	384
AWG Graphite.....	322	Radon.....	385
Pyrolytic Graphite.....	323	Rhenium.....	386
875S Graphite.....	324	Rhodium.....	387
890S Graphite.....	325	Rubidium.....	388
Cerium.....	326	Ruthenium.....	389
Cesium.....	327	Samarium.....	390
Chlorine.....	328	Scandium.....	391
Chromium.....	330	Selenium.....	392
Cobalt.....	331	Silicon.....	394
Copper.....	332	Silver.....	395
Dysprosium.....	333	Sodium.....	396
Erbium.....	334	Strontium.....	397
Europium.....	335	Sulfur.....	398
Fluorine.....	336	Tantalum.....	399
Gadolinium.....	337	Technetium.....	400
Gallium.....	338	Tellurium.....	401
Germanium.....	339	Terbium.....	402
Gold.....	340	Thallium.....	403
Hafnium.....	341	Thorium.....	404
Helium.....	342	Thulium.....	405
Holmium.....	344	Tin.....	406
Hydrogen.....	345	Titanium.....	407
Deuterium.....	348	Tungsten.....	408
Tritium.....	350	Uranium.....	410
Indium.....	351	Vanadium.....	411
Iodine.....	352	Xenon.....	412
Iridium.....	353	Ytterbium.....	414
Iron.....	354	Yttrium.....	415
Armco Iron.....	355	Zinc.....	416
Krypton.....	356	Zirconium.....	417
Lanthanum.....	358	Actinium.....	418
Lead.....	359	Americium.....	418
Lithium.....	360	Astatine.....	418
Lutetium.....	361	Berkelium.....	418
Magnesium.....	362	Californium.....	418
Manganese.....	363	Curium.....	418
Mercury.....	364	Einsteinium.....	418
Molybdenum.....	365	Fermium.....	418
Neodymium.....	366	Francium.....	418
Neon.....	367	Lawrencium.....	418
Neptunium.....	369	Mendelevium.....	418
Nickel.....	370	Nobelium.....	418
Niobium.....	371	Polonium.....	418
Nitrogen.....	372	Protactinium.....	418
Osmium.....	374	Element 104.....	418
Oxygen.....	375	Element 105.....	418
Palladium.....	377	Element 106.....	418
Phosphorus.....	378	Element 118.....	418

1. Introduction

The purpose of this work is to present and discuss the available data and information on the thermal conductivity of each element of the periodic table, to critically evaluate, analyze, and synthesize the data, and to make recommendations for the most probable values of its thermal conductivity over a wide temperature range.

The work is published in two companion versions: a comprehensive volume [1],¹ which is to be published as a supplement to the *Journal of Physical and Chemical Reference Data*, and this abridged version. In addition to the recommended and estimated thermal conductivity values for the elements, the comprehensive volume presents the original data, specimen characterization, and measurement information for the 5200 sets of raw data which were extracted from the primary literature. It contains also a detailed discussion for every element, reviewing the individual pieces of available data and information together with the considerations involved in arriving at the final assessment and recommendations and the theoretical guidelines or semi-empirical correlations on which the critical evaluation, analysis, and synthesis are based. The complete bibliographic citations for the 1630 references are also included. This abridged version of the comprehensive volume is designed for the practical user of data and contains only the recommended and estimated thermal conductivity values.

The thermal conductivity values given cover the widest possible temperature ranges and are for the purest form of each element for which measurements have been made. In the one instance of iron, values for Armco iron, a form of lower purity much used as a thermal conductivity reference material, have also been included.

Experimental thermal conductivity data are available in the world literature for 82 elements and estimated values for four other elements. The elements for which experimental data are lacking comprise all elements having an atomic number above 94 and twelve others: namely, actinium, astatine, barium, calcium, europium, francium, polonium, promethium, protactinium, radium, radon, and strontium. For all these elements estimated values have been included in this work at least for normal temperature.

The original papers upon which this work is based were retrieved through a continuing, comprehensive monitoring of the world literature carried out by the Thermophysical Properties Research Center (TPRC). The cut-off date for literature inclusion in this work was January 1971. The authors are keenly aware of the possibility of omissions or errors which may be encountered in a work of this scope. It is hoped that these faults will not be judged too harshly and that we will receive the benefit of suggestions regarding references

omitted, improvements in presentation, and, most important, any inadvertent errors.

Inherent in the character of this work is the fact that we have drawn most heavily upon the scientific literature and feel a debt of gratitude to the authors whose results have been used. While their often discordant results have caused as much difficulty in reconciling their findings, we consider this to be our challenge and our contribution to the negative entropy of information as an effort is made to create from the randomly distributed data a more orderly state.

2. General Procedures for the Evaluation, Correlation, and Estimation of Thermal Conductivity

In this section it is proposed to outline some of the methods of treatment that have been employed and which are common to many of the elements and to group together some of the resulting thermal conductivity values with a view to revealing any general trends which might be of assistance in the prediction of values for other elements or in data extrapolation.

2.1. Theoretical background

In metals the principal carriers of heat are electrons and lattice waves, and it is commonly assumed that the total thermal conductivity

$$k = k_e + k_g \quad (1)$$

where k_e and k_g are the thermal conductivity components due to the transport of heat respectively by the electrons and by the phonons or lattice waves. In a very pure metal, k_g is extremely small compared with k_e and in the majority of cases it can practically be neglected.

The electronic component is given by

$$k_e = W_e^{-1} = (W_0 + W_i)^{-1} \quad (2)$$

where W_e is the electronic thermal resistivity, W_0 is the residual electronic thermal resistivity due to scattering of electrons by static imperfections, and W_i the intrinsic electronic thermal resistivity due to electron-phonon interactions.

The electrical resistivity is likewise composed of a residual and an intrinsic component

$$\rho = \rho_0 + \rho_i$$

The residual thermal and electrical resistivities are related by the Wiedemann-Franz-Lorenz law

$$\frac{\rho_0}{W_0 T} = L_0$$

¹ Numbers in brackets refer to literature references in Section 5.

hence

$$W_0 = (\rho_0/L_0)T^{-1} = \frac{\beta}{T} \quad (3)$$

where $\beta = \rho_0/L_0$, L_0 is the theoretical Lorenz number ($L_0 = 2.443 \times 10^{-8} V^2 K^{-2}$) and T the absolute temperature. The intrinsic thermal and electrical resistivities are related by the Wiedemann-Franz-Lorenz law only in the high-temperature limit, while at lower temperatures

$$\frac{\rho_i}{W_i T} = L_i$$

is generally less than L_0 . In the limit of low temperatures

$$L_i = \delta(T/\theta)^2$$

where θ is the Debye temperature and the coefficient δ depends on the topology of the Fermi surface.

The derivation of theoretical expressions for W_i and ρ_i involves the solution of the Bloch integral equation [2] which is very complicated. Explicit expressions have been obtained only for the very simplest model, first by Wilson [3] and later by several others [4-13]. The general form of their results is the same. In the low-temperature limit

$$\begin{aligned} \rho_i &\propto T^5 \\ W_i &\propto T^2 \end{aligned} \quad (4)$$

and

$$L_i = \rho_i/W_i T = 7.8 N_a^{-2/3} (T/\theta)^2$$

where N_a is the number of conduction electrons per atom. From equations (2-4), the low-temperature electronic thermal resistivity can therefore be written in the form

$$W_e = \alpha T^2 + \beta/T.$$

Thus

$$k_e = \frac{1}{\alpha T^2 + \beta/T}. \quad (5)$$

Equation (5) has been extensively compared with low-temperature experimental data for high-purity metals whose k_g is negligibly small, and disagreements have been found [14-16] in that the power of T for most metals is not 2 but greater and the coefficient α is not a constant for a metal. Considering the temperature dependence of the coefficient α and the interaction between intrinsic and residual thermal resistivities, Cezairliyan [14] and Cezairliyan and Touloukian [15, 16] have modified equation (5) to become

$$k_e = \frac{1}{\alpha' T^n + \beta/T} \quad (6)$$

or, assuming k_g being negligible, simply

$$k = \frac{1}{\alpha' T^n + \beta/T} \quad (7)$$

where

$$\alpha' = \alpha'' \left(\frac{\beta}{n\alpha''} \right)^{(m-n)(m+1)} \quad (8)$$

and α'' , m , and n are constants for a metal. The value of n lies between 2 and 3 for most metals.

At low temperatures the thermal conductivity of a metal has a maximum value k_m at a corresponding temperature T_m . The purer the sample, the higher is the maximum conductivity and the lower is the temperature at which the maximum occurs. Physically, the constant m in equation (8) is the absolute value of the slope of the straight line (in a logarithmic plot) passing through the maxima of the thermal conductivity curves of different samples of different purity and imperfection, hence different ρ_0 and β .

Figure 1, reproduced from Cezairliyan's treatise shows how, by plotting a reduced thermal conductivity k/k_m (denoted by k^*) against the corresponding reduced temperature T/T_m (denoted by T^*), the data then (1962) available for 22 metals (some 1000 data points for 83 samples) were found to approximate to a single curve

$$k^* = \left[\frac{1}{3} (T^*)^2 + \frac{2}{3T^*} \right]^{-1}. \quad (9)$$

The standard deviation of points from this curve was calculated as 0.032.

In this work for most of the metallic elements whose k is negligibly small, equations (7) and (8) have been used to fit experimental data for deriving recommended thermal conductivity values at temperatures below about 1.5 T_m . For a number of metallic elements the values of the constants m , n , and α'' to be used in equations (7) and (8) for low-temperature thermal conductivity calculations are given in table 1.

In equations (7) and (8), the only parameter is β , and each low-temperature thermal conductivity curve is uniquely determined by its value. An experimental value of β is obtainable by fitting equations (7) and (8) to the measured thermal conductivity data at temperatures below T_m . Using equations (7) and (8) and the constants for each of the metallic elements given in table 1, the low-temperature thermal conductivity of a particular sample can be calculated when the appropriate value of β is used. Different values of β give a family of thermal conductivity curves for each metallic element and a family of recommended curves could have been generated in this way for each metallic element.

In this work, at low temperatures only one recommended curve for one particular sample has been generated and this usually relates to the lowest value of β for the purest sample for which a thermal conductivity measurement has been made. For generating other curves for other samples equations (7) and (8) and the recommended constants of table 1 may be used. It often happens that electrical resistivity investigations

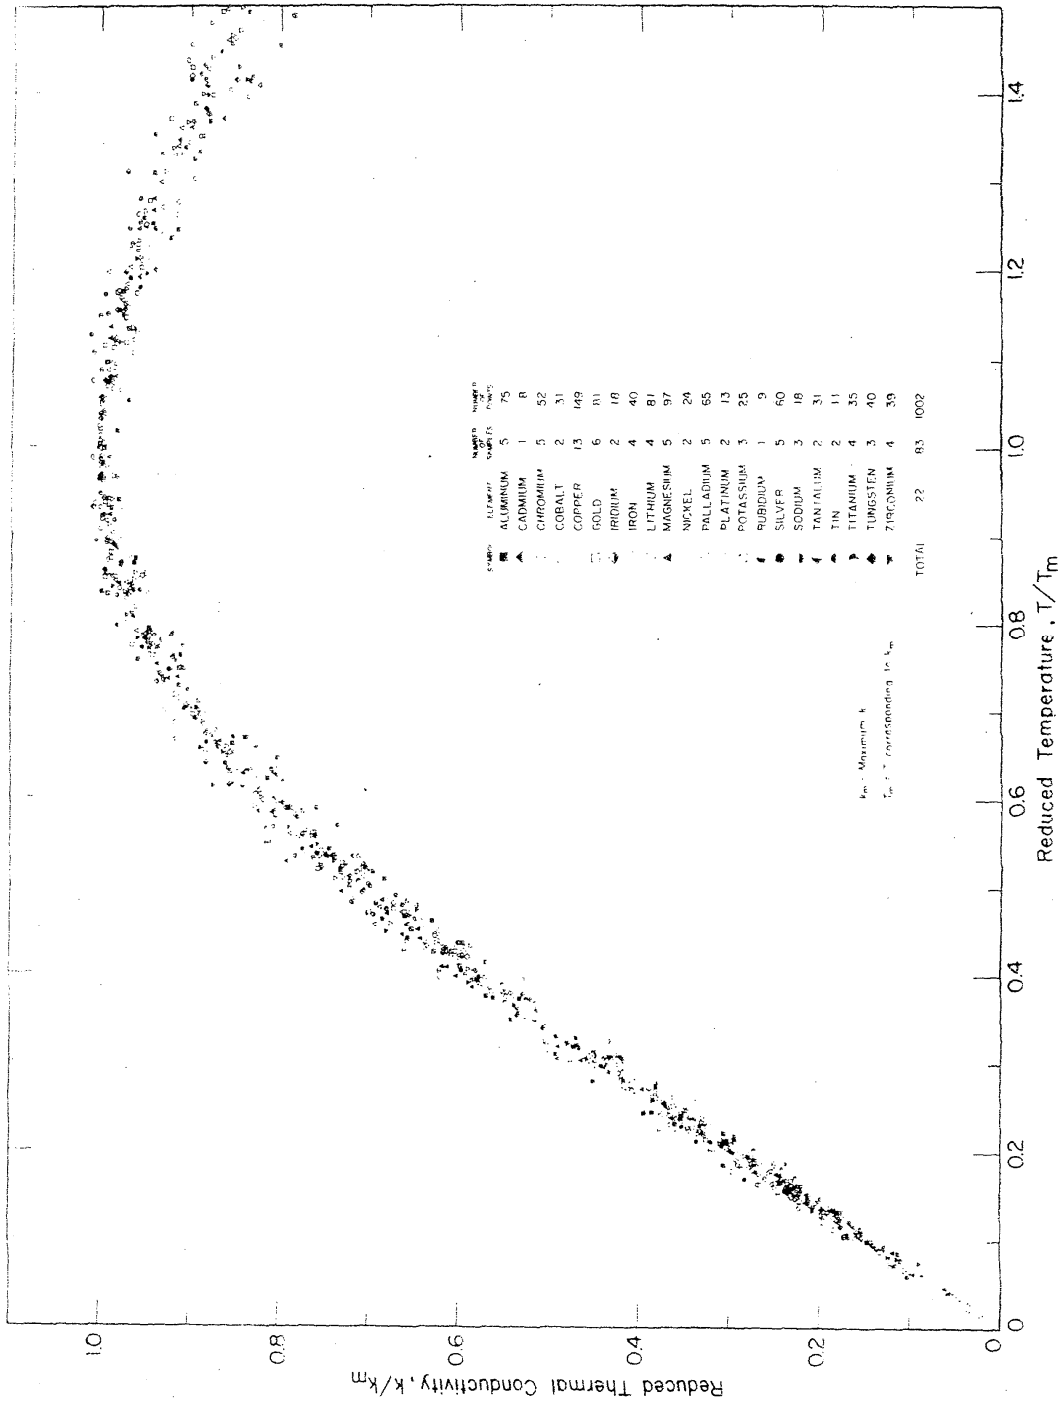


FIGURE 1. REDUCED THERMAL CONDUCTIVITY AS A FUNCTION OF REDUCED TEMPERATURE FOR TWENTY-TWO METALS AT CRYOGENIC TEMPERATURES

TABLE 1. CONSTANTS FOR LOW-TEMPERATURE THERMAL CONDUCTIVITY CALCULATIONS USING EQUATIONS (7) AND (8)

Element	m	n	$\alpha' \times 10^4$
Aluminum	2.62	2.00	0.0479
Cadmium			
(// to c-axis)	5.00	4.50	0.0468
(\perp to c-axis)	5.00	4.50	0.0468
(polycrystalline)	5.00	4.50	0.0468
Chromium	2.20	2.00	0.592
Cobalt	2.20	2.10	0.540
Copper	2.63	2.21	0.0423
Gallium			
(// to a-axis)	2.78	2.00	2.04
(// to b-axis)	2.78	2.00	0.806
(// to c-axis)	2.78	2.00	6.57
Gold	2.46	2.00	0.460
Indium	3.00	2.00	3.50
Iridium	4.40	3.00	0.000272
Iron	2.20	2.00	0.517
Lead	3.50	3.00	4.12
Lithium	2.25	2.00	0.774
Magnesium	2.10	2.00	0.627
Molybdenum	3.20	2.60	0.00967
Nickel	2.60	2.00	0.192
Niobium	2.00	2.00	6.21
Osmium	5.80	3.00	0.0000379
Palladium	2.40	2.00	1.54
Potassium	2.10	2.00	18.0
Rhenium	3.30	2.20	0.0656
Rhodium	3.00	2.80	0.0132
Ruthenium	5.80	2.60	0.0000321
Silver	2.75	2.20	0.0730
Sodium	2.13	2.00	2.89
Tantalum	2.54	2.00	1.39
Thallium	2.80	2.00	26.2
Thorium	2.80	2.79	1.75
Titanium	2.90	2.30	0.188
Tungsten	2.80	2.40	0.0539
Zinc	3.40	3.00	0.0750
Zirconium	2.40	2.00	3.99

have included purer samples yielding much lower values for β , but to use these values seems unwise at present as some doubt exists as to the validity of this simple treatment for samples of much greater purity, especially for transition metals. There is some evidence [17-19] that electron-electron scattering may become important for exceedingly high-purity samples and necessitate one additional term γT such that

$$k = [\alpha T^m + \beta T^{-1} + \gamma T]^{-1}. \quad (10)$$

Also, for many of the elements available data are insufficient to determine the constants m , n , and α' of equation (8).

A further complication may arise with metallic samples of very high purity in that boundary scattering can become important and render the thermal conductivity at very low temperatures dependent on the size of sample or on that of the individual crystallites of which it is composed. Since the late 1930's, see for instance the work of Casimir [20], size dependence has been known for the thermal conductivity of nonmetallic crystals but measurements by Olsen and Wyder [21] and by Boughton and Yaqub [22] have more recently directed attention to the influence of crystal size on the electronic thermal conductivity of a metal of sufficiently high physical and chemical purity. Isotopic content is another factor that has been shown to influence the thermal conductivity at low temperatures. See for instance the work on an isotopically enriched germanium by Geballe and Hull [23], on tellurium by Oskotskii et al. [24], and on solid helium by Berman et al. [25] (see also [26]).

As the temperature rises from the liquid-helium temperature region, the value of the Lorenz function falls quite appreciably to a minimum, but near the Debye temperature it again tends asymptotically towards the theoretical value (see, e.g. Wilson [27], Makinson [4]). For some metals including the transition metals definitely higher values of the Lorenz function may be attained, but the excess seldom exceeds about 30 percent. It follows that in the region from about normal to high temperatures the Lorenz function is generally reasonably close to the theoretical value, and for a particular metal follows a fairly predictable departure curve. Thermal conductivity values can then be calculated from the derived, assumed, or experimentally determined Lorenz function values as a function of temperature and from the measured electrical resistivity data. Considerable use of the Lorenz relationship has therefore been made, both when analyzing thermal conductivity data in the above-normal temperature region and when attempting to make estimations or extrapolations in this range.

For elements such as gallium and yttrium, whose transport properties are strongly anisotropic, uncertainties are associated with the derivation of values from single crystal data that would apply to a polycrystalline sample.

Consider an orthorhombic crystal, such as that of gallium, for which k_a , k_b , and k_c are the thermal conductivity values for the three main crystal axes a , b , and c , and k_p is the thermal conductivity of the polycrystal. By considering the conductivities to be additive, Voigt [28] showed that

$$k_p = \frac{1}{3} (k_a + k_b + k_c). \quad (11)$$

If however the thermal resistivities are considered to be additive, which Hall, Legvold, and Spedding [29] regarded to be preferable in the case of rods of yttrium, then

$$\frac{1}{k_p} = \frac{1}{3} \left(\frac{1}{k_a} + \frac{1}{k_b} + \frac{1}{k_c} \right) \quad (12)$$

or

$$k_p = \frac{3k_a k_b k_c}{k_a k_b + k_a k_c + k_b k_c}. \quad (13)$$

For gallium at 300 K, $k_a = 0.406$, $k_b = 0.883$, and $k_c = 0.159 \text{ W cm}^{-1} \text{ K}^{-1}$. Hence the values of k_p according to equations (11) and (12) are respectively 0.483 and $0.304 \text{ W cm}^{-1} \text{ K}^{-1}$, and differ by some ± 25 percent from the mean value of $0.393 \text{ W cm}^{-1} \text{ K}^{-1}$. A more recent treatment, in which Hashin and Shtrikman [30] used a variational method, shows that for the case where $k_c < k_a < k_b$

$$\frac{k_b(4k_b^2 + 8k_b k_a + 8k_c k_b + 7k_a k_c)}{16k_b^2 + 5k_b k_a + 5k_c k_b + k_a k_c} > k_p > \frac{k_c(4k_c^2 + 8k_c k_a + 8k_c k_b + 7k_a k_b)}{16k_c^2 + 5k_c k_a + 5k_c k_b + k_a k_b} \quad (14)$$

which leads to extreme values of 0.444 and $0.377 \text{ W cm}^{-1} \text{ K}^{-1}$ for k_p in the case of gallium at 300 K. The treatment embraces a narrower ($\pm 8\%$) range of values and gives a mean of $0.410 \text{ W cm}^{-1} \text{ K}^{-1}$ which happens to be only about 1 percent greater than k_a . In this instance the value of k_a has been taken as representing approximately the thermal conductivity of polycrystalline gallium, but it is clear that more attention could well be devoted both experimentally and theoretically to this problem. Electrical conductivity would behave similarly and this property is likely to be measurable with greater accuracy, although high accuracy would not be so necessary with the large differences indicated for gallium. A practical difficulty could however arise in this instance from the ease with which gallium solidifies in the single crystal form, and the difficulty experienced so far in preparing truly polycrystalline samples of this metal.

In this work, the mean of the values given by equations (10) and (11) has been adopted as the value for a polycrystalline sample of an element of large anisotropy.

In connection with the thermal conductivity of molten metals, reference will frequently be made to estimated values that are due to Grosse [31, 32]. These values have been derived from the melting to the critical point using the equation $k=L_0\sigma T$ with derived values for the electrical conductivity, σ , and usually assuming the theoretical Lorenz number, L_0 , to hold throughout the range. To derive an expression for the electrical conductivity, Grosse has proposed an equation of the form of a simple equilateral hyperbola [33]

$$(\sigma' + b)(T' + b) = a \quad (15)$$

where the reduced electrical conductivity $\sigma' = \sigma_T/\sigma_f$, the reduced temperature $T' = (T - T_f)/(T_c - T_f)$, σ_f is the electrical conductivity of the molten metal at the melting point, and σ_T is the electrical conductivity at a temperature T between T_f , the melting point, and T_c , the critical temperature. The quantities a and b are constants. At T_c both σ and k are assumed to be zero.

Since these predictions were made, increasing uncertainty has developed as to the Lorenz function of molten metals and its variation with temperature. Previous work, for instance of Powell [34], had indicated the Lorenz function to approximate to the theoretical value, as was assumed by Grosse [31, 32], but according to the work of Filippov [35] on tin and lead and some other recent measurements [36, 37] the Lorenz function continues to decrease with increase in temperature to values that are well below L_0 . This uncertainty needs resolving and, pending confirmation and theoretical support for the lower values, values closer to those of Grosse have provisionally been adopted in the present work.

2.2. Data Evaluation

The data analysis and synthesis employed in this work have included critical evaluation of the validity and accuracy of available data and related information, resolution and reconciliation of disagreement in conflicting data, correlation of data in terms of various parameters (sometimes in reduced forms using the principle of corresponding states), curve fitting with theoretical or empirical equations, and comparison of resulting data with theoretical predictions or with results derived from semi-theoretical relationships or from generalized empirical correlations. Besides critical evaluation and analysis of the existing data, thermodynamic, kinetic, or statistical mechanical principles and semiempirical techniques have been employed to fill gaps and to extrapolate existing data so that the resulting recommended values are internally consistent and cover as wide a range of the controlling parameters as possible.

In the critical evaluation of the validity and uncertainty of a particular set of data, say, the thermal conductivity of a solid substance, the temperature dependence of the thermal conductivity has been

examined and any unusual dependence or anomaly carefully investigated, the experimental technique reviewed to see whether the actual boundary condition in the experiment agree with those assumed in the theory, and the author's estimations of uncertainties checked to ensure that all the possible sources of errors have been considered. For a steady-state absolute measurement of the thermal conductivity of a solid specimen, for example, the sources of errors may include the uncertainty in the measurements of specimen dimensions and of the distances between points of temperature measurements; the uncertainty due to the effect of thermal expansion; the uncertainty in determining the power input to the specimen heater; the uncertainty in determining the heat gains or losses to or from the specimen due to direct radiation interchange or to conduction through the surrounding insulation, along the electric leads, and along the thermocouple wires and the ceramic insulating tubings or beads; the uncertainty in temperature measurements due to poor thermocouple calibration, poor thermocouple contact, poor sensitivity of the measuring circuits, and temperature drift; the uncertainty due to thermal contact resistance; the uncertainty for measurements at elevated temperatures due to thermocouple contamination, specimen oxidation, or reaction of specimen with apparatus components; etc. In a comparative measurement, additional uncertainties may come from the conductivity mismatch between the specimen and the reference sample(s), from the additional interfacial thermal contact resistance, and from the additional uncertainty in the conductivity of the reference sample (especially, if the conductivity values of the "reference" sample are blindly taken from a handbook). For a nonsteady-state measurement, large uncertainty may result if the density and specific heat values are taken from the literature and not directly measured on the specimen for which the thermal diffusivity data are obtained. The above-mentioned and other possible sources of errors have been carefully considered in this work.

Many authors have included detailed error estimates in their published papers, and from these it is possible to evaluate the uncertainty for a particular method. However, experience has shown that the uncertainty estimates of most authors are unreliable. In many cases the difference between the results of two sets of data is much larger than that given by the sum of their stated uncertainties. Cases even occur where measurements reported to be accurate to within 1 or 2 percent differ from each other by more than 100 percent. In these cases either the actual error must greatly exceed its estimated value, or the author was unaware of the additional sources of error, or there must be essential unrecorded sample differences.

Besides evaluating and analyzing individual data sets, correlation of data in terms of various relevant parameters is a valuable technique that is frequently used in

data analysis. These parameters may include purity, composition, residual electrical resistivity or electrical resistivity ratio (if a metal), density or porosity, hardness, crystal axis orientation, degree of cold working, degree of heat treatment, etc. Applying the principle of corresponding states, reduced property values may be correlated with reduced temperature and other reduced parameters. Certain properties of the elements may also be correlated with the atomic numbers of the elements in the periodic system. Examples are critical temperatures, critical pressures, critical volumes, and atomic volumes at 0 K. Wherever appropriate, such correlation techniques have been applied to the thermal conductivity of the elements in the present work.

Several properties of the same material can also be cross-correlated. For example, thermal conductivity, specific heat, and density can be correlated with thermal diffusivity, and viscosity and specific heat of a gas can be correlated with thermal conductivity through the Chapman-Enskog theory or through the experimental Prandtl number. For a fluid, the property of the saturated liquid may also be correlated with that of the saturated vapor.

For meaningful data correlation, the information on specimen characterization is very important, especially for solid specimens. A full description of a solid specimen should include, whenever applicable, the following: purity or chemical composition, carrier concentration; type of crystal, crystal axis orientation for a single crystal; microstructure, grain size, preferred grain orientation, pore size and shape and orientation, inhomogeneity and additional phases for a polycrystalline specimen; specimen shape and dimensions, method and procedure of fabrication; thermal history and cold work history, heat treatment, mechanical, irradiative, and other treatments; manufacturer and supplier, stock number, and catalog number; test environment, degree of vacuum or pressure, heat flow direction, strength and orientation of an applied magnetic field; pertinent physical properties such as density, porosity, hardness, electrical resistivity (residual, ratio, and temperature variations), Lorenz function, transition temperature, etc.; and reference material and its property values for a comparative method of measurement. Data (no matter how accurate) on poorly characterized materials can hardly be analyzed or used for data correlation. It has been found in this and other studies that the specimen purity or composition reported by the author is often unreliable. This is because in many cases the stated purity or composition is the result of ladle analysis which the author obtained from the company who supplied the specimen and it can at best represent only the nominal purity or composition. In other cases there is a strong tendency for only certain elements to be covered by a chemical analysis, which could miss other quite important constituents.


Besides specimen characterization, a full description of experimental details should, of course, be given by


the author in order that his data can be meaningfully evaluated and fully utilized. Sometimes, as an initial method of evaluating the quality of a paper, consideration has been given to the amount of experimental details reported in the paper. Lack of experimental details has led to the results being given less weight.


In estimating the degree of uncertainty of our recommended values for the various ranges of temperature, it is apparent from the above discussion that only for the few much studied materials has it been possible to place close error limits that can be considered reliable. For the less well studied materials, wider limits of uncertainty are generally given; these are based on other factors and considerations such as general knowledge of the worker, the accuracy of measurements of other materials using the same or similar apparatus, etc. The estimated uncertainty also takes into consideration behavior of the material itself. For a well-behaved material narrower limits are given when the temperature dependence is predictable from theoretical considerations or from empirical correlations. For an ill-behaved material or a material with phase or magnetic transformation, such as the rare earths, the estimated uncertainties are greater. For the recommended values of the thermal conductivity of fluids, the uncertainty estimation is based on the degree of agreement of our values with those proposed by other experimental or analysis specialists, coupled with a more personal opinion of the experimental accuracy of the existing measurement techniques. Finally, the scatter around the recommended value of those experimental points considered reliable has been included in the uncertainty estimates.


2.3 Summary Graphs


With a view to bringing out any similarities or differences between the proposed values for the elements of a particular group of the periodic table, these values for all the elements of each group have been plotted in figures 2 to 13, which show some of the generalizations for the property of thermal conductivity that were mentioned at the beginning of this section. These figures may prove helpful when making estimations to temperatures not covered in the sections which follow. In figure 14 the thermal conductivity of each element at 300 K is plotted against the atomic number of the element. A fairly definite pattern can be traced, and this has been of assistance in deriving estimated values for certain elements for which no information is available. These include actinium, francium, and the trans-plutonium elements. Estimated values for barium, calcium, europium, polonium, protactinium, and strontium have also been based on electrical resistivity data, and those for radon are based mainly on a generalized correlation by Owens and Thodos [38]. The value for radium comes from collected data by Samsonov [39], and is attributed to Chirkin [40], but no details are given.

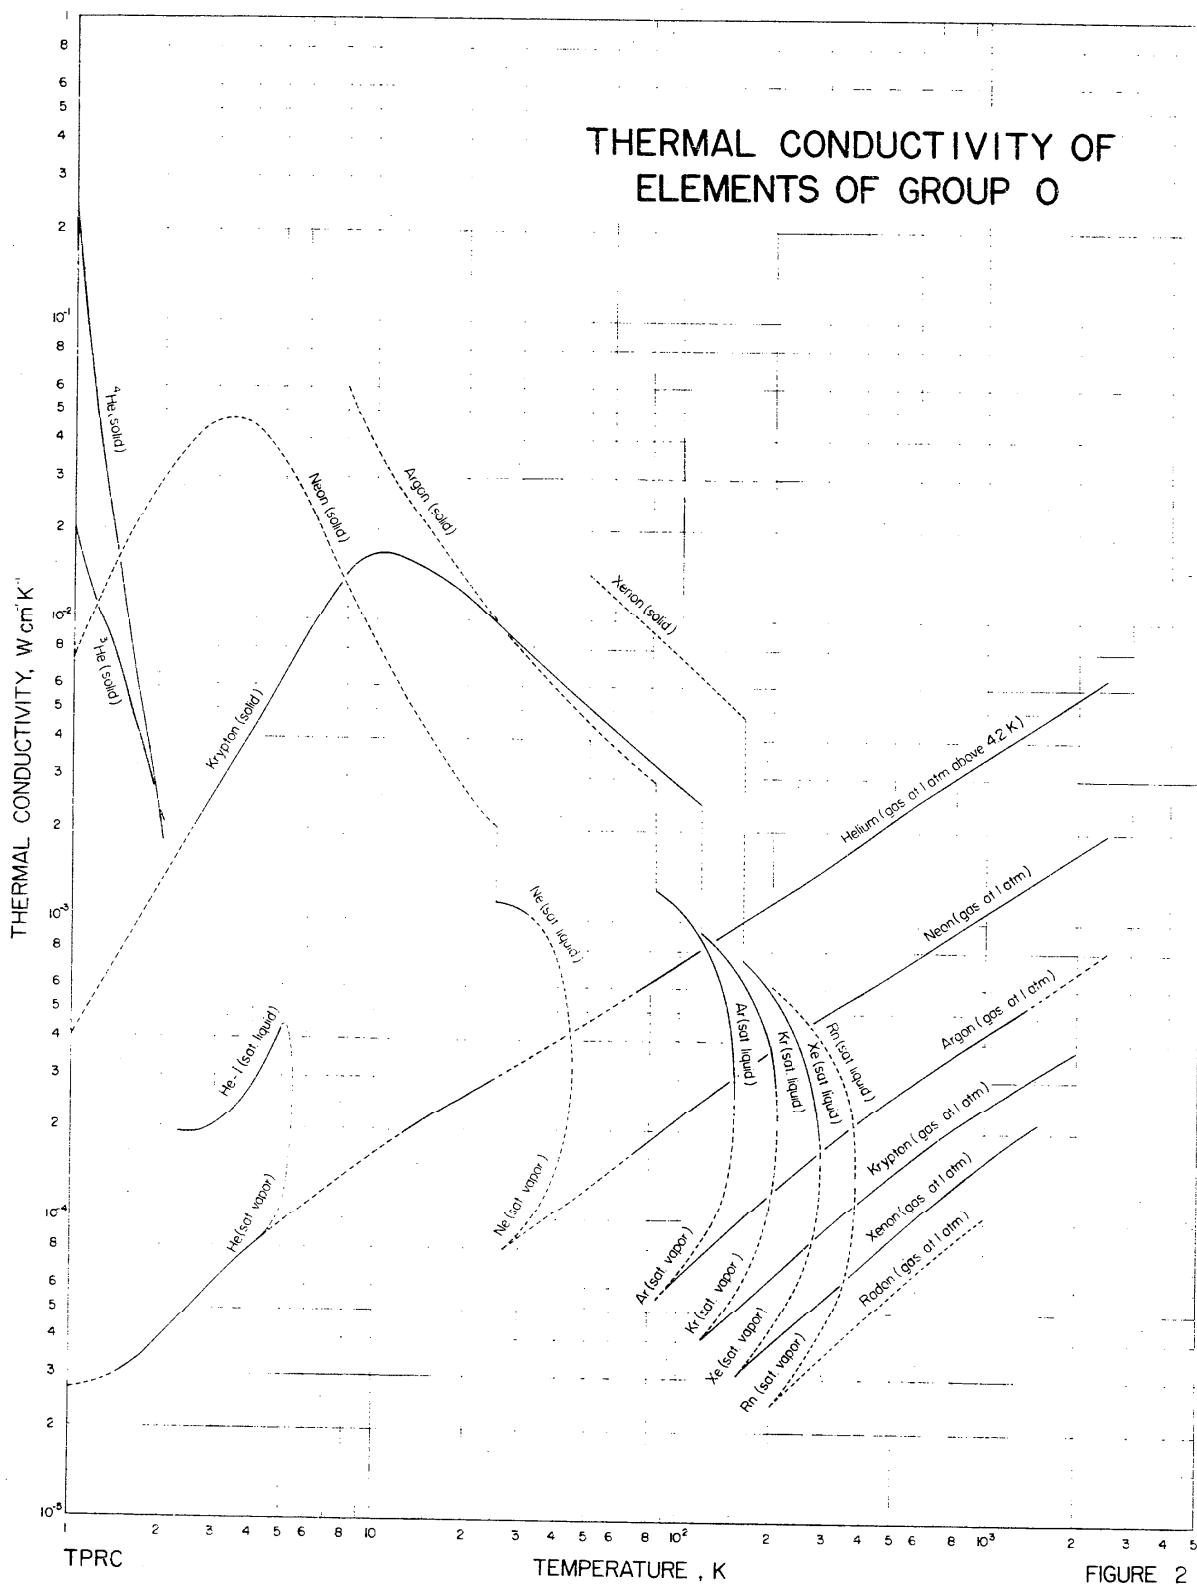

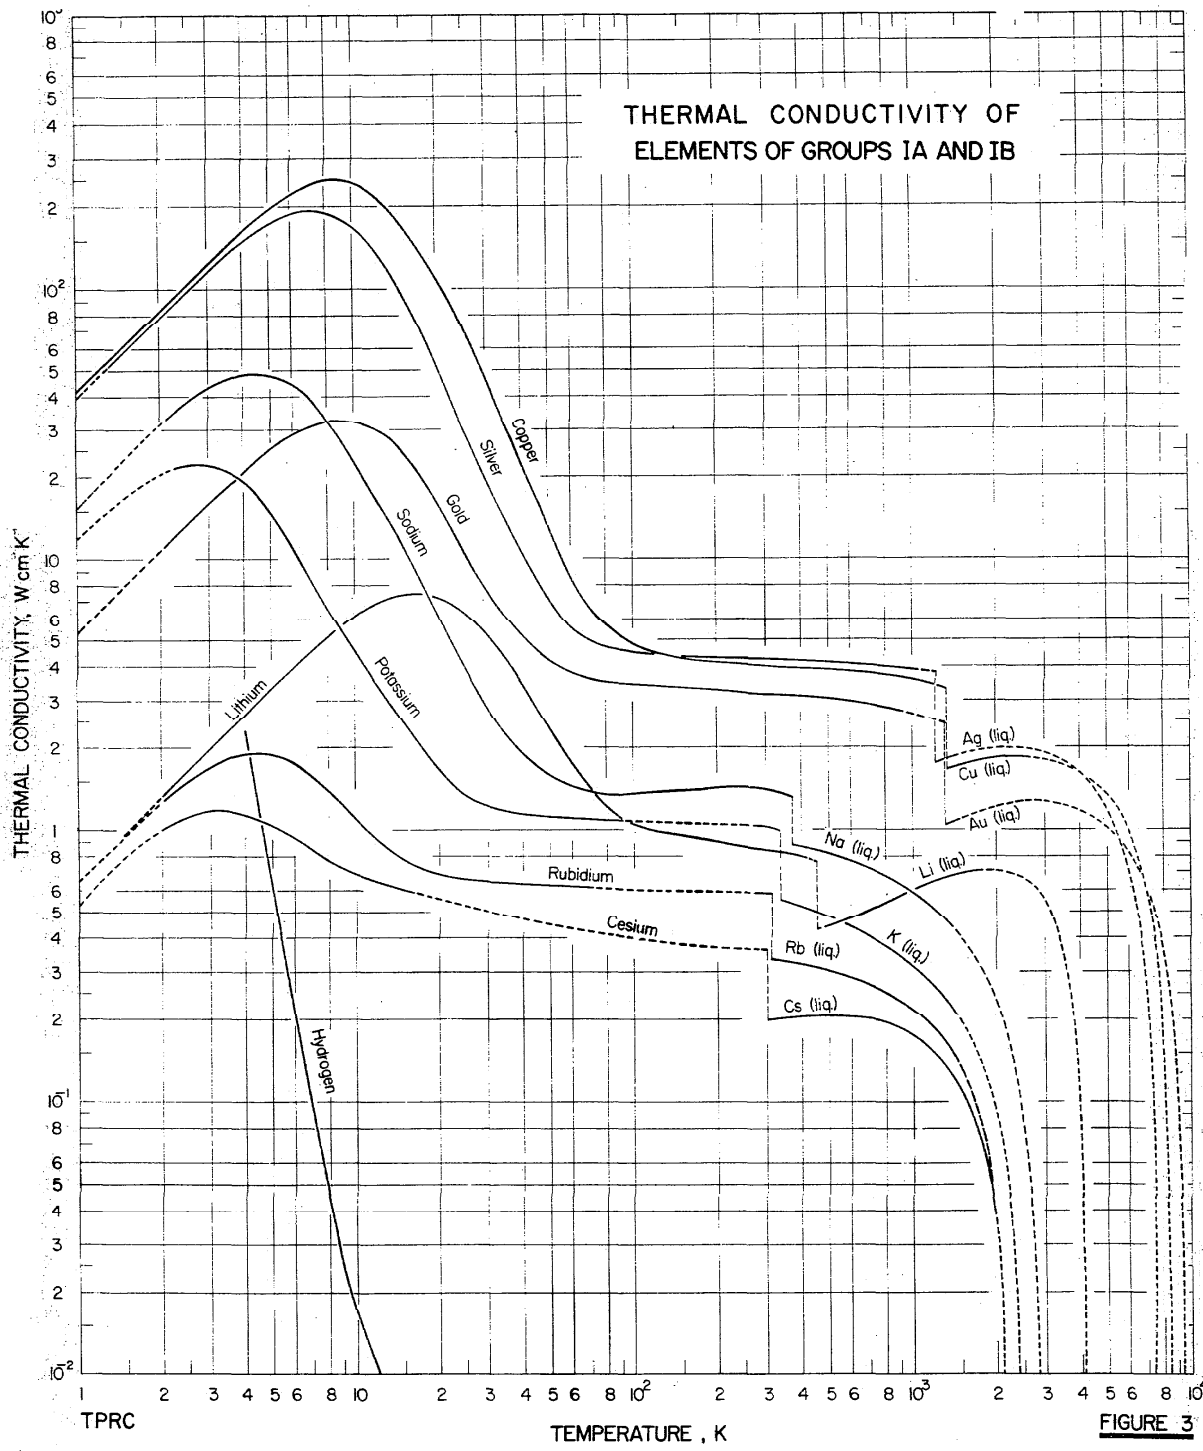

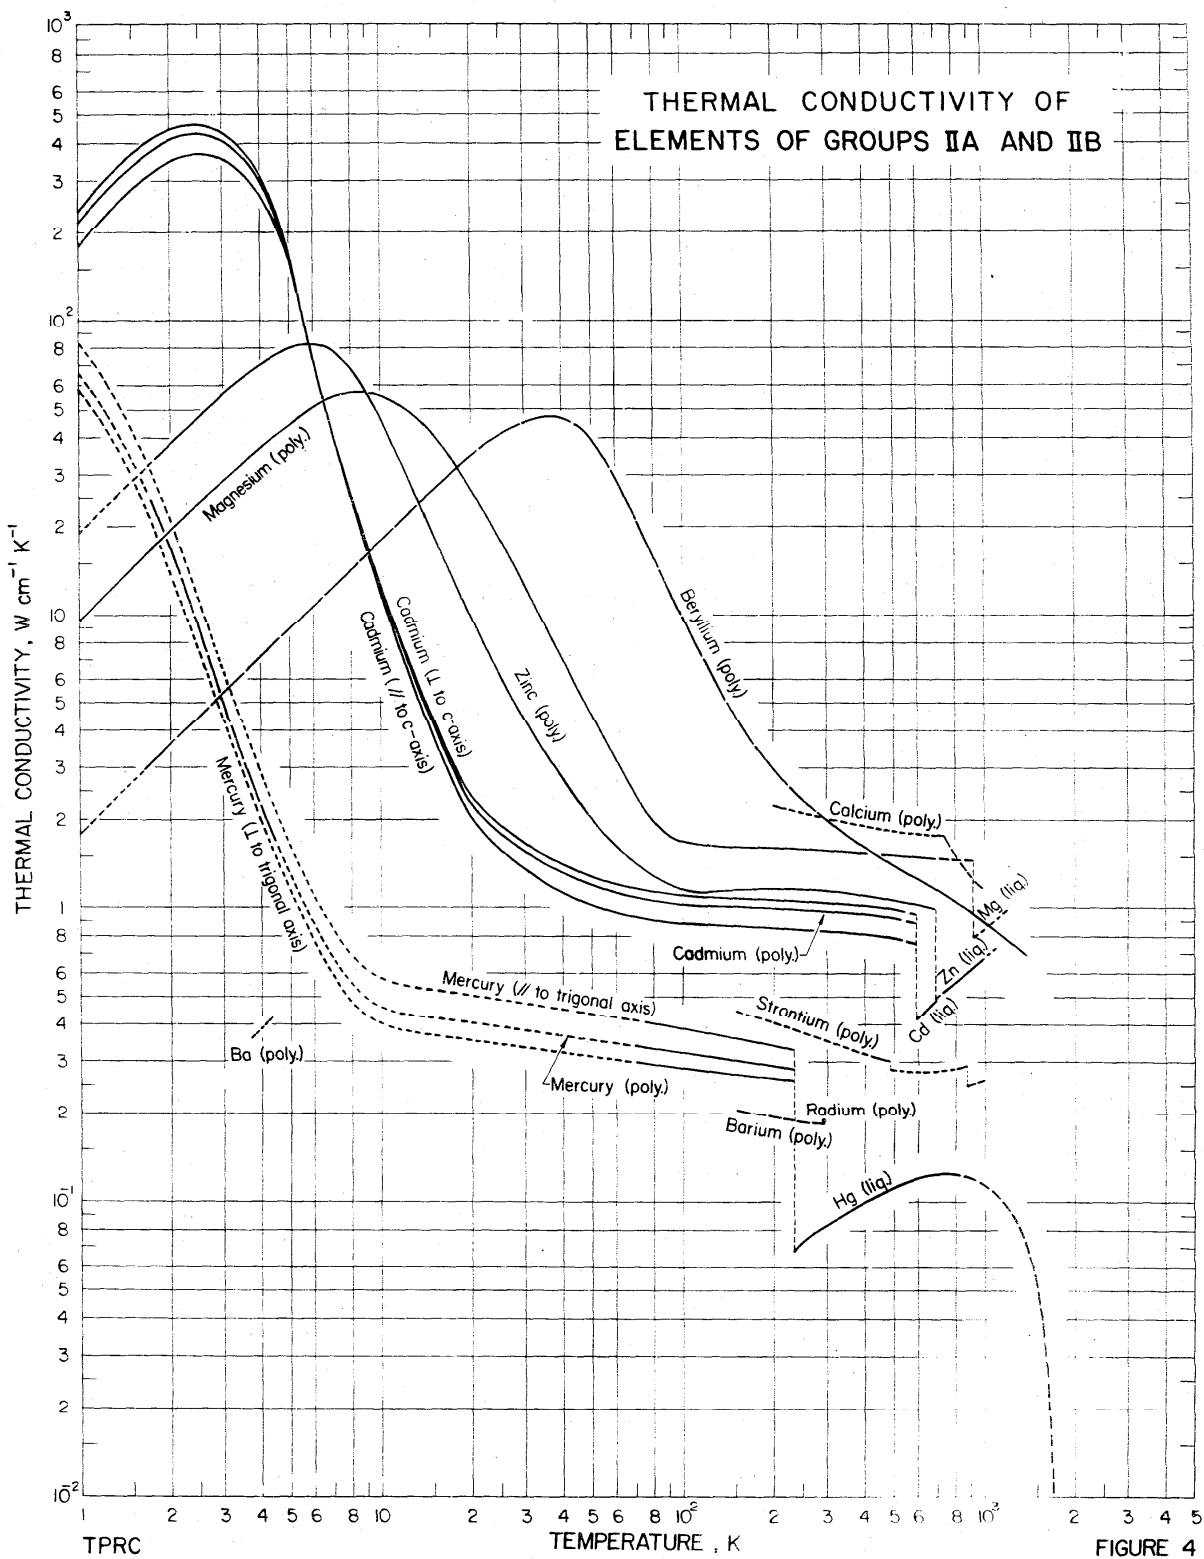

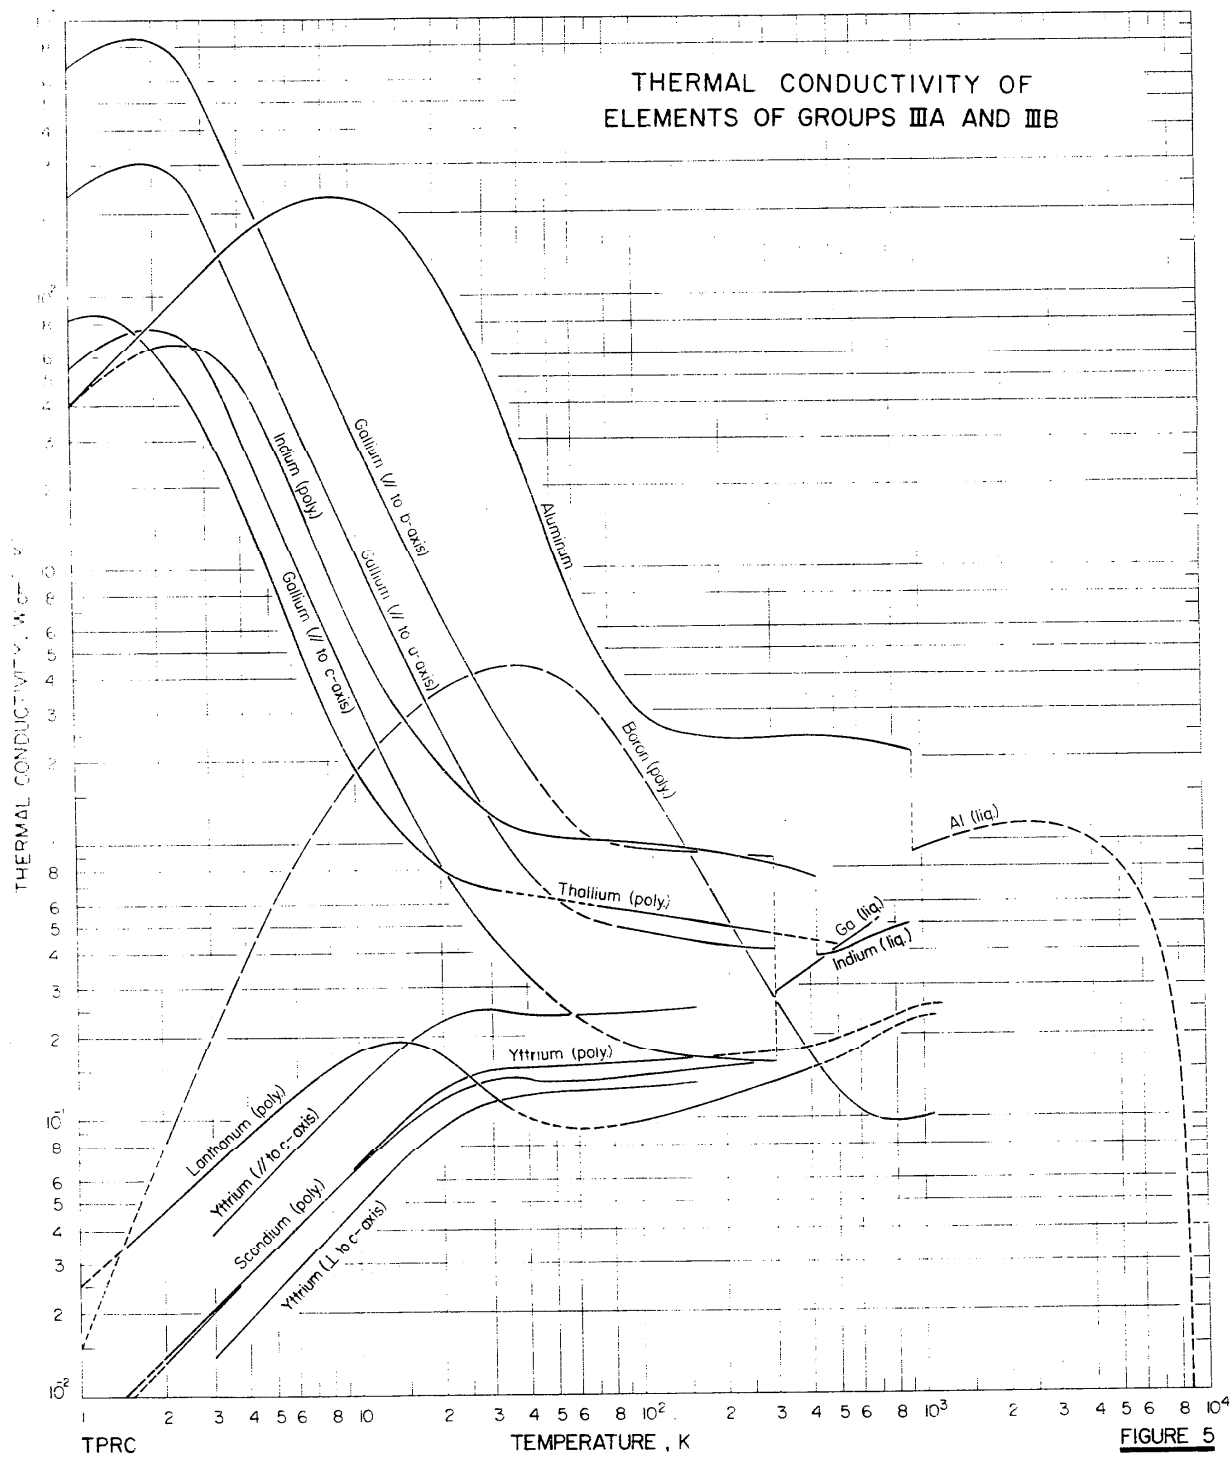

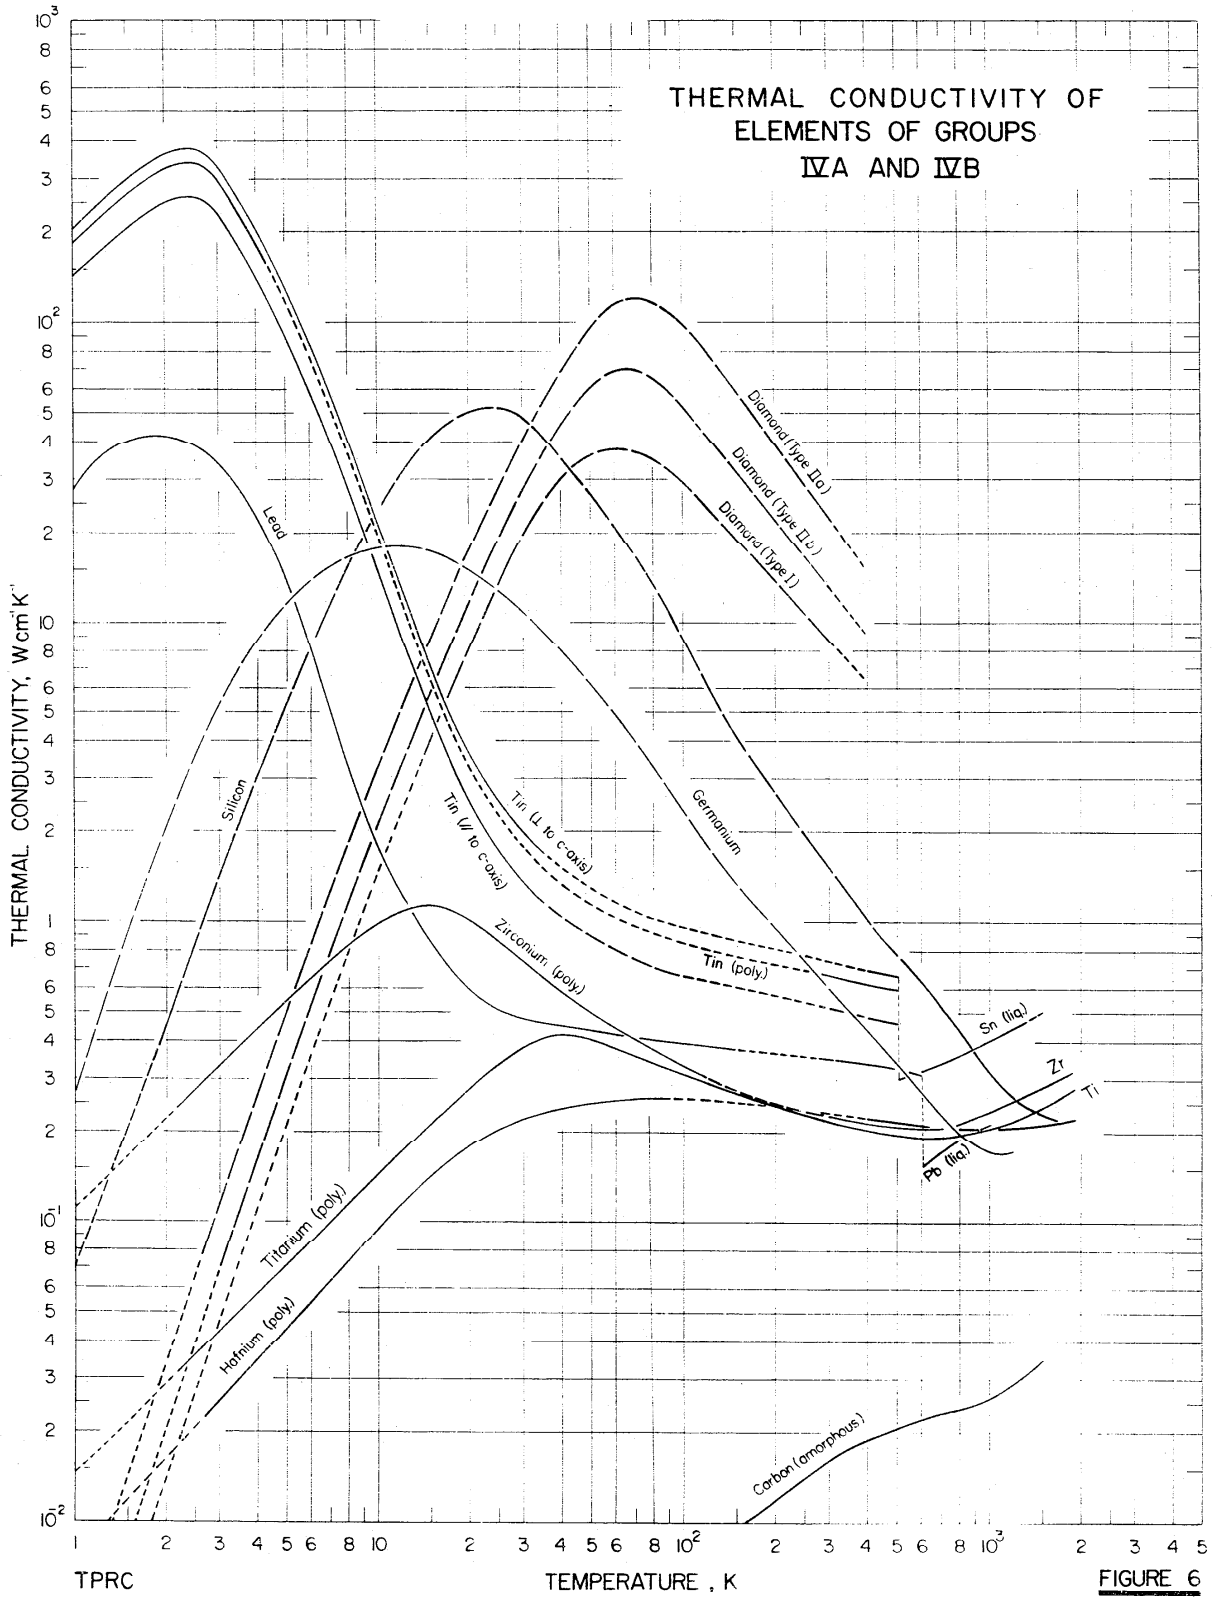

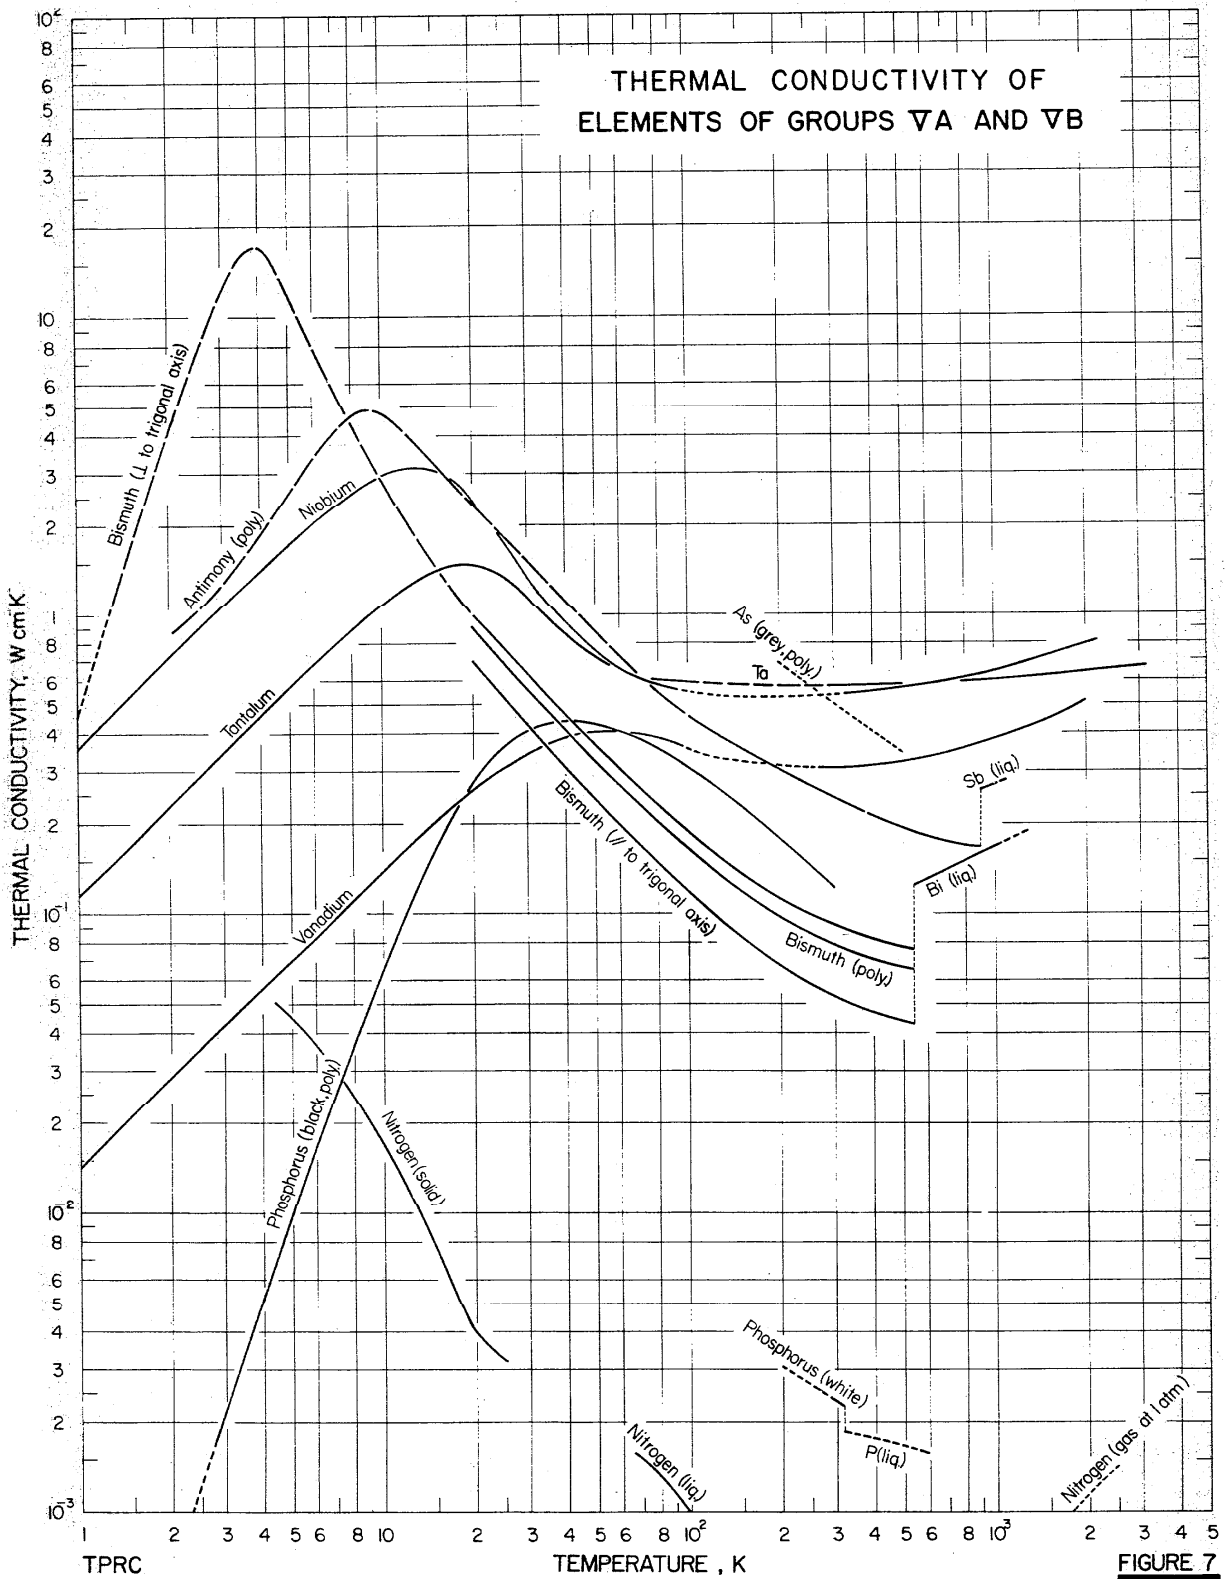
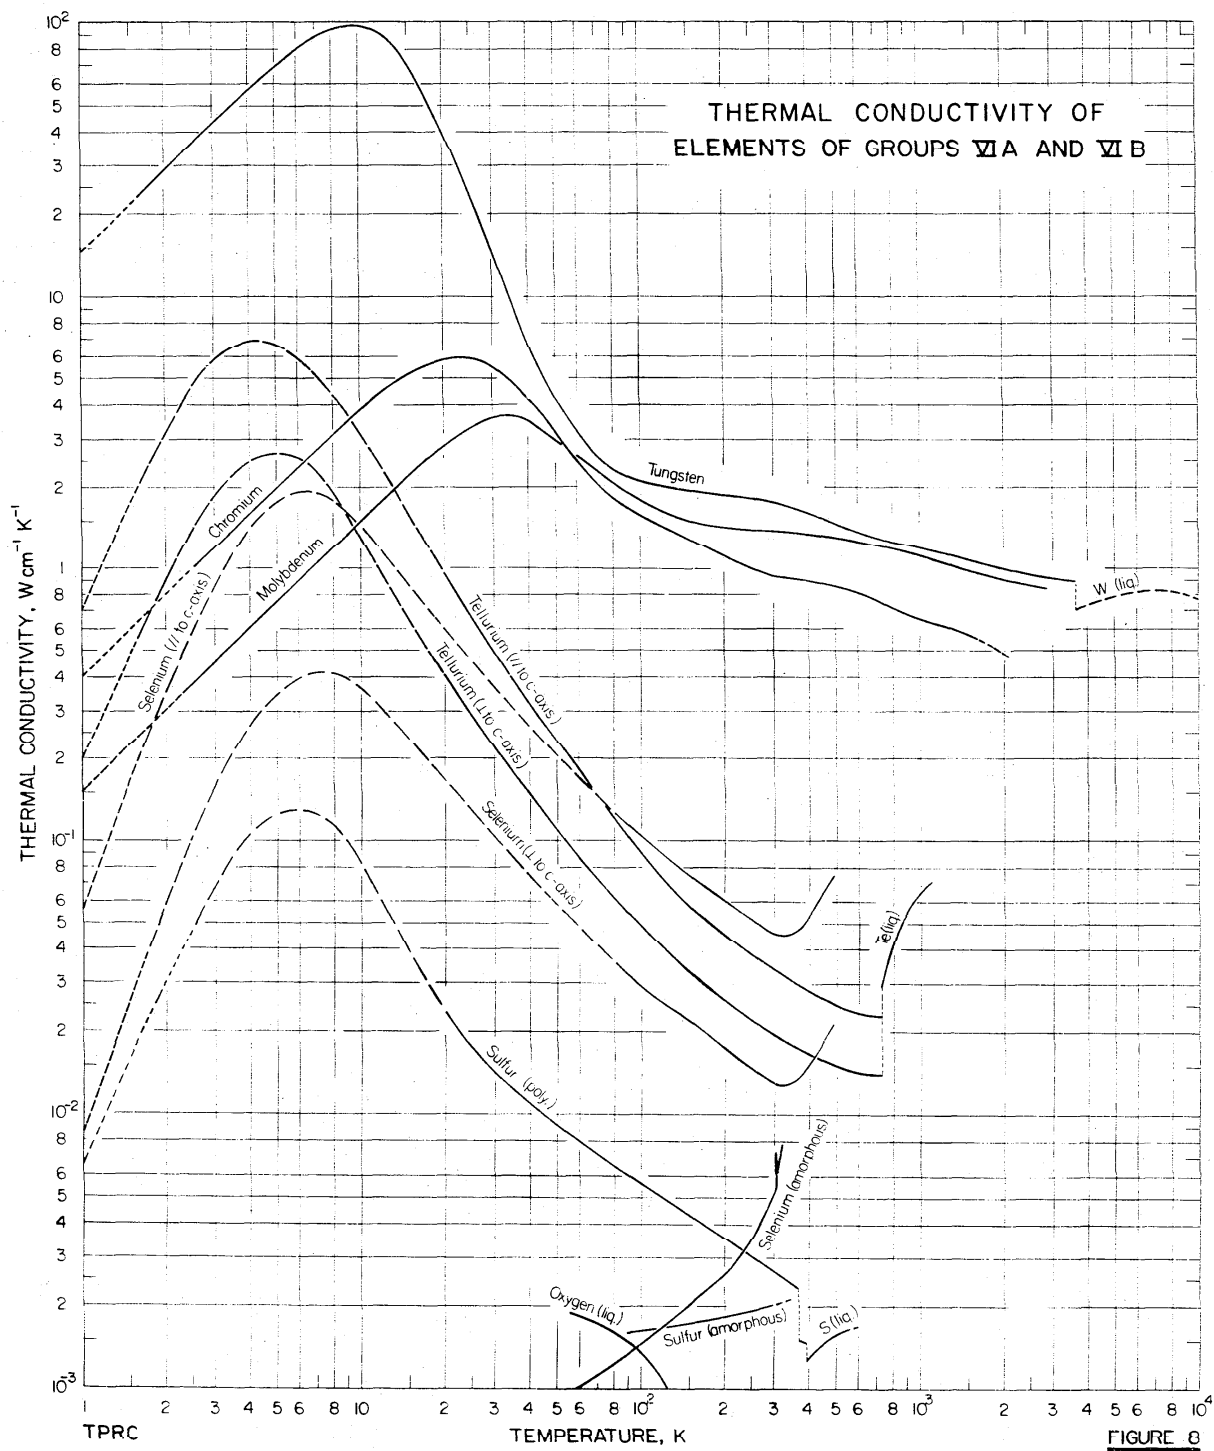
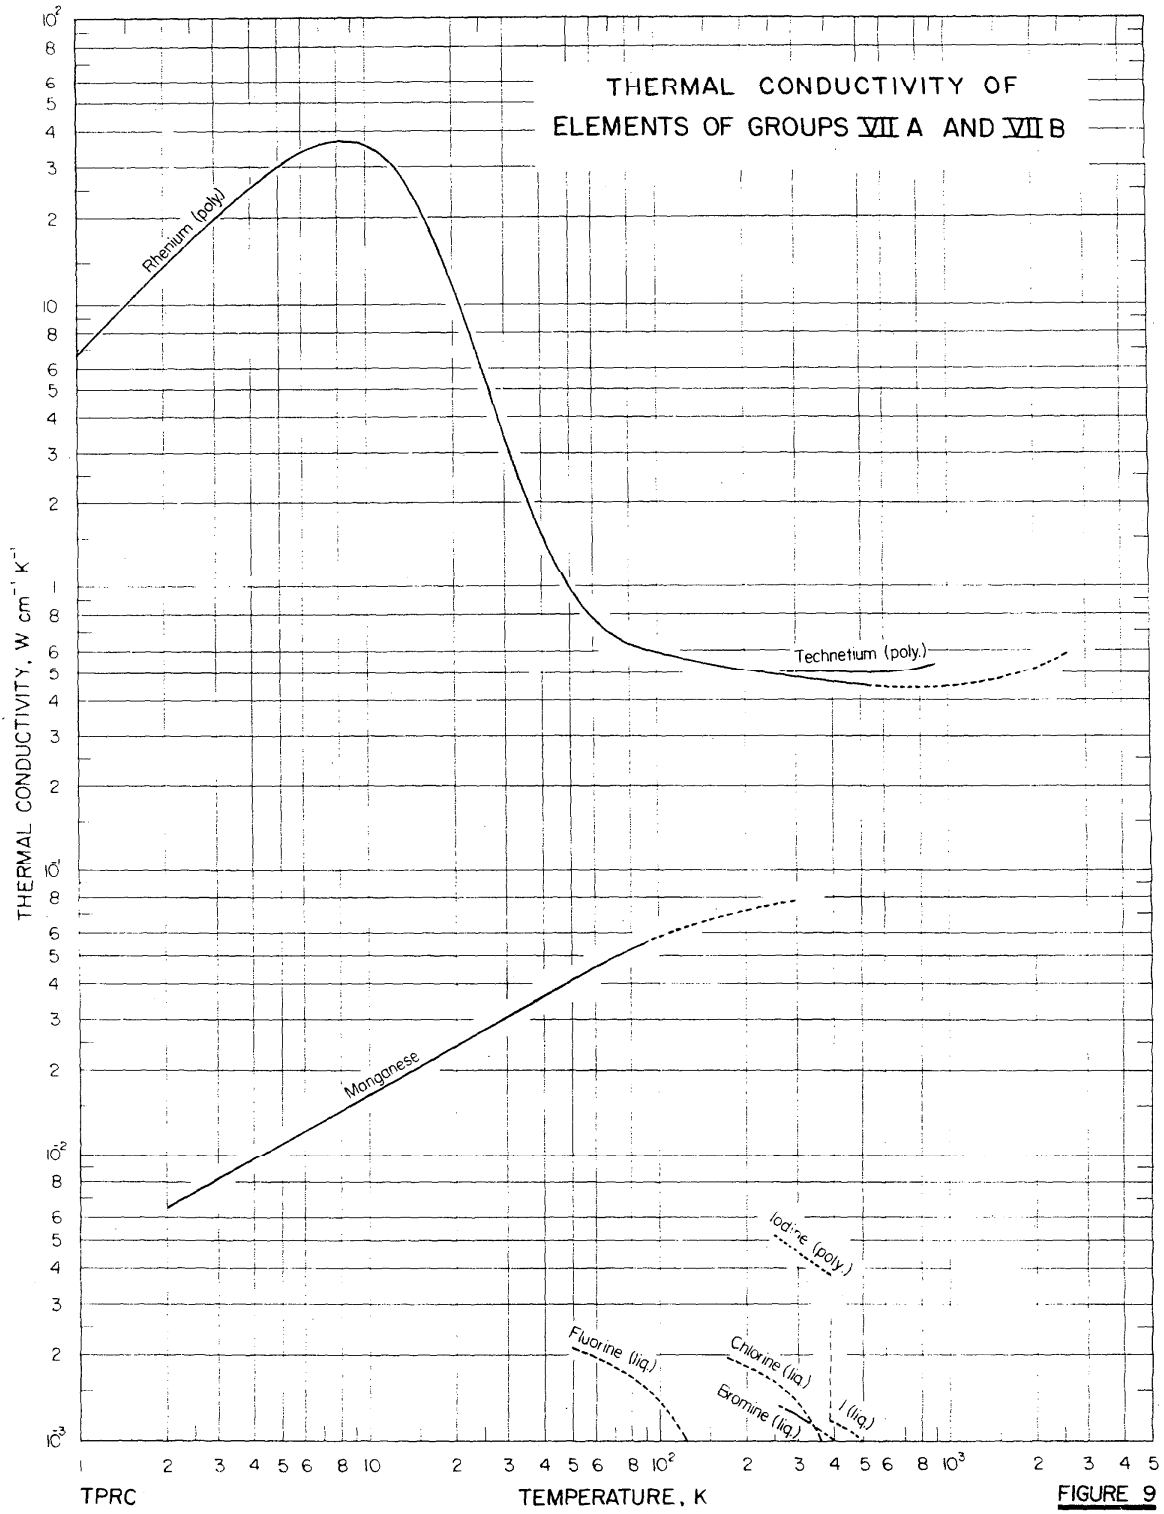
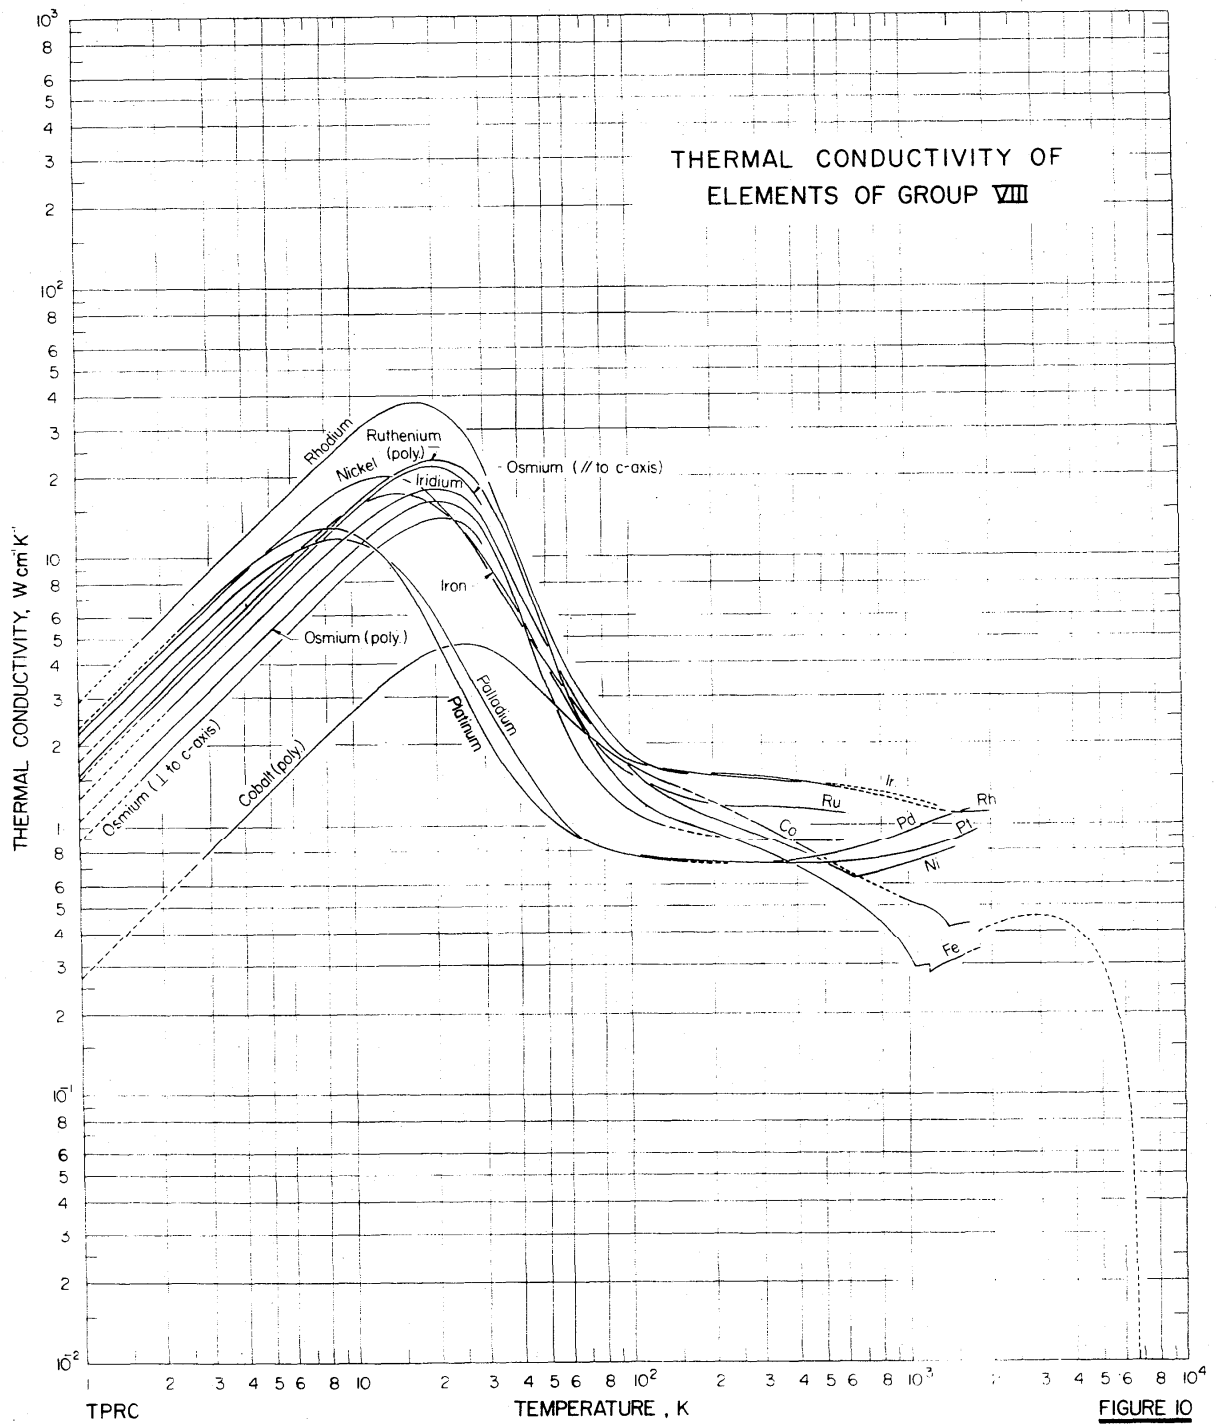
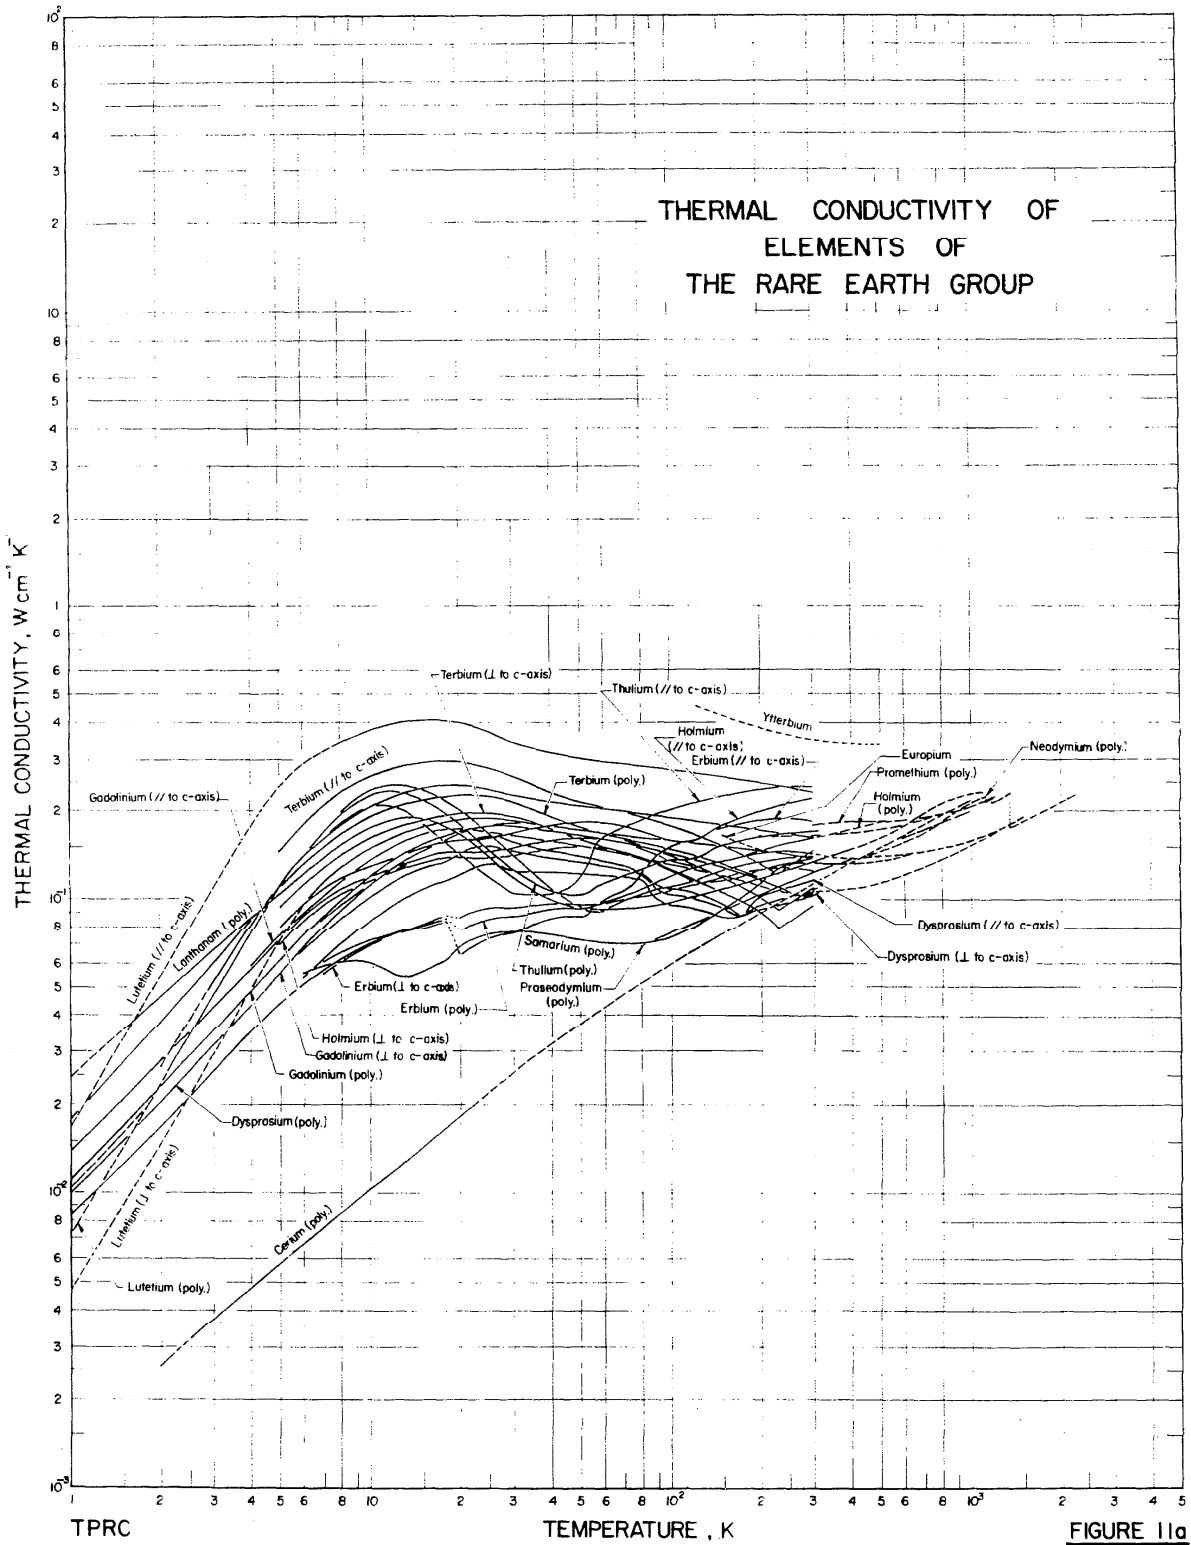



FIGURE 7











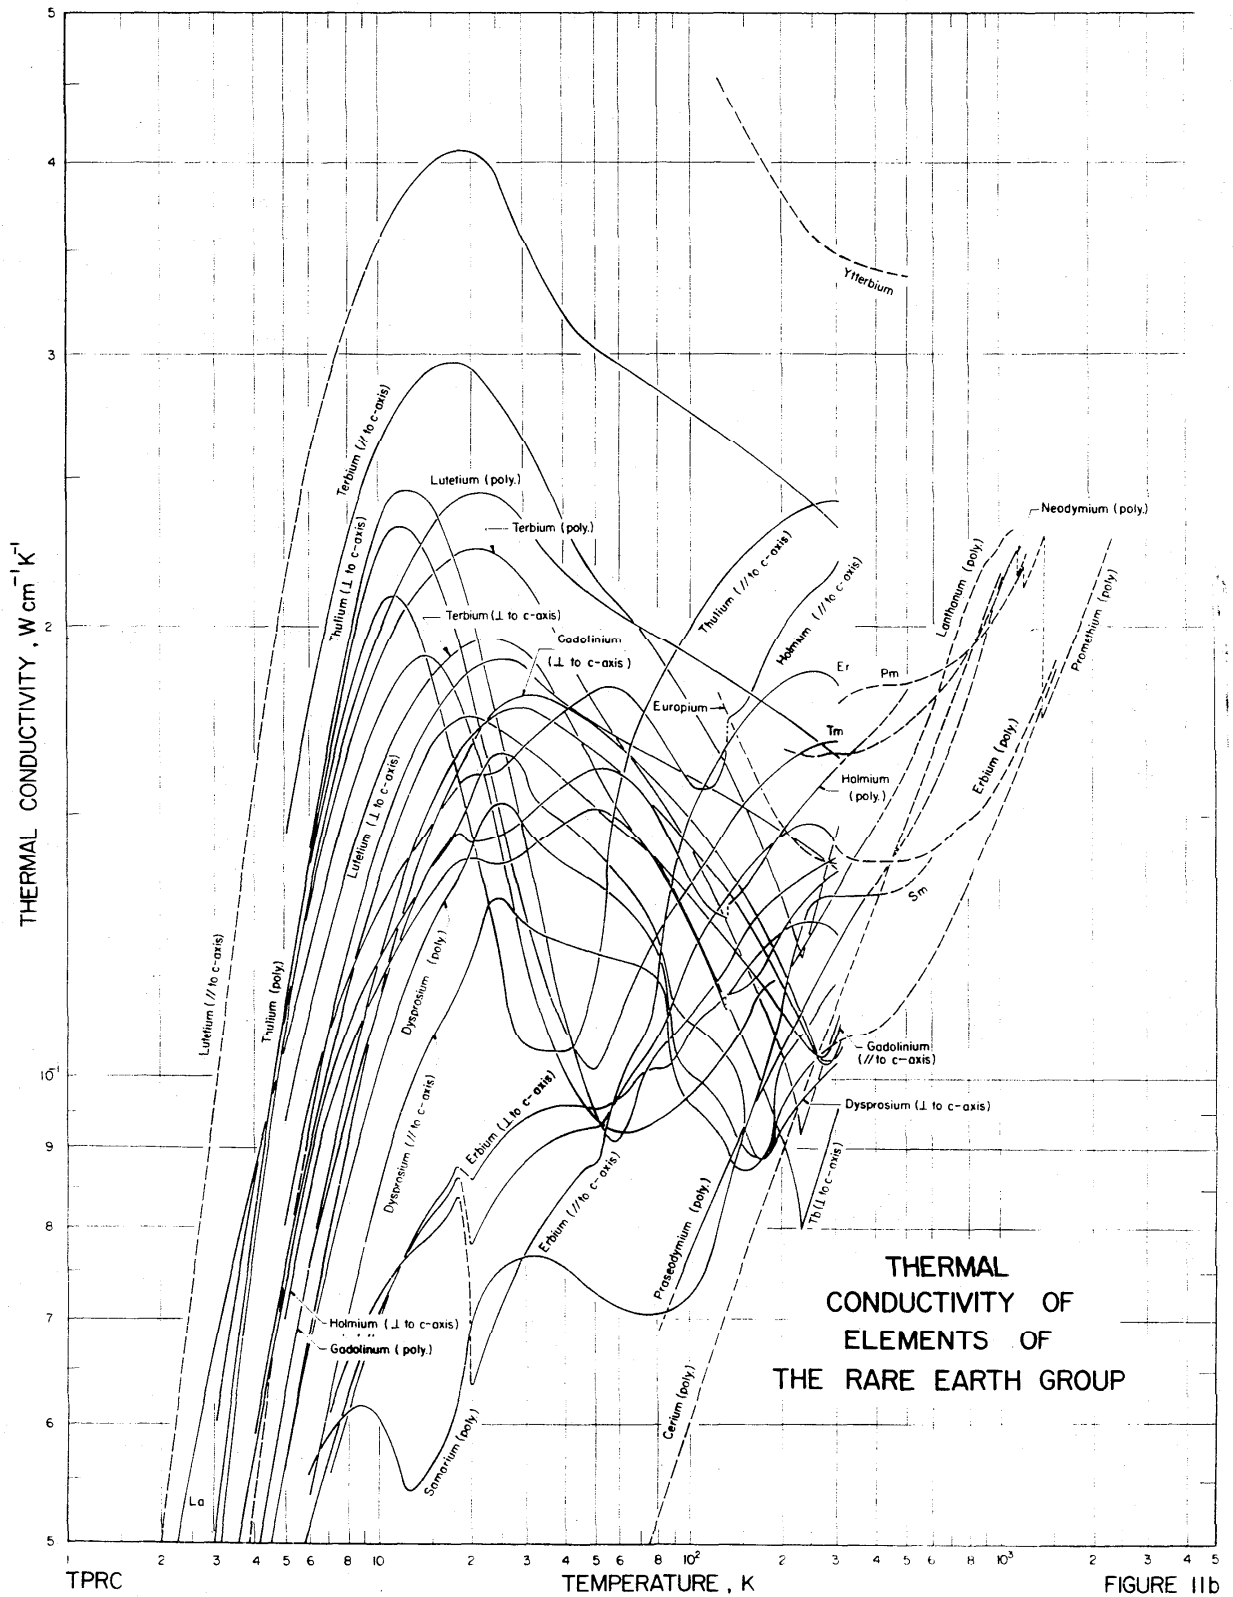

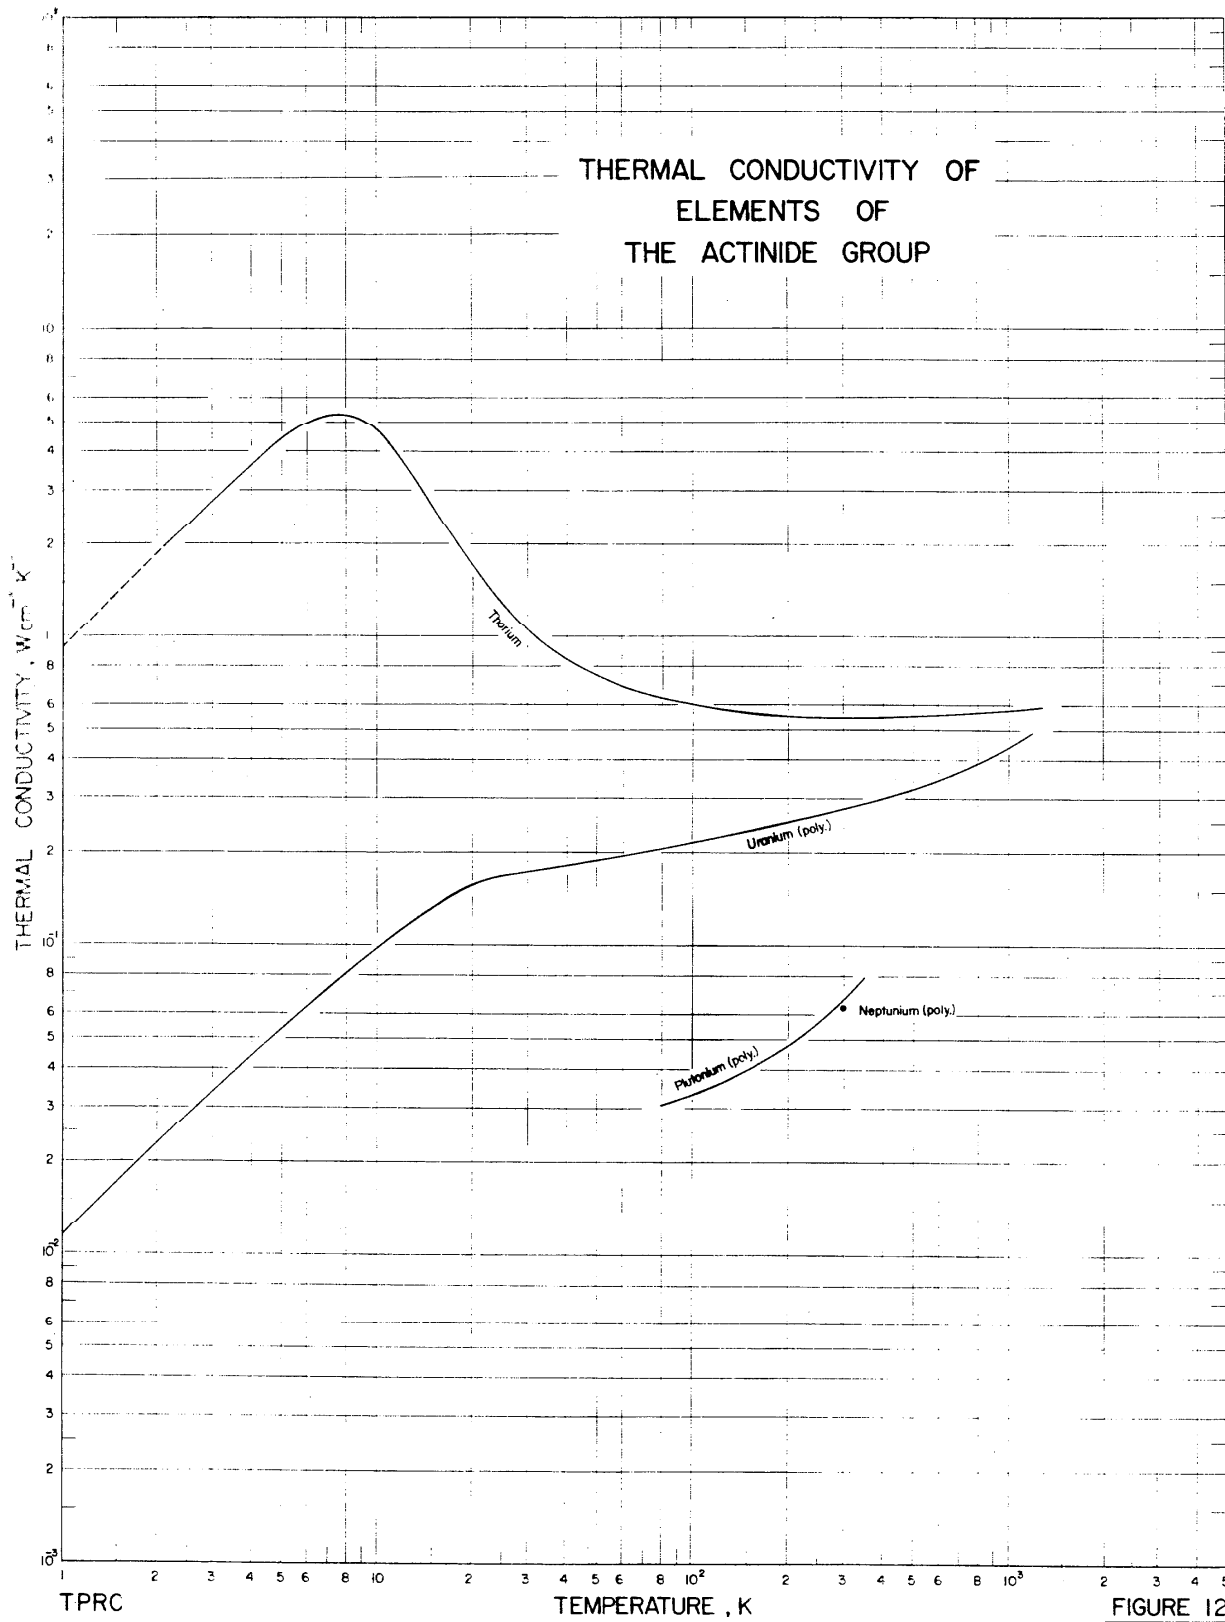

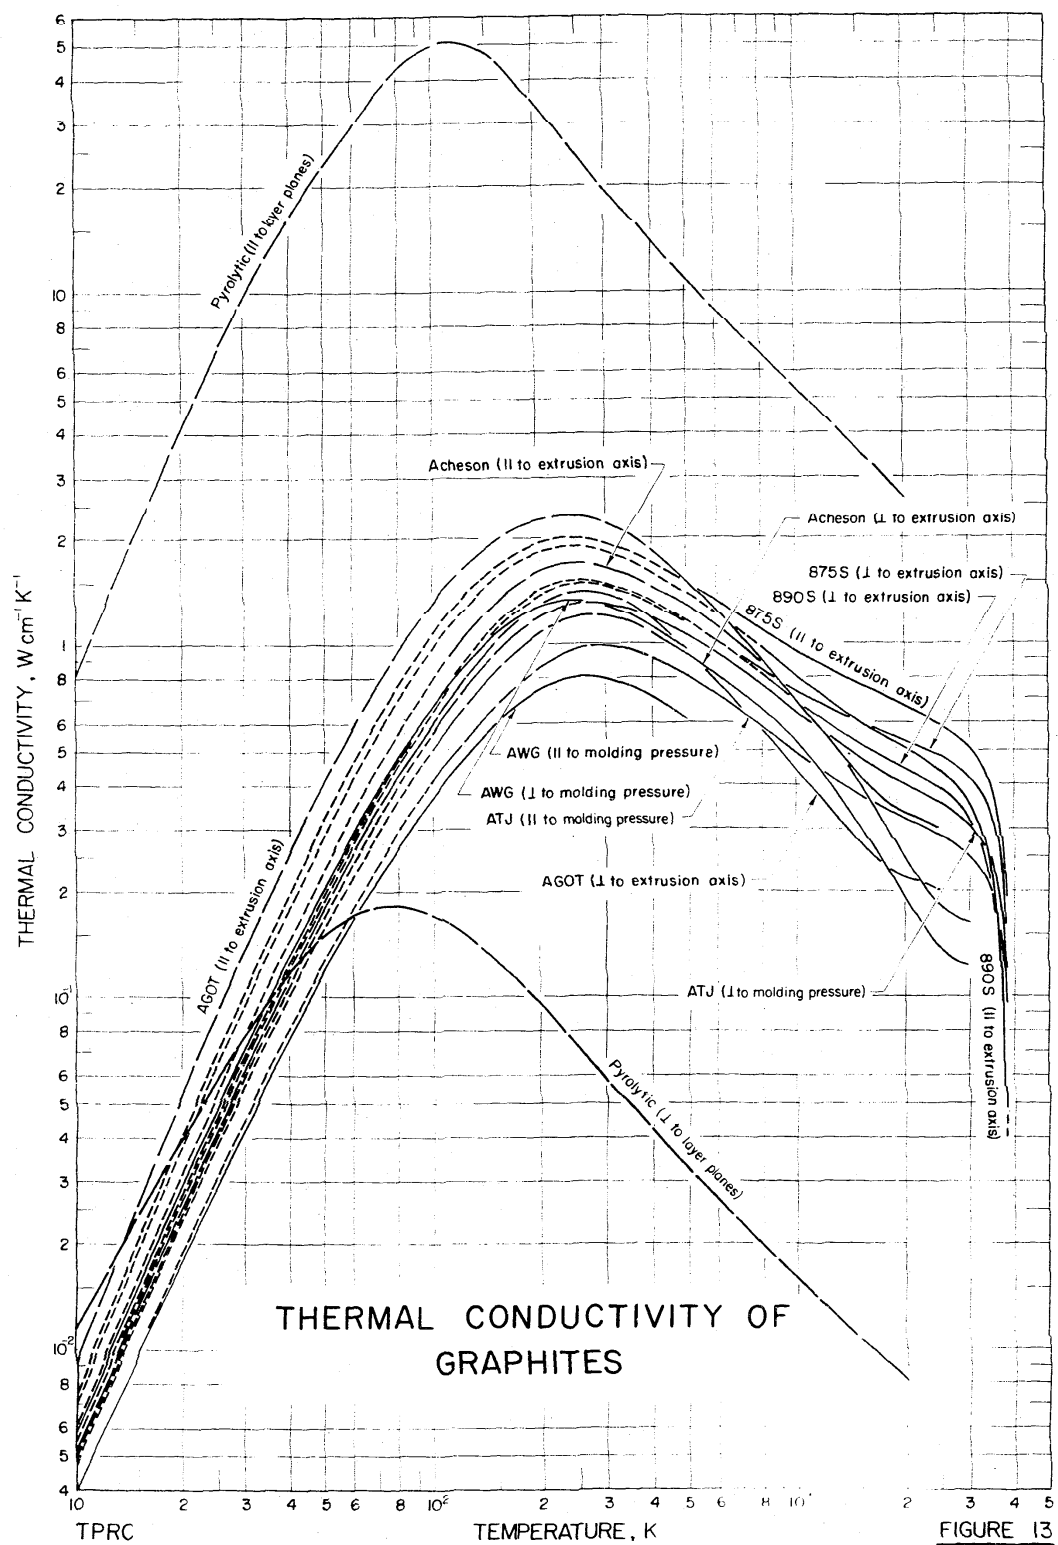

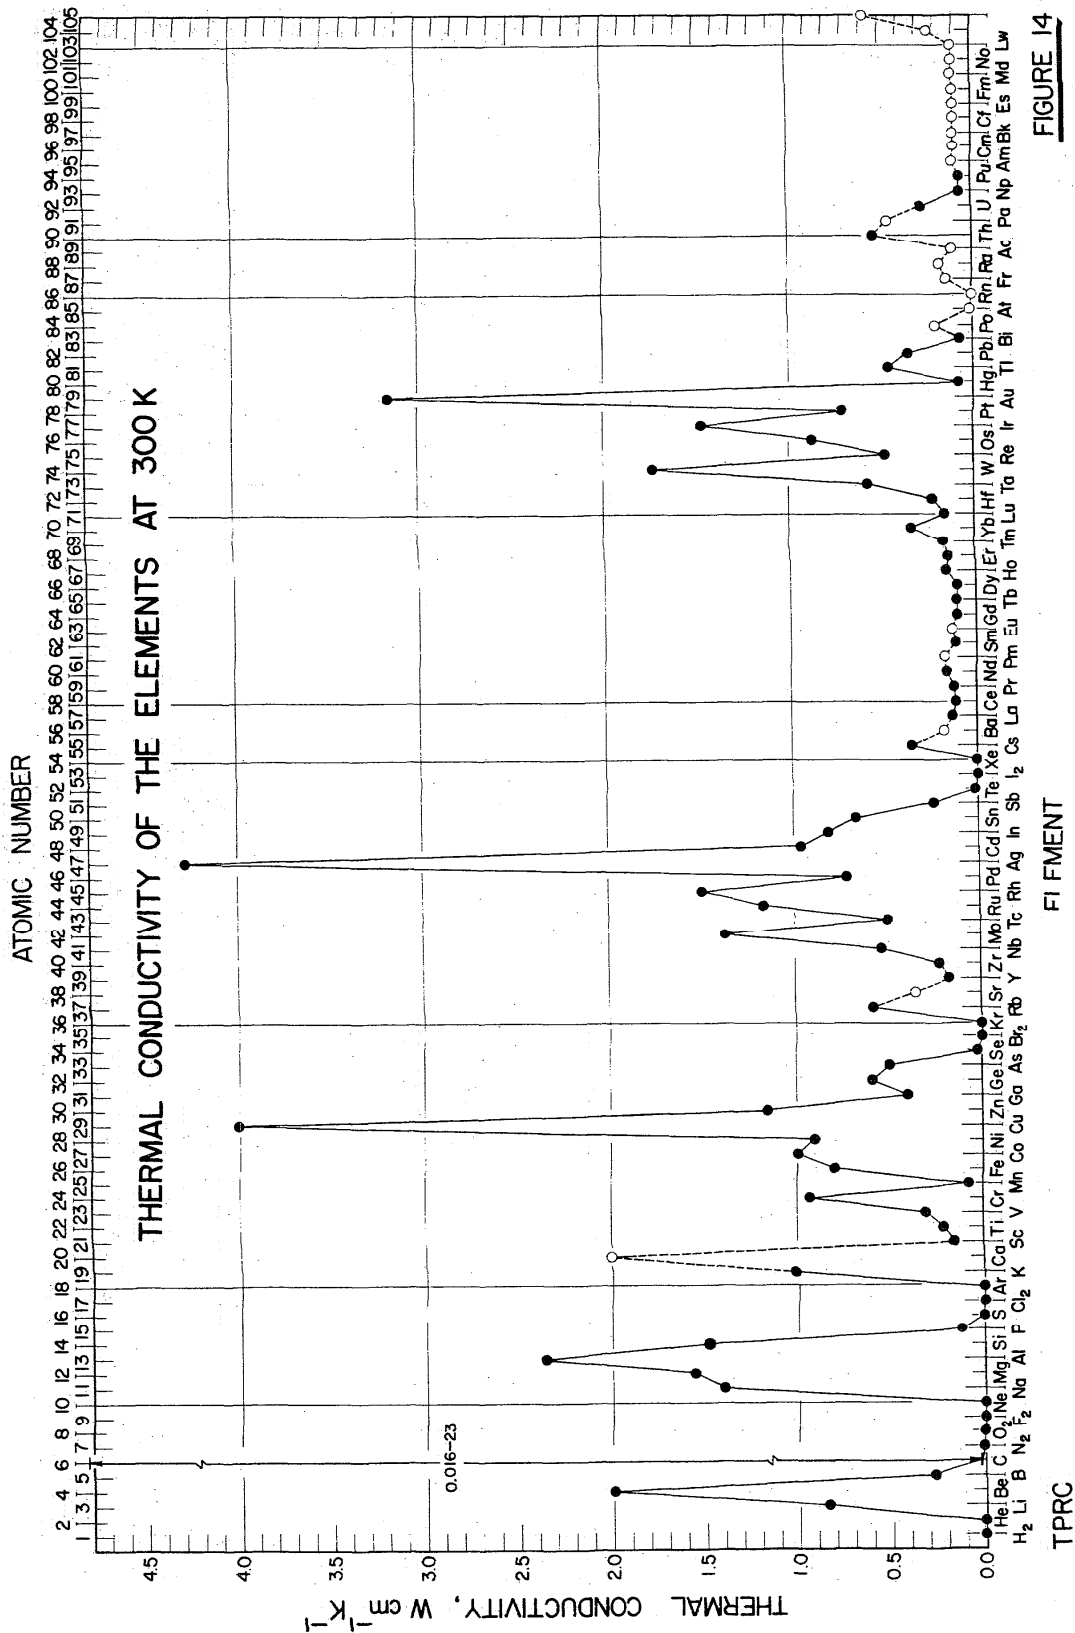


FIGURE 14

FI FMENT

TPRC

3. Specific Considerations Concerning the Body of Data

This compilation consists of graphs and tables of thermal conductivity as a function of temperature. The conventions used in this presentation and special comments on the interpretation and use of the data are given below.

The thermal conductivities of the elements are presented alphabetically by the names of the elements, but it should be noted that where information is given for different forms of a particular element, these follow that element. Thus, entries for amorphous carbon, diamond, and for several types of graphite come in the entry for carbon, and those for deuterium and tritium are found after the entry for hydrogen. For the nonmetallic elements which are liquid or gaseous at normal temperature and pressure (N.T.P.), and for iodine, thermal conductivity values are given mostly for the solid, saturated liquid, saturated vapor, and gas. For the other elements, values are given only for the solid state or solid and liquid states.

In the figures, solid curves represent recommended or provisional values. Accompanying sections of short-dashed lines represent values in the temperature range where experimental data are not available. In some instances, notably for semimetals and nonmetals at low temperatures, where the specimen cannot be uniquely characterized to correspond exactly with the thermal conductivity values, a curve considered as typical is composed of longer-dashed lines. For all the elements, logarithmic plotting of thermal conductivity against temperature is adopted.

In the figures, the melting point (M.P.), phase transition point (T.P.), superconducting transition point (T.P. (s.c.)), critical temperature (C.T.), Curie temperature, Néel temperature, etc. of the elements have been indicated. The inclusion of these transition points is intended to caution the reader of the existence of such transitions so that one must be extremely cautious in attempting the extrapolate the thermal conductivity values across any such transition temperature, since at such temperature the thermal conductivity generally exhibits sharp discontinuities. No attempt has been made to critically evaluate these transition temperatures, and they should not be considered as recommended values. Some of the given values, however, are the defining fixed points or secondary reference points of the International Practical Temperature Scale of 1968 (IPTS-68) such as the indicated melting points of gold, silver, tin, zinc, aluminum, antimony, bismuth, cadmium, cobalt, copper, indium, iridium, lead, mercury, nickel, palladium, platinum, rhodium, and tungsten, and boiling point of mercury.

The compiled 5200 sets of original thermal conductivity data which are presented in the comprehensive volume [1] were published over a period of 110 years from 1861 to 1970. It is realized that many different

temperature scales were used for these data. However, in thermal conductivity measurements, the thermal conductivity values are determined by the measured differences in temperature and not by the absolute magnitude of temperature. Furthermore the thermal conductivity is only a weak function of temperature and the effect of using different temperature scales on the reported thermal conductivity values is practically negligible. Consequently, no attempt has been made to convert the original data to a common scale. For the recommended values, the temperatures are based on the IPTS-68.

In the Thirteenth General Conference of Weights and Measures held in October 1967 in Paris, the unit "watt per metre-kelvin" (symbol: $\text{W m}^{-1}\text{K}^{-1}$) was adopted as the SI unit for thermal conductivity. In this work, the unit " $\text{W cm}^{-1}\text{K}^{-1}$ " is used which is a slight modification of the SI unit. Table 2 gives conversion factors which may be used to convert the thermal conductivity values in $\text{W cm}^{-1}\text{K}^{-1}$ presented in this work to values in the SI unit or to any of the several other units listed.

In the tables of recommended, provisional, or typical thermal conductivities, the values are presented with uniform but step-increasing increments in temperature as the temperature increases. For those elements which are solid at NTP and for mercury, the values are presented such that temperatures with uniform increments in both kelvin and Celsius are accommodated. In other words, those values given for temperatures 123.2 K, 173.2 K, 223.2 K, 273.2 K, 323.2 K, . . . are for -150°C , -100°C , -50°C , 0°C , 50°C , . . . The ".2" has been dropped for temperatures above 3000 K.

In the tables the third and occasionally the fourth significant figures are given for the thermal conductivity values, but this is only for internal comparison and for tabular smoothness and should not be considered indicative of the degree of accuracy. The accuracy of the recommended or provisional values for each element in different temperature ranges is given in the REMARKS. The thermal conductivity is zero at absolute zero temperature, i.e. at the point ($T=0$, $k=0$). This is a theoretical consequence based upon the premise that the specific heat is zero at absolute zero temperature according to the third law of thermodynamics.

For a solid element at moderate and high temperatures the true thermal conductivity values for different well-annealed high-purity (99.99+%) samples at any given temperature should be close, and therefore a set of recommended thermal conductivity values can be given for a well-annealed high-purity element. At low temperatures, however, the thermal conductivity values for different samples with small differences in purity and/or imperfection differ greatly, and a set of recommended or provisional values applies only to a sample of a particular purity and imperfection. Ideally the low-temperature thermal conductivity of a solid element should be represented by a family (or families, for a non-cubic

TABLE 2. Conversion factors for units of thermal conductivity

MULTIPLY by appropriate factor to ↓	$Btu_{IT} h^{-1} ft^{-1} F^{-1}$	$Btu_{IT} h^{-1} ft^{-1} F^{-1}$	$Btu_{IT} in. h^{-1} ft^{-2} F^{-1}$	$Btu_{IT} in. h^{-1} ft^{-2} F^{-1}$	$Btu_{IT} in. h^{-1} ft^{-2} F^{-1}$	$Btu_{IT} in. h^{-1} ft^{-2} F^{-1}$	$cal_{IT} s^{-1} cm^{-1} C^{-1}$	$cal_{th} s^{-1} cm^{-1} C^{-1}$	$kcal_{th} h^{-1} m^{-1} C^{-1}$	$J s^{-1} cm^{-1} K^{-1}$	$W cm^{-1} K^{-1}$	$W m^{-1} K^{-1}$	$mW cm^{-1} K^{-1}$
	1	12	1.00067	12.0080	1.00067	12.0080	4.13379×10^{-3}	4.13656×10^{-3}	1.48916	1.73073×10^{-2}	1.73073×10^{-2}	1.73073	17.3073
	8.33333×10^{-2}	1	8.33891 $\times 10^{-2}$	1.00067	1.00067	8.33891 $\times 10^{-2}$	3.44482×10^{-4}	3.44713×10^{-4}	0.124097	1.44228×10^{-3}	1.44228×10^{-3}	0.144228	1.44228
	0.999331	11.9920	1	12	1	11.9920	4.13102×10^{-3}	4.13379×10^{-3}	1.48816	1.72958×10^{-2}	1.72958×10^{-2}	1.72958	17.2958
	8.32776×10^{-2}	0.999331	8.33333 $\times 10^{-2}$	1	1	8.33333 $\times 10^{-2}$	3.44252×10^{-4}	3.44482×10^{-4}	0.124014	1.44131×10^{-3}	1.44131×10^{-3}	0.144131	1.44131
	2.41909 $\times 10^2$	2.90291 $\times 10^3$	2.42071 $\times 10^2$	2.90485 $\times 10^3$	1	2.42071 $\times 10^2$	1	1.00067	3.60241 $\times 10^2$	4.1868	4.1868	4.1868 $\times 10^2$	4.1868 $\times 10^{-3}$
	2.41747 $\times 10^2$	2.90096 $\times 10^3$	2.41909 $\times 10^2$	2.90291 $\times 10^3$	1	2.41909 $\times 10^2$	0.999331	1	3.6 $\times 10^2$	4.184	4.184	4.184 $\times 10^2$	4.184 $\times 10^{-3}$
	0.671520	8.05824	0.671969	8.06363	1	0.671969	2.77592×10^{-3}	2.77778×10^{-3}	1	1.16222×10^{-2}	1.16222×10^{-2}	1.16222	11.6222
	57.7789	6.93347 $\times 10^2$	57.8176	6.93811 $\times 10^2$	1	57.8176	0.238846	0.239006	86.0421	1	1	1 $\times 10^2$	1 $\times 10^3$
	57.7789	6.93347 $\times 10^2$	57.8176	6.93811 $\times 10^2$	1	57.8176	0.238846	0.239006	86.0421	1	1	1 $\times 10^2$	1 $\times 10^3$
	0.577789	6.93347	0.578176	6.93811	1	0.578176	2.38846×10^{-3}	2.39006×10^{-3}	0.860421	1 $\times 10^{-3}$	1 $\times 10^{-2}$	1	10
	5.77789 $\times 10^{-2}$	0.693347	5.78176 $\times 10^{-2}$	0.693811	1	5.78176 $\times 10^{-2}$	2.38846×10^{-4}	2.39006×10^{-4}	8.60421 $\times 10^{-2}$	1 $\times 10^{-2}$	1 $\times 10^{-3}$	0.1	1

crystal) of curves, each of which is recommended for a sample of a particular purity and imperfection, and hence having a particular residual electrical resistivity for a metal. In this work, such a family of recommended curves for specimens of different hypothetical impurities and imperfections has not been generated. Instead, a single, well defined curve is drawn to link with the recommended curve for moderate and high temperatures so as to complete the functions for the full range of temperature. The recommended low-temperature values in the table, which are for the purest form of each element for which measurements have been made, are of course only applicable to that particular characterized sample whose residual electrical resistivity has clearly been specified in the REMARKS. Consequently, this recommended curve should not be interpreted as a unique function for the low temperature region but it is only applicable to a sample of specified conditions. For samples having different impurities and imperfections, i.e., having different residual electrical resistivities for a metallic element, the reader may similarly derive low-temperature thermal conductivity curves following the same guidelines and procedures as used in this work.

As mentioned before, the residual electrical resistivity ρ_0 is used for the characterization of a metallic sample to correspond with the recommended low-temperature thermal conductivity values. At temperatures around 4 K or below, $\rho_0 \gg \rho_i$, and hence ρ_0 may be written as

$$\rho_0 = \frac{L_0 T}{k_c} \quad (16)$$

It is ρ_0 which is determined experimentally as the residual electrical resistivity resulting from electron-defect scattering. If however ρ_0 is calculated from an equation similar to (16) but using a measured value of the thermal conductivity, this value is k and not k_c . Denoting the value so calculated by ρ_0' , then

$$\rho_0' = \frac{L_0 T}{k} = \frac{L_0 T}{k_c + k_g} = \frac{\rho_0}{1 + k_g/k_c} \quad (17)$$


It can be seen from equation (17) that if $k_g \geq 0$ then $\rho_0' \leq \rho_0$. This is usually true, and the experimental ρ_0

is then the value given to correspond with the recommended k values.

It happens occasionally, however, that $\rho_0' > \rho_0$ implying that $k_g < 0$. As negative values for k_g seem impossible, the measured ρ_0 is concluded to be in error and in this case, the calculated value ρ_0' has been given as corresponding with the recommended k values.

Regarding those elements which are liquid or gaseous at N.T.P., the provision of recommended values of the thermal conductivity at the critical point takes no account of anomalies in the immediate vicinity of this point. While evidence seems to be accumulating that a rapid increase in thermal conductivity to very large, if not infinite, values does occur in the immediate vicinity of the critical point, the temperature span of any such departure is very short, and in the preparation of the present tables this factor has been disregarded. The values recommended here for the critical point are thus obtained through arbitrary extrapolations of the saturated liquid and vapor curves with no considerations being given to such anomalies. This approach was considered justified by the very meager and indefinite investigations which have been concerned with such an effect. The present approach has been taken so that interpolation of the recommended critical-point values with those tabulated for lower temperatures will enable intermediate temperature values to be obtained which will be accurate except for the small temperature region where anomalies may occur. Furthermore, the values at the critical point are needed for data correlation using the principle of the corresponding states. Likewise, the error estimates refer to possible errors in estimating such values. Should recent studies on anomalies prove to be confirmed, the present values might be regarded as "pseudo-critical" values of thermal conductivities. While the merit of our present approach could be questioned by some, it might be added that the above defined "critical" thermal conductivities have been found to give consistent values when comparing "critical" thermal conductivities of families of substances. At the present time, similar treatments of "true" critical values present serious difficulties.

The recommended values for the various gases, which cover very wide ranges of temperature, are only for a pressure of one atmosphere. The pressure dependence of thermal conductivity is not yet included in this work.

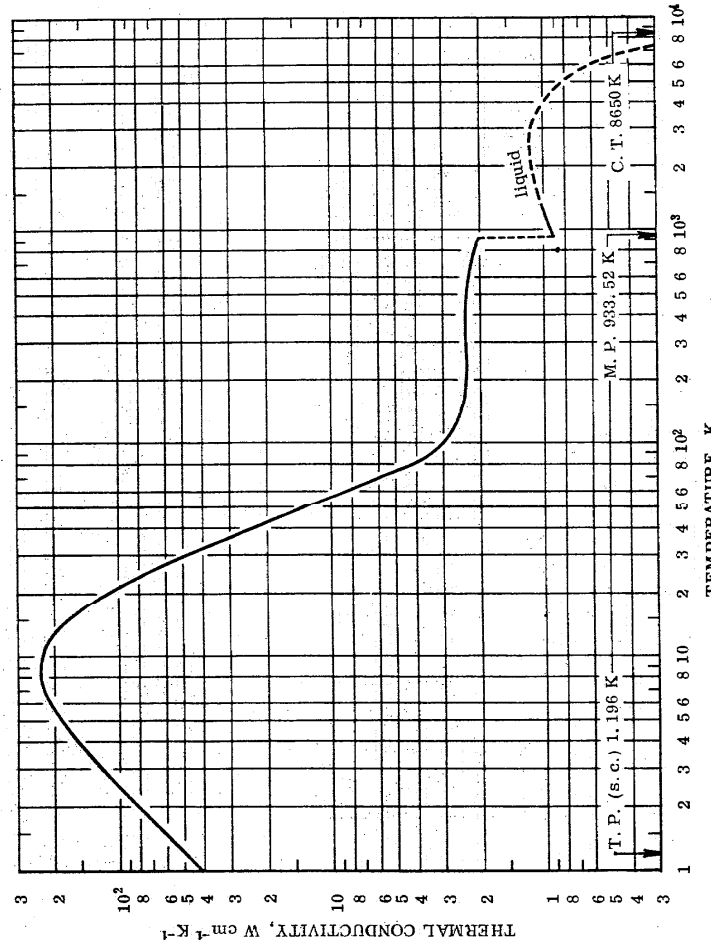

RECOMMENDED VALUES †
[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]

SOLID		LIQUID	
T	k	T	k
0	0	933.52	0.907*
1	41.1	973.2	0.921
2	81.8	1000	0.930
3	121	1073.2	0.955
4	157	1100	0.964
5	188	1173.2	0.986
6	213	1200	0.994
7	229	1273.2	1.01
8	237	1300	1.02*
9	239	1373.2	1.04*
10	235	1400	1.05*
11	226	1473.2	1.07*
12	214	1500	1.07*
13	201	1573.2	1.08*
14	189	1600	1.09*
15	176	1673.2	1.10*
16	163	1700	1.11*
18	138	1773.2	1.11*
20	117	1800	1.12*
25	75.2	1873.2	1.13*
30	49.5	1900	1.13*
35	33.8	1973.2	1.14*
40	24.0	2000	1.14*
45	17.7	2073.2	1.14*
50	13.5	2173.2	1.15*
		2200	1.15*
		2273.2	1.15*
		2400	1.15*
		2473.2	1.15*
		2600	1.15*
		8000	0.156*
		8273	0.0915*
		8500	0.0365*

REMARKS


The recommended values are for well-annealed high-purity aluminum and are thought to be accurate to within $\pm 5\%$ of the true values at temperatures below room temperature and ± 2 to $\pm 3\%$ above. For molten aluminum near the melting point the values are probably good to within $\pm 8\%$. The thermal conductivity at temperatures near and below the corresponding temperature, T_m , of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens, and the conductivity values below 150 K are applicable only to a specimen having residual electrical resistivity $\rho_0 = 0.000594 \mu\Omega \text{ cm}$. Values at temperatures below about 1.5 T_m are calculated to fit the experimental data by using eq. (7) and using the constants m , n , α' as given in Table I and $\beta = 0.0243$. The values for molten aluminum above 1273 K are provisional values.

* Estimated or extrapolated.
† Values above 1273 K are provisional.

THERMAL CONDUCTIVITY OF ANTIMONY

PROVISIONAL VALUES †
[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]

T	SOLID		LIQUID	
	k	T	k	T
2	0.87	173.2	0.326	903.89
3	1.27	200	0.302	973.2
4	1.86	223.2	0.283	1000
5	2.58	250	0.267	1073.2
6	3.34	273.2	0.255	1100
7	4.06	298.2	0.244	
8	4.63	300	0.243	
9	4.89	323.2	0.235	
10	4.80	350	0.226	
11	4.50	373.2	0.219	
12	4.07	400	0.213	
13	3.79	473.2	0.199	
14	3.51	500	0.185	
15	3.25	573.2	0.186	
16	3.04	600	0.183	
18	2.67	673.2	0.176	
20	2.38	700	0.174	
25	1.87	773.2	0.170	
30	1.54	800	0.168	
35	1.30	850	0.167	
40	1.13	873.2	0.167	
45	0.994	900	0.167	
50	0.883	903.89	0.167	
60	0.725			
70	0.620			
80	0.550			
90	0.500			
100	0.454			
123.2	0.405			
150	0.356			

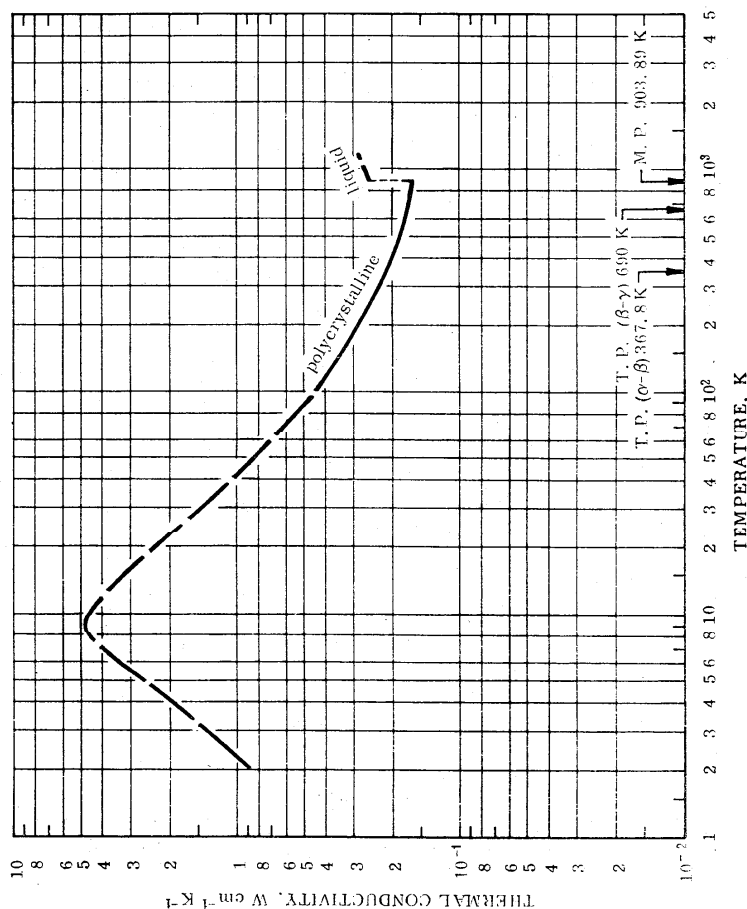


DISCUSSION

The values above 100 K are provisional for well-annealed high-purity antimony and are considered accurate to within $\pm 1\%$ of the true values at moderate temperatures and $\pm 2\%$ near the melting point and above. The thermal conductivity at maximum is highly sensitive to small physical and chemical variations among different specimens, and the conductivity values below 100 K only represent a typical curve serving to indicate the general trend of the low-temperature behavior of the thermal conductivity.

* Extrapolated

† Values below 100 K are merely typical values.

THERMAL CONDUCTIVITY OF ARGON

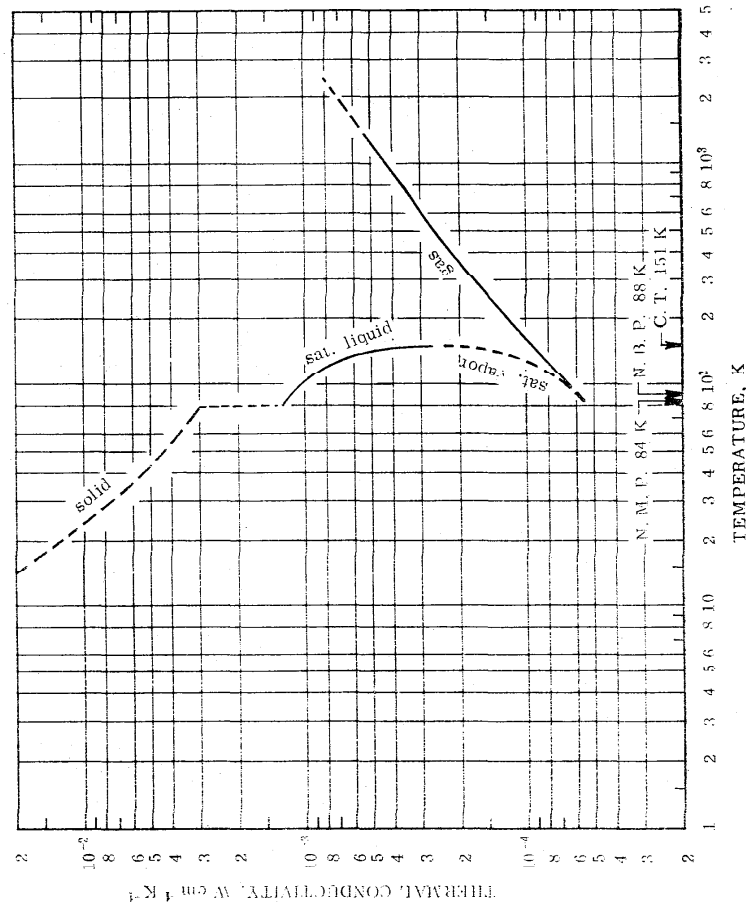

SOLID		SATURATED LIQUID		SATURATED VAPOR	
T	k x 10 ³	T	k x 10 ³	T	k x 10 ³
8	60*	84	1.270*	85	0.055*
9	46*	85	1.258	90	0.059*
10	37*	90	1.201	95	0.064*
12	27*	95	1.142	100	0.068*
14	22*	100	1.082	105	0.072*
15	18*	105	1.021	110	0.077*
16	16*	110	0.963	115	0.082*
18	13.6*	115	0.903	120	0.088*
20	9.9*	120	0.842	125	0.095*
25	7.8*	125	0.780	130	0.103*
30	6.5*	130	0.718	135	0.109*
35	5.6*	135	0.655	140	0.120*
40	5.1*	140	0.592	145	0.140*
45	4.6*	145	0.518	150	0.19*
50	3.8*	150	0.404	151	0.25*†
60	3.3*	151	0.25†		
70	3.0*				
80					

THERMAL CONDUCTIVITY, W cm⁻¹ K⁻¹

TEMPERATURE, K

REMARKS

Values for the solid are of only moderate accuracy, due to structural variations produced by impurities. From 8 to 20 K the uncertainty may be as much as 50%, the uncertainty gradually decreasing to 10% at the highest temperatures tabulated. Saturated liquid values below 140 K should be accurate to a few percent. At higher temperatures the uncertainty increases to as much as 25% at the critical point. Saturated vapor values should have a similar uncertainty below 125 K and at the critical point. At intermediate temperatures the uncertainty is somewhat larger. The gas values should be accurate to within 1% from 100 to 500 K, 5% below 100 K and from 500 to 1500 K and 10% above 1500 K.

* Estimated or extrapolated, hence provisional.

† Pseudo-critical value.

THERMAL CONDUCTIVITY OF ARGON (continued)

RECOMMENDED VALUES


GAS

(At 1 atm)

T	k x 10 ³	T	k x 10 ³	T	k x 10 ³	T	k x 10 ³
88	0.0574 [*]	420	0.2359	780	0.362	1650	0.602 [*]
90	0.0587	440	0.2430	790	0.366	1700	0.615 [*]
100	0.0652	450	0.2441	800	0.369	1750	0.628 [*]
110	0.0716	460	0.2451	810	0.372	1800	0.641 [*]
120	0.0779	470	0.2520	820	0.375	1850	0.654 [*]
130	0.0839	480	0.2559	830	0.378	1900	0.667 [*]
140	0.0898	490	0.2599	840	0.381	1950	0.680 [*]
150	0.0957	500	0.2638	850	0.384	2000	0.692 [*]
160	0.1016	510	0.263	860	0.387	2100	0.717 [*]
170	0.1074	520	0.272	870	0.390	2200	0.741 [*]
180	0.1131	530	0.275	880	0.393	2300	0.766 [*]
190	0.1188	540	0.280	890	0.396	2400	0.790 [*]
200	0.1244	550	0.283	900	0.398	2500	0.815 [*]
210	0.1300	560	0.287	910	0.401		
220	0.1355	570	0.290	920	0.404		
230	0.1409	580	0.294	930	0.407		
240	0.1462	590	0.297	940	0.410		
250	0.1515	600	0.301	950	0.413		
260	0.1567	610	0.305	960	0.416		
270	0.1619	620	0.308	970	0.418		
280	0.1671	630	0.311	980	0.421		
290	0.1722	640	0.315	990	0.424		
300	0.1772	650	0.319	1000	0.427		
310	0.1822	660	0.322	1050	0.441		
320	0.1871	670	0.326	1100	0.454		
330	0.1919	680	0.329	1150	0.468		
340	0.1966	690	0.333	1200	0.481		
350	0.2013	700	0.336	1250	0.495		
360	0.2059	710	0.339	1300	0.508		
370	0.2103	720	0.343	1350	0.521		
380	0.2147	730	0.346	1400	0.535 [*]		
390	0.2190	740	0.349	1450	0.548 [*]		

* Estimated or extrapolated.

THERMAL CONDUCTIVITY OF ARSENIC

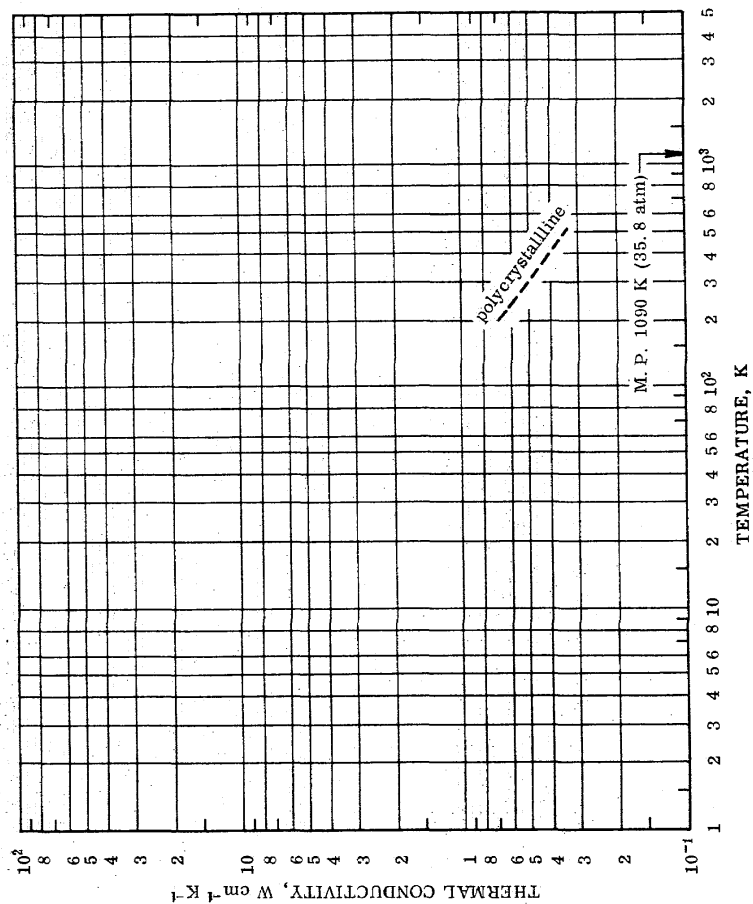

PROVISIONAL VALUES
 [Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]


SOLID	
Gray, polycrystalline	
T	k
200	0.690*
223.2	0.633*
250	0.578*
273.2	0.539*
293.2	0.510
298.2	0.502*
300	0.500*
323.2	0.474*
350	0.446*
373.2	0.427*
400	0.406*
473.2	0.360*
500	0.348*

REMARKS

The provisional values are for well-annealed high-purity polycrystalline grey arsenic and should be good to within ±15%.

* Extrapolated or estimated.

THERMAL CONDUCTIVITY OF BARIUM

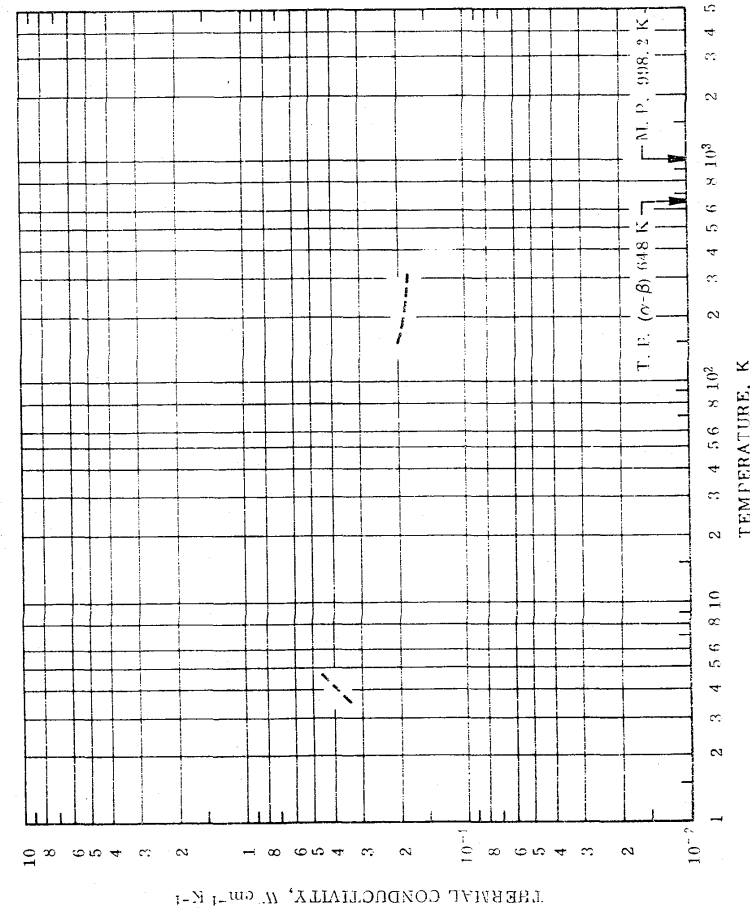

PROVISIONAL VALUES
 [Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]


SOLID	
T	k
4	0.39*
150	0.205*
173.2	0.199*
200	0.194*
223.2	0.190*
250	0.186*
273.2	0.185*
295	0.184*

REMARKS

The provisional values are for well-annealed high-purity barium and should be good to ±20%. The value at 4 K is applicable only to barium having residual electrical resistivity $\rho_0 \leq 0.25 \mu\Omega \text{ cm}$.

* Estimated.

THERMAL CONDUCTIVITY OF BERYLLIUM

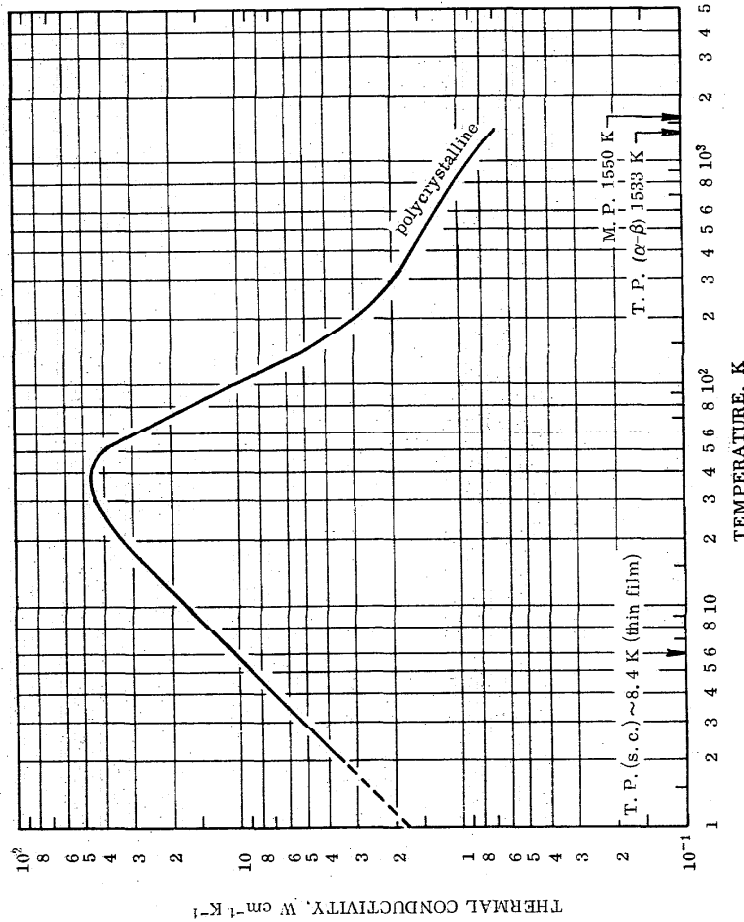

REMARKS

The recommended values (above 290 K) are based on measurements on high-purity beryllium and their uncertainty is thought to be of the order of $\pm 10\%$. The thermal conductivity at temperatures near and below the corresponding temperature, T_m , of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens, and the conductivity values below 290 K, which are provisional are only applicable to beryllium having residual electrical resistivity $\rho_0 = 0.0135\ \mu\Omega\ cm$. Values at temperatures below about 1.5 K are calculated to fit the experimental data by using equation (7) and using $n = 2.80$, $\alpha' = 2.56 \times 10^{-7}$, and $\beta = 0.553$.

RECOMMENDED VALUES †
 [Temperature, T, K; Thermal Conductivity, k, $W\ cm^{-1}\ K^{-1}$]

SOLID

T	k	T	k
0	0	250	2.36
1	1.81*	273.2	2.18
2	3.62	298.2	2.01
3	5.42	300	2.00
4	7.23	323.2	1.88
5	9.04	350	1.78
6	10.8	373.2	1.68
7	12.6	400	1.61
8	14.4	473.2	1.44
9	16.2	500	1.39
10	18.0	573.2	1.29
11	19.8	600	1.26
12	21.6	673.2	1.18
13	23.3	700	1.15
14	25.1	773.2	1.09
15	26.8	800	1.06
16	28.4	873.2	1.00
18	31.7	900	0.982
20	34.8	973.2	0.927
25	41.2	1000	0.908
30	45.6	1073.2	0.858
35	47.2	1100	0.842
40	46.2	1173.2	0.802
45	44.2	1200	0.787
50	40.0	1273.2	0.751
60	29.8	1300	0.738
70	21.7	1373.2	0.705
80	16.2	1400	0.694
90	12.5		
100	9.90		
123.2	6.54		
150	4.51		
173.2	3.64		
200	3.01		
223.2	2.66		

* Extrapolated.
 † Values below 290 K are provisional.

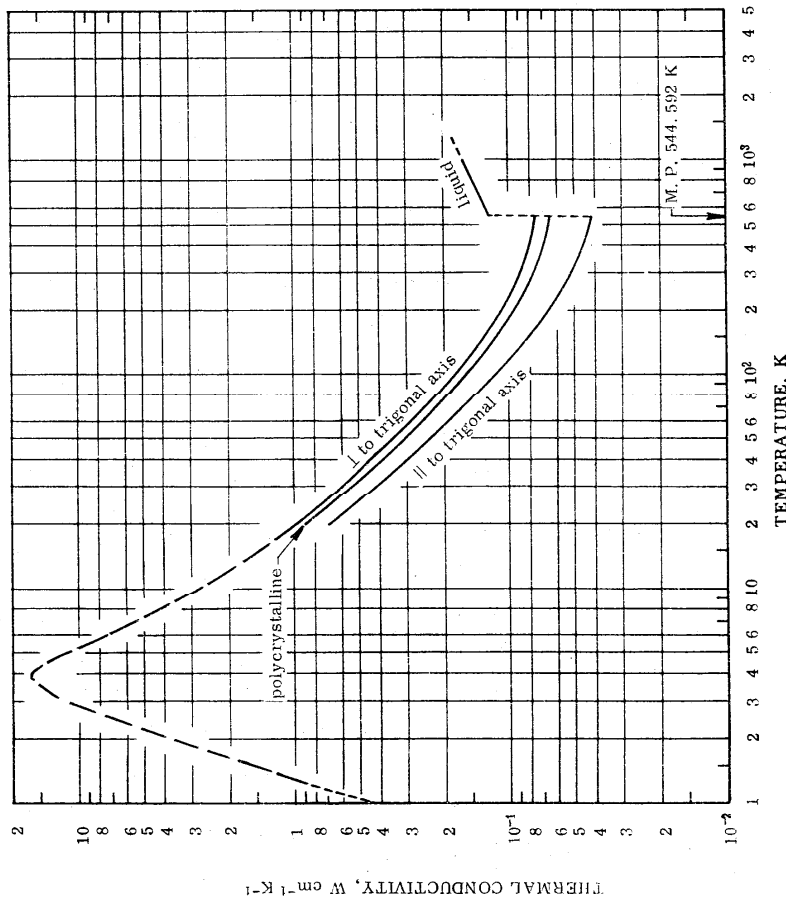


FIGURE 1

The values are for well-annealed high-purity bismuth. The probable uncertainty of the recommended values (those above 20 K) is of the order of ± 5 to $\pm 10\%$ for the solid state at room temperature and above, increasing to ± 15 to $\pm 20\%$ for the molten state. The thermal conductivity at temperatures near and below the corresponding temperature of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens, and the conductivity values below 20 K only represent a typical curve serving to indicate the general trend of the low-temperature behavior of the thermal conductivity.

RECOMMENDED VALUES

[Temperature, T, K; Thermal Conductivity, k, $W\ cm^{-1}\ K^{-1}$]

SOLID

T	// to trigonal axis k	⊥ to trigonal axis k	Polycrystalline k	T	// to trigonal axis k	⊥ to trigonal axis k	Polycrystalline k
0	0	0	0	250	0.0581	0.0995	0.0857
1	0.452*	0.452*	0.452*	273.2	0.0554	0.0953	0.0822
2	3.94	3.94	3.94	298.2	0.0530	0.0919	0.0792
3	11.8	11.8	11.8	300	0.0528	0.0915	0.0786
4	17.1	17.1	17.1	323.2	0.0510	0.0890	0.0766
5	11.9	11.9	11.9	350	0.0491	0.0860	0.0737
6	7.98	7.98	7.98	373.2	0.0481	0.0844	0.0722
7	5.77	5.77	5.77	400	0.0469	0.0822	0.0704
8	4.40	4.40	4.40	473.2	0.0446	0.0784	0.0669
9	3.50	3.50	3.50	500	0.0438	0.0775	0.0663
10	2.88	2.88	2.88	544.592	0.0429	0.0761	0.0650
11	2.45	2.45	2.45				
12	2.11	2.11	2.11				
13	1.85	1.85	1.85				
14	1.65	1.65	1.65				
15	1.48	1.48	1.48				
16	1.36	1.36	1.36				
18	1.15	1.15	1.15				
20	1.00	1.00	1.00				
25	0.538	0.780	0.695				
30	0.434	0.635	0.568				
35	0.364	0.536	0.478				
40	0.311	0.465	0.414				
45	0.272	0.410	0.365				
50	0.243	0.367	0.326				
60	0.199	0.303	0.268				
70	0.168	0.260	0.231				
80	0.148	0.230	0.203				
90	0.131	0.206	0.182				
100	0.119	0.188	0.165				
123.2	0.0904	0.159	0.138				
150	0.0826	0.136	0.118				
173.2	0.0739	0.123	0.107				
200	0.0667	0.112	0.0961				
223.2	0.0612	0.105	0.0904				

LIQUID


T	k
544.592	0.124
573.2	0.128
600	0.131
673.2	0.138
700	0.141
773.2	0.148
800	0.150
873.2	0.157
900	0.159
973.2	0.166
1000	0.168
1073.2	0.172*
1100	0.175*
1173.2	0.179*
1200	0.182*
1273.2	0.185*
1300	0.188*

* Extrapolated.

THERMAL CONDUCTIVITY OF BORON

RECOMMENDED VALUES †
 [Temperature, T, K; Thermal Conductivity, k , $W\text{ cm}^{-1}\text{ K}^{-1}$]

T		k	
0	123.2	1.85	
1	150	0.985	
2	173.2	0.718	
3	200	0.551	
4	223.2	0.454	
5	250	0.371	
6	273.2	0.318	
7	288.2	0.274	
8	300	0.270	
9	323.2	0.240	
10	350	0.209	
11	373.2	0.188	
12	400	0.168	
13	473.2	0.133	
14	500	0.125	
15	573.2	0.109	
16	600	0.106	
18	673.2	0.0994	
20	700	0.0981	
25	773.2	0.0964	
30	800	0.0960	
35	873.2	0.0966	
40	900	0.0969	
45	973.2	0.0980	
50	1000	0.0985	
60	1073.2	0.100	
70	1100	0.101	
80	2.63		
90	2.24		
100	1.90		

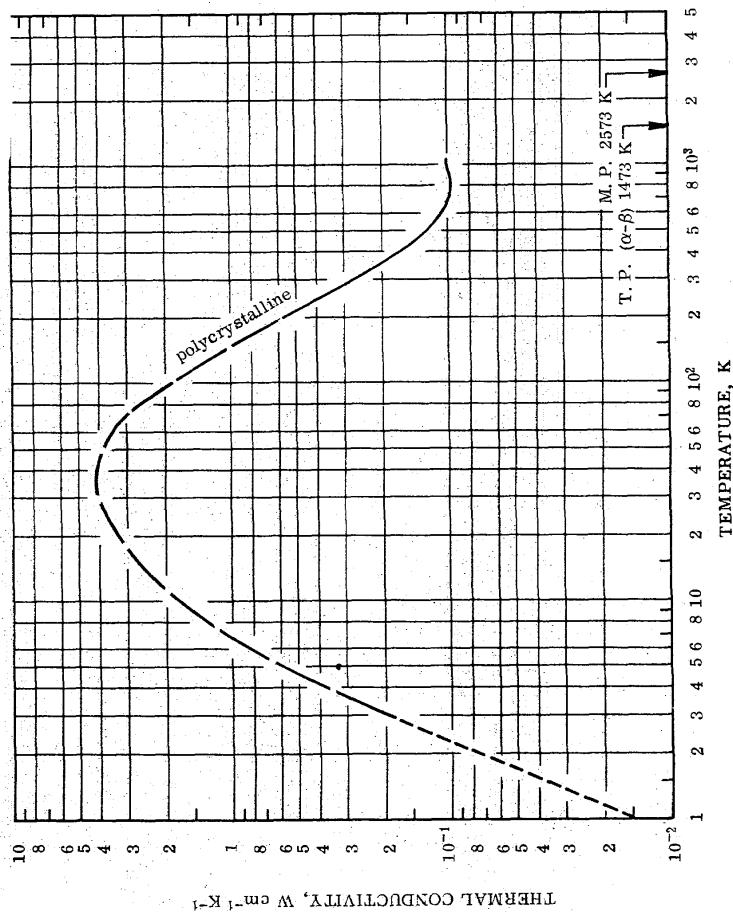


REMARKS

The values are for well-annealed high-purity boron. The recommended values (those above 200 K) are probably accurate to within ± 10 to $\pm 15\%$. The thermal conductivity at temperatures near and below the corresponding temperature of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens, and the conductivity values below 200 K only represent a typical curve serving to indicate the general trend of the low-temperature behavior of the thermal conductivity.

* Extrapolated.
 † Values below 200 K are merely typical values.

THERMAL CONDUCTIVITY OF BROMINE

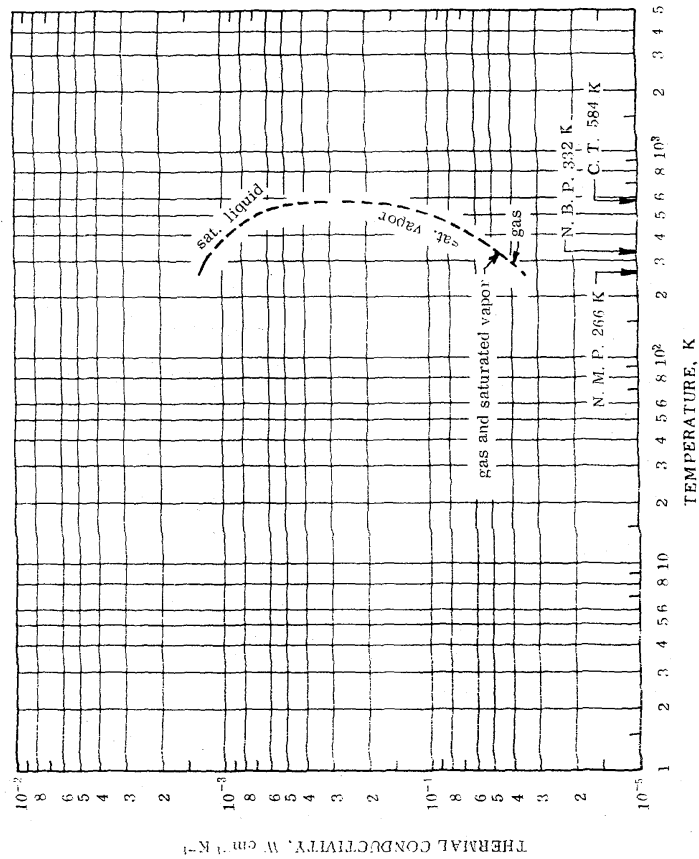


SATURATED LIQUID		SATURATED VAPOR		GAS	
T	k x 10 ³	T	k x 10 ³	T	k x 10 ³
266	1.31*	300	0.047*	250	0.038*
270	1.30*	310	0.049*	260	0.040*
280	1.27	320	0.051*	270	0.042*
280	1.27	330	0.053*	280	0.044*
280	1.25	340	0.055*	290	0.046*
300	1.22	350	0.057*	300	0.048*
310	1.20	360	0.059*	310	0.049*
320	1.18	370	0.061*	320	0.051*
330	1.16*	380	0.063*	330	0.053*
340	1.14*	390	0.065*	340	0.055*
350	1.11*	400	0.068*	350	0.057*
360	1.09*	410	0.070*		
370	1.06*	420	0.072*		
380	1.04*	430	0.075*		
390	1.02*	440	0.078*		
400	0.99*	450	0.080*		
410	0.97*	460	0.084*		
420	0.94*	470	0.087*		
430	0.92*	480	0.091*		
440	0.89*	490	0.095*		
450	0.87*	500	0.099*		
460	0.84*	510	0.104*		
470	0.82*	520	0.109*		
480	0.79*	530	0.116*		
490	0.76*	540	0.123*		
500	0.73*	550	0.144*		
510	0.70*	560	0.16*		
520	0.66*	570	0.19*		
530	0.63*	580	0.23*		
540	0.59*	584	0.28*†		
550	0.55*				
560	0.50*				
570	0.44*				
580	0.35*				
584	0.28*†				

REMARKS

Severe disagreement exists between experimental and estimated values for the liquid above 305 K. No experimental measurements above 325 K were found. An uncertainty of 15% below 500 K and an unknown amount at higher temperatures appears probable. The vapor values are based on a correlation. Uncertainties of 10% below 450 K, 15% from 450 to 550 K and unknown accuracy above 550 K appear probable. The gas values are of uncertain accuracy.

* Estimated or extrapolated, hence provisional.
 † Pseudo-critical value.

THERMAL CONDUCTIVITY OF CADMIUM

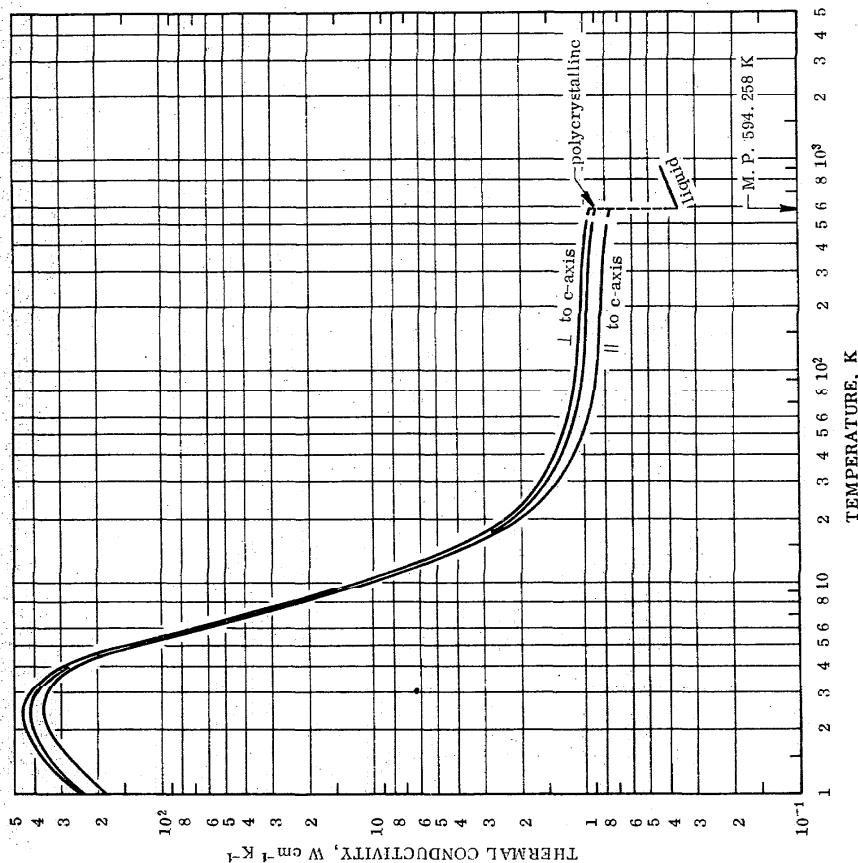

REMARKS

The recommended values are for well-annealed high-purity cadmium and are thought to be accurate to within $\pm 20\%$ at low temperatures, $\pm 4\%$ at normal and moderate temperatures, $\pm 6\%$ for the solid and $\pm 12\%$ for the liquid near the melting point. The thermal conductivity at temperatures near and below the corresponding temperature, T_m , of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens, and the conductivity values below 100 K for k_{II} , k_I , and k_{poly} are applicable only to samples having residual electrical resistivities of 0.000134, 0.000103, and 0.000112 $\mu\Omega$ cm, respectively. Values at temperatures below about 1.5 T_m are calculated by equation (7) and using the constants m , h , α^* as given in Table I and the parameter $\beta = 0.0055$, 0.0042, and 0.0046, respectively, for k_{II} , k_I , and k_{poly} .

* Estimated or extrapolated, hence provisional.
 † Pseudo-critical value.

RECOMMENDED VALUES †

[Temperature, T, K; Thermal Conductivity, k, $W\ cm^{-1}\ K^{-1}$]

T	// to c-axis		I to c-axis		II to c-axis		T	// to c-axis		I to c-axis		T	// to c-axis		I to c-axis	
	k	k	k	k	k	k		k	k	k	k		k	k	k	k
0	0	0	0	0	0	0	250	0.840	1.05	0.840	1.05	0.980	0.840	1.05	0.840	1.05
1	182	239	220	273.2	273.2	273.2	273.2	0.855	1.04	0.855	1.04	0.975	0.855	1.04	0.855	1.04
2	343	442	409	498.2	498.2	498.2	300	0.830	1.04	0.830	1.04	0.968	0.830	1.04	0.830	1.04
3	354	432	406	432	432	432	323.2	0.826	1.03	0.826	1.03	0.963	0.826	1.03	0.826	1.03
4	264	314	297	314	314	314	350	0.821	1.03	0.821	1.03	0.958	0.821	1.03	0.821	1.03
5	157	167	164	167	167	167	373.2	0.816	1.02	0.816	1.02	0.953	0.816	1.02	0.816	1.02
6	73.8	76.8	75.8	76.8	76.8	76.8	400	0.811	1.01	0.811	1.01	0.947	0.811	1.01	0.811	1.01
7	40.0	42.8	41.9	42.8	42.8	42.8	473.2	0.793	0.990	0.793	0.990	0.928	0.793	0.990	0.793	0.990
8	24.6	26.7	25.7	26.7	26.7	26.7	500	0.786	0.980	0.786	0.980	0.920	0.786	0.980	0.786	0.980
9	16.3	17.6	17.2	17.6	17.6	17.6	573.2	0.760	0.951	0.760	0.951	0.891	0.760	0.951	0.760	0.951
10	11.5	12.5	12.2	12.5	12.5	12.5	594.258	0.751	0.942	0.751	0.942	0.880	0.751	0.942	0.751	0.942
11	8.68	9.50	9.23	9.50	9.50	9.50										
12	6.74	7.44	7.21	7.44	7.44	7.44										
13	5.44	6.05	5.85	6.05	6.05	6.05										
14	4.44	5.01	4.83	5.01	5.01	5.01										
15	3.76	4.26	4.09	4.26	4.26	4.26										
16	3.23	3.67	3.52	3.67	3.67	3.67										
18	2.56	2.88	2.75	2.88	2.88	2.88										
20	2.07	2.44	2.32	2.44	2.44	2.44										
25	1.59	1.92	1.81	1.92	1.92	1.92										
30	1.37	1.67	1.57	1.67	1.67	1.67										
35	1.23	1.51	1.42	1.51	1.51	1.51										
40	1.13	1.41	1.32	1.41	1.41	1.41										
45	1.07	1.34	1.24	1.34	1.34	1.34										
50	1.03	1.28	1.20	1.28	1.28	1.28										
60	0.970	1.21	1.13	1.21	1.21	1.21										
70	0.930	1.16	1.08	1.16	1.16	1.16										
80	0.905	1.13	1.06	1.13	1.13	1.13										
90	0.892	1.11	1.04	1.11	1.11	1.11										
100	0.883	1.10	1.03	1.10	1.10	1.10										
123.2	0.872	1.09	1.02	1.09	1.09	1.09										
150	0.854	1.08	1.01	1.08	1.08	1.08										
173.2	0.856	1.07	1.00	1.07	1.07	1.07										
200	0.851	1.06	0.993	1.06	1.06	1.06										
223.2	0.846	1.05	0.987	1.05	1.05	1.05										


† Values for the liquid state are provisional.

THERMAL CONDUCTIVITY OF CALCIUM

PROVISIONAL VALUES
 [Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]

SOLID

T	k
200	2.21*
223.2	2.16*
250	2.10*
273.2	2.06*
298.2	2.01*
300	2.01*
323.2	1.98*
350	1.94*
373.2	1.92*
400	1.89*
473.2	1.83*
500	1.82*
573.2	1.79*
600	1.78*
673.2	1.77*
700	1.76*
737	1.76*
773.2	1.63*
800	1.53*
873.2	1.32*
900	1.27*
973.2	1.18*
1000	1.16*

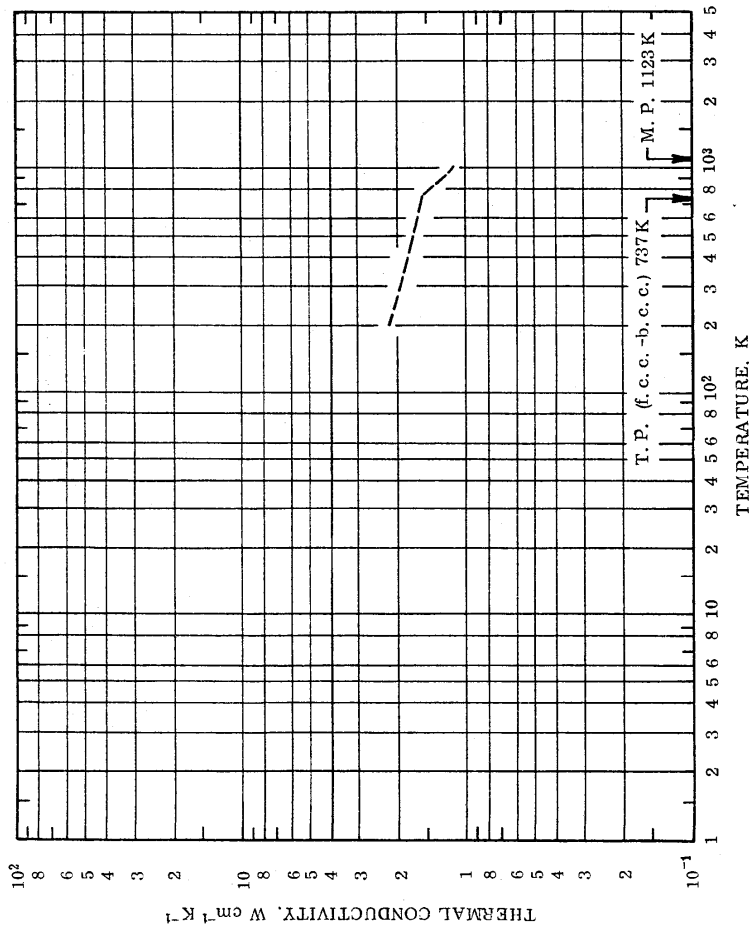


REMARKS

The provisional values are estimates based on the reported electrical resistivity for high-purity calcium and should be good to $\pm 20\%$.

* Estimated, hence provisio

THERMAL CONDUCTIVITY OF CARBON (amorphous)

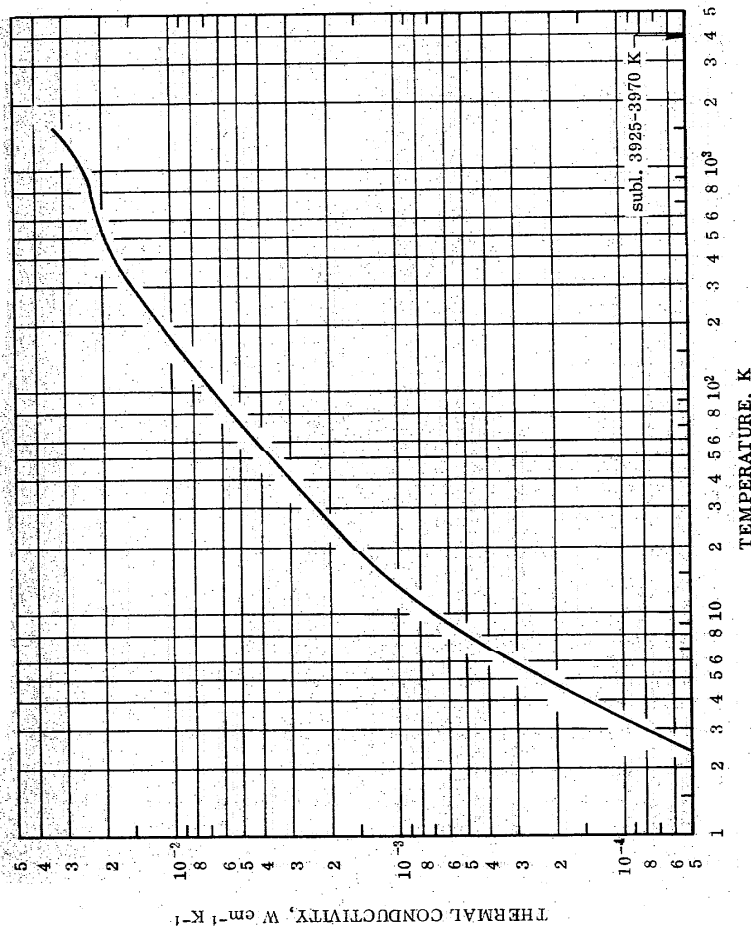

RECOMMENDED VALUES †

† Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹


T	k	T	k
0	0	250	0.0140
1	0.0000361	273.2	0.0150
2	0.0000859	298.2	0.0159
3	0.000155	300	0.0160
4	0.000236	323.2	0.0168
5	0.000325	350	0.0176
6	0.000419	373.2	0.0182
7	0.000514	400	0.0187
8	0.000610	473.2	0.0202
9	0.000705	500	0.0206
10	0.000795	573.2	0.0216
11	0.000890	600	0.0219
12	0.000982	673.2	0.0226
13	0.00107	700	0.0229
14	0.00117	773.2	0.0235
15	0.00126	800	0.0237
16	0.00143	873.2	0.0242
18	0.00160	900	0.0244
20	0.00200	973.2	0.0250
25	0.00239	1000	0.0253
30	0.00276	1073.2	0.0262
35	0.00312	1100	0.0267
40	0.00345	1173.2	0.0279
45	0.00377	1200	0.0284
50	0.00440	1273.2	0.0297
60	0.00500	1300	0.0302
70	0.00558	1373.2	0.0318
80	0.00614	1400	0.0324
90	0.00668	1473.2	0.0341
100	0.00798	1500	0.0348
123.2	0.00938		
150	0.0106		
173.2	0.0118		
200	0.0129		
223.2			

† Values below room temperature are provisional.

REMARKS

The recommended values are for high-purity amorphous carbon and are thought to be accurate to within ±10 to 20% above room temperature. Values below room temperature are provisional and their uncertainty is considerably larger.

THERMAL CONDUCTIVITY OF DIAMOND

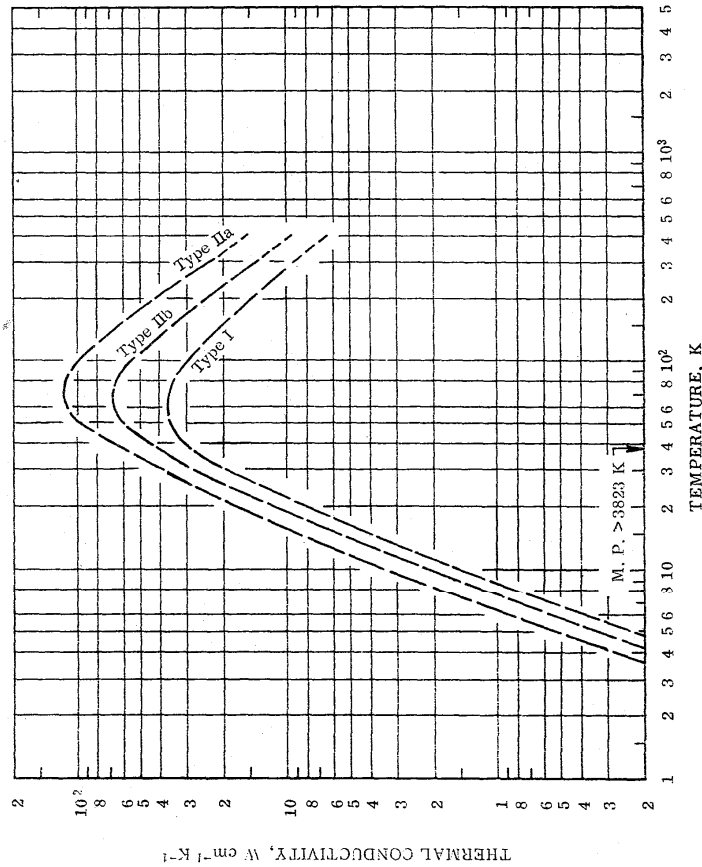

TYPICAL VALUES
[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]

SOLID


T	Type I k	Type IIa k	Type IIb k	T	Type I k	Type IIa k	Type IIb k
2	0.0138*	0.0331*	0.0200*	40	29.4	65.9	44.0
3	0.0461	0.111	0.0676	45	32.9	70.3	52.3
4	0.108	0.261	0.160	50	35.3	92.1	59.1
5	0.206	0.494	0.307	60	37.4	112	67.5
6	0.344	0.820	0.510	70	36.9	119	69.1
7	0.523	1.24	0.778	80	35.1	117	65.7
8	0.762	1.77	1.12	90	32.7	109	60.0
9	1.05	2.41	1.53	100	30.0	100	54.2
10	1.40	3.17	2.03	123.2	24.2	79.2	41.8
11	1.79	4.00	2.58	150	19.5	60.2	32.5
12	2.24	5.00	3.22	173.2	16.6	49.3	27.0
13	2.76	6.10	3.96	200	14.1	40.3	22.6
14	3.33	7.32	4.77	223.2	12.5	34.7	19.7
15	3.96	8.65	5.66	250	11.0	29.7	17.0
16	4.65	10.0	6.62	273.2	9.94	26.2	15.2
18	6.15	13.2	8.75	298.2	9.00	23.2	13.6
20	7.87	16.8	11.2	300	8.95	23.0	13.5
25	12.9	27.1	18.2	323.2	8.26*	20.7*	12.3*
30	18.8	38.9	26.5	350	7.55*	18.5*	11.1*
35	24.5	51.8	35.0	373.2	7.03*	17.0*	10.2*
				400	6.50*	15.4*	9.32*

REMARKS

The 3 sets of thermal conductivity values only represent 3 typical curves serving to indicate the general trend of the thermal conductivity of the three types of diamond.

* Extrapolated.

THERMAL CONDUCTIVITY OF ACHESON GRAPHITE

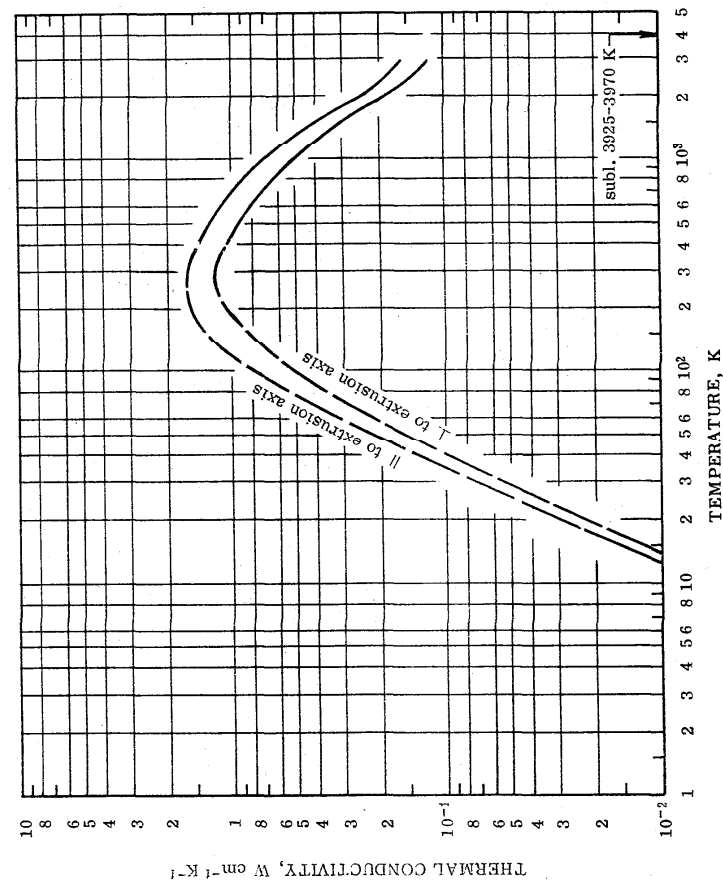

REMARKS

The values above 400 K are recommended values for Acheson graphite and are considered accurate to within ± 10 to $\pm 20\%$. The values below 400 K are merely typical values and represent a typical curve serving only to indicate the general trend of the thermal conductivity of Acheson graphite at moderate and low temperatures, since the thermal conductivity at temperatures near and below the corresponding temperature of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens.

RECOMMENDED VALUES †

[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]


SOLID

T	to axis of extrusion k	⊥ to axis of extrusion k	T	to axis of extrusion k	⊥ to axis of extrusion k
10	0.00606*	0.00470*	1073.2	0.644	0.488
20	0.0320*	0.0235*	1100	0.626	0.474
30	0.0791*	0.0568*	1173.2	0.576	0.436
40	0.148*	0.103*	1200	0.559	0.422
50	0.235*	0.158*	1273.2	0.516	0.389
60	0.337*	0.223*	1300	0.501	0.377
70	0.450*	0.293*	1373.2	0.462	0.348
80	0.571†	0.366*	1400	0.449	0.338
90	0.694*	0.439*	1473.2	0.412	0.312
100	0.814	0.513*	1500	0.401	0.304
123.2	1.07	0.674	1573.2	0.372	0.281
150	1.32	0.844	1600	0.361	0.274
173.2	1.48	0.966	1673.2	0.337	0.255
200	1.62	1.08	1700	0.327	0.248
223.2	1.68	1.16	1773.2	0.308	0.232
250	1.70	1.19	1800	0.296	0.226
273.2	1.69	1.21	1873.2	0.277	0.212
298.2	1.65	1.19	1900	0.269	0.207
303	1.65	1.19	1973.2	0.252	0.195
323.2	1.61	1.18	2000	0.247	0.190
350	1.55	1.14	2073.2	0.233*	0.179
373.2	1.50	1.11	2173.2	0.217*	0.166
400	1.45	1.07	2200	0.213*	0.166
473.2	1.31	0.963	2273.2	0.203*	0.155
500	1.27	0.927	2400	0.191*	0.144
573.2	1.16	0.846	2473.2	0.185*	0.139
600	1.12	0.816	2600	0.176*	0.132
673.2	1.02	0.751	2673.2	0.171*	0.129
700	0.988	0.729	2800	0.166*	0.125
773.2	0.906	0.674	2873.2	0.163*	0.123
800	0.875	0.654	3000	0.161*	0.122
873.2	0.803	0.607			
900	0.778	0.589			
973.2	0.717	0.544			
1000	0.695	0.528			

* Extrapolated.

† Values below 400 K are merely typical values.

THERMAL CONDUCTIVITY OF AGOT GRAPHITE

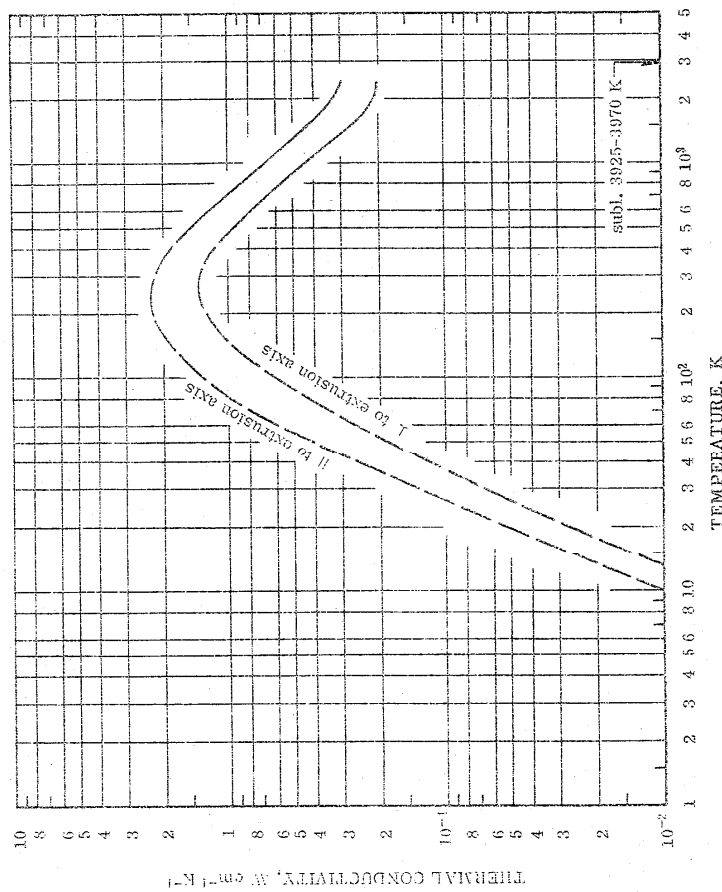

REMARKS

The values above 400 K are recommended values for AGOT graphite and are considered accurate to within ± 10 to $\pm 20\%$. The values below 400 K are merely typical values and represent a typical curve serving only to indicate the general trend of the thermal conductivity of AGOT graphite at moderate and low temperatures, since the thermal conductivity at temperatures near and below the corresponding temperature of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens.

RECOMMENDED VALUES †

† Temperature, T, K; Thermal Conductivity, k, $W\ cm^{-1}\ K^{-1}$

SOLID

T	to axis of extrusion k	l. to axis of extrusion k	T	to axis of extrusion k	l. to axis of extrusion k
10	0.00994	0.00515	1073.2	0.635	0.405
20	0.0531	0.0256	1100	0.618	0.394
30	0.138	0.0628	1173.2	0.573	0.366
40	0.262	0.117	1200	0.558	0.355
50	0.414	0.184	1273.2	0.516	0.330
60	0.587	0.261	1300	0.503	0.323
70	0.776	0.345	1373.2	0.479	0.303
80	0.968	0.434	1400	0.459	0.295
90	1.16	0.523	1473.2	0.431	0.277
100	1.33	0.612	1500	0.421	0.272
123.2	1.67	0.810	1573.2	0.400	0.259
150	1.98	1.02	1600	0.392	0.255
173.2	2.16	1.18	1673.2	0.375	0.245
200	2.28	1.31	1700	0.369	0.242
223.2	2.32	1.38	1773.2	0.356	0.234
250	2.30	1.41	1800	0.352	0.231
273.2	2.28	1.41	1873.2	0.341	0.224
298.2	2.21	1.38	1900	0.340	0.222
300	2.20	1.38	1973.2	0.332	0.218
323.2	2.14	1.34	2000	0.330	0.217
350	2.03	1.27	2073.2	0.324	0.214
373.2	1.95	1.22	2173.2	0.317	0.212
400	1.85	1.16	2200	0.316	0.211
473.2	1.59	0.998	2273.2	0.312	0.209
500	1.50	0.945	2400	0.304	0.204
573.2	1.31	0.820	2473.2	0.297*	0.200*
600	1.24	0.779			
673.2	1.10	0.691			
700	1.05	0.660			
773.2	0.936	0.591			
800	0.898	0.569			
873.2	0.810	0.505			
900	0.780	0.497			
973.2	0.711	0.454			
1000	0.688	0.440			

* Extrapolated.

† Values below 400 K are merely typical values.

THERMAL CONDUCTIVITY OF THE ELEMENTS


RECOMMENDED VALUES †

[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]

SOLID

T	// to molding pressure k	⊥ to molding pressure k	T	// to molding pressure k	⊥ to molding pressure k
10	0.00396*	0.00529 [‡]	1073.2	0.465	0.607
20	0.0192*	0.0245*	1100	0.458	0.595
30	0.0457*	0.0597*	1173.2	0.437	0.566
40	0.0826*	0.109*	1200	0.430	0.556
50	0.128*	0.171*	1273.2	0.413	0.532
60	0.181*	0.241*	1300	0.407	0.524
70	0.238*	0.319*	1373.2	0.393	0.504
80	0.298*	0.400*	1400	0.389	0.497
90	0.357*	0.488*	1473.2	0.376	0.480
100	0.415	0.571	1500	0.372	0.474
123.2	0.541	0.752	1573.2	0.361	0.460
150	0.673	0.946	1600	0.358	0.455
173.2	0.771	1.08	1673.2	0.349	0.443
200	0.865	1.20	1700	0.346	0.438
223.2	0.922	1.27	1773.2	0.338	0.438
250	0.965	1.30	1800	0.336	0.424
273.2	0.984	1.31	1873.2	0.329	0.414
298.2	0.982	1.29	1900	0.327	0.411
300	0.982	1.29	1973.2	0.321	0.403
323.2	0.972	1.27	2000	0.319	0.400
350	0.952	1.24	2073.2	0.314	0.392
373.2	0.933	1.21	2173.2	0.307	0.383
400	0.907	1.18	2200	0.305	0.380
473.2	0.834	1.08	2273.2	0.301	0.374
500	0.808	1.05	2400	0.293	0.364
573.2	0.742	0.967	2473.2	0.288	0.358
600	0.718	0.938	2600	0.280	0.346
673.2	0.665	0.870	2673.2	0.275	0.340
700	0.645	0.844	2800	0.266	0.328
773.2	0.599	0.785	2873.2	0.260	0.321
800	0.583	0.763	3000	0.250	0.308
873.2	0.546	0.712	3073	0.244*	0.300*
900	0.532	0.693	3200	0.233*	0.283*
973.2	0.501	0.653	3273	0.225*	0.273*
1000	0.491	0.640	3400	0.209*	0.252*
			3600	0.170*	0.204*
			3800	0.095*	0.113*


* Extrapolated.
† Values below 400 K are merely typical values.

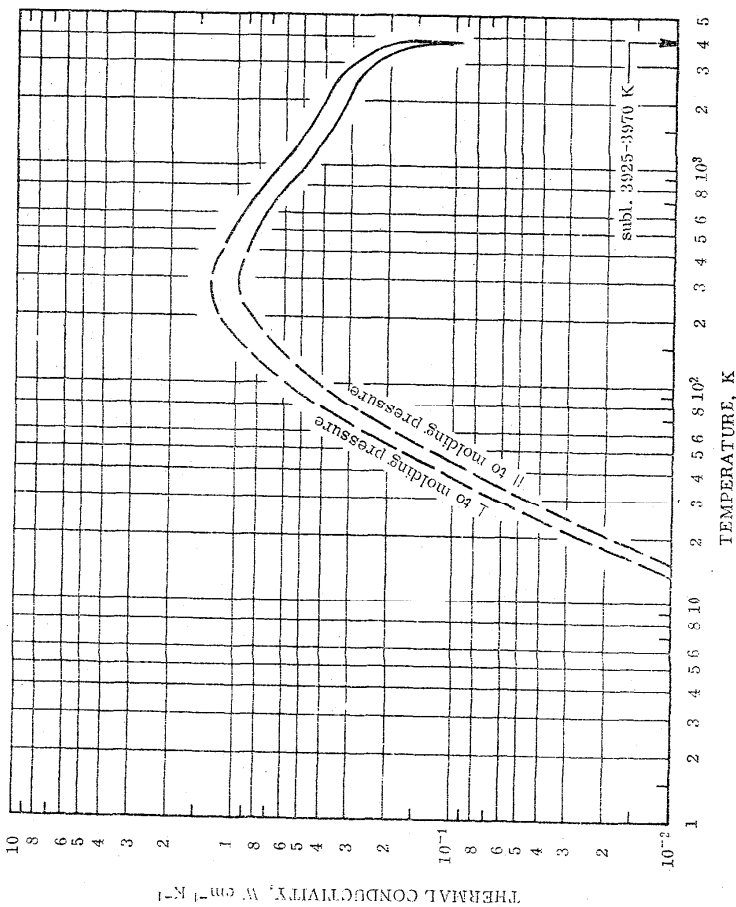

REMARKS

The values above 400 K are recommended values for ATJ graphite and are considered accurate to within ±10 to ±20%. The values below 400 K are merely typical values and represent two typical curves serving only to indicate the general trend of the thermal conductivity of ATJ graphite at moderate and low temperatures, since the thermal conductivity at temperatures near and below the corresponding temperature of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens.

THERMAL CONDUCTIVITY OF AWG GRAPHITE

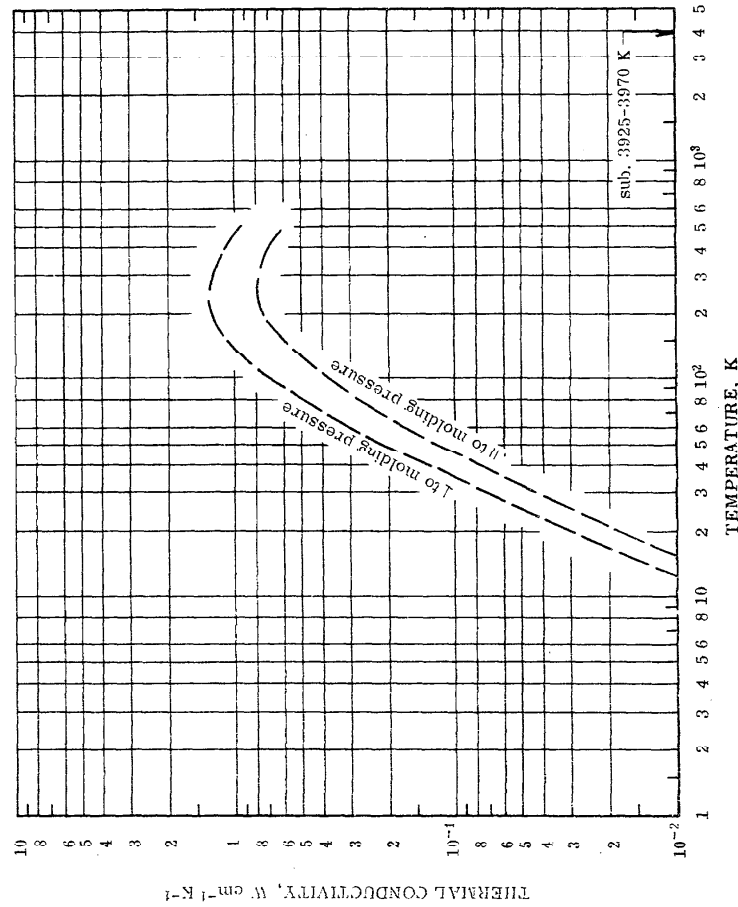


TYPICAL VALUES
[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]

SOLID		
T	// to molding pressure k	⊥ to molding pressure k
10	0.00397	0.00583
20	0.0181	0.0298
30	0.0428	0.0730
40	0.0783	0.133
50	0.122	0.209
60	0.168	0.296
70	0.212	0.389
80	0.269	0.483
90	0.327	0.582
100	0.375	0.677
123.2	0.486	0.878
150	0.604	1.08
173.2	0.682	1.20
200	0.748	1.29
223.2	0.785	1.33
250	0.803	1.33
273.2	0.807	1.32
288.2	0.796	1.28
300	0.795	1.28
323.2	0.778	1.24
350	0.754	1.20
373.2	0.733	1.16
400	0.705	1.12
473.2	0.635	1.00
500	0.611	0.965

REMARKS

The values are merely typical values and represent two typical curves serving only to indicate the general trend of the thermal conductivity of AWG graphite.

THERMAL CONDUCTIVITY OF PYROLYTIC GRAPHITE

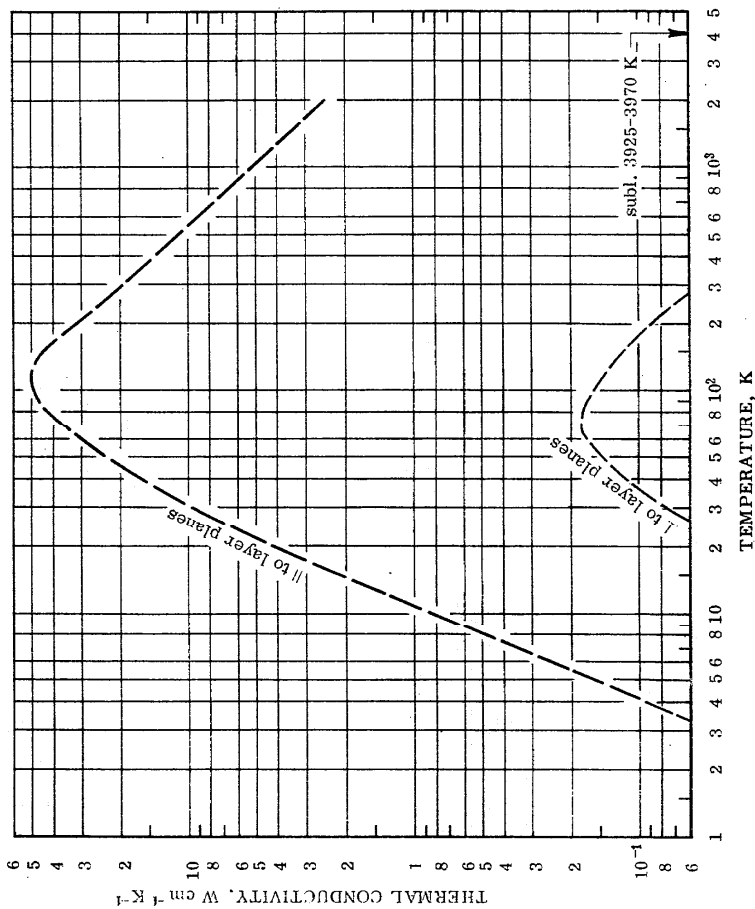

TYPICAL VALUES

[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]


SOLID

T	to layer planes k	⊥ to layer planes k	T	to layer planes k	⊥ to layer planes k
0	0	0	500	10.8	0.0322
10	0.811	0.1116	573.2	9.36	0.0281
20	4.20	0.0397	600	8.92	0.0268
30	9.86	0.0786	673.2	7.92	0.0238
40	16.4	0.120	700	7.59	0.0229
50	23.1	0.152	773.2	6.88	0.0207
60	29.8	0.173	800	6.67	0.0201
70	36.6	0.181	873.2	6.13	0.0184
80	42.8	0.181	900	5.94	0.0178
90	47.5	0.176	973.2	5.49	0.0164
100	49.7	0.168	1000	5.34	0.0160
123.2	50.4	0.148	1073.2	5.00	0.0148
150	45.1	0.125	1100	4.88	0.0145
173.2	38.7	0.108	1173.2	4.57	0.0136
200	32.3	0.0923	1200	4.48	0.0134
223.2	28.2	0.0814	1273.2	4.22	0.0126
250	24.4	0.0711	1300	4.13	0.0124
273.2	21.3	0.0636	1373.2	3.91	0.0118
298.2	19.6	0.0573	1400	3.84	0.0116
300	19.5	0.0570	1473.2	3.64	0.0110
323.2	17.8	0.0522	1500	3.57	0.0108
350	16.2	0.0477	1573.2	3.40	0.0102
373.2	15.1	0.0442	1600	3.33	0.0100
400	13.9	0.0409	1673.2	3.18	0.00962
473.2	11.4	0.0341	1700	3.12	0.00947
			1773.2	2.97	0.00909
			1800	2.93	0.00895
			1883.2	2.80	0.00860
			1900	2.77	0.00848
			1973.2	2.66	0.00817
			2000	2.62	0.00807

REMARKS

The values are merely typical values and represent two typical curves serving only to indicate the general trend for the thermal conductivity of pyrolytic graphite.

THERMAL CONDUCTIVITY OF 875S GRAPHITE

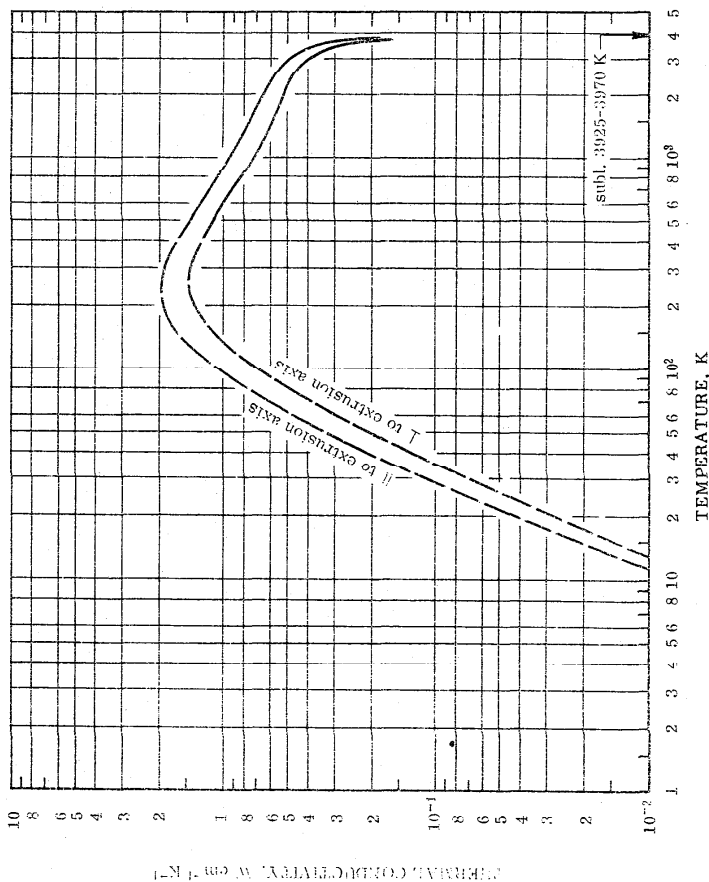

REMARKS

The values above 400 K are recommended values for 875S graphite and are considered accurate to within ± 10 to $\pm 20\%$. The values below 400 K are merely typical values and represent a typical curve serving only to indicate the general trend of the thermal conductivity of 875S graphite at moderate and low temperatures, since the thermal conductivity at temperatures near and below the corresponding temperature of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens.

RECOMMENDED VALUES†

[Temperature, T, K; Thermal Conductivity, k , $\text{W cm}^{-1} \text{K}^{-1}$]

SOLID

T	k	l to axis of extrusion	k	l to axis of extrusion	T	k	l to axis of extrusion	k	l to axis of extrusion
10	0.00750*	0.00529*	0.910	0.706	1073.2	0.910	0.706	0.910	0.706
20	0.0411*	0.0270*	0.898	0.696	1100	0.898	0.696	0.898	0.696
30	0.105*	0.0667*	0.868	0.673	1173.2	0.868	0.673	0.868	0.673
40	0.159*	0.122*	0.858	0.666	1200	0.858	0.666	0.858	0.666
50	0.321*	0.193*	0.833	0.646	1273.2	0.833	0.646	0.833	0.646
60	0.465*	0.277*	0.823	0.640	1300	0.823	0.640	0.823	0.640
70	0.616*	0.367*	0.800	0.623	1373.2	0.800	0.623	0.800	0.623
80	0.772*	0.463*	0.792	0.618	1400	0.792	0.618	0.792	0.618
90	0.930*	0.559*	0.773	0.603	1473.2	0.773	0.603	0.773	0.603
100	1.06*	0.660*	0.766	0.598	1500	0.766	0.598	0.766	0.598
125.2	1.34*	0.880*	0.748	0.586	1573.2	0.748	0.586	0.748	0.586
150	1.61*	1.10*	0.742	0.582	1600	0.742	0.582	0.742	0.582
175.2	1.82*	1.27*	0.725	0.570	1673.2	0.725	0.570	0.725	0.570
200	1.95*	1.39*	0.720	0.567	1700	0.720	0.567	0.720	0.567
225.2	1.99*	1.46*	0.704	0.556	1773.2	0.704	0.556	0.704	0.556
250	1.99*	1.49*	0.699	0.552	1800	0.699	0.552	0.699	0.552
275.2	1.97*	1.49*	0.685	0.542	1873.2	0.685	0.542	0.685	0.542
300	1.93*	1.46*	0.680	0.540	1900	0.680	0.540	0.680	0.540
325.2	1.87*	1.43*	0.667	0.532	1973.2	0.667	0.532	0.667	0.532
350	1.81*	1.38*	0.663	0.529	2000	0.663	0.529	0.663	0.529
375.2	1.75*	1.34*	0.652	0.522	2073.2	0.652	0.522	0.652	0.522
400	1.69*	1.29*	0.636	0.512	2173.2	0.636	0.512	0.636	0.512
475.2	1.54	1.18	0.632	0.510	2200	0.632	0.510	0.632	0.510
500	1.49	1.14	0.620	0.502	2273.2	0.620	0.502	0.620	0.502
575.2	1.38	1.04	0.601	0.490	2400	0.601	0.490	0.601	0.490
600	1.32	1.01	0.590	0.483	2473.2	0.590	0.483	0.590	0.483
675.2	1.23	0.941	0.571	0.470	2600	0.571	0.470	0.571	0.470
700	1.19	0.918	0.560	0.463	2673.2	0.560	0.463	0.560	0.463
775.2	1.11	0.861	0.540	0.448	2800	0.540	0.448	0.540	0.448
800	1.09	0.842	0.528	0.439	2873.2	0.528	0.439	0.528	0.439
875.2	1.03	0.795	0.508	0.421	3000	0.508	0.421	0.508	0.421
900	1.01	0.781	0.496	0.410	3073	0.496	0.410	0.496	0.410
975.2	0.962	0.745	0.471	0.390	3200	0.471	0.390	0.471	0.390
1000	0.946	0.734	0.454	0.376	3273	0.454	0.376	0.454	0.376
			0.418	0.348	3400	0.418	0.348	0.418	0.348
			0.340	0.283	3600	0.340	0.283	0.340	0.283
			0.190*	0.160*	3800	0.190*	0.160*	0.190*	0.160*

* Extrapolated.

† Values below 400 K are merely typical values.

THERMAL CONDUCTIVITY OF THE ELEMENTS


RECOMMENDED VALUES*
[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]

SOLID

T	// to axis of extrusion k	⊥ to axis of extrusion k	T	// to axis of extrusion k	⊥ to axis of extrusion k
10	0.0070*	0.00542*	1073.2	0.764	0.650
20	0.0381*	0.0278*	1100	0.749	0.638
30	0.0961*	0.0687*	1173.2	0.711	0.609
40	0.182*	0.127*	1200	0.699	0.600
50	0.289*	0.200*	1273.2	0.668	0.577
60	0.419*	0.287*	1300	0.659	0.569
70	0.559*	0.379*	1373.2	0.634	0.530
80	0.705*	0.475*	1400	0.626	0.543
90	0.845*	0.574*	1473.2	0.605	0.525
100	0.984*	0.678*	1500	0.597	0.520
123.2	1.27*	0.908*	1573.2	0.579	0.504
150	1.55*	1.15*	1600	0.573	0.498
173.2	1.71*	1.31*	1673.2	0.559	0.484
200	1.83*	1.43*	1700	0.554	0.479
223.2	1.88*	1.49*	1773.2	0.541	0.468
250	1.89*	1.52*	1800	0.536	0.464
273.2	1.87*	1.51*	1873.2	0.524	0.455
298.2	1.83*	1.48*	1900	0.520	0.452
300	1.82*	1.48*	1973.2	0.508	0.443
323.2	1.77*	1.44*	2000	0.504	0.440
350	1.71*	1.40*	2073.2	0.494	0.432
373.2	1.66*	1.36*	2173.2	0.481	0.422
400	1.59*	1.32*	2200	0.477	0.419
473.2	1.43*	1.20*	2273.2	0.467	0.412
500	1.38*	1.15*	2400	0.450	0.399
573.2	1.25*	1.05*	2473.2	0.440	0.392
600	1.21*	1.01*	2600	0.422	0.377
673.2	1.11*	0.933*	2673.2	0.411	0.369
700	1.08*	0.906*	2800	0.392	0.353
773.2	0.998*	0.843*	2873.2	0.380	0.342
800	0.970*	0.821*	3000	0.358	0.320
873.2	0.902	0.768	3073	0.344	0.307
900	0.880	0.749	3200	0.313	0.282
973.2	0.828	0.703	3273	0.293	0.265
1000	0.810	0.687	3400	0.251	0.232
			3600	0.160	0.150
			3800	0.0430*	0.0400*

* Extrapolated.


† Values below 400 K are merely typical values.

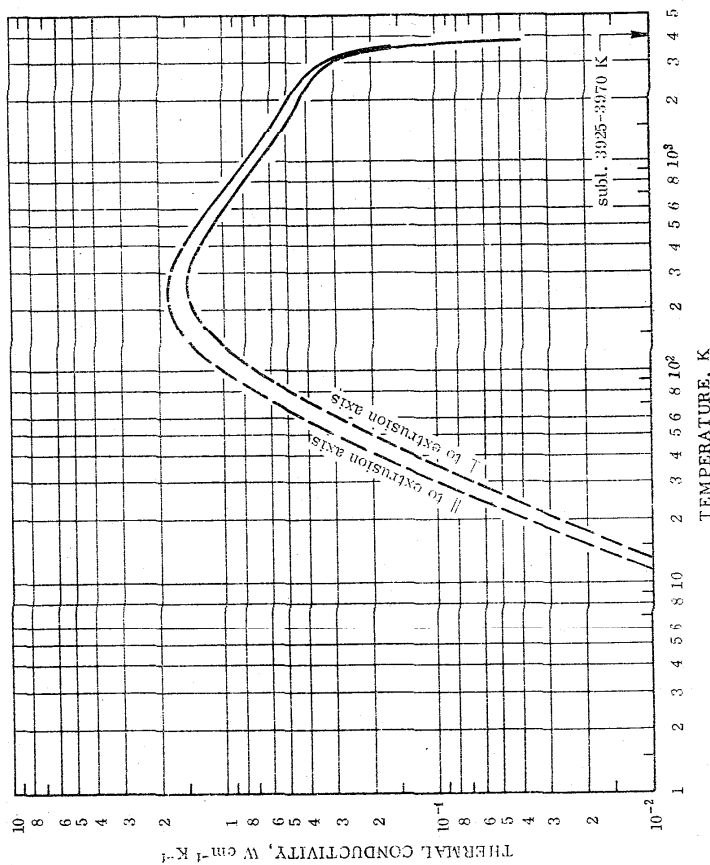

REMARKS

The values above 400 K are recommended values for 9995 graphite and are considered accurate to within ±10 to ±20%. The values below 400 K are merely typical values and represent a typical curve serving only to indicate the general trend of the thermal conductivity of 9995 graphite at moderate and low temperatures, since the thermal conductivity at temperatures near and below the corresponding temperature of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens.

THERMAL CONDUCTIVITY OF CERIUM

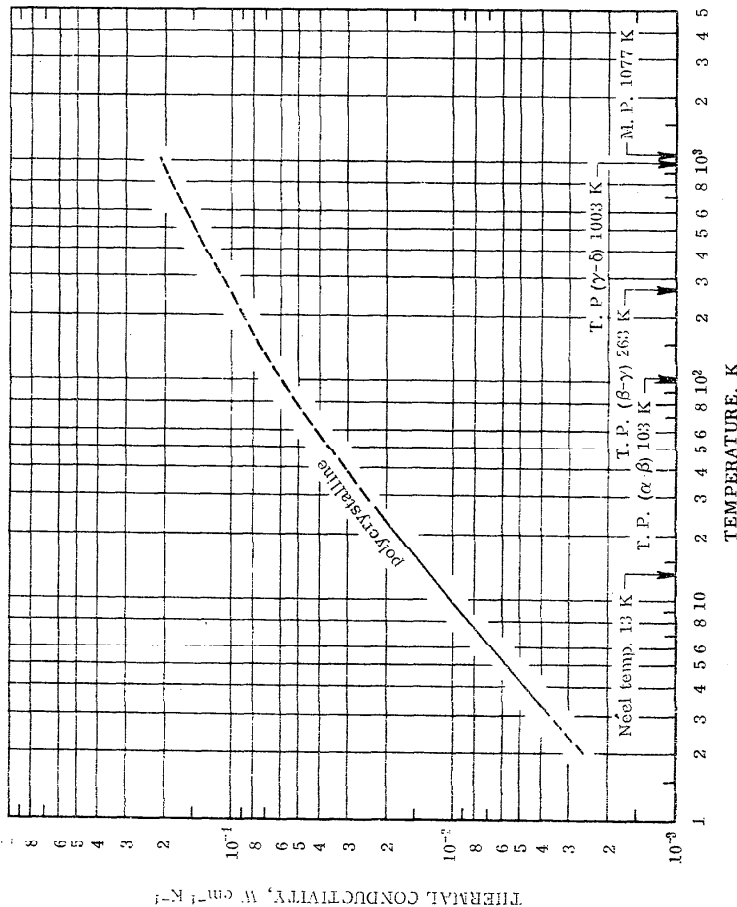

PROVISIONAL VALUES

[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]

SOLID

Polycrystalline	
T	k
2	0.00260*
3	0.00373
4	0.00482
5	0.00584
6	0.00683
7	0.00776
8	0.00868
9	0.00959
10	0.0105
11	0.0113
12	0.0122
13	0.0130
14	0.0138
15	0.0147
16	0.0155
18	0.0171
20	0.0186
25	0.0224*
30	0.0260*
35	0.0293*
40	0.0323*
45	0.0352*
50	0.0379*
60	0.0432*
70	0.0478*
80	0.0521*
90	0.0561*
100	0.0600*
123.2	0.0679*
150	0.0766*
173.2	0.0828*
200	0.0900*
223.2	0.0958*
250	0.1025*
273.2	0.108*
298.2	0.113
300	0.114
323.2	0.119*
350	0.124*
373.2	0.128*
400	0.133*
473.2	0.145*
500	0.150*
573.2	0.161*
600	0.165*
673.2	0.176*
700	0.180*
773.2	0.189*
800	0.193*
873.2	0.202*
900	0.206*
973.2	0.215*
1000	0.218*


REMARKS

Near room temperature the uncertainty of the provisional values is probably of the order of ±20% but it will be greater at lower temperatures on account of the phase changes and the magnetic transformation. The values below 270 K are applicable only to cerium having electrical resistivity ratio $\rho(293\text{ K})/\rho(20\text{ K}) = 1.93$.

* Extrapolated or interpolated.

THERMAL CONDUCTIVITY OF THE ELEMENTS

THERMAL CONDUCTIVITY OF CESIUM

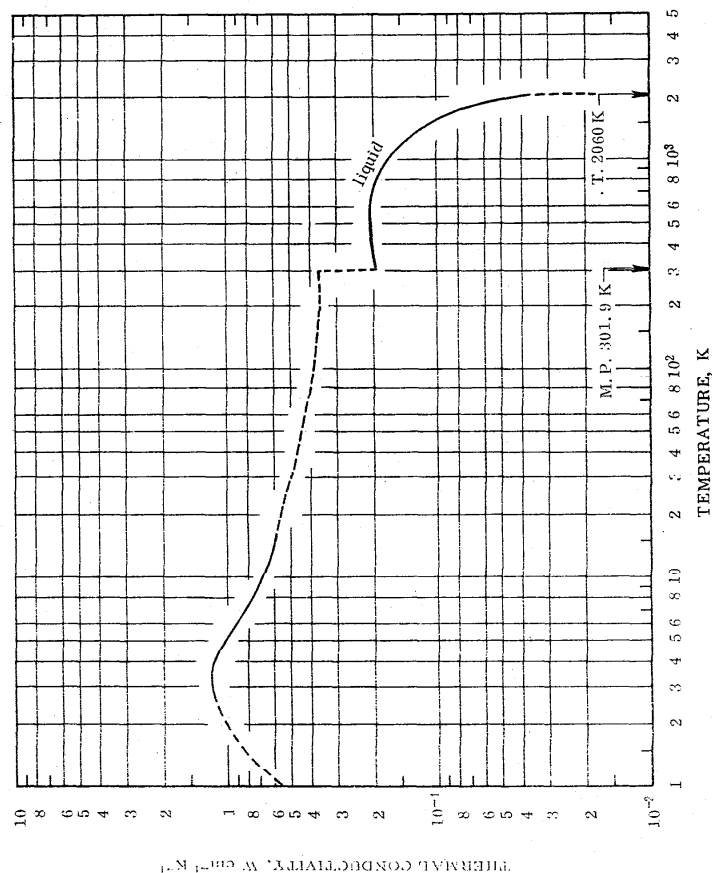

RECOMMENDED VALUES
[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]


SOLID		LIQUID	
T	k	T	k
0	0	301.9	0.197
1	0.574*	323.2	0.198
2	1.02*	350	0.200
3	1.19	373.2	0.201
4	1.14	400	0.203
5	1.04	473.2	0.205
6	0.935	500	0.205
7	0.837	573.2	0.206
8	0.769	600	0.205
9	0.720	673.2	0.202
10	0.689	700	0.201
11	0.666	773.2	0.196
12	0.647	800	0.194
13	0.630	873.2	0.187
14	0.615	973.2	0.177
15	0.600	1073.2	0.166
16	0.590	1100	0.163
18	0.572*	1173.2	0.153
20	0.554*	1200	0.150
25	0.523*	1273.2	0.140
30	0.500*	1300	0.136
35	0.483*	1373.2	0.126
40	0.470*	1400	0.122
45	0.457*	1473.2	0.112
50	0.447*	1500	0.108
60	0.430*	1573.2	0.098
70	0.420*	1600	0.094
80	0.410*	1673.2	0.084
90	0.402*	1700	0.080
100	0.397*	1773.2	0.070
123.2	0.387*	1800	0.066
150	0.378*	1873.2	0.055
173.2	0.373*	1900	0.051
200	0.368*	1973.2	0.036*
223.2	0.365*	2000	0.029*
250	0.363*		
273.2	0.361*		
298.2	0.359		
300	0.359		
301.9	0.359		

* Extrapolated, interpolated, or estimated, hence provisional.

REMARKS

The recommended values are for high-purity cesium and are thought to be accurate to within ±8% of the true values at temperatures below 15 K and from room temperature to about 1500 K. The thermal conductivity at temperature near and below the corresponding temperature, T_m, of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens, and the recommended values below 40 K are applicable only to cesium having residual electrical resistivity $\rho_0 = 0.0418 \mu\Omega \text{ cm}$. Values at temperatures below about 1.1 T_m are calculated to fit experimental data by using equation (7) and using $n = 2.00$, $\alpha' = 0.0300$, and $\beta = 1.71$.

THERMAL CONDUCTIVITY OF CHLORINE

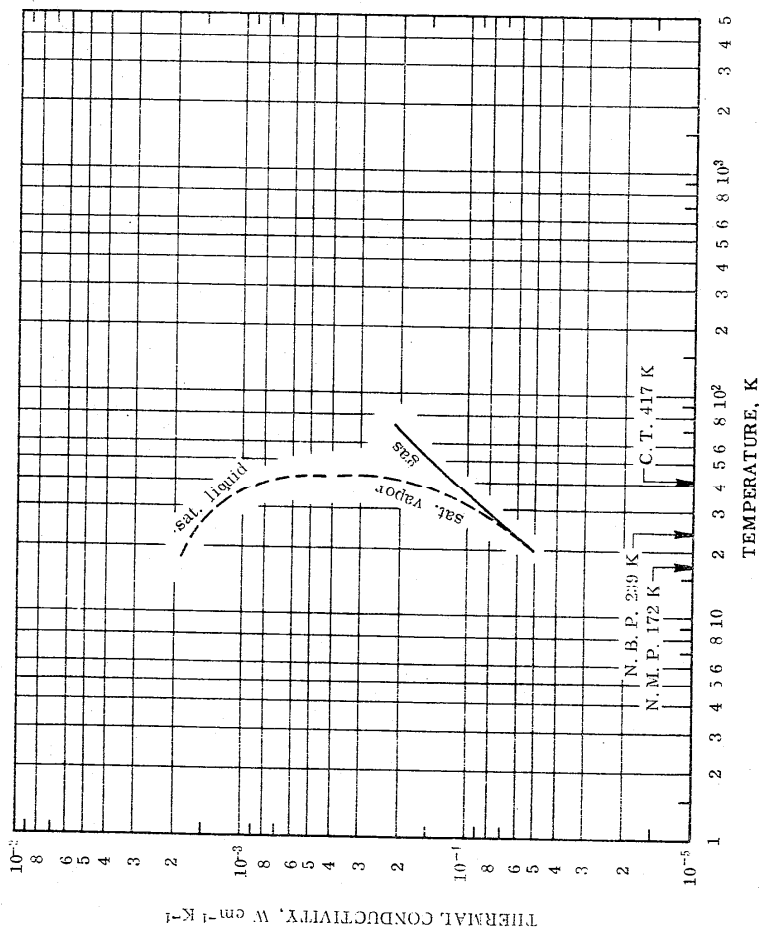

SATURATED LIQUID		SATURATED VAPOR	
T	$k \times 10^3$	T	$k \times 10^3$
172	1.93*	200	0.054*
180	1.89*	210	0.058*
190	1.85*	220	0.061*
200	1.81*	230	0.065*
210	1.76*	240	0.068*
220	1.72*	250	0.074*
230	1.67*	260	0.078*
240	1.63*	270	0.082*
250	1.58*	280	0.086*
260	1.54*	290	0.092*
270	1.49*	300	0.097*
280	1.44*	310	0.103*
290	1.39*	320	0.110*
300	1.34*	330	0.117*
310	1.29*	340	0.125*
320	1.24*	350	0.134*
330	1.18*	360	0.144*
340	1.13*	370	0.155*
350	1.07*	380	0.168*
360	1.01*	390	0.185*
370	0.95*	400	0.210*
380	0.88*	410	0.25*
390	0.80*	417	0.40*†
400	0.72*		
410	0.62*		
417	0.40*†		

REMARKS


The liquid and vapor values are based on a correlation for diatomic substances. No experimental data were located to verify the present estimates, which must be regarded as provisional. The gas values, based on subatmospheric pressure experiments of a single source, should be accurate to 5%.

* Estimated, hence provisional.
 † Pseudo-critical value.

THERMAL CONDUCTIVITY OF CHLORINE (continued)

RECOMMENDED VALUES GAS (At 1 atm)		T	$k \times 10^3$	T	$k \times 10^3$
T	$k \times 10^3$				
239	0.068				
240	0.068				
250	0.071	500	0.156		
260	0.075	510	0.160		
270	0.078	520	0.163		
280	0.082	530	0.166		
290	0.085	540	0.170		
300	0.089	550	0.173		
310	0.093	560	0.176		
320	0.096	570	0.180		
330	0.100	580	0.183		
340	0.103	590	0.186		
350	0.107	600	0.190		
360	0.110	610	0.192		
370	0.114	620	0.195		
380	0.117	630	0.197		
390	0.120	640	0.200		
400	0.124	650	0.202		
410	0.127	660	0.205		
420	0.131	670	0.207		
430	0.134	680	0.210		
440	0.137	690	0.212		
450	0.141	700	0.215		
460	0.144				
470	0.147				
480	0.150				
490	0.153				

THERMAL CONDUCTIVITY OF CHROMIUM

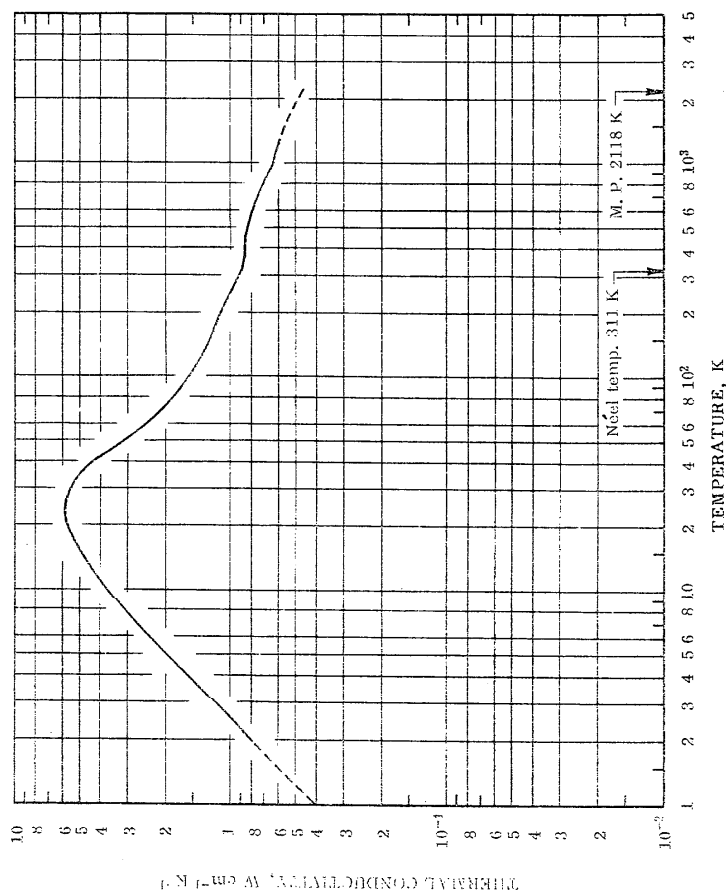

REMARKS

The recommended values are for well-annealed high-purity chromium and are thought to be accurate to within $\pm 1\%$ of the true values at temperatures below 150 K and above 700 K , and $\pm 3\%$ from 150 to 700 K except possibly near the Neel temperature. The thermal conductivity at temperatures near and below the corresponding temperature, T_m , of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens, and the recommended values below 150 K are applicable only to a specimen having residual electrical resistivity $\rho_0 = 0.068 \mu\Omega \text{ cm}$. Values at temperatures below about $1.5 T_m$ are calculated to fit experimental data by using equation (7) and using constants m , n , and α' as given in Table I and $\beta = 2.43$.

RECOMMENDED VALUES


[Temperature, T, K; Thermal Conductivity, k , $\text{W cm}^{-1} \text{K}^{-1}$]

SOLID

Polycrystalline		Polycrystalline	
T	k	T	k
0	0	350	0.929
1	0.402*	373.2	0.921
2	0.803	400	0.909
3	1.20	473.2	0.874
4	1.60	500	0.860
5	2.00	573.2	0.822
6	2.39	600	0.807
7	2.27	673.2	0.769
8	3.14	700	0.756
9	3.50	773.2	0.726
10	3.85	800	0.713
11	4.17	873.2	0.688
12	4.48	900	0.678
13	4.76	973.2	0.660
14	5.01	1000	0.654
15	5.24	1073.2	0.640
16	5.44	1100	0.636
18	5.74	1173.2	0.624
20	5.93	1200	0.619
25	5.93	1273.2	0.608
30	5.49	1300	0.604
35	4.88	1373.2	0.592
40	4.25	1400	0.588
45	3.67	1473.2	0.576
50	3.17	1500	0.572
60	2.48	1573.2	0.561
70	2.07	1600	0.556
80	1.84	1673.2	0.546*
90	1.69	1700	0.542*
100	1.59	1773.2	0.530*
123.2	1.43	1800	0.526*
150	1.29	1873.2	0.514*
173.2	1.20	1900	0.510*
200	1.11	1973.2	0.498*
223.2	1.06	2000	0.494*
250	1.00	2073.2	0.482*
273.2	0.965	2100	0.478*
298.2	0.939	2118	0.475*
300	0.937		
323.2	0.933		

* Extrapolated.

THERMAL CONDUCTIVITY OF COBALT

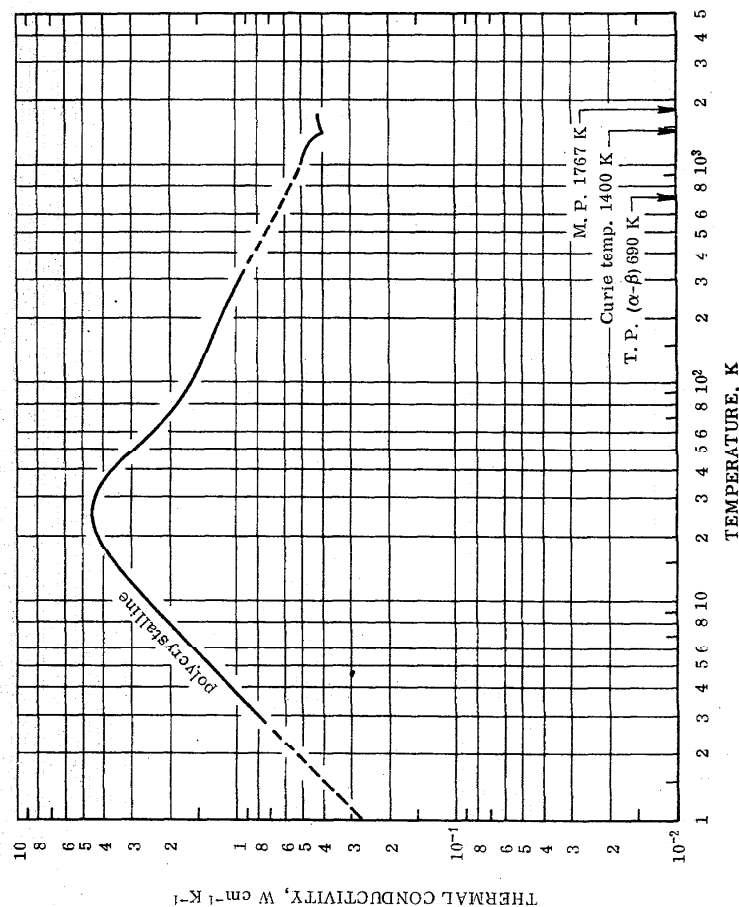


RECOMMENDED VALUES
[Temperature, T, K; Thermal Conductivity, k, $W\ cm^{-1}\ K^{-1}$]

SOLID		T	k	T	k
Polycrystalline		0	0	250	1.10
		1	0.270*	273.2	1.05
		2	0.539*	298.2	1.00
		3	0.808	300	1.00
		4	1.08	323.2	0.963
		5	1.34	350	0.922
		6	1.61	373.2	0.890
		7	1.87	400	0.854
		8	2.13	473.2	0.771*
		9	2.38	500	0.747*
		10	2.63	573.2	0.693*
		11	2.87	600	0.674*
		12	3.10	673.2	0.633*
		13	3.31	700	0.621*
		14	3.52	773.2	0.592*
		15	3.71	800	0.582*
		16	3.89	873.2	0.556*
		18	4.19	900	0.548*
		20	4.43	973.2	0.527
		25	4.70	1000	0.521
		30	4.58	1073.2	0.509
		35	4.24	1100	0.505
		40	3.78	1173.2	0.495
		45	3.34	1200	0.493
		50	2.99	1273.2	0.482
		60	2.49	1300	0.472
		70	2.17	1373.2	0.425
		80	1.94	1400	0.417
		90	1.78	1473.2	0.424
		100	1.67	1500	0.425
		123.2	1.53	1573.2	0.428
		150	1.38	1600	0.429
		173.2	1.30	1673.2	0.430
		200	1.22	1700	0.430
		223.2	1.16	1767	0.431*

* Extrapolated or interpolated.

THERMAL CONDUCTIVITY OF COPPER

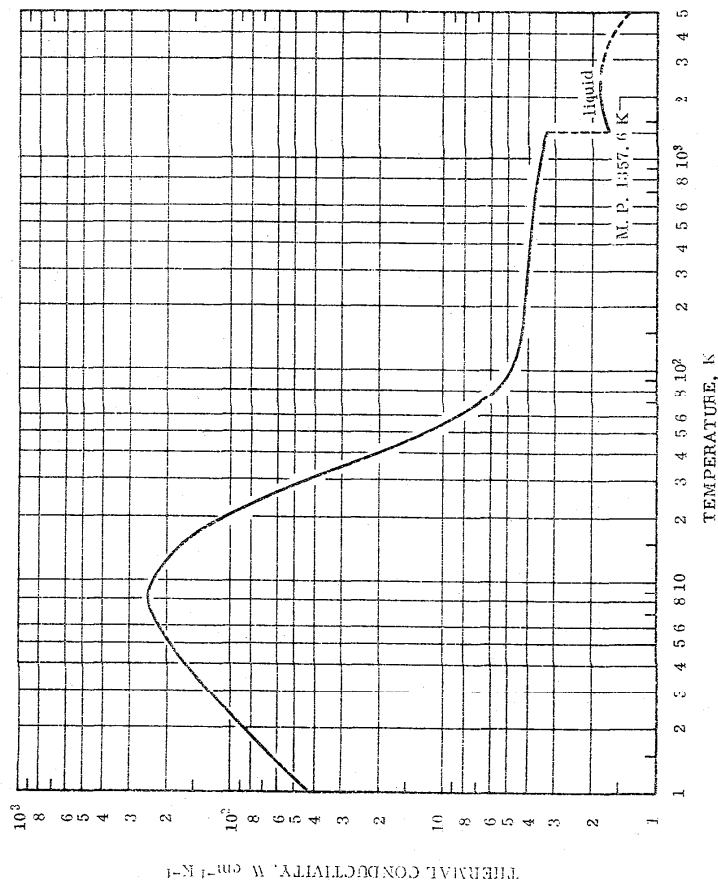

REMARKS

The recommended values are for well-annealed high-purity copper and are considered accurate to within $\pm 2\%$ of the true values near room temperature and $\pm 4\%$ at low and high temperatures. The values for molten copper up to about 2000 K should be good to $\pm 15\%$. The thermal conductivity at temperatures near and below the corresponding temperature, T_m , of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens, and the recommended values below 100 K are applicable only to a specimen having residual electrical resistivity $\rho_0 = 0.000579\ \mu\Omega\ cm$. Values at temperatures below about 1.5 T_m are calculated to fit experimental data by using equation (7) and using constants m , n , and α'' as listed in Table I and $\beta = 0.0237$.


RECOMMENDED VALUES †
[Temperature, T, K; Thermal Conductivity, k , $W\ cm^{-1}\ K^{-1}$]

SOLID			LIQUID				
T	k	T	k	T	k		
0	0	123.2	4.47	1357.6	1.66	3473	1.73*
1	42.2	150	4.29	1373.2	1.66	3600	1.70*
2	84.0	173.2	4.20	1400	1.67	3673	1.66*
3	125	200	4.13	1473.2	1.70	3800	1.66*
4	162	223.2	4.09	1500	1.71	3873	1.65*
5	195	250	4.06	1573.2	1.73	4000	1.61*
6	222	273.2	4.03	1600	1.74	4073	1.60*
7	239	298.2	4.01	1673.2	1.76	4273	1.54*
8	248	300	4.01	1700	1.77	4500	1.48*
9	249	323.2	3.99	1773.2	1.79	4773	1.40*
10	243	350	3.96	1800	1.79	5000	1.33*
11	232	373.2	3.95	1873.2	1.80	5273	1.24*
12	218	400	3.93	1900	1.81	5500	1.17*
13	202	473.2	3.88	1973.2	1.82	5773	1.07*
14	186	500	3.86	2000	1.82	6000	0.989*
15	171	573.2	3.81	2073.2	1.83	6273	0.889*
16	157	600	3.79	2173.2	1.84	6500	0.804*
18	131	673.2	3.74	2200	1.84	6773	0.698*
20	108	700	3.73	2273.2	1.84	7000	0.611*
25	68.3	773.2	3.68	2400	1.84	7273	0.503*
30	44.5	800	3.66	2473.2	1.84	7500	0.414*
35	30.4	873.2	3.61	2600	1.84*	7773	0.305*
40	21.7	900	3.59	2673.2	1.84*	8000	0.212*
45	16.2	973.2	3.54	2800	1.83*	8273	0.097*
50	12.5	1000	3.52	2873.2	1.82*	C.T.=8500	0.036*
60	8.29	1073.2	3.47	3000	1.80*		
70	6.47	1100	3.46	3073	1.79*		
80	5.57	1173.2	3.41	3200	1.78*		
90	5.08	1200	3.39	3273	1.76*		
100	4.82	1273.2	3.34	3400	1.74*		
		1300	3.32				
		1357.6	3.28				

* Extrapolated or estimated.

† Values above 3000 K are provisional.

THERMAL CONDUCTIVITY OF DYSPROSIUM

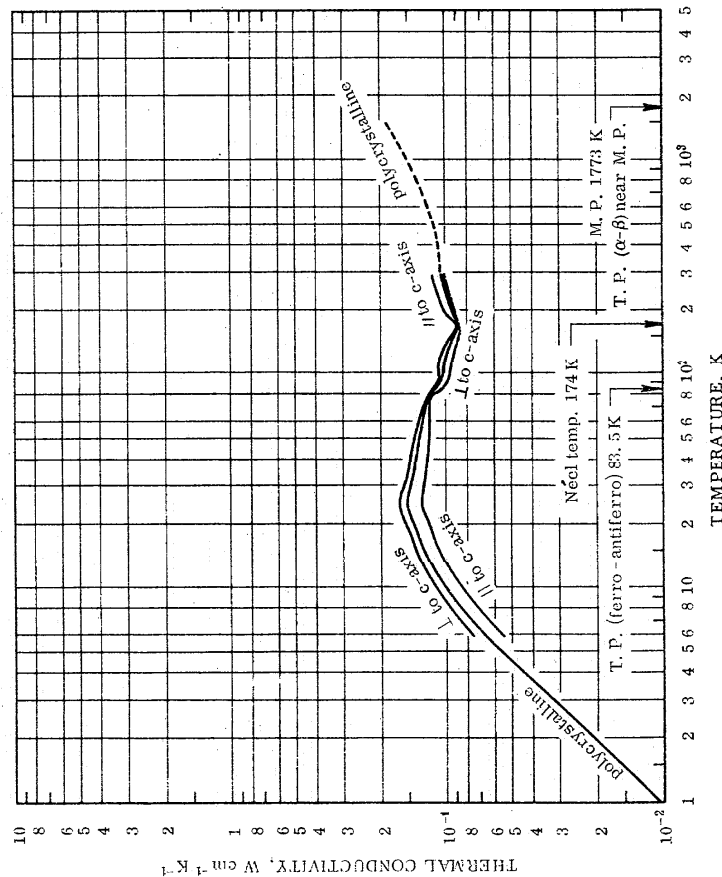

REMARKS

The provisional values are for well-annealed high-purity dysprosium and are considered accurate to within ±15% of the true values at temperatures from 200 to 300 K and ±15 to ±25% above 300 K. At temperatures below 200 K the values are highly conditioned by purity and imperfection, and the values for $k_{||}$, k_{\perp} , and k_{pol} are applicable only to samples having residual electrical resistivities of 5.77, 4.59, and 4.93 $\mu\Omega$ cm, respectively. Reliable uncertainty limits for the values below 200 K can hardly be given.

PROVISIONAL VALUES


[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]

SOLID

T	// to c-axis k	⊥ to c-axis k	Poly-crystalline k	T	// to c-axis k	⊥ to c-axis k	Poly-crystalline k
1			0.0102	250	0.111	0.0987	0.103
2			0.0208	273.2	0.114	0.101	0.105
3			0.0324	298.2	0.117	0.103	0.107
4			0.0442	300	0.117	0.103	0.107
5			0.0561	323.2			0.108*
6	0.0539	0.0757	0.0676	350			0.108*
7	0.0626	0.0865	0.0776	373.2			0.108*
8	0.0704	0.0964	0.0868	400			0.109*
9	0.0778	0.106	0.0953	473.2			0.113*
10	0.0844	0.113	0.102	500			0.115*
11	0.0901	0.120	0.109	573.2			0.119*
12	0.0956	0.126	0.115	600			0.121*
13	0.100	0.131	0.120	673.2			0.127*
14	0.104	0.136	0.124	700			0.129*
15	0.108	0.139	0.128	773.2			0.135*
16	0.111	0.142	0.131	800			0.137*
18	0.116	0.148	0.136	873.2			0.143*
20	0.121	0.156	0.143	900			0.145*
25	0.132	0.165	0.153	973.2			0.150*
30	0.127	0.158	0.147	1000			0.152*
35	0.125	0.151	0.142	1073.2			0.158*
40	0.124	0.148	0.139	1100			0.160*
45	0.123	0.145	0.137	1173.2			0.165*
50	0.123	0.142	0.135	1200			0.167*
60	0.121	0.136	0.131	1273.2			0.172*
70	0.120	0.131	0.127	1300			0.174*
80	0.117	0.124	0.122	1373.2			0.180*
90	0.101	0.113	0.105	1400			0.182*
100	0.0969	0.110	0.101	1473.2			0.187*
123.2	0.0929	0.106	0.0971	1500			0.189*
150	0.0874	0.0968	0.0904				
173.2	0.0887	0.0887	0.0887				
200	0.103	0.0931	0.0963				
223.2	0.107	0.0960	0.0995				

* Extrapolated or estimated.

THERMAL CONDUCTIVITY OF ERBIUM

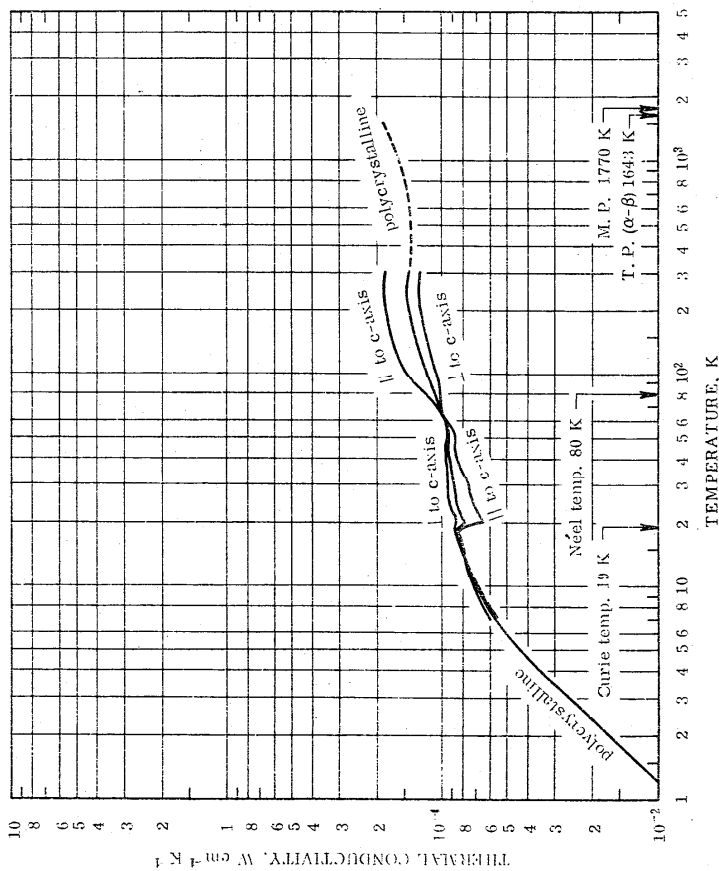

REMARKS

The provisional values are for well-annealed high-purity erbium and are thought to be accurate to within $\pm 15\%$ at temperatures from 200 to 300 K and $\pm 20\%$ above 300 K. At temperatures below 200 K the values are very uncertain.

PROVISIONAL VALUES


[Temperature, T, K; Thermal Conductivity, k, $W\ cm^{-1}\ K^{-1}$]

SOLID

T	// to c-axis k	⊥ to c-axis k	Poly-crystalline k	T	// to c-axis k	⊥ to c-axis k	Poly-crystalline k
0	0	0	0	250	0.188	0.128	0.148
1			0.00856	273.2	0.187	0.127	0.147
2			0.0171	298.2	0.184	0.126	0.145
3			0.0261	300	0.184	0.126	0.143
4			0.0356	323.2			0.143
5			0.0442	350			0.140*
6			0.0515	373.2			0.140*
7	0.0612	0.0558	0.0576	400			0.140*
8	0.0660	0.0612	0.0628	473.2			0.140*
9	0.0696	0.0658	0.0672	500			0.141*
10	0.0722	0.0698	0.0706	573.2			0.142*
11	0.0743	0.0731	0.0735	600			0.143*
12	0.0760	0.0761	0.0762	673.2			0.145*
13	0.0774	0.0788	0.0783	700			0.146*
14	0.0787	0.0810	0.0802	773.2			0.149*
15	0.0797	0.0830	0.0819	800			0.150*
16	0.0809	0.0845	0.0833	873.2			0.153*
18	0.0840	0.0880	0.0867	900			0.154*
20	0.0839	0.0863	0.0782	973.2			0.158*
25	0.0729	0.0834	0.0866	1000			0.159*
30	0.0762	0.0838	0.0875	1073.2			0.163*
35	0.0820	0.0955	0.0908	1100			0.165*
40	0.0858	0.0963	0.0926	1173.2			0.169*
45	0.0876	0.0966	0.0935	1200			0.171*
50	0.0874	0.0957	0.0929	1273.2			0.176*
60	0.0992	0.0974	0.0980	1300			0.178*
70	0.107	0.101	0.103	1373.2			0.183*
80	0.121	0.102	0.108	1400			0.185*
90	0.139	0.104	0.115	1473.2			0.190*
100	0.150	0.108	0.122	1500			0.191*
123.2	0.163	0.113	0.130				
150	0.174	0.119	0.137				
173.2	0.180	0.123	0.142				
200	0.185	0.126	0.146				
223.2	0.187	0.128	0.148				

* Extrapolated or estimated.

THERMAL CONDUCTIVITY OF EUROPIUM

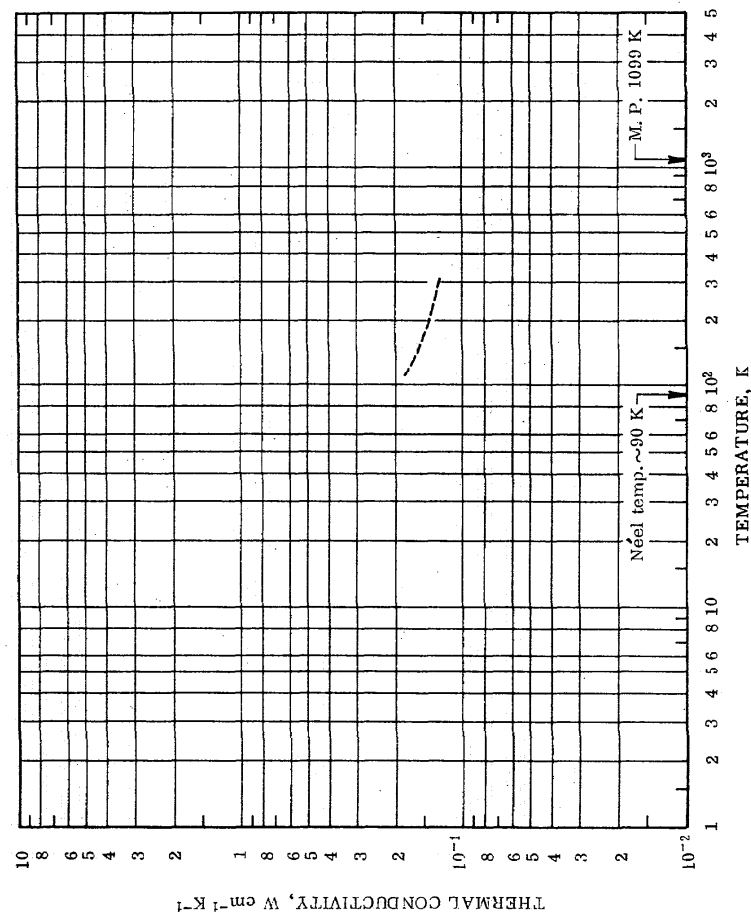

PROVISIONAL VALUES
 [Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]

T	k
123.2	0.182*
150	0.165*
173.2	0.156*
200	0.148*
223.2	0.144*
250	0.141*
273.2	0.140*
298.2	0.139*
300	0.139*


SOLID

REMARKS

The provisional values are for high-purity europium and are probably good to within ±20%.

* Estimated.

THERMAL CONDUCTIVITY OF FLUORINE

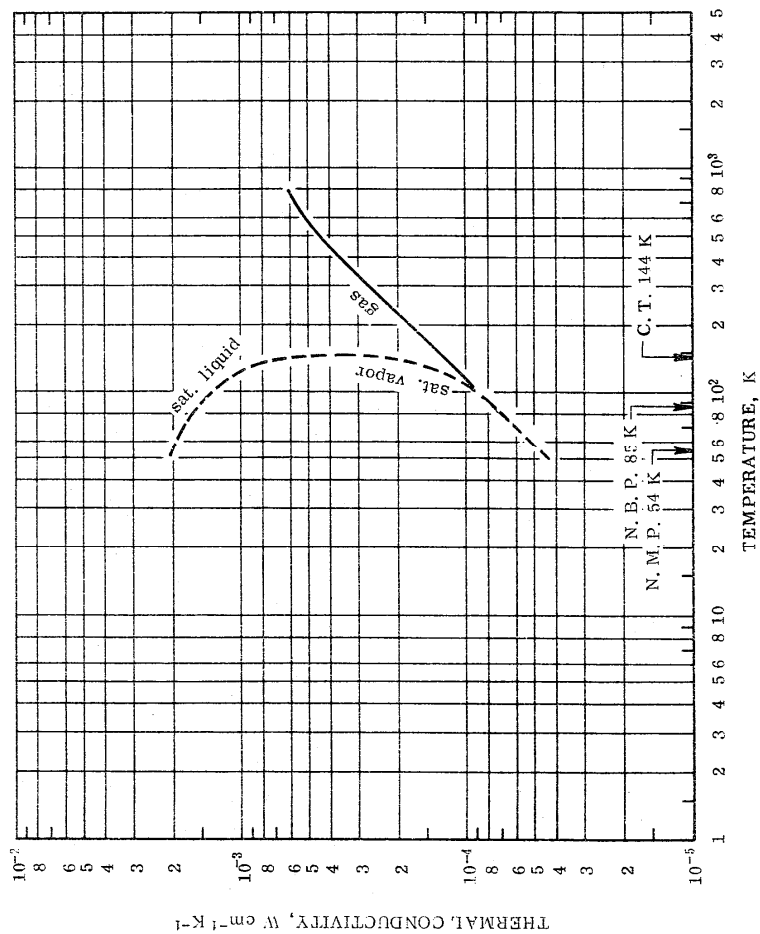

REMARKS

The values for the liquid and vapor states are based on a correlation for diatomic substances. No experimental data were located. They should be accurate to 10% below 125 K and uncertain at higher temperatures. The gas values, based on subatmospheric pressure studies, are more probably accurate to within a 10% uncertainty for most, if not all, of the entire temperature range tabulated.

RECOMMENDED VALUES

[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]

SATURATED LIQUID		GAS (At 1 atm)	
T	k x 10 ³	T	k x 10 ³
60	2.04*	85	0.076*
70	1.95*	90	0.081
80	1.80*	100	0.090
90	1.50*	110	0.100
100	1.35*	120	0.109
110	1.21*	130	0.118
120	1.06*	140	0.128
130	0.90*	150	0.137
140	0.66*	160	0.146
144	0.40*†	170	0.156
		180	0.165
		190	0.174
		200	0.184
		210	0.193
		220	0.202
		230	0.212
		240	0.221
		250	0.231
		260	0.241
		270	0.251
		280	0.260
		290	0.269
		300	0.279
		310	0.288
		320	0.298
		330	0.307
		340	0.316
		350	0.326
		360	0.335
		370	0.344
		380	0.354
		390	0.363
		400	0.371
		410	0.378
		420	0.388
		430	0.397
		440	0.405
		450	0.413
		460	0.421
		470	0.430
		480	0.438
		490	0.446
		500	0.455
		510	0.463
		520	0.471
		530	0.479
		540	0.486
		550	0.493
		560	0.500
		570	0.507
		580	0.514
		590	0.520
		600	0.527
		610	0.534
		620	0.541
		630	0.547
		640	0.552
		650	0.557
		660	0.563
		670	0.568
		680	0.573
		690	0.579
		700	0.583
		710	0.588
		720	0.592
		730	0.596
		740	0.599
		750	0.603
		760	0.607
		770	0.610
		780	0.613
		790	0.616
		800	0.618


* Estimated or extrapolated, hence provisional.

† Pseudo-critical value.

PROVISIONAL VALUES
 [Temperature, T, K; Thermal Conductivity, k , $W\ cm^{-1}\ K^{-1}$]

SOLID


T	// to c-axis k	⊥ to c-axis k	Poly-crystalline k
0			0
1			0.0113
2			0.0231
3			0.0357
4			0.0488
5	0.0594	0.0442	0.0621
6	0.0754	0.0563	0.0752
7	0.0902	0.0686	0.0875
8	0.104	0.0803	0.0994
9	0.116	0.0918	0.110
10	0.127	0.103	0.121
11	0.137	0.113	0.130
12	0.145	0.123	0.137
13	0.152	0.130	0.143
14	0.158	0.136	0.149
15	0.164	0.142	0.154
16	0.168	0.147	0.158
17	0.170	0.152	0.165
18	0.174	0.161	0.170
19	0.175	0.168	0.176
20	0.175	0.175	0.177
25	0.171	0.179	0.177
30	0.166	0.182	0.174
35	0.162	0.180	0.171
40	0.158	0.178	0.168
45	0.155	0.175	0.165
50	0.152	0.172	0.160
60	0.147	0.167	0.155
70	0.143	0.162	0.151
80	0.139	0.157	0.147
90	0.136	0.153	0.143
100	0.133	0.149	0.136
123.2	0.127	0.141	0.129
150	0.121	0.133	0.123
173.2	0.117	0.127	0.117
200	0.112	0.119	0.111
223.2	0.108	0.113	0.106
250	0.105	0.107	0.103
273.2	0.104	0.103	0.105
298.2	0.108	0.104	0.105
300	0.108	0.104	0.107
310	0.110	0.106	

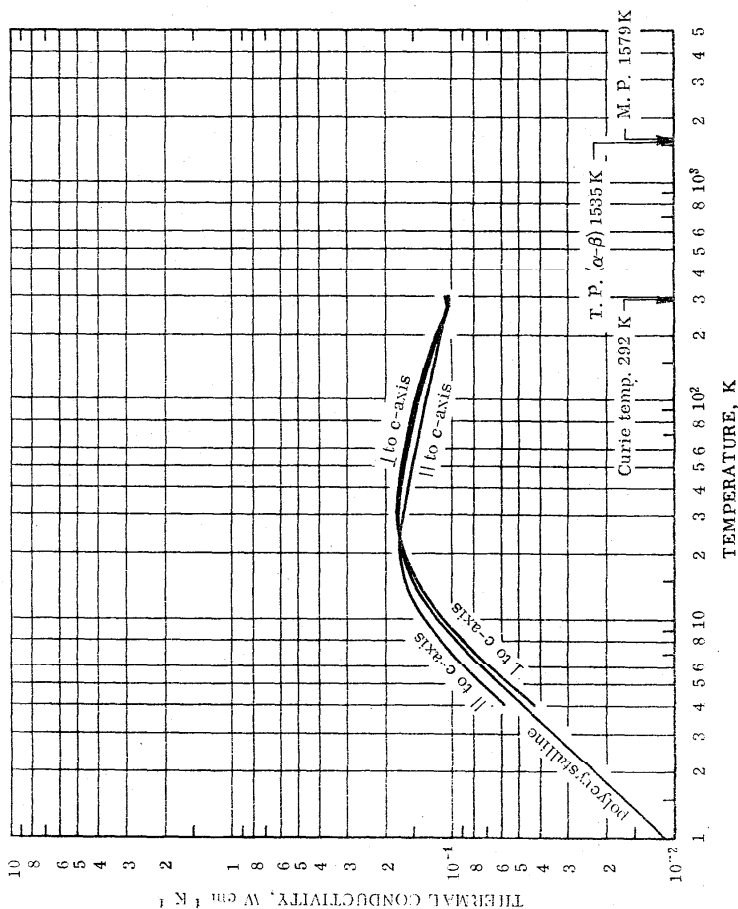

REMARKS

The provisional values are for well-annealed high-purity gadolinium and are thought to be accurate to within $\pm 10\%$ at temperatures above 100 K. At temperatures below 100 K the values for k_{\perp} , k_{\parallel} , and k_{poly} are applicable only to samples having residual electrical resistivity $\rho_0 = 2.62, 4.43,$ and $3.71\ \mu\Omega\ cm$. These values are very uncertain.

THERMAL CONDUCTIVITY OF GALLIUM

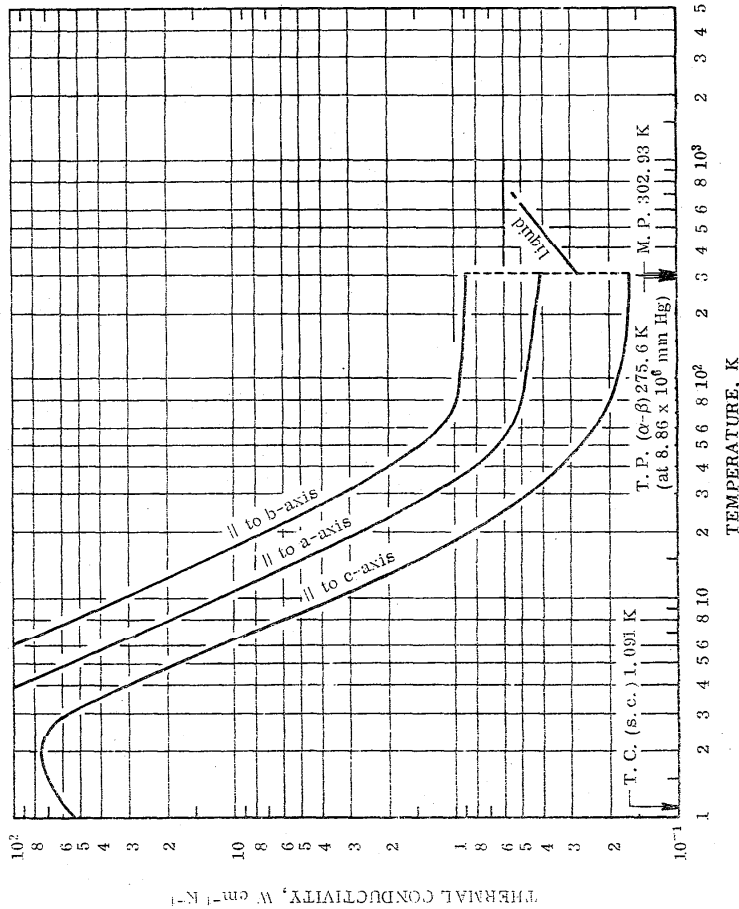

RECOMMENDED VALUES †


[Temperature, T, K; Thermal Conductivity, κ cm⁻¹ K⁻¹]

T	SOLID		LIQUID	
	// to a-axis#	// to b-axis	// to c-axis	T
0	0	0	0	302.93
1	226	657	54.1	325.2
2	298	832	76.0	375.2
3	194	524	58.2	400
4	99.3	272	31.1	475.2
5	59.2	163	18.2	500
6	38.8	107	11.8	575.2
7	27.2	74.0	8.15	600
8	19.9	54.2	5.93	675.2
9	15.2	41.4	4.47	700
10	11.9	32.5	3.49	
15	4.48	13.2	1.44	
20	2.65	17.3	0.835	
25	1.71	4.54	0.588	
30	1.23	3.22	0.462	
35	0.952	2.46	0.385	
40	0.795	1.98	0.333	
50	0.634	1.42	0.269	
60	0.555	1.15	0.233	
70	0.516	1.02	0.210	
80	0.494	0.983	0.196	
90	0.483	0.960	0.187	
100	0.474	0.951	0.181	
123.2	0.457	0.933	0.172	
150	0.443	0.918	0.167	
173.2	0.433	0.906	0.165	
200	0.424	0.896	0.163	
223.2	0.418	0.890	0.162	
250	0.414	0.885	0.160	
275.2	0.410	0.884	0.160	
298.2	0.408	0.883	0.159	
300	0.406	0.883	0.159	
302.93	0.406	0.883	0.159	

* Extrapolated.
 † Values above 500 K are provisional.
 ‡ The values for k_a are also good for polycrystalline gallium.

REMARKS

The recommended values are for high-purity gallium and are considered accurate to within $\pm 20\%$ of the true values at temperatures below 10 K due to additional uncertainty in the location of the maxima, $\pm 10\%$ from 10 K to 100 K, and $\pm 5\%$ from 100 K to the melting point. For liquid gallium the uncertainty of the values is probably $\pm 10\%$ near the melting point and increase to $\pm 20\%$ at the highest temperatures. The thermal conductivity at temperatures near and below the corresponding temperature, T_m , of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens, and the recommended values below 60 K for k_a , k_b , and k_c are applicable only to specimens having residual electrical resistivities of 0.000100, 0.000342, and 0.000425 $\mu\Omega$ cm, respectively. Values at temperatures below about 1.5 T_m are calculated to fit experimental data by using equation (7) and using the constants m , n , and α' given in Table 1 for gallium and $\beta = 0.00409$, 0.00140, and 0.0174 for k_a , k_b , and k_c , respectively. The values for k_a are also good for polycrystalline gallium.

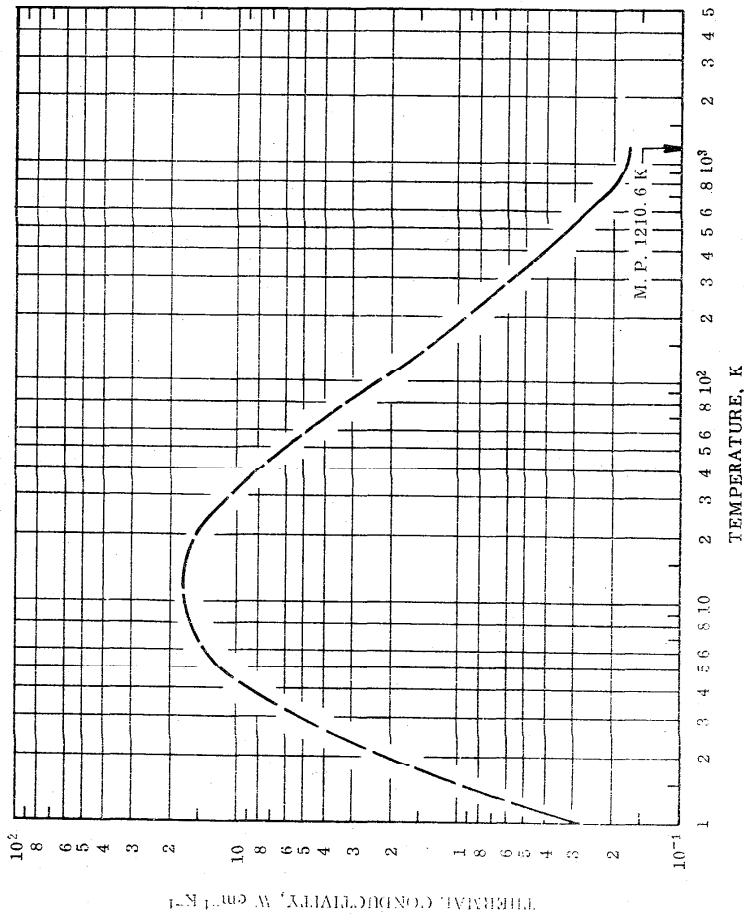

RECOMMENDED VALUES*

[Temperature, T, K; Thermal Conductivity, k, $W\ cm^{-1}\ K^{-1}$]

SOLID


T	k	T	k
0	0	123.2	1.68
1	0.274	150	1.32
2	2.06	173.2	1.13
3	5.35	200	0.968
4	8.77	223.2	0.859
5	11.6	250	0.749
6	13.9	273.2	0.667
7	15.5	298.2	0.602
8	16.6	300	0.599
9	17.3	323.2	0.548
10	17.7	350	0.495
11	17.9	373.2	0.465
12	18.0	400	0.432
13	17.9	473.2	0.359
14	17.7	500	0.338
15	17.3	573.2	0.288
16	16.9	600	0.273
18	15.9	673.2	0.237
20	14.9	700	0.227
25	12.7	773.2	0.204
30	10.8	800	0.198
35	9.20	873.2	0.185
40	7.98	900	0.182
45	6.95	973.2	0.176
50	6.15	1000	0.174
60	4.87	1073.2	0.171
70	3.93	1100	0.170
80	3.25	1173.2	0.172
90	2.70	1200	0.174
100	2.32		

REMARKS

The values are for well-annealed high-purity germanium. The recommended values (those above 290 K) are considered accurate to within $\pm 10\%$ of the true values. The thermal conductivity at temperatures near and below the corresponding temperature of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens and the conductivity values below 290 K are only typical values representing a typical curve to indicate the general trend of the low-temperature behavior of the thermal conductivity.

* Values below 290 K are merely typical values.

THERMAL CONDUCTIVITY OF GOLD

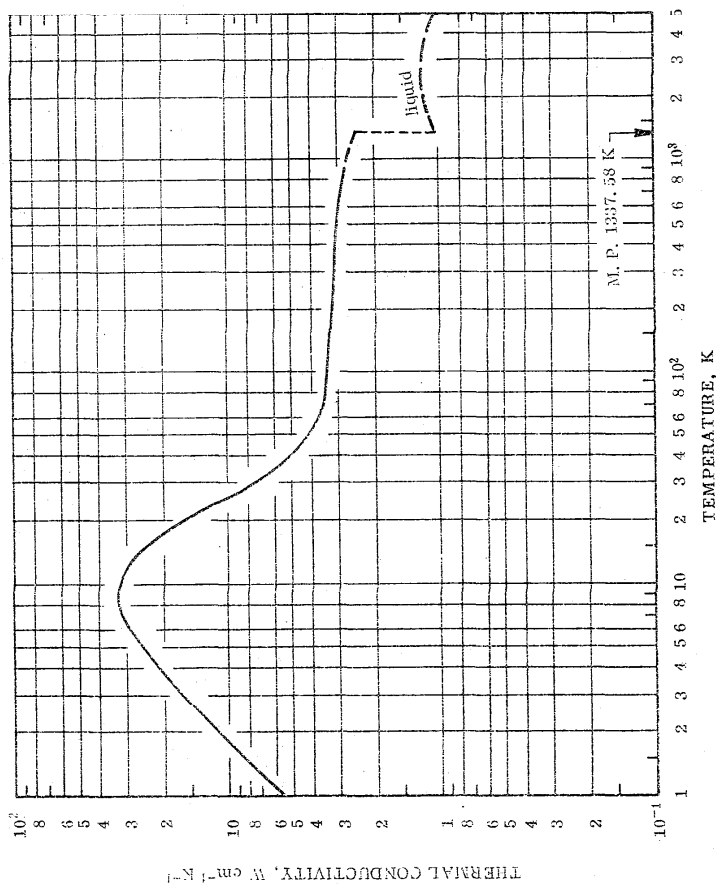

REMARKS

The recommended values are for well-annealed high-purity gold and are considered accurate to within $\pm 2\%$ of the true values near room temperature, and $\pm 5\%$ below 80 K and at 1200 K. The thermal conductivity at temperatures near and below the corresponding temperature, T_m , of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens, and the recommended values below 80 K are applicable only to a specimen having residual electrical resistivity $\rho_0 = 0.00550 \mu\Omega \text{ cm}$. Values at temperatures below about 1.5 T m are calculated to fit experimental data by using equation (7) and using the constants m , r , and α'' given in Table 1 for gold and $\beta = 0.225$. No experimental data are available for molten gold. The values given here are estimated and are provisional values. They are probably good to $\pm 27\%$ from melting point to 2000 K.

RECOMMENDED VALUES †

[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]


SOLID				LIQUID			
T	k	T	k	T	k	T	k
0	0	123.2	3.26	1337.58	1.04*	3300	1.21*
1	5.46	150	3.25	1373.2	1.06*	3373	1.21*
2	10.9	173.2	3.24	1400	1.06*	3800	1.10*
3	16.1	200	3.23	1473.2	1.09*	3873	1.18*
4	20.9	223.2	3.22	1500	1.08*	4000	1.17*
5	25.2	250	3.21	1573.2	1.10*	4073	1.17*
6	28.5	273.2	3.19	1673.2	1.14*	4273	1.14*
7	30.9	288.2	3.18	1700	1.13*	4500	1.11*
8	32.3	300	3.17	1773.2	1.15*	4773	1.06*
9	32.7	323.2	3.16	1800	1.16*	5000	1.02*
10	32.4	350	3.14	1873.2	1.17*	5273	0.974*
11	31.5	373.2	3.13	1900	1.17*	5500	0.933*
12	30.0	400	3.11	1973.2	1.18*	5773	0.884*
13	28.4	473.2	3.06	2000	1.19*	6000	0.839*
14	26.6	500	3.04	2073.2	1.20*	6273	0.781*
15	24.6	573.2	2.99	2173.2	1.21*	6500	0.731*
16	22.7	600	2.98	2200	1.22*	6773	0.761*
18	18.9	673.2	2.93	2273.2	1.22*	7000	0.620*
20	15.8	700	2.91	2400	1.23*	7273	0.557*
25	10.3	773.2	2.86	2473.2	1.24*	7500	0.504*
30	7.55	800	2.84	2600	1.25*	7773	0.430*
35	6.00	873.2	2.79	2673.2	1.25*	8000	0.384*
40	5.15	900	2.77	2800	1.25*	8273	0.316*
45	4.59	973.2	2.72	2873.2	1.25*	8500	0.256*
50	4.21	1000	2.70	3000	1.25*	8773	0.186*
60	3.74	1073.2	2.64	3073	1.24*	9000	0.131*
70	3.48	1100	2.62	3200	1.24*	9273	0.0601*
80	3.32	1173.2	2.57	3273	1.23*		
90	3.28	1200	2.55	3400	1.23*		
100	3.27	1273.2	2.49*	3473	1.22*		
		1300	2.47*				
		1337.58	2.44*				

* Extrapolated or estimated.
 † Values for molten gold are merely provisional values.

RECOMMENDED VALUES
[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]

SOLID		T	k	T	k
Polycrystalline					
0	0	350	0.226	350	0.226
1	0.00764*	373.2	0.224	373.2	0.224
2	0.0163*	400	0.223	400	0.223
3	0.0255	473.2	0.219	473.2	0.219
4	0.0349	500	0.217	500	0.217
5	0.0445	573.2	0.214	573.2	0.214
6	0.0544	600	0.213	600	0.213
7	0.0645	673.2	0.211	673.2	0.211
8	0.0746	700	0.210	700	0.210
9	0.0848	773.2	0.209	773.2	0.209
10	0.0952	800	0.208	800	0.208
11	0.106	873.2	0.207	873.2	0.207
12	0.116	900	0.207	900	0.207
13	0.126	973.2	0.207	973.2	0.207
14	0.135	1000	0.207	1000	0.207
15	0.144	1073.2	0.207	1073.2	0.207
16	0.152	1100	0.207	1100	0.207
18	0.167	1173.2	0.208	1173.2	0.208
20	0.180	1200	0.208	1200	0.208
25	0.205	1273.2	0.209	1273.2	0.209
30	0.222	1300	0.209	1300	0.209
35	0.233	1373.2	0.211	1373.2	0.211
40	0.241	1400	0.211	1400	0.211
45	0.247	1473.2	0.212	1473.2	0.212
50	0.251	1500	0.213	1500	0.213
60	0.256	1573.2	0.215	1573.2	0.215
70	0.259	1600	0.215	1600	0.215
80	0.260	1673.2	0.217	1673.2	0.217
90	0.260	1700	0.218	1700	0.218
100	0.260*	1773.2	0.220	1773.2	0.220
123.2	0.256*	1800	0.220	1800	0.220
150	0.251*	1873.2	0.222	1873.2	0.222
173.2	0.248*	1900	0.223	1900	0.223
300	0.244*	1973.2	0.225*	1973.2	0.225*
223.2	0.240*	2000	0.226*	2000	0.226*
250	0.236*				
273.2	0.233*				
298.2	0.230				
300	0.230				
323.2	0.228				


* Extrapolated or interpolated.

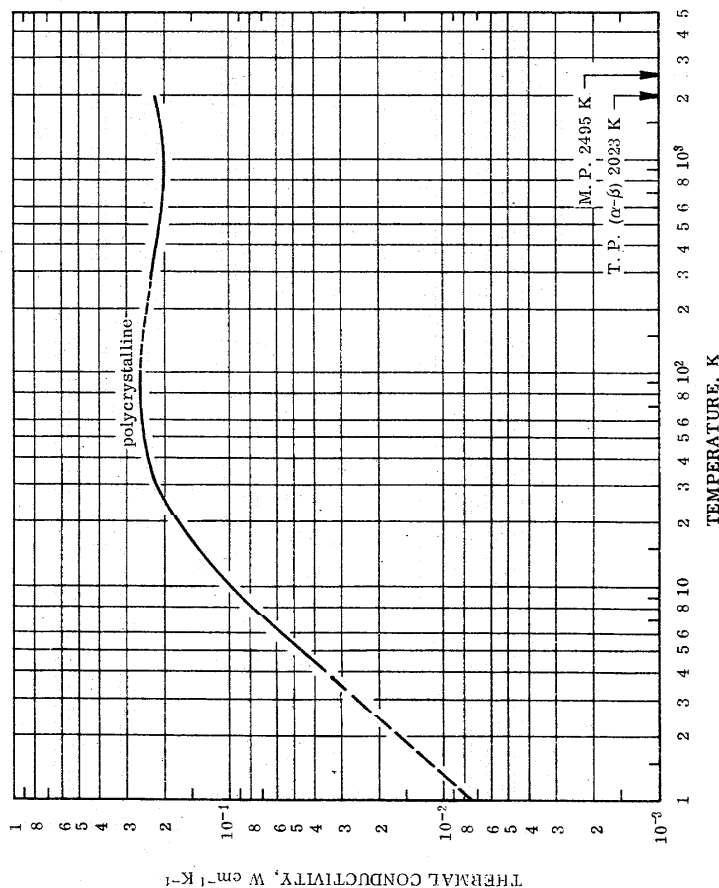

REMARKS

The recommended values above 150 K are for well-annealed high-purity polycrystalline hafnium and are considered accurate to within ± 10% of the true values at temperatures below 900 K and ± 20% above 900 K. Values below 150 K are applicable only to a sample having residual electrical resistivity $\rho_0 = 4.23 \mu\Omega$ cm and electrical resistivity ratio $\rho(295 K)/\rho_0 = 8.58$.

THERMAL CONDUCTIVITY OF HELIUM

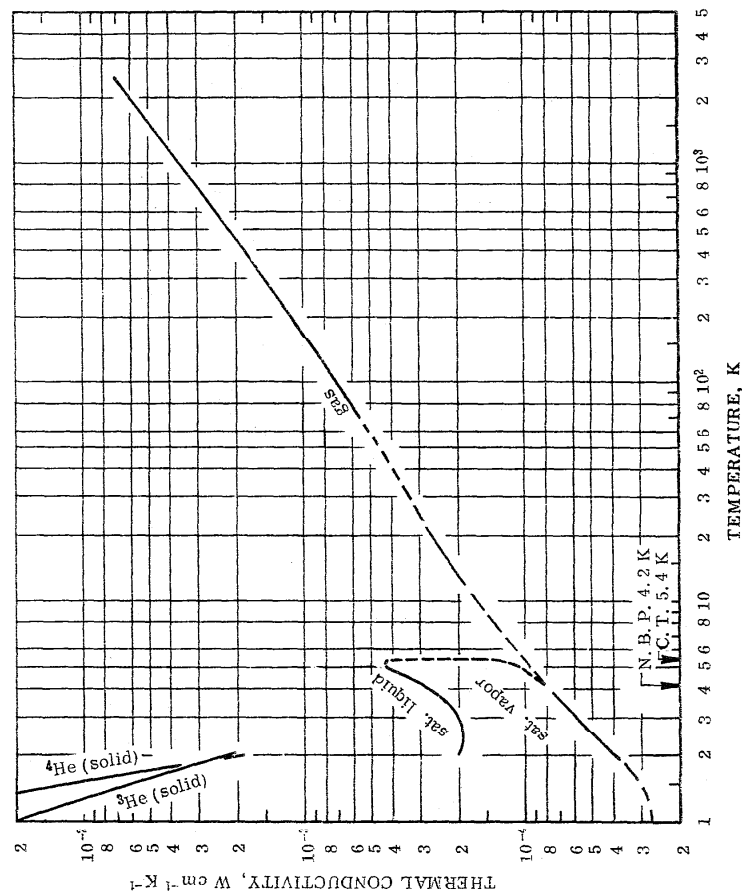

RECOMMENDED VALUES
 [Temperature, T, K; Thermal Conductivity, k , $\text{W cm}^{-1} \text{K}^{-1}$]

SOLID	
T	$k(^3\text{He})$
0.6	0.250
0.7	0.104
0.8	0.055
0.9	0.033
1.0	0.020
1.1	0.0144
1.2	0.0108
1.3	0.0089
1.4	0.0073
1.5	0.0057
1.6	0.0046
1.7	0.0038
1.8	0.0030
1.9	0.0025
2.0	0.0021

SATURATED LIQUID -- He-I	
T	$k \times 10^3$
2.5	0.191
3.0	0.203
3.5	0.232
4.0	0.281
4.5	0.348
5.0	0.434

REMARKS

Values of the thermal conductivity of the solid presented here are offered as order of magnitude values. Detailed specification of the sample size, orientation, density, etc. will be needed for a more accurate recommendation. The liquid values should be accurate to within 2%. Due to the lack of any experimental values for the gas from 4 to 14 K and from 21 to 73 K, the recommended values below 100 K may be uncertain to 5%. From 100 to 700 K the accuracy should be 2%, from 700 to 1500 K 5%, and above 1500 K 10%.

THERMAL CONDUCTIVITY OF HELIUM (continued)

RECOMMENDED VALUES


GAS

(At 1 atm above 4.2 K)

T	k x 10 ³	T	k x 10 ³	T	k x 10 ³	T	k x 10 ³
0.08	0.00044*	50	0.4623*	450	2.038	850	3.20
0.09	0.00053*	60	0.521*	460	2.071	860	3.23
0.10	0.00064*	70	0.578*	470	2.104	870	3.25
0.15	0.00130*	80	0.631	480	2.136	880	3.28
0.20	0.00231*	90	0.679	490	2.169	890	3.30
0.25	0.0039*	100	0.730	500	2.202	900	3.32
0.30	0.0062*	110	0.776	510	2.234	910	3.35
0.35	0.0089*	120	0.819	520	2.266	920	3.37
0.40	0.0120*	130	0.863	530	2.297	930	3.40
0.45	0.0154*	140	0.907	540	2.329	940	3.43
0.5	0.0187*	150	0.950	550	2.361	950	3.45
0.6	0.0231*	160	0.992	560	2.392	960	3.47
0.7	0.0282*	170	1.033	570	2.423	970	3.50
0.8	0.0262*	180	1.072	580	2.453	980	3.52
0.9	0.0266*	190	1.112	590	2.484	990	3.54
1.0	0.0269*	200	1.151	600	2.515	1000	3.57
1.25	0.0281*	210	1.190	610	2.55	1050	3.69
1.5	0.0306*	220	1.228	620	2.58	1100	3.80
2.0	0.0393	230	1.266	630	2.60	1150	3.91
2.5	0.0502	240	1.304	640	2.63	1200	4.03
3.0	0.0607	250	1.338	650	2.66	1250	4.14
3.5	0.0710	260	1.374	660	2.69	1300	4.25
4.0	0.0803	270	1.411	670	2.72	1350	4.36
4.5	0.0879*	280	1.447	680	2.75	1400	4.47
5.0	0.0962*	290	1.484	690	2.78	1450	4.57
6	0.1113*	300	1.520	700	2.81	1500	4.68
7	0.1247*	310	1.555	710	2.83	1550	4.78
8	0.1393*	320	1.591	720	2.86	1600	4.88
9	0.1523*	330	1.626	730	2.89	1650	4.98
10	0.1640*	340	1.662	740	2.91	1700	5.08
12	0.1866*	350	1.697	750	2.94	1750	5.18
14	0.2067	360	1.732	760	2.97	1800	5.28
16	0.2259	370	1.766	770	3.00	1850	5.38
18	0.2435	380	1.801	780	3.02	1900	5.47
20	0.2582	390	1.835	790	3.05	1950	5.57
25	0.2962*	400	1.870	800	3.08	2000	5.66
30	0.3330*	410	1.904	810	3.10	2100	5.85
35	0.3669*	420	1.937	820	3.13	2200	6.03
40	0.4000*	430	1.971	830	3.15	2300	6.22
45	0.4314*	440	2.004	840	3.18	2400	6.40
						2500	6.57

* Estimated or extrapolated.

THERMAL CONDUCTIVITY OF HOLMIUM

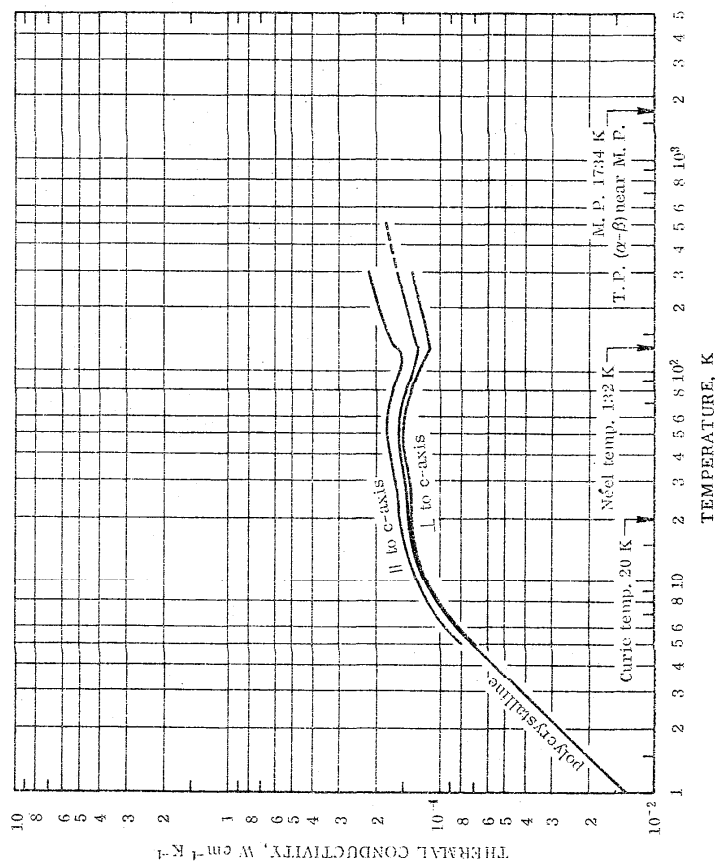


REMARKS

The provisional values are for well-annealed high-purity holmium and are thought to be accurate to within $\pm 20\%$ at temperatures above 150 K. Values below 150 K for k_l , k_t , and k_{poly} are applicable only to specimens having residual electrical resistivities of 3.21, 2.82, and 2.67 $\mu\Omega$ cm, respectively. These values are very uncertain.

PROVISIONAL VALUES											
[Temperature, T, K; Thermal Conductivity, k, $W\ cm^{-1}\ K^{-1}$]											
SOLID											
T	# to c-axis		Poly-crystalline		T	# to c-axis		Poly-crystalline		# to c-axis	
	k	k	k	k		k	k	k	k	k	k
0			0	0.0140	60	0.182	0.149	0.149	0.160		
1				0.0282	70	0.176	0.144	0.144	0.156		
2				0.0428	80	0.170	0.139	0.139	0.149		
3				0.0580	90	0.163	0.133	0.133	0.142		
4					100	0.158	0.127	0.127	0.136		
5	0.0803	0.0701	0.0733	0.0846	123.2	0.159	0.116	0.116	0.129		
6	0.0962	0.0846	0.0883		132	0.166	0.113	0.113	0.128		
7	0.109	0.0967	0.101		132	0.169	0.115	0.115	0.131		
8	0.118	0.105	0.109		150	0.179	0.116	0.116	0.135		
9	0.124	0.112	0.116		173.2	0.190	0.120	0.120	0.140		
10	0.130	0.117	0.121		200	0.200	0.126	0.126	0.147		
11	0.135	0.121	0.125		223.2	0.207	0.130	0.130	0.152		
12	0.139	0.125	0.129		250	0.212	0.134	0.134	0.156		
13	0.142	0.128	0.132		273.2	0.215	0.136	0.136	0.159		
14	0.146	0.131	0.136		298.2	0.222	0.138	0.138	0.162		
15	0.149	0.134	0.138		300	0.222	0.138	0.138	0.162		
16	0.152	0.136	0.141		323.2				0.165*		
18	0.157	0.140	0.146		350				0.167*		
20	0.160	0.140	0.144		373.2				0.170*		
25	0.161	0.139	0.146		400				0.173*		
30	0.168	0.142	0.150		473.2				0.180*		
35	0.173	0.146	0.154		500				0.183*		
40	0.177	0.149	0.158								
45	0.180	0.150	0.160								
50	0.182	0.152	0.161								

* Extrapolated or estimated.

THEMAL CONDUCTIVITY OF HYDROGEN

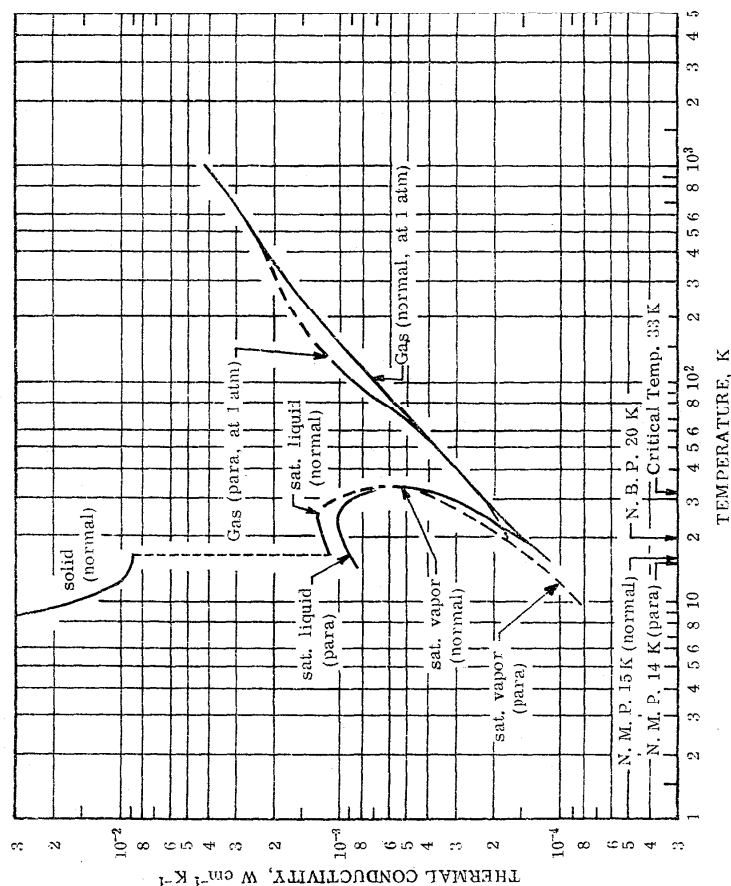

RECOMMENDED VALUES

[Temperature, T, K; Thermal Conductivity, k , $W\ cm^{-1}\ K^{-1}$]

SOLID (normal-Hydrogen)		SATURATED LIQUID (normal-Hydrogen)		SATURATED VAPOR (normal-Hydrogen)	
T	k	T	$k \times 10^3$	T	$k \times 10^3$
4	2.30	15	1.022	15	0.117*
5	0.550	16	1.055	16	0.126*
6	0.190	17	1.088	17	0.134*
7	0.083	18	1.121	18	0.142*
8	0.043	19	1.153	19	0.150*
9	0.023	20	1.184	20	0.159*
10	0.0158	21	1.213	21	0.169*
11	0.0125	22	1.258	22	0.180*
12	0.0100	23	1.288	23	0.192*
13	0.0095	24	1.272	24	0.205*
14	0.0090	25	1.269	25	0.22*
15	0.0090	26	1.251*	26	0.23*
16	0.0089	27	1.217*	27	0.25*
17	0.0089	28	1.168*	28	0.27*
		29	1.17*	29	0.29*
		30	1.06*	30	0.31*
		31	1.00*	31	0.35*
		32	0.91*	32	0.40*
		33	0.60*†	33	0.60*†

REMARKS

No overlap between two different experimental studies for the solid occurs. While the values from 5 to 10 K appear accurate to within 5%, from 10 to 17 K to within 15% and at 4 K to within 25%, confirmatory measurements are very desirable. The liquid values below 25 K are probably accurate to about 3%. However, an error of 100% at the critical point could occur. The saturated vapor values should have similar uncertainties. The gas values should be accurate to within 2% from 100 to 400 K and 5% for other tabulated temperatures.

The para form uncertainties for the liquid may be accurate to within 2%, although a 5% uncertainty for both liquid and vapor forms is not ruled out. The gas values between 100 and 400 K should check to within 3% and other table entries to within 5%.

* Estimated or extrapolated, hence provisional.
 † Pseudo-critical value.

THERMAL CONDUCTIVITY OF HYDROGEN (continued)

RECOMMENDED VALUES (normal-Hydrogen, at 1 atm)			RECOMMENDED VALUES (para-Hydrogen)			RECOMMENDED VALUES (para-Hydrogen)			
T	$k \times 10^3$	T	$k \times 10^3$	T	$k \times 10^3$	T	$k \times 10^3$	T	$k \times 10^3$
20	0.159	350	2.033	700	3.25	14†	0.824	10	0.081*
25	0.193	360	2.069	710	3.29	15	0.855	11	0.089*
30	0.227	370	2.106	720	3.32	16	0.885	12	0.096*
35	0.261	380	2.142	730	3.36	17	0.910	13	0.103*
40	0.294	390	2.177	740	3.39	18	0.933	14	0.111*
45	0.328	400	2.212	750	3.43	19	0.954	15	0.118*
50	0.361	410	2.248	760	3.46	20	0.972	16	0.128*
60	0.426	420	2.283	770	3.50	21	0.988	17	0.137*
70	0.489	430	2.318	780	3.53	22	0.999	18	0.147*
80	0.552	440	2.354	790	3.56	23	1.007	19	0.157*
90	0.614	450	2.389	800	3.60	24	1.006	20	0.168*
100	0.676	460	2.424	810	3.63	25	0.998	21	0.181*
110	0.738	470	2.459	820	3.67	26	0.975	22	0.194*
120	0.801	480	2.494	830	3.70	27	0.947	23	0.209*
130	0.864	490	2.529	840	3.74	28	0.910	24	0.224*
140	0.926	500	2.564	850	3.77	29	0.870	25	0.242*
150	0.986	510	2.60	860	3.80	30	0.826	26	0.260*
160	1.046	520	2.64	870	3.84	31	0.74*	27	0.280*
170	1.105	530	2.67	880	3.87	32	0.58*†	28	0.304*
180	1.164	540	2.70	890	3.91			29	0.332*
190	1.222	550	2.74	900	3.94			30	0.363*
200	1.280	560	2.77	910	3.97			31	0.45*
210	1.338	570	2.80	920	4.01			32	0.58*†
220	1.395	580	2.84	930	4.04				
230	1.451	590	2.88	940	4.08				
240	1.506	600	2.91	950	4.11				
250	1.560	610	2.95	960	4.14				
260	1.613	620	2.98	970	4.18				
270	1.665	630	3.01	980	4.21				
280	1.717	640	3.05	990	4.25				
290	1.767	650	3.08	1000	4.28				
300	1.815	660	3.12						
310	1.863	670	3.15						
320	1.910	680	3.19						
330	1.954	690	3.22						
340	1.994								

* Estimated or extrapolated, hence provisional.

† Pseudo-critical value.


THERMAL CONDUCTIVITY OF HYDROGEN (continued)

RECOMMENDED VALUES
GAS
(para-Hydrogen, at 1 atm)

T	k x 10 ³	T	k x 10 ³	T	k x 10 ³
20	0.168				
25	0.198	300	1.880*	650	3.08*
30	0.229	310	1.920*	660	3.12*
35	0.261	320	1.958*	670	3.15*
40	0.294	330	1.994*	680	3.19*
45	0.328	340	2.028*	690	3.22*
50	0.363	350	2.061*	700	3.25*
60	0.434	360	2.093*	710	3.29*
70	0.513	370	2.126*	720	3.32*
80	0.601	380	2.159*	730	3.36*
90	0.696	390	2.191*	740	3.39*
100	0.797	400	2.223*	750	3.43*
110	0.899	410	2.258*	760	3.46*
120	1.000	420	2.292*	770	3.50*
130	1.093*	430	2.326*	780	3.53*
140	1.177*	440	2.361*	790	3.56*
150	1.251*	450	2.395*	800	3.60*
160	1.316*	560	2.429*	810	3.63*
170	1.372*	470	2.463*	820	3.67*
180	1.426*	480	2.497*	830	3.70*
190	1.470*	490	2.532*	840	3.74*
200	1.512*	500	2.565*	850	3.77*
210	1.551*	510	2.60*	860	3.80*
220	1.588*	520	2.64*	870	3.84*
230	1.624*	530	2.67*	880	3.87*
240	1.660*	540	2.70*	890	3.91*
250	1.696*	550	2.74*	900	3.94*
260	1.732*	560	2.77*	910	3.97*
270	1.768*	570	2.80*	920	4.01*
280	1.806*	580	2.84*	930	4.04*
290	1.843*	590	2.88*	940	4.08*
		600	2.91*	950	4.11*
		610	2.95*	960	4.14*
		620	2.98*	970	4.18*
		630	3.01*	980	4.21*
		640	3.05*	990	4.25*
				1000	4.28*

* Estimated or extrapolated, hence provisional.

THERMAL CONDUCTIVITY OF DEUTERIUM (Hydrogen Isotope)

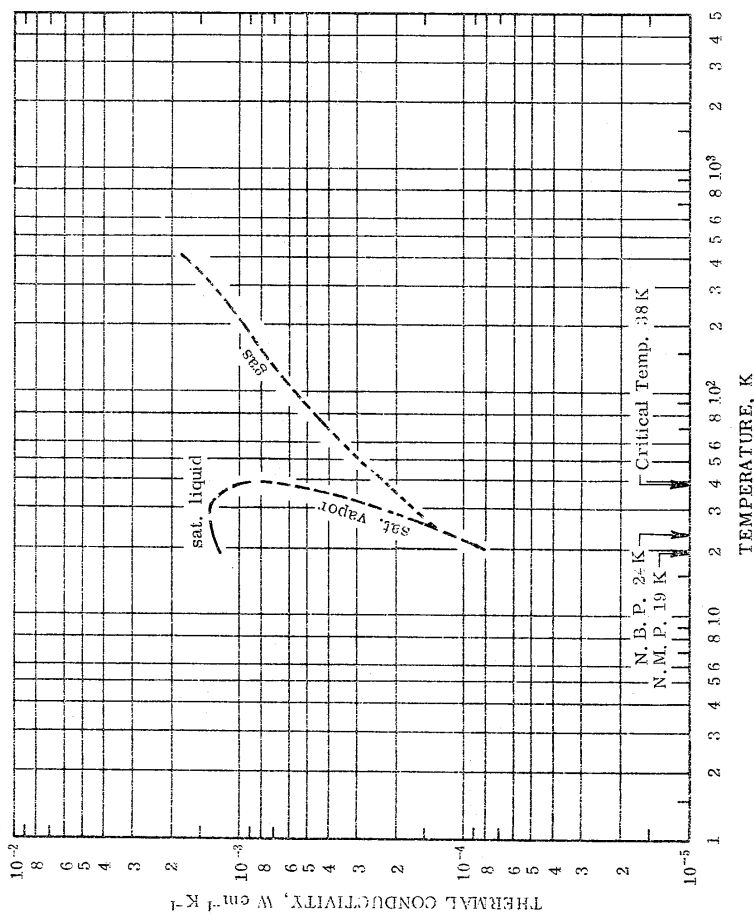

REMARKS

The liquid state apparently exhibits a maximum in conductivity at about 28 K. While some earlier tabulations neglected this, the present values are thought accurate to within 5% below 30 K and 10% from 30 to 35 K, with an unknown uncertainty at higher temperatures. The vapor values are provisional. The gas values are based on a set of measurements from 15 to 25 K, from 65 to 89 K and measurements at the ice point. Between 20 and 280 K they may be accurate to within 5%.

RECOMMENDED VALUES

[Temperature, T, K; Thermal Conductivity, k , $\text{W cm}^{-1} \text{K}^{-1}$]

SATURATED LIQUID		SATURATED VAPOR	
T	$k \times 10^3$	T	$k \times 10^3$
19	1.24*	20	0.084*
20	1.26	21	0.086*
21	1.28	22	0.109*
22	1.30	23	0.123*
23	1.33	24	0.138*
24	1.34	25	0.155*
25	1.36*	26	0.174*
26	1.37*	27	0.193*
27	1.38*	28	0.215*
28	1.38*	29	0.238*
29	1.38*	30	0.26*
30	1.37*	31	0.29*
31	1.35*	32	0.32*
32	1.32*	33	0.36*
33	1.29*	34	0.40*
34	1.25*	35	0.45*
35	1.21*	36	0.51*
36	1.15*	37	0.58*
37	1.07*	38	0.83*†
38	0.83*†		

* Estimated or extrapolated, hence provisional.
 † Pseudo-critical value.

* Estimated or extrapolated, hence provisional.
 † Pseudo-critical value.


THERMAL CONDUCTIVITY OF DEUTERIUM BLENDED ISOTOPE (continued)

RECOMMENDED VALUES

GAS (At 1 atm)		T	k x 10 ³
T	k x 10 ³	T	k x 10 ³
24	0.135	200	1.014*
25	0.139	210	1.056*
30	0.175	220	1.097*
35	0.206	230	1.138*
40	0.236	240	1.178*
45	0.268	250	1.217*
50	0.299	260	1.256*
60	0.360	270	1.294*
70	0.421	280	1.331*
80	0.475	290	1.369*
90	0.527	300	1.406*
100	0.577*	310	1.444*
110	0.625*	320	1.48*
120	0.672*	330	1.51*
130	0.718*	340	1.55*
140	0.762*	350	1.59*
150	0.806*	360	1.62*
160	0.848*	370	1.66*
170	0.890*	380	1.69*
180	0.931*	390	1.73*
190	0.973*	400	1.76*

* Estimated or extrapolated, hence provisional.

THERMAL CONDUCTIVITY OF TRITIUM (Hydrogen Isotope)

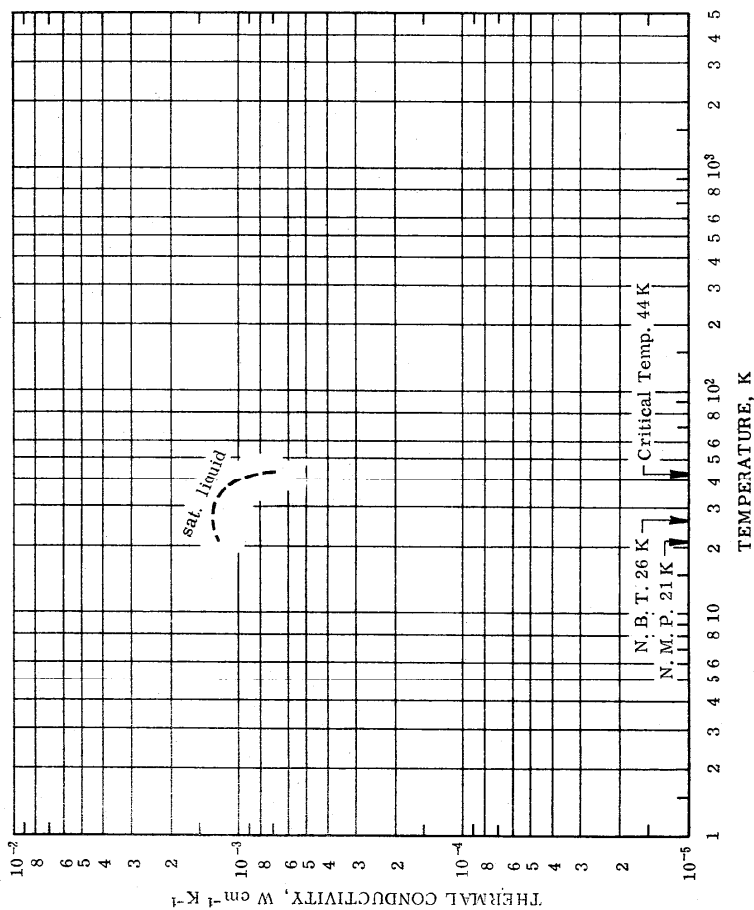

PROVISIONAL VALUES
 [Temperature, T, K; Thermal Conductivity, k , $\text{W cm}^{-1} \text{K}^{-1}$]

SATURATED LIQUID


T	$k \times 10^3$
21	1.25*
22	1.28*
24	1.32*
26	1.36*
28	1.37*
30	1.34*
32	1.30*
34	1.25*
36	1.18*
38	1.10*
40	1.00*
42	0.89*
44	0.68*†

REMARKS

The liquid values presented here are based on a correlation which, while apparently reasonable, lacks experimental substantiation. No error estimate is offered.

* Estimated or extrapolated.
 † Pseudo-critical value.

THE THERMAL CONDUCTIVITY OF INDIUM

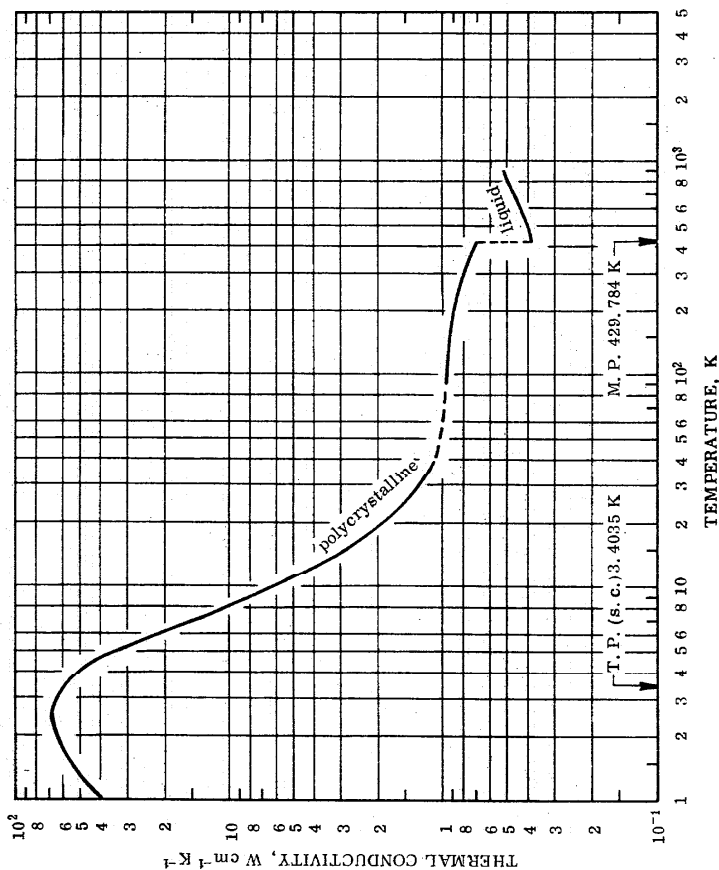

REMARKS

The recommended values are for well-annealed high-purity polycrystalline indium and are considered accurate to within $\pm 15\%$ of the true values at temperatures below 100 K and $\pm 5\%$ above. For liquid indium the values are probably good to $\pm 15\%$. The thermal conductivity at temperatures near and below the corresponding temperature, T_m , of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens, and the recommended values below 60 K are applicable only to a specimen having residual electrical resistivity $\rho_0 = 0.00587 \mu\Omega \text{ cm}$. Values at temperatures below about 1.5 Tm are calculated to fit experimental data by using equation (7) and using the constants m, n, and α' given in Table I for indium and $\beta = 0.0240$.

RECOMMENDED VALUES †


[Temperature, T, K; Thermal Conductivity, k, $\text{W cm}^{-1} \text{K}^{-1}$]

SOLID		
Polycrystalline		Polycrystalline
T	k	T
0	0	
1	40.2*	60
2	64.9	70
3	64.0	80
4	49.6	90
5	32.4	100
6	20.7	123.2
7	14.1	150
8	10.1	173.2
9	7.47	200
10	5.88	223.2
11	4.86	250
12	4.12	273.2
13	3.59	298.2
14	3.18	300
15	2.86	323.2
16	2.61	350
18	2.22	373.2
20	1.94	400
25	1.51	429.784
30	1.28	
35	1.15*	
40	1.09*	
45	1.06*	
50	1.04*	
LIQUID		
T	k	T
429.784	0.382	
473.2	0.387	
500	0.394	
573.2	0.417	
600	0.425	
673.2	0.446	
700	0.453	
773.2	0.472	
800	0.479	
873.2	0.482	
900	0.494	

* Extrapolated or interpolated.

† Values for the liquid state are provisional.

THERMAL CONDUCTIVITY OF IODINE

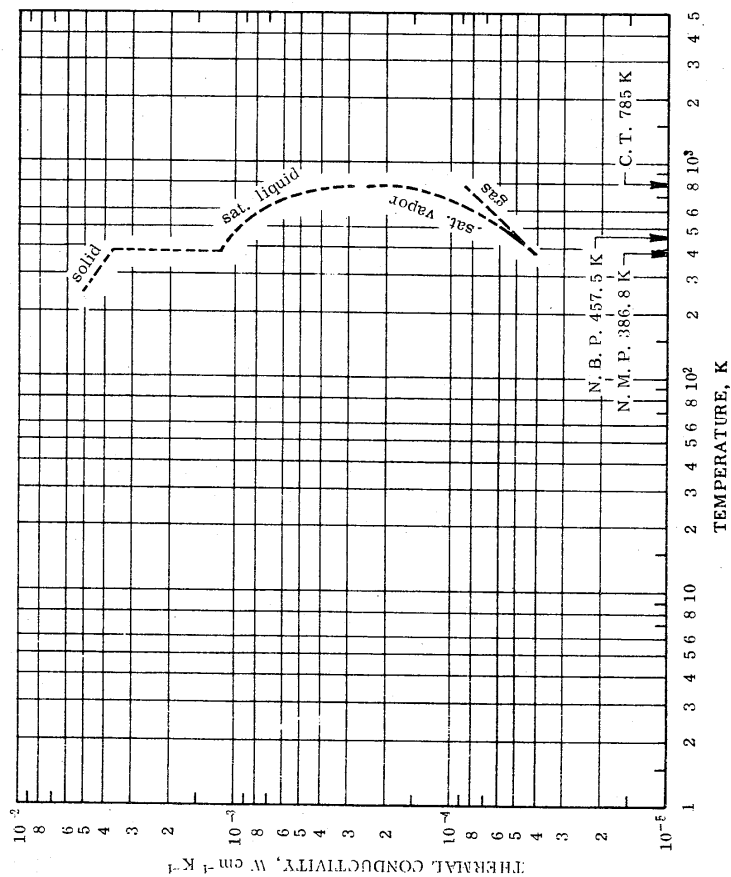

RECOMMENDED VALUES [Temperature, T, K; Thermal Conductivity, k , $W\ cm^{-1}\ K^{-1}$]			SATURATED LIQUID			SATURATED VAPOR		
SOLID			SATURATED LIQUID			SATURATED VAPOR		
T	$k \times 10^3$		T	$k \times 10^3$		T	$k \times 10^3$	
250	5.12*		386.8†	1.16*		350	0.038*	
273.2	4.81*		400	1.14*		375	0.041*	
275	4.79*		425	1.11*		400	0.044*	
300	4.49		450	1.07*		425	0.047*	
325	4.24		475	1.03*		450	0.050*	
350	4.01*		500	0.99*		475	0.053*	
375	3.83*		525	0.95*		500	0.056*	
386.8†	3.73*		550	0.90*		525	0.060*	
			575	0.86*		550	0.064*	
			600	0.82*		575	0.069*	
			625	0.77*		600	0.074*	
			650	0.71*		625	0.079*	
			675	0.65*		650	0.085*	
			700	0.58*		675	0.093*	
			725	0.51*		700	0.104*	
			750	0.43*		725	0.119*	
			775	0.32*		750	0.143*	
			785	0.26*†		775	0.186*	
						785	0.26*†	

GAS
(At 1 atm)

T	$k \times 10^3$		T	$k \times 10^3$
457.5	0.951		600	0.065
475	0.952		625	0.068
500	0.955		650	0.071
525	0.958		675	0.073
550	0.960		700	0.076
575	0.963		725	0.079*
			750	0.082*
			775	0.084*
			800	0.087*

REMARKS


Few experimental values exist for any phase for this element. The few that are available enable an estimate to be made, that the recommended values for the solid are accurate to within 10% from 300 to 330 K and for the gas to within 25%. All other values are considered provisional.

* Estimated or extrapolated, hence provisional.

† Pseudo-critical value.

‡ Normal melting point.

THERMAL CONDUCTIVITY OF IRIIDIUM

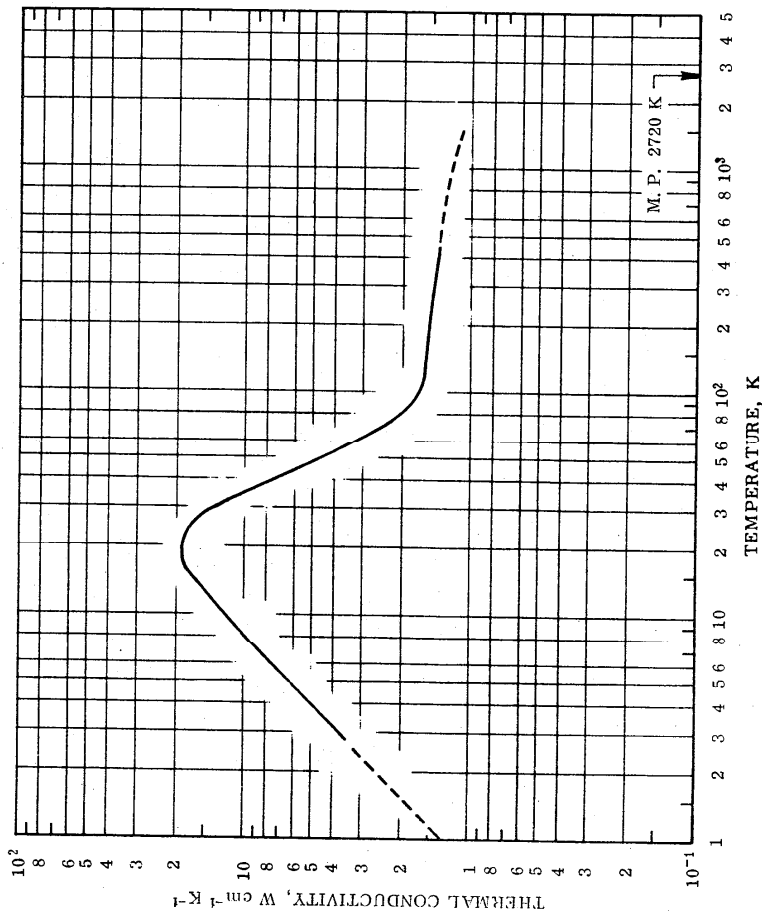

REMARKS

The recommended values are for well-annealed high-purity iridium and are considered accurate to within $\pm 5\%$ of the true values at temperatures below 500 K and $\pm 10\%$ above. The thermal conductivity at temperatures near and below the corresponding temperature, T_m , of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens, and the recommended values below 150 K are applicable only to a specimen having residual electrical resistivity $\rho_{30} = 0.0191 \mu\Omega \text{ cm}$. Values at temperatures below about 1.5 Tm are calculated to fit experimental data by using equation (7) and using the constants m, n, and α' given in Table 1 for iridium and $\beta = 0.781$.


RECOMMENDED VALUES

[Temperature, T, K; Thermal Conductivity, k, $\text{W cm}^{-1} \text{K}^{-1}$]

T		SOLID	
T	k	T	k
0		250	1.50
1	1.30*	273.2	1.48
2	2.60	298.2	1.47
3	3.90	300	1.47
4	5.19	323.2	1.47
5	6.48	350	1.46
6	7.77	373.2	1.45
7	9.04	400	1.44
8	10.3	473.2	1.42
9	11.5	500	1.41*
10	12.7	573.2	1.39*
11	13.8	600	1.38*
12	14.9	673.2	1.36*
13	15.9	700	1.35*
14	16.7	773.2	1.33*
15	17.5	800	1.32*
16	18.1	873.2	1.30*
18	18.9	900	1.29*
20	19.0	973.2	1.27*
25	17.2	1000	1.26*
30	13.7	1073.2	1.24*
35	10.1	1100	1.23*
40	7.50	1173.2	1.21*
45	5.89	1200	1.20*
50	4.72	1273.2	1.18*
60	3.31	1300	1.17*
70	2.54	1373.2	1.15*
80	2.09	1400	1.14*
90	1.84	1473.2	1.12*
100	1.72	1500	1.11*
123.2	1.65		
150	1.59		
173.2	1.56		
200	1.53		
223.2	1.51		

* Extrapolated.

THERMAL CONDUCTIVITY OF IRON

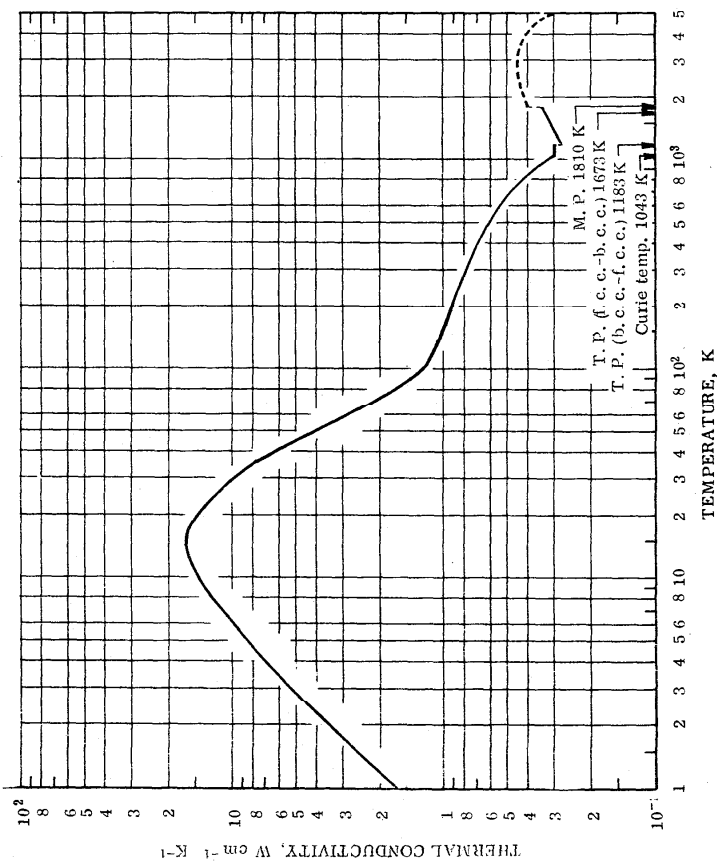

REMARKS

The recommended values are for well-annealed high-purity iron and are considered accurate to within $\pm 5\%$ of the true values at temperatures below 100 K, $\pm 3\%$ from 100 K to room temperature, $\pm 2\%$ from room temperature to about 1000 K, the uncertainty probably increasing to about $\pm 8\%$ at 1600 K and $\pm 15\%$ at the melting point. Reliable estimation of the uncertainty of the provisional values for molten iron can hardly be given. The thermal conductivity at temperatures near and below the corresponding temperature, T_m , of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens, and the recommended values below 200 K are applicable only to a specimen having residual electrical resistivity $\rho_0 = 0.0143 \mu\Omega$ cm. Values at temperatures below about 1.5 T_m are calculated to fit experimental data by using equation (7) and using the constants m , n , and α' given in Table 1 for iron and the parameter $\beta = 0.585$.

RECOMMENDED VALUES †


[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]

SOLID			LIQUID		
T	k	T	k	T	k
0	0	250	0.865	1810	0.403*
1	1.71*	273.2	0.833	1873.2	0.413*
2	3.42	298.2	0.804	1900	0.415*
3	5.11	300	0.802	1973.2	0.423*
4	6.77	323.2	0.774	2000	0.426*
5	8.39	350	0.744	2073.2	0.432*
6	9.93	373.2	0.720	2173.2	0.439*
7	11.4	400	0.695	2200	0.441*
8	12.7	473.2	0.634	2273.2	0.446*
9	13.9	500	0.613	2400	0.450*
10	14.8	573.2	0.564	2473.2	0.452*
11	15.6	600	0.547	2600	0.455*
12	16.3	673.2	0.504	2673.2	0.456*
13	16.7	700	0.488	2800	0.458*
14	16.9	773.2	0.448	2873.2	0.459*
15	17.0	800	0.433	3000	0.458*
16	16.9	873.2	0.394	3073	0.458*
18	16.3	900	0.380	3200	0.456*
20	15.4	973.2	0.340	3273	0.454*
25	12.7	1000	0.323	3400	0.451*
30	10.0	1043	0.295	3600	0.442*
35	7.88	1073.2	0.298	3800	0.430*
40	6.23	1100	0.298	4000	0.415*
45	4.99	1173.2	0.300	4500	0.368*
50	4.05	1183	0.300	5000	0.306*
60	2.85	1183	0.280	5500	0.233*
70	2.16	1200	0.283	6000	0.147*
80	1.75	1273.2	0.296	6500	0.051*
90	1.50	1300	0.300		
100	1.34	1373.2	0.309		
123.2	1.15	1400	0.312		
150	1.04	1473.2	0.319		
173.2	0.991	1500	0.329		
200	0.940	1573.2	0.327		
223.2	0.904	1600	0.330		
		1673.2	0.335*		
		1700	0.338*		
		1773.2	0.343*		
		1800	0.345*		
		1810	0.346*		

* Extrapolated or estimated.

† Values for molten iron are provisional.

Thermal Conductivity of Armco Iron

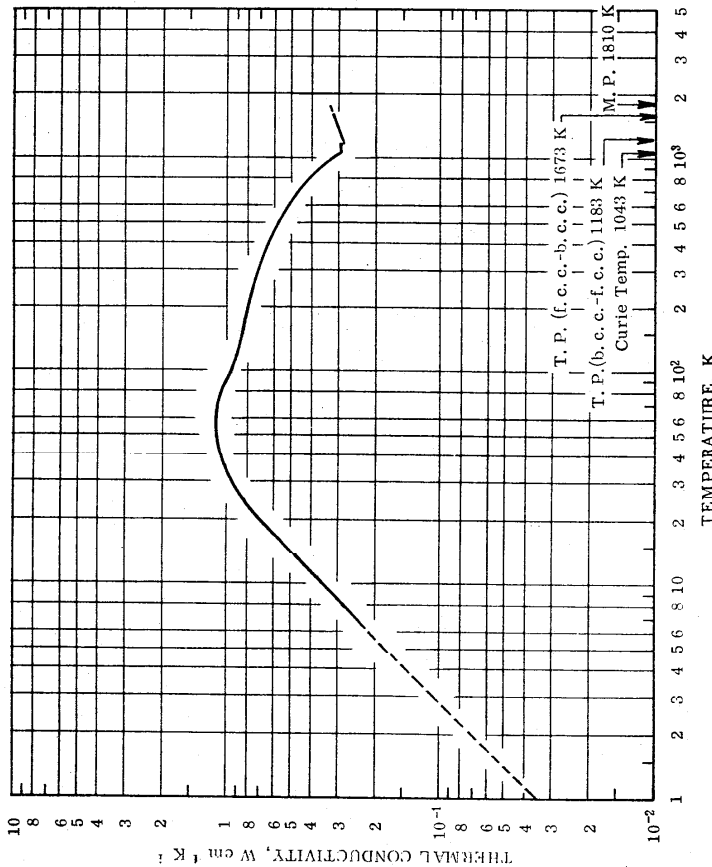

REMARKS

The recommended values are for well-annealed Armco iron and are considered accurate to within $\pm 5\%$ of the true values at temperatures below 100 K, $\pm 3\%$ from 100 K to room temperature, $\pm 2\%$ from room temperature to about 1000 K, the uncertainty probably increasing to about $\pm 8\%$ at 1600 K and $\pm 15\%$ at the melting point. The thermal conductivity at temperatures near and below the corresponding temperature of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens, and the recommended values below 200 K are applicable only to a specimen having residual electrical resistivity $\rho_0 = 0.690 \mu\Omega \text{ cm}$. For other specimens having different residual electrical resistivities, thermal conductivity values may be derived from measured electrical resistivity data and values of the Lorenz function given in the table.


RECOMMENDED VALUES

[Temperature, T, K; Thermal Conductivity, k, $\text{W cm}^{-1} \text{K}^{-1}$;
Lorenz Function, L, $10^{-8} \text{V}^2 \text{K}^{-2}$]

T	k	T	k	T	L
0	0.765	250	0.747	6	2.505
1	0.0358*	273.2	0.728	7	2.523
2	0.0718*	298.2	0.727	8	2.531
3	0.108*	300	0.710	9	2.533
4	0.144*	323.2	0.691	10	2.532
5	0.180*	350	0.676	12	2.529
6	0.217	373.2	0.657	14	2.528
7	0.253	400	0.610	16	2.528
8	0.290	473.2	0.593	18	2.527
9	0.326	500	0.547	20	2.521
10	0.362	573.2	0.531	25	2.477
11	0.398	600	0.488	30	2.395
12	0.434	673.2	0.473	35	2.292
13	0.470	700	0.435	40	2.188
14	0.505	773.2	0.422	45	2.096
15	0.541	800	0.386	50	2.021
16	0.575	873.2	0.372	55	1.965
18	0.644	900	0.336	60	1.927
20	0.712	973.2	0.323	65	1.905
25	0.858	1000	0.298	70	1.895
30	0.882	1059	0.283	75	1.895
35	1.07	1073.2	0.294	80	1.903
40	1.13	1100	0.296	85	1.917
45	1.15	1173.2	0.285	90	1.935
50	1.15	1183	0.285	95	1.956
60	1.13	1183	0.287	100	1.980
70	1.09	1200	0.284	110	2.034
80	1.05	1273.2	0.294	120	2.091
90	1.00	1300	0.303	130	2.150
100	0.956	1373.2	0.306	140	2.209
123.2	0.896	1400	0.312	150	2.266
150	0.855	1473.2	0.314	160	2.320
173.2	0.831	1500	0.320	170	2.371
200	0.806	1573.2	0.322*	180	2.418
223.2	0.786	1600	0.328*	190	2.461
		1673.2	0.330*	200	2.499
		1700	0.336*		
		1773.2	0.338*		
		1800			

* Extrapolated.

THERMAL CONDUCTIVITY OF KRYPTON

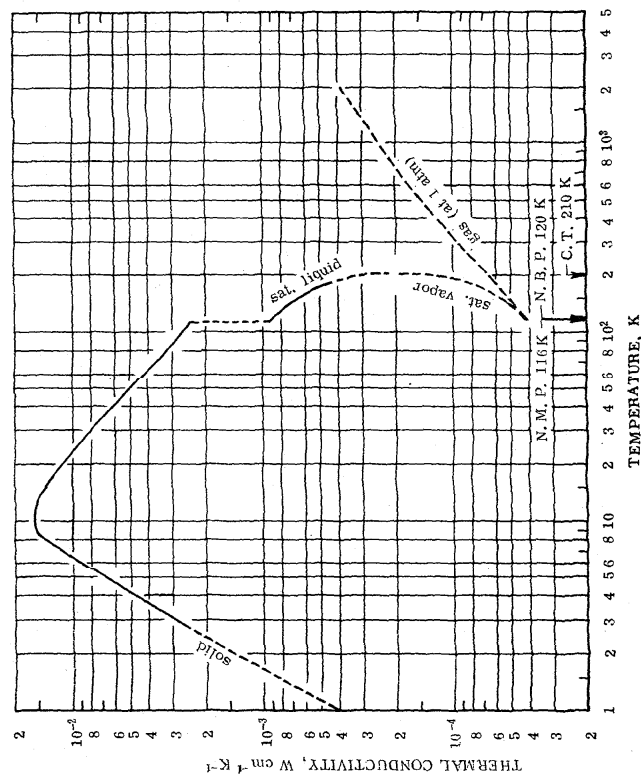

REMARKS

Serious differences exist in measurements for the solid, possibly produced by varying impurity contents. These produce an uncertainty of possibly 40% above 25 K. No reliable estimate at lower temperatures is felt possible. The saturated liquid values below 150 K should be accurate to within 2%, the uncertainty steadily increasing to possibly 20% at the critical point. For the vapor a 3% uncertainty below 150 K is considered to increase to 20% at the critical point. The gas values are considered accurate to within 2% below 600 K, 5% from 600 to 1500 K, and possibly within 10% at 2000 K.

RECOMMENDED VALUES			SATURATED LIQUID			SATURATED VAPOR		
[Temperature, T, K; Thermal Conductivity, k, W cm ⁻¹ K ⁻¹]			T			T		
SOLID			k x 10 ³			k x 10 ³		
T	k x 10 ³		T	k x 10 ³		T	k x 10 ³	
1	0.4*		116†	0.931		120	0.0406*	
1.5	0.8*		120	0.90†		125	0.0429*	
2	1.3*		125	0.872		130	0.0452*	
2.5	2.0*		130	0.83†		135	0.0476*	
3	2.7		135	0.806		140	0.0501*	
3.5	3.5		140	0.77‡		145	0.0527*	
4	4.4		145	0.746		150	0.0554*	
4.5	5.4		150	0.708		155	0.059*	
5	6.5		155	0.675		160	0.062*	
6	8.9		160	0.642		165	0.065*	
7	10.7		165	0.609		170	0.070*	
8	14.4		170	0.576		175	0.074*	
9	16		175	0.543		180	0.079*	
10	17		180	0.510		185	0.085*	
12	16		185	0.477		190	0.093*	
14	15		190	0.444		195	0.101*	
16	14		195	0.403		200	0.112*	
18	13		200	0.363		205	0.135*	
20	12		205	0.31*		210	0.31**†	
25	9.8		210	0.21**†				
30	8.3							
35	7.1							
40	6.2							
45	5.6							
50	5.1							
60	4.3							
70	3.8							
80	3.4							
90	3.1							
100	2.8							
110	2.6							
116‡	2.5							

* Estimated or extrapolated.

† Pseudo-critical value.


‡ Normal-boiling point.

THERMAL CONDUCTIVITY OF KRYPTON (continued)

RECOMMENDED VALUES

GAS (AT 1 atm)		k x 10 ³	
T	T	T	T
120	500	0.147	900
130	510	0.149	910
140	520	0.151	920
150	530	0.154	930
160	540	0.156	940
170	550	0.158	950
180	560	0.160	960
190	570	0.162	970
200	580	0.165	980
210	590	0.167	990
220	600	0.169	1000
230	610	0.171	1050
240	620	0.173	1100
250	630	0.176	1150
260	640	0.178	1200
270	650	0.180	1250
280	660	0.182	1300
290	670	0.184	1350
300	680	0.186	1400
310	690	0.188	1450
320	700	0.190	1500
330	710	0.192	1550
340	720	0.194	1600
350	730	0.196	1650
360	740	0.198	1700
370	750	0.200	1750
380	760	0.201	1800
390	770	0.203	1850
400	780	0.205	1900
410	790	0.207	1950
420	800	0.209	2000
430	810	0.211	
440	820	0.212	
450	830	0.214	
460	840	0.216	
470	850	0.218	
480	860	0.220	
490	870	0.221	
	880	0.223	
	890	0.225	
	900	0.227	
	910	0.228	
	920	0.230	
	930	0.231	
	940	0.233	
	950	0.235	
	960	0.237	
	970	0.239	
	980	0.240	
	990	0.242	
	1000	0.244	
	1050	0.252	
	1100	0.260	
	1150	0.268	
	1200	0.276	
	1250	0.284	
	1300	0.291	
	1350	0.299	
	1400	0.306	
	1450	0.313	
	1500	0.320	
	1550	0.327	
	1600	0.334	
	1650	0.341	
	1700	0.347	
	1750	0.353	
	1800	0.359	
	1850	0.365	
	1900	0.371	
	1950	0.377	
	2000	0.382	

THERMAL CONDUCTIVITY OF LANTHANUM

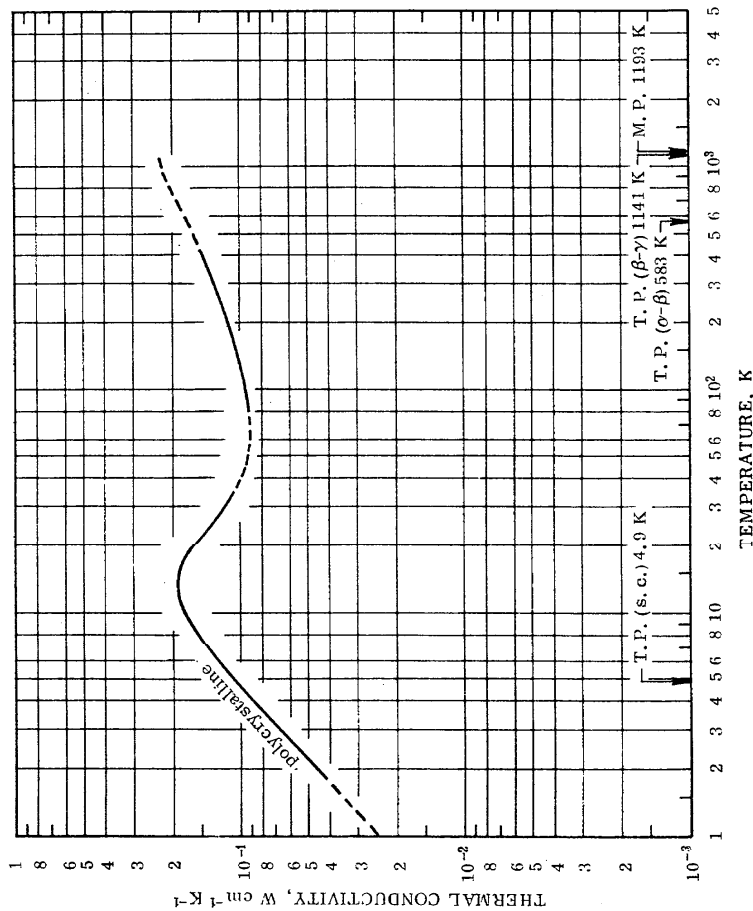

REMARKS

The values are for well-annealed high-purity lanthanum. Above 80 K the values are recommended values and are considered accurate to within $\pm 5\%$ of the true values at temperatures within ± 100 K of room temperature and ± 10 to $\pm 15\%$ at other temperatures. The provisional values above 10K are very uncertain, and those below 10K should be good to $\pm 15\%$. The thermal conductivity at temperatures near and below the corresponding temperature of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens, and the values below 50 K are applicable only to lanthanum having residual electrical resistivity $\rho_0 = 1.29 \mu\Omega \text{ cm}$.

RECOMMENDED VALUES †


[Temperature, T, K; Thermal Conductivity, k, $\text{W cm}^{-1} \text{K}^{-1}$]

SOLID		k		T	
Polycrystalline					
T	k	T	k	T	k
0	0	123.2	0.103		
1	0.0250*	150	0.109		
2	0.0468	173.2	0.116		
3	0.0674	200	0.118		
4	0.0875	223.2	0.122		
5	0.107	250	0.127		
6	0.124	273.2	0.131		
7	0.140	298.2	0.134		
8	0.154	300	0.135		
9	0.166	323.2	0.138		
10	0.176	350	0.142		
11	0.183	373.2	0.145		
12	0.188	400	0.149		
13	0.191	473.2	0.158*		
14	0.192	500	0.162*		
15	0.191	573.2	0.175*		
16	0.188	600	0.179*		
18	0.179	673.2	0.192*		
20	0.168	700	0.196*		
25	0.141	773.2	0.207*		
30	0.121	800	0.211*		
35	0.108	873.2	0.219*		
40	0.101	900	0.222*		
45	0.0969*	973.2	0.227*		
50	0.0943*	1000	0.229*		
60	0.0927*	1073.2	0.232*		
70	0.0929*	1100	0.232*		
80	0.0941*				
90	0.0958				
100	0.0978				

* Extrapolated or interpolated.

† Values below 80 K are provisional.

THERMAL CONDUCTIVITY OF LEAD

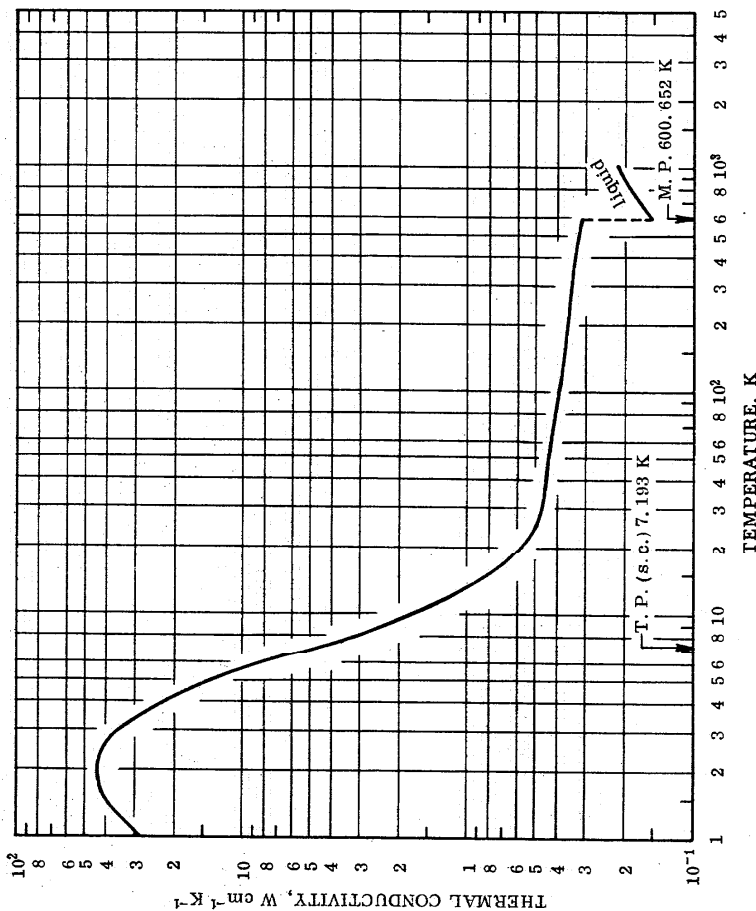

RECOMMENDED VALUES †
[Temperature, T, K; Thermal Conductivity, k, $\text{W cm}^{-1} \text{K}^{-1}$]


SOLID			LIQUID		
T	k	T	k	T	k
0	0	60	0.425	600.652	0.155
1	27.9	70	0.416	673.2	0.170
2	44.6	80	0.409	700	0.175
3	35.8	90	0.403	773.2	0.187
4	22.2	100	0.397	800	0.192
5	13.8	123.2	0.389	873.2	0.201
6	8.10	150	0.379	900	0.205
7	4.86	173.2	0.372	973.2	0.212
8	3.20	200	0.367	1000	0.215
9	2.30	223.2	0.365		
10	1.78	250	0.360		
11	1.46	273.2	0.356		
12	1.23	298.2	0.353		
13	1.07	300	0.353		
14	0.944	323.2	0.350		
15	0.845	350	0.347		
16	0.772	373.2	0.344		
18	0.661	400	0.340		
20	0.591	473.2	0.330		
25	0.507	500	0.328		
30	0.477	573.2	0.318		
35	0.462	600	0.314		
40	0.451	600.652	0.314		
45	0.442				
50	0.436				

REMARKS

The recommended values are for well-annealed high-purity lead and are considered accurate to within $\pm 3\%$ of the true values at moderate temperatures, $\pm 5\%$ at high temperatures, and $\pm 10\%$ at low temperatures and for molten lead within about 200 K of the melting point. The thermal conductivity at temperatures near and below the corresponding temperature, T_m , of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens, and the recommended values below 30 K are applicable only to lead in the normal state having residual electrical resistivity $\rho_0 = 0.000862 \mu\Omega \text{ cm}$. Values at temperatures below about 1.5 T_m are calculated by using equation (7) and using the constants m , n , and α' given for lead in Table 1 and the parameter $\beta = 0.0353$.

† Values above 800 K are provisional.

THERMAL CONDUCTIVITY OF LITHIUM

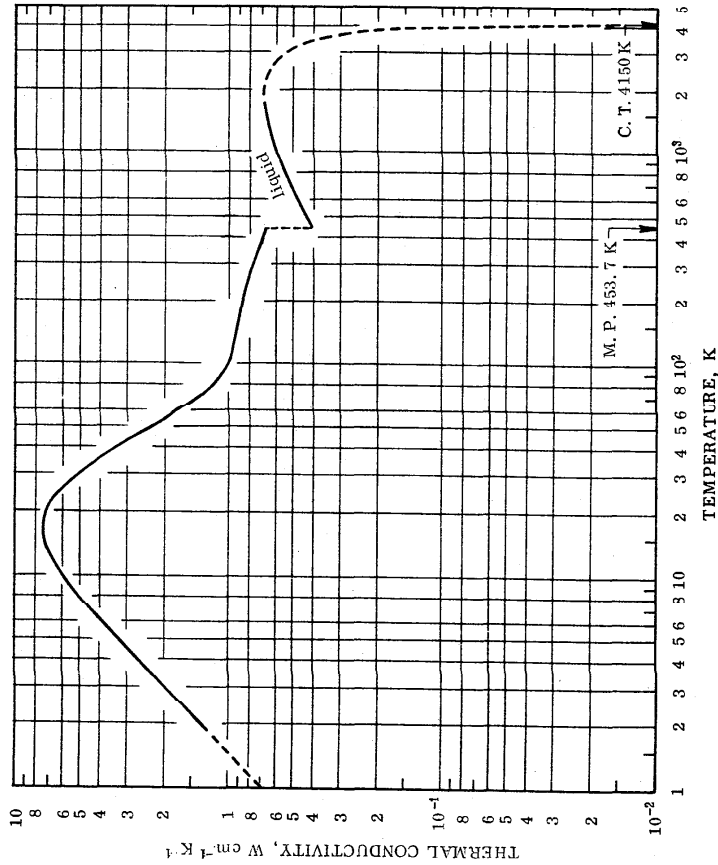

RECOMMENDED VALUES †
[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]

SOLID			LIQUID		
T	k	T	k	T	k
0	0	60	1.75	453.7	0.428*
1	0.658*	70	1.40	473.2	0.434
2	1.32	80	1.20	500	0.443
3	1.97	90	1.10	573.2	0.467
4	2.62	100	1.04	600	0.476
5	3.29	123.2	0.986	673.2	0.500
6	3.86	150	0.949	700	0.509
7	4.56	173.2	0.925	773.2	0.533
8	5.15	200	0.901	800	0.541
9	5.67	223.2	0.887	873.2	0.564
10	6.13	250	0.871	900	0.572
11	6.51	273.2	0.859	973.2	0.593
12	6.82	298.2	0.848	1000	0.600
13	7.09	300	0.847	1073.2	0.619
14	7.25	323.2	0.839	1100	0.625
15	7.38	350	0.828	1173.2	0.641
16	7.40	373.2	0.818	1200	0.647
18	7.39	400	0.804	1273.2	0.661
20	7.20	453.7	0.772*	1300	0.665
25	6.30			1373.2	0.676
30	5.20			1400	0.680
35	4.22			1473.2	0.688
40	3.43			1500	0.691
45	2.81			1573.2	0.697
50	2.35			1600	0.699
				1673.2	0.703 C.T. = 4150
				1700	0.704
				1773.2	0.706
				1800	0.707*
				1873.2	0.707*


REMARKS

The recommended values are for well-annealed high-purity lithium and are considered accurate to within about ±5% for the solid state and for molten lithium to about 700 K. The uncertainty increases to about ±10% by 1600 K and continues to increase at higher temperatures. The thermal conductivity at temperatures near and below the corresponding temperature, T_m, of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens, and the recommended values below 150 K are applicable only to lithium having residual electrical resistivity ρ₀ = 0.0372 μΩ cm. Values at temperatures below about 1.5 T_m are calculated to fit experimental data by using equation (7) and using the constants m, n, and α' given for lithium in Table 1 and the parameter β = 1.52.

* Extrapolated or estimated.

† Values above 1800 K are provisional.

THERMAL CONDUCTIVITY OF LUTETIUM

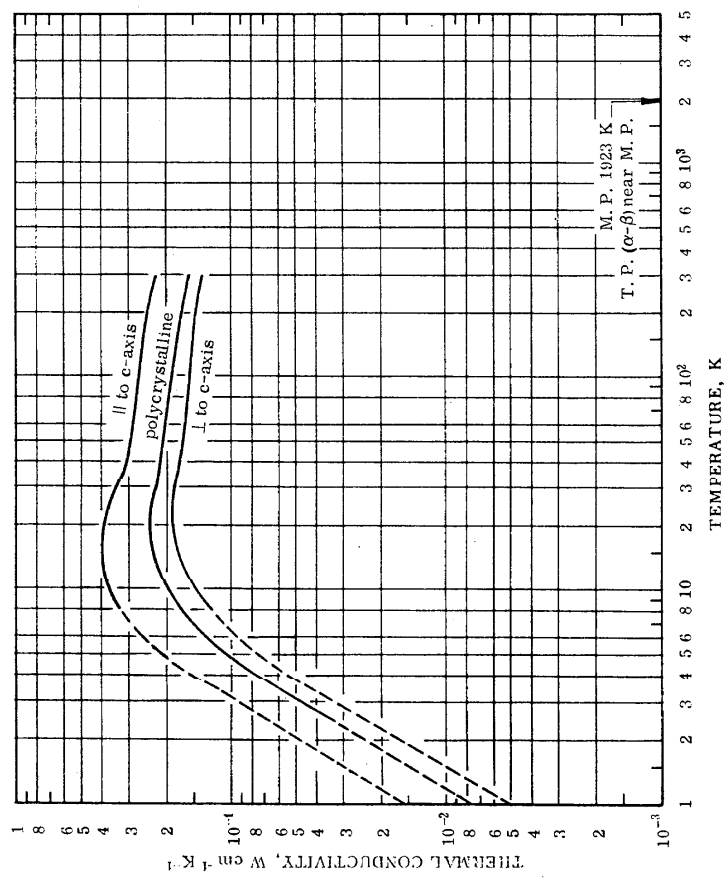

REMARKS

The provisional values are for well-annealed high-purity lutetium and are considered accurate to within $\pm 20\%$ of the true values at temperatures from 10 to 100 K and $\pm 15\%$ above 100 K. The values below 10 K are very uncertain. At temperatures below 100 K the values for $k_{||}$, k_{\perp} , and k_{poly} are applicable only to samples having residual electrical resistivities of 0.76, 2.65, and 1.45 $\mu\Omega$ cm, respectively.


PROVISIONAL VALUES

[Temperature, T, K; Thermal Conductivity, k, $W\ cm^{-1}\ K^{-1}$]

T	SOLID			Poly-crystalline k
	// to c-axis k	⊥ to c-axis k		
0	0	0	0	0
1	0.0155*	0.00510*	0	0.00757*
2	0.0496*	0.0165*	0	0.0244*
3	0.0984*	0.0328	0	0.0484
4	0.160*	0.0532	0	0.0786
5	0.217*	0.0742	0	0.108
6	0.262*	0.0934	0	0.134
7	0.295*	0.110	0	0.155
8	0.322	0.124	0	0.173
9	0.343	0.136	0	0.188
10	0.359	0.145	0	0.199
11	0.372	0.153	0	0.208
12	0.383	0.160	0	0.216
13	0.391	0.166	0	0.223
14	0.397	0.171	0	0.229
15	0.402	0.175	0	0.233
16	0.406	0.179	0	0.237
18	0.408	0.185	0	0.243
20	0.406	0.188	0	0.245
25	0.384	0.191	0	0.242
30	0.353	0.188	0	0.233
35	0.330	0.182	0	0.223
40	0.317	0.178	0	0.216
45	0.308	0.175	0	0.212
50	0.303	0.173	0	0.209
60	0.296	0.169	0	0.204
70	0.290	0.166	0	0.200
80	0.285	0.163	0	0.197
90	0.280	0.161	0	0.194
100	0.277	0.160	0	0.192
133.2	0.267	0.155	0	0.186
150	0.260	0.152	0	0.182
173.2	0.255	0.149	0	0.179
200	0.249	0.146	0	0.175
233.2	0.245	0.144	0	0.173
250	0.240	0.142	0	0.170
273.2	0.236	0.140	0	0.167
298.2	0.232	0.138	0	0.164
300	0.232	0.138	0	0.164

* Extrapolated.

THERMAL CONDUCTIVITY OF MAGNESIUM

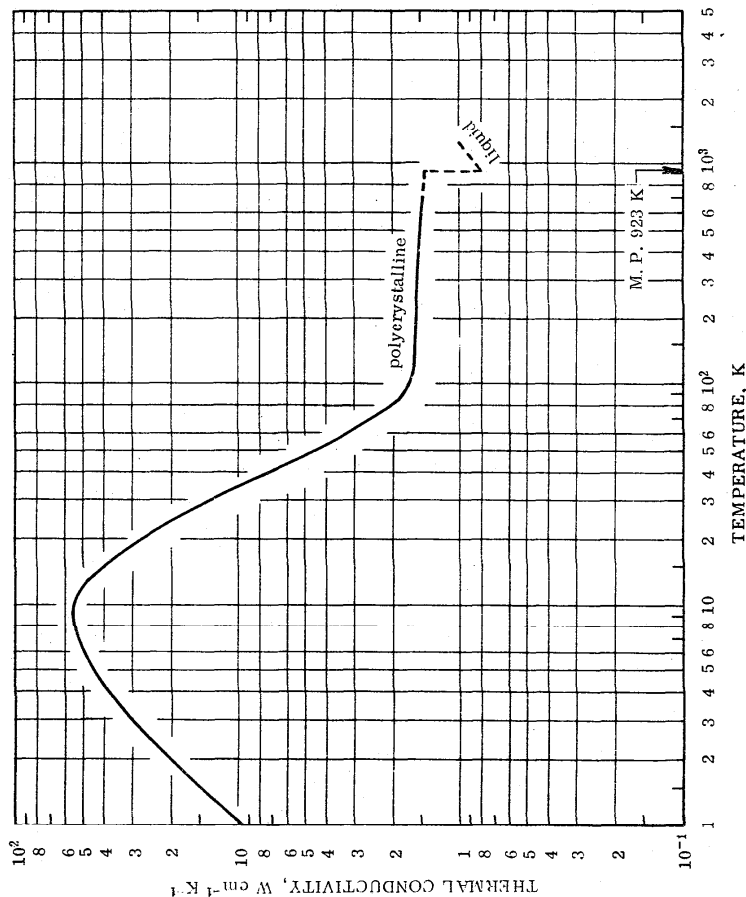

RECOMMENDED VALUES †
[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]


T	POLYCRYSTALLINE		LIQUID	
	k	T	k	T
0	0	123.2	1.63	923.2
1	9.86	150	1.61	973.2
2	19.6	173.2	1.60	1000
3	29.0	200	1.59	1073.2
4	37.6	250	1.57	1100
5	45.0	273.2	1.57	1173.2
6	50.8	298.2	1.56	1200
7	54.7	300	1.56	
8	56.7	323.2	1.55	
9	57.0	350	1.55	
10	55.8	373.2	1.54	
11	53.7	400	1.53	
12	50.9	473.2	1.52	
13	47.8	500	1.51	
14	44.4	573.2	1.50	
15	41.1	600	1.49	
16	37.9	673.2	1.48	
18	32.2	700	1.47	
20	27.2	773.2	1.46*	
25	18.3	800	1.46*	
30	12.9	873.2	1.45*	
35	9.45	900	1.45*	
40	7.19	923.2	1.45*	
45	5.70			
50	4.65			
60	3.27			
70	2.49			
80	2.02			
90	1.78			
100	1.69			

REMARKS

The recommended values are for well-annealed high-purity magnesium and are considered accurate to within ±3% of the true values at moderate temperatures. ±10% for low temperatures and as the melting point is approached, and ±1.5% for the liquid state within some 200 K of the melting point. The thermal conductivity at temperatures near and below the corresponding temperature, T_m, of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens, and the recommended values below 100 K are applicable only to magnesium having residual electrical resistivity ρ₀ = 0.00261 μΩ cm. Values at temperatures below about 1.5 T_m are calculated to fit experimental data by using equation (7) and using the constants m, n, and α' given for magnesium in Table 1 and the parameter β = 0.101.

* Extrapolated or estimated.
† Values for molten magnesium are provisional.

THERMAL CONDUCTIVITY OF MANGANESE

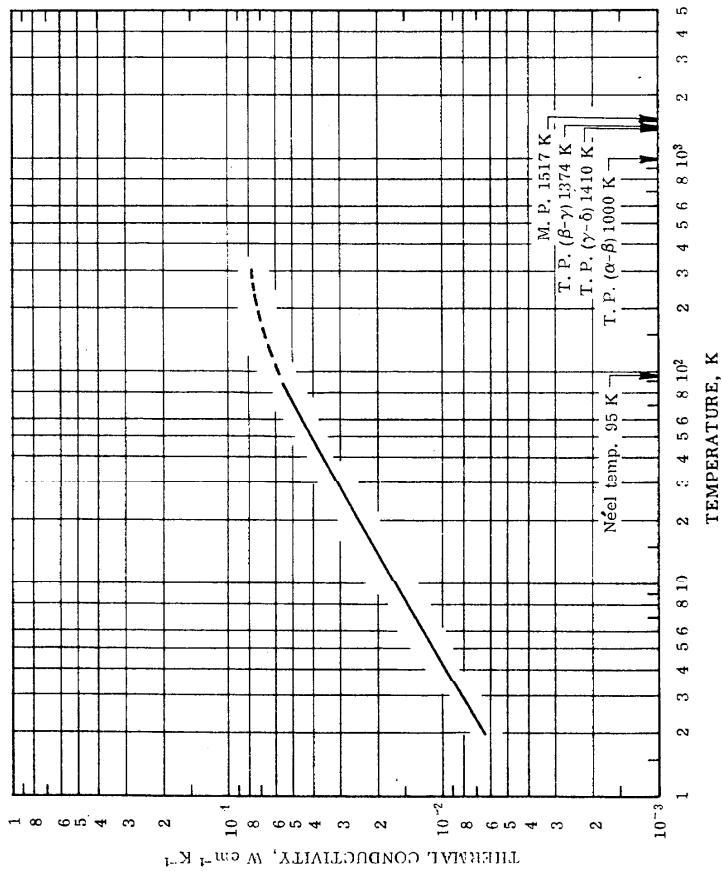

REMARKS

The values around room temperature are for well-annealed high-purity manganese and are considered accurate to within ± 20%. The accuracy may be slightly better around room temperature. Values below room temperature are applicable only to manganese of 99.99% pure having residual electrical resistivity $\rho_0 = 11.3 \mu\Omega \text{ cm}$.


PROVISIONAL VALUES

[Temperature, T, K; Thermal Conductivity, k, $\text{W cm}^{-1} \text{K}^{-1}$]

T	k
2	0.00645*
3	0.00813
4	0.00956
5	0.0109
6	0.0121
7	0.0132
8	0.0143
9	0.0153
10	0.0163
11	0.0172
12	0.0180
13	0.0188
14	0.0196
15	0.0205
16	0.0213
18	0.0227
20	0.0241
25	0.0274
30	0.0304
35	0.0332
40	0.0358
45	0.0382
50	0.0406
60	0.0450
70	0.0491
80	0.0526
90	0.0555
100	0.0579*
123.2	0.0624*
150	0.0663*
173.2	0.0691*
200	0.0717*
223.2	0.0735*
250	0.0754*
273.2	0.0768*
298.2	0.0781
300	0.0782*

* Extrapolated or interpolated.

THERMAL CONDUCTIVITY OF NEON

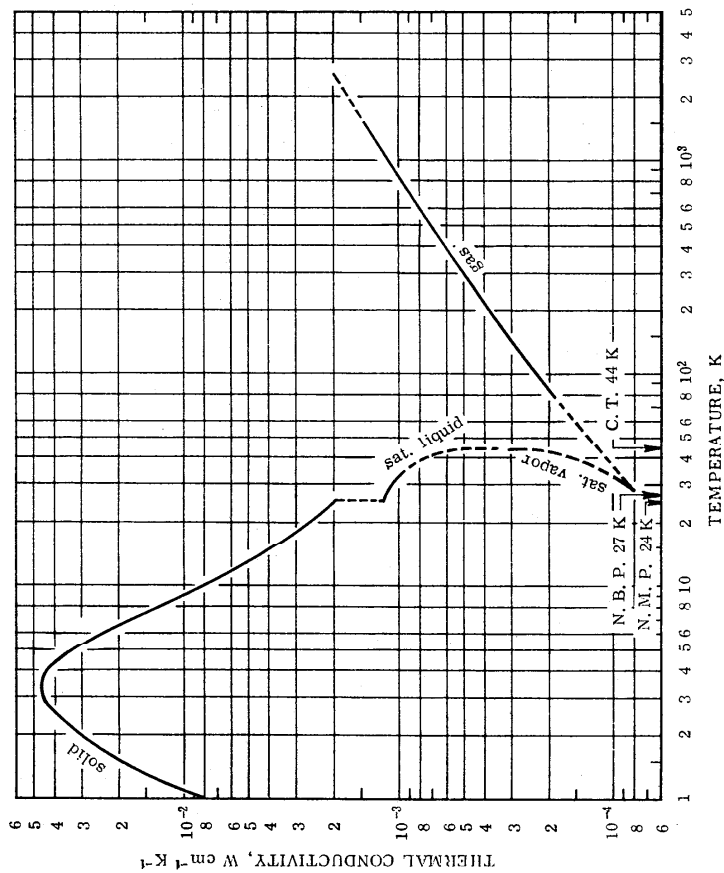

REMARKS

The paucity of experimental data for the solid restricts the error estimate to that the recommended values are probably accurate to within 20% above 5 K. Severe disagreement exists between some measurements and correlations for the liquid phase, resulting in a probable uncertainty of 20% below 35 K and as much as 40% at the critical point. Similar uncertainties are probable for the vapor. The gas values should be accurate to within 2% up to 400 K, 4% at 1000 K, and 10% at 2500 K.

SOLID		SATURATED LIQUID		SATURATED VAPOR	
T	$k \times 10^3$	T	$k \times 10^3$	T	$k \times 10^3$
1.0	7.3*	24	1.17	27	0.079*
1.5	18.5*	26	1.15	28	0.082*
2.0	29.5*	27	1.13	29	0.085*
2.5	39.8*	28	1.12	30	0.089*
3.0	45.7*	29	1.10	31	0.095*
3.5	47.1*	30	1.08	32	0.097*
4.0	44.0*	31	1.06	33	0.102*
4.5	39.3*	32	1.04	34	0.107*
5	33.6*	33	1.02*	35	0.112*
6	24.5*	34	0.99*	36	0.118*
7	17.0*	35	0.96*	37	0.124*
8	13.0*	36	0.92*	38	0.131*
9	10.2*	37	0.88*	39	0.138*
10	8.4*	38	0.84*	40	0.147*
12	6.0*	39	0.79*	41	0.16*
14	4.5*	40	0.73*	42	0.17*
16	3.7*	41	0.67*	43	0.19*
18	3.1*	42	0.61*	44	0.33*†
20	2.7*	43	0.54*		
22	2.3*	44	0.33*†		
24	2.1*				

* Estimated or extrapolated, hence provisional.
 † Pseudocritical value.

THERMAL CONDUCTIVITY OF NEON (continued)


RECOMMENDED VALUES

GAS
(At 1 atm)

T	k x 10 ³	T	k x 10 ³	T	k x 10 ³	T	k x 10 ³
27*	0.079*	350	0.544	650	0.815	950	1.054
30	0.086*	360	0.553	660	0.824	960	1.061
35	0.097*	370	0.563	670	0.833	970	1.069
40	0.107*	380	0.572	680	0.842	980	1.076
45	0.117*	390	0.581	690	0.851	990	1.084
50	0.128*	400	0.590	700	0.861	1000	1.091
60	0.148*	410	0.600	710	0.870	1050	1.129
70	0.168*	420	0.609	720	0.879	1100	1.166
80	0.186	430	0.618	730	0.888	1150	1.202
90	0.204	440	0.628	740	0.897	1200	1.238
100	0.222	450	0.637	750	0.906	1250	1.273
110	0.239	460	0.647	760	0.914	1300	1.307
120	0.256	470	0.656	770	0.922	1350	1.340
130	0.272	480	0.666	780	0.929	1400	1.372
140	0.288	490	0.675	790	0.937	1450	1.404
150	0.303	500	0.685	800	0.945	1500	1.435
160	0.318	510	0.693	810	0.952	1550	1.467*
170	0.333	520	0.702	820	0.960	1600	1.499*
180	0.347	530	0.710	830	0.967	1650	1.530*
190	0.361	540	0.719	840	0.975	1700	1.561*
200	0.375	550	0.727	850	0.982	1750	1.590*
210	0.388	560	0.736	860	0.989	1800	1.618*
220	0.401	570	0.744	870	0.996	1850	1.648*
230	0.414	580	0.753	880	1.003	1900	1.673*
240	0.426	590	0.762	890	1.010	1950	1.700*
250	0.438	600	0.771	900	1.017	2000	1.727*
260	0.449	610	0.780	910	1.024	2100	1.79*
270	0.461	620	0.789	920	1.032	2200	1.84*
280	0.472	630	0.797	930	1.039	2300	1.90*
290	0.483	640	0.806	940	1.047	2400	1.95*
300	0.493					2500	2.00*
310	0.504						
320	0.514						
330	0.524						
340	0.534						

* Estimated or extrapolated.

THERMAL CONDUCTIVITY OF NEPTUNIUM

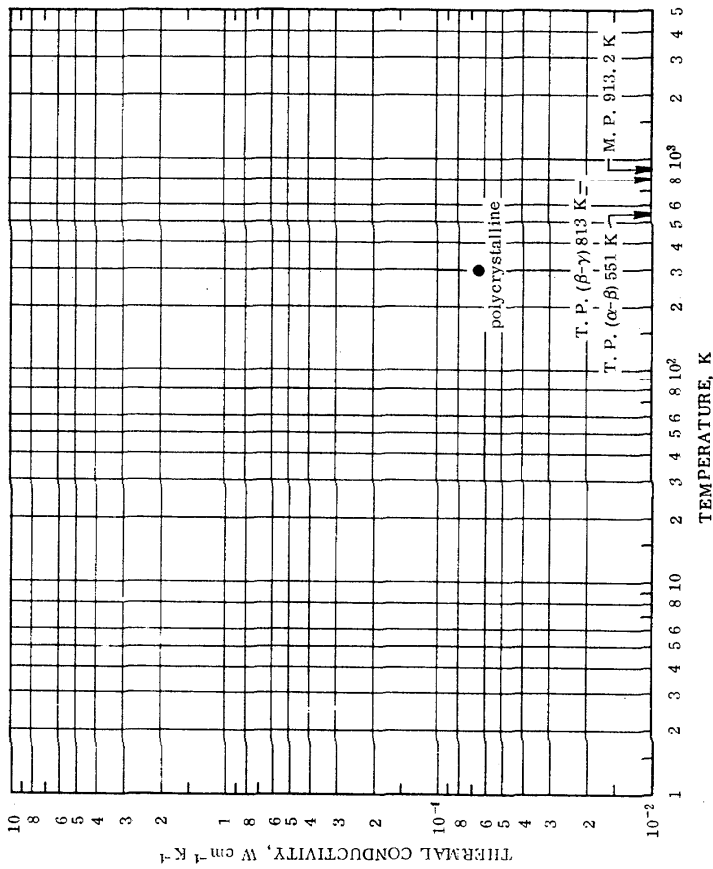

PROVISIONAL VALUES
 [Temperature, T, K; Thermal Conductivity, k, $\text{W cm}^{-1} \text{K}^{-1}$]


SOLID
 Polycrystalline
 T k
 300 0.063*

REMARKS

The provisional value is for high-purity polycrystalline neptunium and is probably good to within $\pm 20\%$.

* Estimated.

THERMAL CONDUCTIVITY OF NICKEL

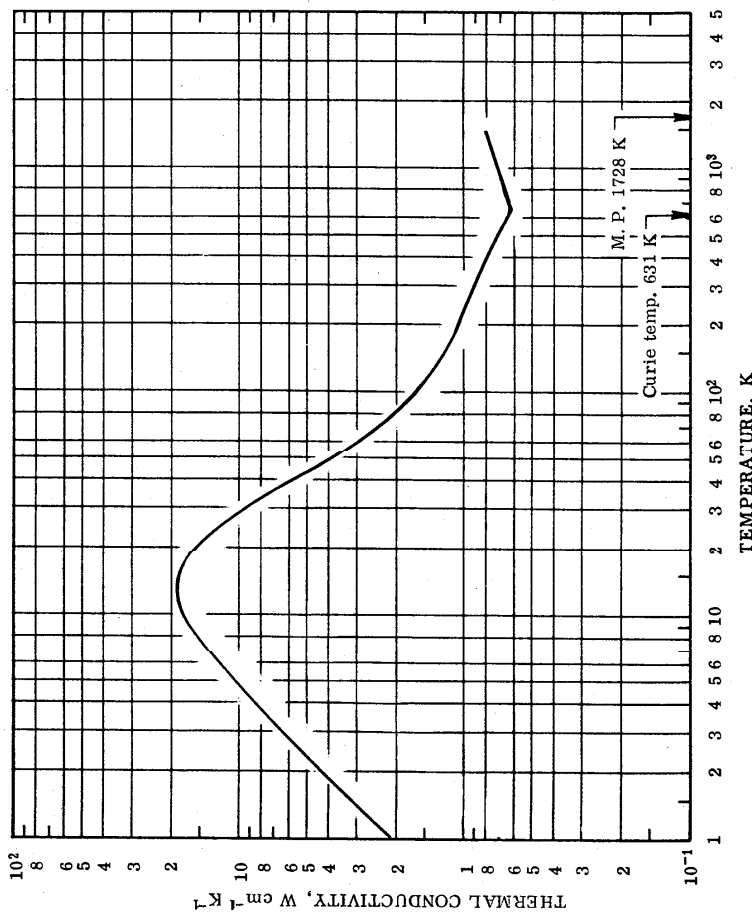

RECOMMENDED VALUES
[Temperature, T, K; Thermal Conductivity, k, $\text{W cm}^{-1} \text{K}^{-1}$]


SOLID

T	k	T	k
0	0	250	0.975
1	2.17	273.2	0.941
2	4.34	298.2	0.909
3	6.49	300	0.907
4	8.59	323.2	0.880
5	10.6	350	0.850
6	12.5	373.2	0.827
7	14.2	400	0.802
8	15.8	473.2	0.741
9	17.1	500	0.722
10	18.1	573.2	0.673
11	18.9	600	0.656
12	19.4	630	0.639
13	19.7	673.2	0.648
14	19.7	700	0.654
15	19.5	773.2	0.670
16	19.1	800	0.676
18	18.1	873.2	0.693
20	16.5	900	0.697
25	12.6	973.2	0.712
30	9.56	1000	0.718
35	7.36	1073.2	0.734
40	5.82	1100	0.740
45	4.75	1173.2	0.756
50	4.00	1200	0.762
60	3.08	1273.2	0.777
70	2.50	1300	0.783
80	2.10	1373.2	0.798
90	1.83	1400	0.804
100	1.64	1473.2	0.820
123.2	1.37	1500	0.826
150	1.22		
173.2	1.13		
200	1.07		
223.2	1.02		

REMARKS

The recommended values are for well-annealed high-purity nickel and are considered accurate to within $\pm 10\%$ of the true values. The thermal conductivity at temperatures near and below the corresponding temperature, T_m , of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens, and the recommended values below room temperature are applicable only to nickel having residual electrical resistivity $\rho_0 = 0.0112 \mu\Omega \text{ cm}$. Values at temperatures below about 1.5 T_m are calculated to fit experimental data by using equation (7) and using the constants m , n , and α' given by nickel in Table 1 and the parameter $\beta = 0.460$.

THERMAL CONDUCTIVITY OF NIOBIUM

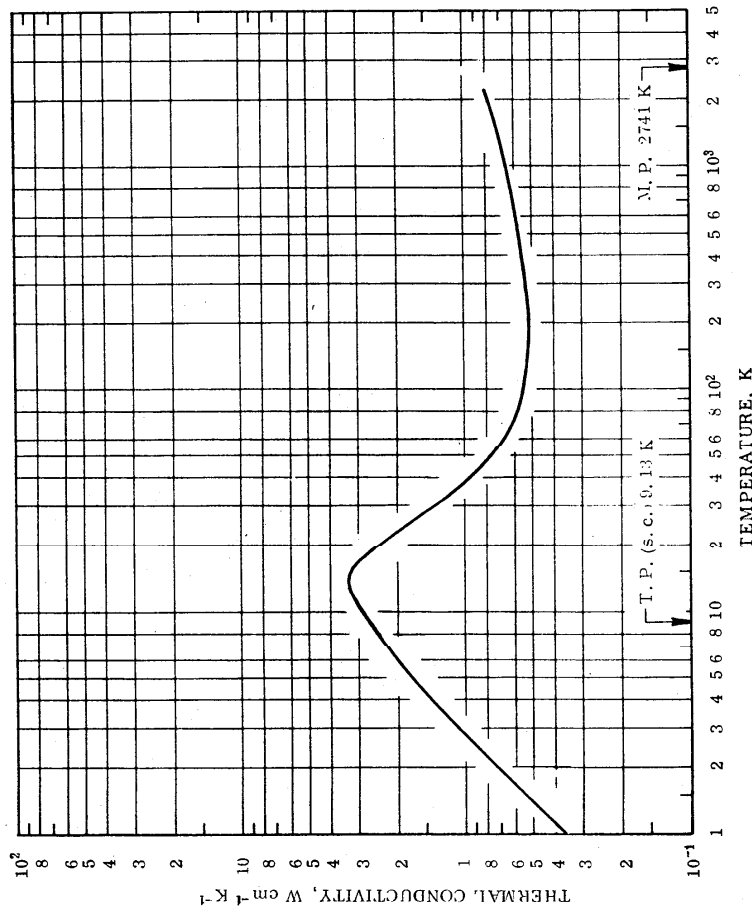

RECOMMENDED VALUES

[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]


SOLID

T	k	T	k
0	0	350	0.544
1	0.360	373.2	0.548
2	0.718	400	0.552
3	1.07	473.2	0.563
4	1.42	500	0.567
5	1.75	573.2	0.578
6	2.06	600	0.582
7	2.34	673.2	0.594
8	2.58	700	0.598
9	2.78	773.2	0.609
10	2.94	800	0.613
11	3.05	873.2	0.625
12	3.11	900	0.629
13	3.14	973.2	0.640
14	3.12	1000	0.644
15	3.08	1073.2	0.656
16	3.01	1100	0.659
18	2.81	1173.2	0.671
20	2.49	1200	0.675
25	1.82	1273.2	0.686
30	1.39	1300	0.690
35	1.12	1373.2	0.701
40	0.953	1400	0.705
45	0.838	1473.2	0.717
50	0.758	1500	0.721
60	0.661	1573.2	0.732
70	0.612	1600	0.736
80	0.584	1673.2	0.747
90	0.566	1700	0.751
100	0.552	1773.2	0.761
123.2	0.537	1800	0.765
150	0.530	1873.2	0.775
173.2	0.527	1900	0.778
200	0.526	1973.2	0.787
223.2	0.527	2000	0.791
250	0.530	2073.2	0.801
273.2	0.533	2173.2	0.812
298.2	0.537	2200	0.815
300	0.537		
323.2	0.540		

REMARKS

The recommended values are for well-annealed high-purity niobium and are considered accurate to within ±5 to ±10% of the true values at moderate temperatures and ±15% at low and high temperatures. The thermal conductivity at temperatures near and below the corresponding temperature, T_m, of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens, and the recommended values below 150 K are applicable only to niobium having residual electrical resistivity ρ₀ = 0.0679 μΩ cm. Values at temperatures below about 1.5 T_m are calculated to fit experimental data by using equation (7) and using the constants m, n, and α' given for niobium in Table 1 and the parameter β = 2.78.

THERMAL CONDUCTIVITY OF NITROGEN

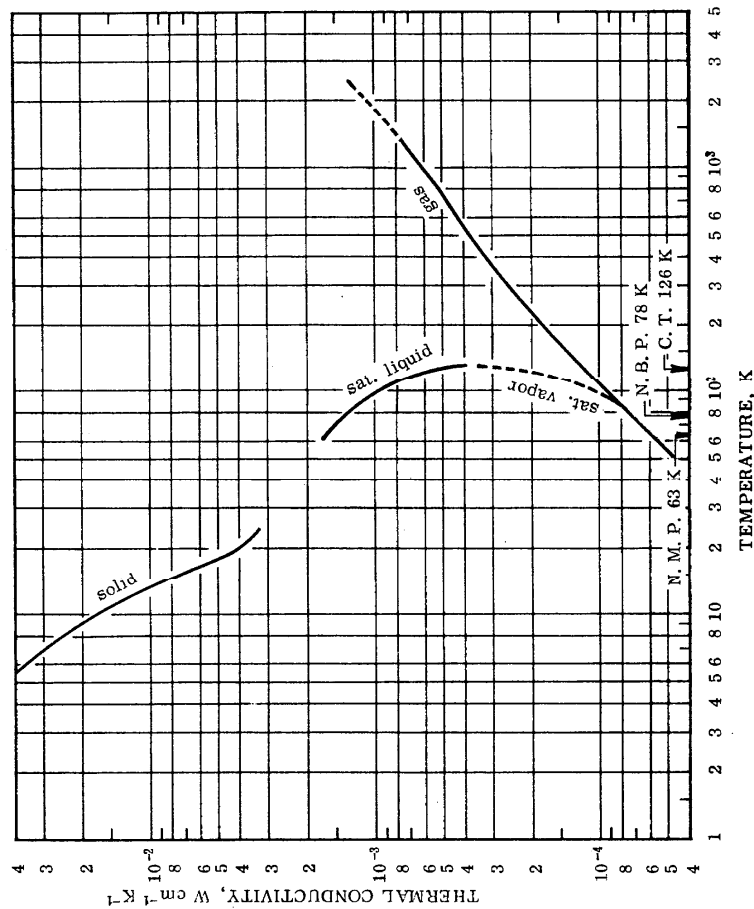

RECOMMENDED VALUES			
[Temperature, T, K; Thermal Conductivity, k, W cm ⁻¹ K ⁻¹]			
SOLID		SATURATED LIQUID	SATURATED VAPOR
T	k x 10 ³	T	k x 10 ³
4	56		
5	45		0.056*
6	37		0.061*
7	30	63	0.066*
8	25	65	0.071*
9	20	70	0.077*
10	17	75	0.084*
11	14	80	0.091*
12	12	85	0.100*
13	10	90	0.111*
14	9.2	95	0.123*
15	7.6	100	0.138*
16	6.5	105	0.160*
17	5.6	110	0.185*
18	4.9	115	0.210*
19	4.5	120	0.265*
20	4.0	125	0.320**
21	3.8	126	0.37**†
22	3.6		
23	3.5		
24	3.3		
25	3.2		

REMARKS

The values recommended here for the solid must be regarded as tentative below 12 K as the experimental evidence was insufficient to determine if a maximum in conductivity occurred below or above 4 K. From 12 to 25 K an uncertainty of 10% appears probable. The liquid values should be accurate to a few percent below 120 K, the uncertainty then increasing to 5% at 125 K and higher near the critical point. For the vapor, a similar increase occurs from a few percent below 90 K to 10% at 100 K, etc. The gas values should be accurate to 2% below 350 K, 5% from 350 to 1200 K, and 10% at higher temperatures.

* Estimated or extrapolated.

† Pseudo-critical value.

THEMAL CONDUCTIVITY OF NITROGEN (continued)


RECOMMENDED VALUES

GAS
(At 1 atm)

T	k x 10 ³	T	k x 10 ³	T	k x 10 ³
78	0.0745	450	0.3564	850	0.564
80	0.0762	460	0.3626	860	0.569
90	0.0852	470	0.3688	870	0.574
100	0.0941	480	0.3749	880	0.578
110	0.1030	490	0.3808	890	0.583
120	0.1119	500	0.3864	900	0.587
130	0.1208	510	0.392	910	0.592
140	0.1296	520	0.398	920	0.596
150	0.1385	530	0.403	930	0.600
160	0.1474	540	0.408	940	0.605
170	0.1562	550	0.414	950	0.609
180	0.1651	560	0.420	960	0.613
190	0.1739	570	0.425	970	0.618
200	0.1826	580	0.431	980	0.622
210	0.1908	590	0.436	990	0.626
220	0.1989	600	0.441	1000	0.631
230	0.2067	610	0.446	1050	0.651
240	0.2145	620	0.452	1100	0.672
250	0.2222	630	0.457	1150	0.693
260	0.2298	640	0.462	1200	0.713
270	0.2374	650	0.467	1250	0.733
280	0.2449	660	0.472	1300	0.754
290	0.2524	670	0.478	1350	0.775
300	0.2598	680	0.483	1400	0.797
310	0.2671	690	0.488	1450	0.819
320	0.2741	700	0.493	1500	0.842
330	0.2808	710	0.498	1550	0.867*
340	0.2874	720	0.503	1600	0.893*
350	0.2939	730	0.508	1650	0.921*
360	0.3002	740	0.513	1700	0.950*
370	0.3065	750	0.517	1750	0.981*
380	0.3127	760	0.522	1800	1.013*
390	0.3189	770	0.526	1850	1.046*
400	0.3252	780	0.531	1900	1.080*
410	0.3314	790	0.536	1950	1.113*
420	0.3376	800	0.541	2000	1.146*
430	0.3438	810	0.546	2100	1.207*
440	0.3501	820	0.551	2200	1.263*
		830	0.555	2300	1.314*
		840	0.559	2400	1.361*
				2500	1.406*

* Estimated or extrapolated.

THERMAL CONDUCTIVITY OF OSMIUM

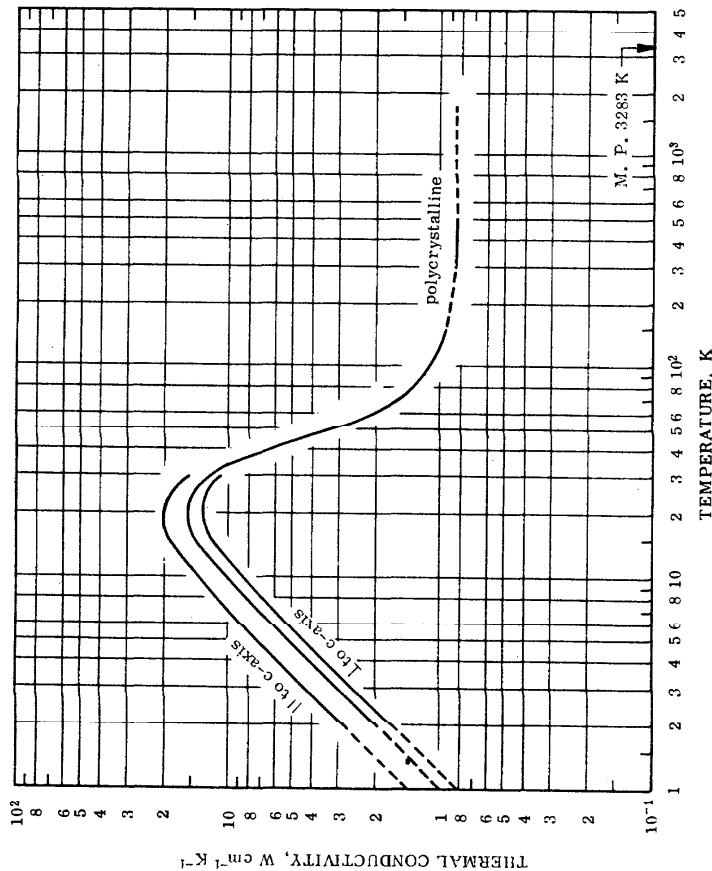


REMARKS

The recommended values are for well-annealed high-purity polycrystalline osmium and are considered accurate to within $\pm 10\%$ of the true values at temperatures below 300 K, $\pm 5\%$ from 300 to 500 K, and $\pm 10\%$ above 500 K. The thermal conductivity at temperatures near and below the corresponding temperature, T_m , of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens, and the conductivity values below 150 K for k_p , k_l , and k_{poly} are applicable only to osmium having residual electrical resistivities of 0.0167, 0.0278, and 0.0234 $\mu\Omega$ cm, respectively. Values at temperatures below about 1.5 T_m are calculated to fit experimental data by using equation (7) and using the constants m , n , and α' given in Table 1 and the parameter $\beta = 0.682$, 1.137, and 0.957, respectively, for k_u , k_L , and k_{poly} .

T	RECOMMENDED VALUES [Temperature, T, K; Thermal Conductivity, k , $W\ cm^{-1}\ K^{-1}$]			
	// to c-axis	l to c-axis	poly-crystalline	poly-crystalline
T	k	k	k	k
0	0	0	0	0.886*
1	1.47*	0.88*	1.05*	0.880*
2	2.93	1.76	2.09	0.876*
3	4.40	2.64	3.14	0.876*
4	5.86	3.52	4.18	0.874
5	7.32	4.39	5.22	0.870
6	8.77	5.27	6.26	0.870
7	10.2	6.13	7.28	0.869
8	11.6	6.99	8.29	0.869
9	13.0	7.83	9.29	0.869
10	14.3	8.65	10.2	0.869*
11	15.6	9.44	11.2	0.869*
12	16.8	10.2	12.1	0.869*
13	17.9	10.9	12.9	0.869*
14	18.9	11.6	13.7	0.869*
15	19.7	12.2	14.3	0.869*
16	20.4	12.7	14.9	0.869*
18	21.3	13.4	15.7	0.869*
20	21.5	13.8	16.0	0.869*
25	19.4	13.2	15.0	0.869*
30	15.4	11.1	12.4	0.869*
35			9.17	0.869*
40			6.38	0.869*
45			4.58	0.869*
50			3.42	0.869*
60			2.18	0.869*
70			1.65	0.869*
80			1.39	0.869*
90			1.24	0.869*
100			1.14	0.869*
123.2			1.02	0.869*
150			0.962*	0.869*
173.2			0.932*	0.869*
200			0.908*	0.869*
223.2			0.896*	0.869*

* Extrapolated or interpolated.

THEMAL CONDUCTIVITY OF OXYGEN

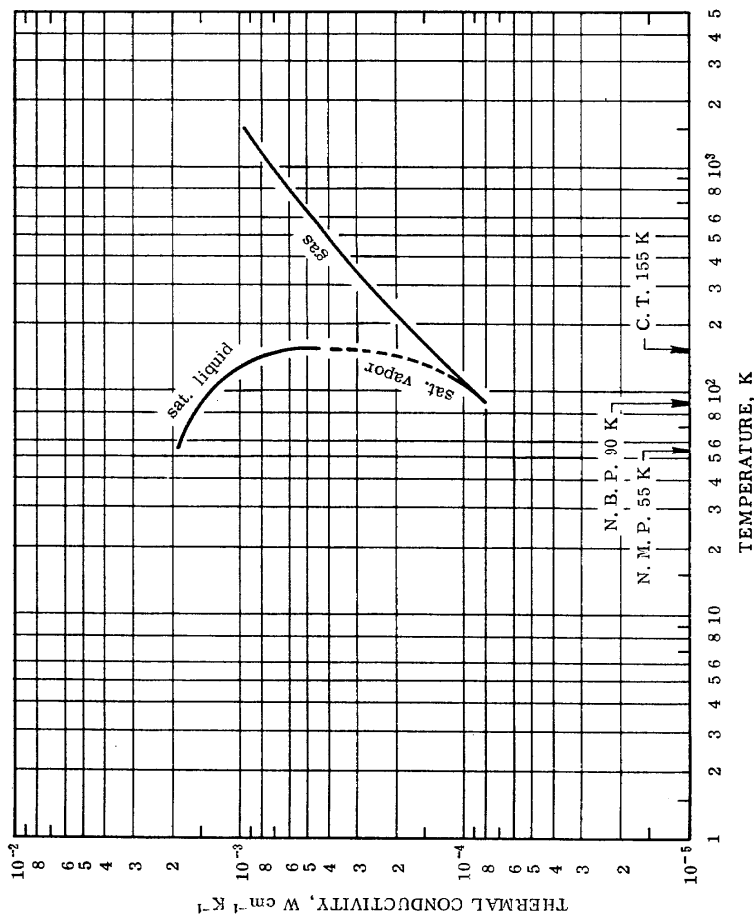

RECOMMENDED VALUES	
[Temperature, T, K; Thermal Conductivity, k, W cm ⁻¹ K ⁻¹]	
SATURATED LIQUID	
T	k x 10 ³
55	1.90
60	1.85
65	1.80
70	1.74
75	1.682
80	1.623
85	1.563
90	1.501
95	1.437
100	1.372
105	1.306
110	1.237
115	1.168
120	1.096
125	1.023
130	0.949
135	0.873
140	0.796
145	0.712
150	0.610
155	0.41**†

SATURATED VAPOR	
T	k x 10 ³
90	0.081*
95	0.087*
100	0.093*
105	0.100*
110	0.108*
115	0.116*
120	0.124*
125	0.135*
130	0.15*
135	0.16*
140	0.18*
145	0.21*
150	0.25*
155	0.41**†

REMARKS

The liquid values recommended here should be accurate to within 2% below 150 K and within 15% at the critical point. The vapor uncertainties are assessed as being a few percent below 100 K, increasing to about 10% at 125 K, etc. The gas values are considered to be well within a few percent below 600 K, 4% from 600 to 900 K, and probably within 6% at the higher temperatures.

* Estimated or extrapolated.
 † Pseudo-critical value.


THERMAL CONDUCTIVITY OF OXYGEN (continued)

RECOMMENDED VALUES

GAS
(At 1 atm)

T	$k \times 10^3$	T	$k \times 10^3$	T	$k \times 10^3$	T	$k \times 10^3$
90	0.0813						
100	0.0905	450	0.377	800	0.603	1150	0.796
110	0.0998	460	0.384	810	0.609	1160	0.801
120	0.1092	470	0.391	820	0.615	1170	0.806
130	0.1187	480	0.398	830	0.620	1180	0.811
140	0.1281	490	0.405	840	0.626	1190	0.816
150	0.1376	500	0.412	850	0.632	1200	0.821
160	0.1466	510	0.419	860	0.638	1210	0.826
170	0.1556	520	0.426	870	0.644	1220	0.831
180	0.1646	530	0.433	880	0.650	1230	0.836
190	0.1735	540	0.440	890	0.655	1240	0.841
200	0.1824	550	0.447	900	0.661	1250	0.846
210	0.1911	560	0.453	910	0.667	1260	0.851
220	0.1997	570	0.460	920	0.672	1270	0.856
230	0.2083	580	0.467	930	0.678	1280	0.861
240	0.2168	590	0.474	940	0.684	1290	0.866
250	0.2254	600	0.480	950	0.689	1300	0.871
260	0.2339	610	0.487	960	0.695	1310	0.876
270	0.2424	620	0.493	970	0.701	1320	0.881
280	0.2509	630	0.500	980	0.706	1330	0.886
290	0.2592	640	0.506	990	0.712	1340	0.891
300	0.2674	650	0.513	1000	0.717	1350	0.896
310	0.2753	660	0.519	1010	0.723	1360	0.901
320	0.2831	670	0.525	1020	0.728	1370	0.906
330	0.2907	680	0.532	1030	0.734	1380	0.911
340	0.2982	690	0.538	1040	0.739	1390	0.916
350	0.3056	700	0.544	1050	0.745	1400	0.921
360	0.3130	710	0.550	1060	0.750	1410	0.926
370	0.3204	720	0.556	1070	0.755	1420	0.931
380	0.3276	730	0.562	1080	0.760	1430	0.936
390	0.3348	740	0.568	1090	0.765	1440	0.941
400	0.342	750	0.574	1100	0.771	1450	0.946
410	0.349	760	0.579	1110	0.776	1460	0.951
420	0.356	770	0.585	1120	0.781	1470	0.956
430	0.363	780	0.591	1130	0.786	1480	0.960
440	0.370	790	0.597	1140	0.791	1490	0.965
						1500	0.970

THERMAL CONDUCTIVITY OF PALLADIUM

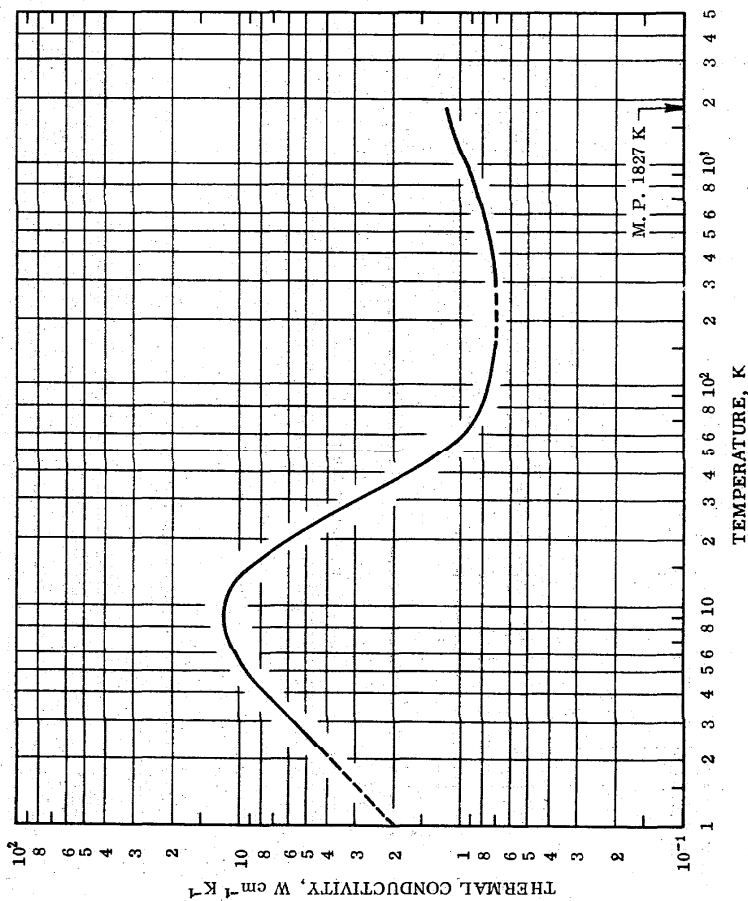

RECOMMENDED VALUES
[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]


SOLID		k		T	
T	k	T	k	T	k
0	0	250	0.715*		
1	1.99*	273.2	0.716*		
2	3.96*	298.2	0.718		
3	5.86	300	0.718		
4	7.61	323.2	0.721		
5	9.13	350	0.726		
6	10.3	373.2	0.730		
7	11.1	400	0.736		
8	11.6	473.2	0.755		
9	11.7	500	0.763		
10	11.5	573.2	0.787		
11	11.2	600	0.797		
12	10.7	673.2	0.823		
13	10.1	700	0.833		
14	9.49	773.2	0.860		
15	8.88	800	0.869		
16	8.28	873.2	0.896		
18	7.08	900	0.906		
20	5.98	973.2	0.932		
25	4.04	1000	0.942		
30	2.85	1073.2	0.971		
35	2.15	1100	0.981		
40	1.73	1173.2	1.01		
45	1.44	1200	1.02		
50	1.24	1273.2	1.04		
60	0.983	1300	1.05		
70	0.868	1373.2	1.07		
80	0.811	1400	1.07		
90	0.783	1473.2	1.09		
100	0.765	1500	1.10		
123.2	0.742	1573.2	1.11		
150	0.727	1600	1.12		
173.2	0.720*	1673.2	1.13		
200	0.716*	1700	1.14		
223.2	0.715*	1773.2	1.15*		
		1800	1.15*		

REMARKS

The recommended values are for well-annealed high-purity palladium and are considered accurate to within $\pm 5\%$ of the true values at temperatures from room temperature to about 1000 K and $\pm 10\%$ below room temperature and above 1000 K. The thermal conductivity at temperatures near and below the corresponding temperature, T_m , of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens, and the recommended values below 150 K are applicable only to palladium having residual electrical resistivity $\rho_{300} = 0.0123 \mu\Omega \text{ cm}$. Values at temperatures below about 1.5 Tm are calculated to fit experimental data by using equation (7) and using the constants m, n, and α'' given for palladium in Table 1 and the parameter $\beta = 0.502$.

* Extrapolated or interpolated.

THERMAL CONDUCTIVITY OF PHOSPHORUS

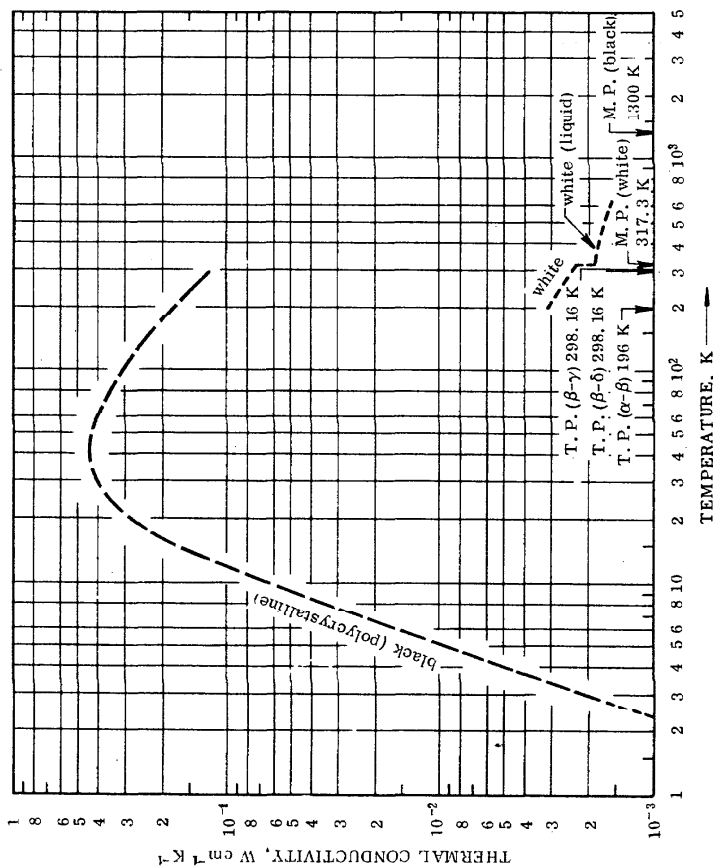

REMARKS

The values for white phosphorus are recommended values for high-purity white phosphorus and are considered accurate to within ± 10% of the true values at temperatures around the melting point. The values for polycrystalline black phosphorus are merely typical values and represent a typical curve serving to indicate the general trend of the thermal conductivity of black phosphorus at moderate and low temperatures.


RECOMMENDED VALUES †
[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]

SOLID		LIQUID	
Black, polycrystalline		White	
T	k	T	k
0	0	200	0.00308*
1	0.000796*	223.2	0.00287*
2	0.000645*	250	0.00265*
3	0.00220	273.2	0.00250*
4	0.00511	298.2	0.00236*
5	0.00998	300	0.00235
6	0.0167	317.3	0.00226*
7	0.0255		
8	0.0367		
9	0.0497		
10	0.0653		
11	0.0822		
12	0.101		
13	0.122		
14	0.144		
15	0.165		
16	0.187		
18	0.230		
20	0.272		
25	0.357		
30	0.401		
35	0.425		
40	0.435		
45	0.434		
50	0.427		
60	0.402		
70	0.377		
80	0.352		
90	0.328		
100	0.307		
123.2	0.266		
150	0.227		
173.2	0.201		
200	0.177		
223.2	0.160		
250	0.144		
273.2	0.132		
298.2	0.121		
300	0.121		

* Extrapolated.

† Values for polycrystalline black phosphorus are merely typical values and those for white phosphorus below 273 K and above 400 K are provisional.

THERMAL CONDUCTIVITY OF PLATINUM

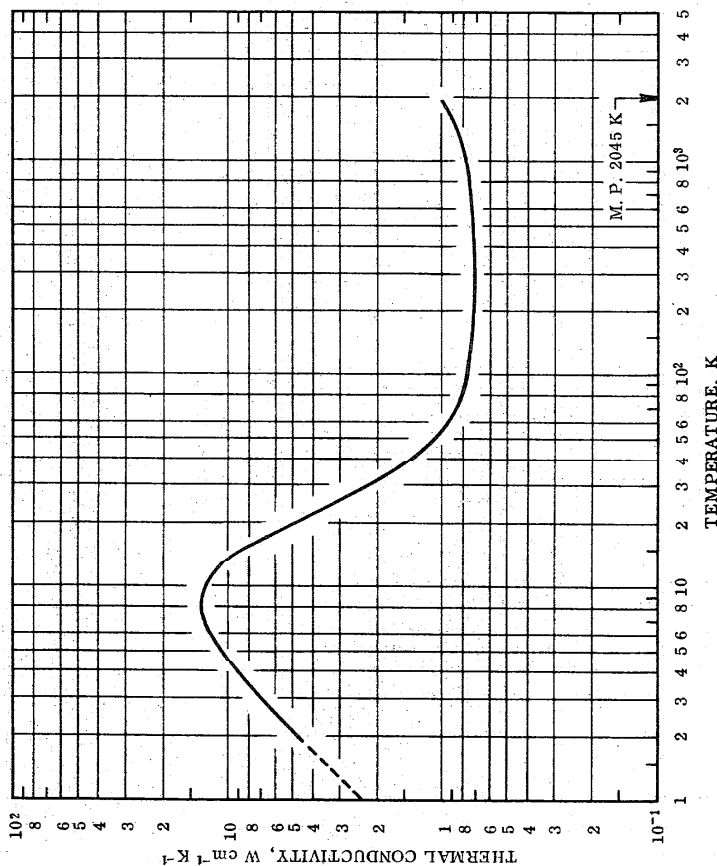

RECOMMENDED VALUES

[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]


T		k		T		k	
0	0	2.31	0.717	350	0.717		
1	2.31	4.60	0.717	373.2	0.717		
2	4.60	6.79	0.718	400	0.718		
3	6.79	8.8	0.722	473.2	0.722		
4	8.8	10.5	0.723	500	0.723		
5	10.5	11.8	0.729	573.2	0.729		
6	11.8	12.6	0.732	600	0.732		
7	12.6	12.9	0.740	673.2	0.740		
8	12.9	12.8	0.743	700	0.743		
9	12.8	12.3	0.752	773.2	0.752		
10	12.3	11.7	0.756	800	0.756		
11	11.7	10.9	0.767	873.2	0.767		
12	10.9	10.1	0.771	900	0.771		
13	10.1	9.30	0.783	973.2	0.783		
14	9.30	8.41	0.787	1000	0.787		
15	8.41	7.59	0.800	1073.2	0.800		
16	7.59	6.12	0.806	1100	0.806		
18	6.12	4.95	0.820	1173.2	0.820		
20	4.95	3.13	0.826	1200	0.826		
25	3.13	2.15	0.842	1273.2	0.842		
30	2.15	1.68	0.848	1300	0.848		
35	1.68	1.39	0.863	1373.2	0.863		
40	1.39	1.22	0.871	1400	0.871		
45	1.22	1.09	0.889	1473.2	0.889		
50	1.09	0.947	0.895	1500	0.895		
60	0.947	0.862	0.913	1573.2	0.913		
70	0.862	0.815	0.919	1600	0.919		
80	0.815	0.775	0.936	1673.2	0.936		
90	0.789	0.755	0.942	1700	0.942		
100	0.775	0.740	0.957	1773.2	0.957		
123.2	0.755	0.732	0.961	1800	0.961		
150	0.740	0.726	0.974	1873.2	0.974		
173.2	0.732	0.721	0.978	1900	0.978		
200	0.726	0.717	0.990	1973.2	0.990		
223.2	0.721	0.716	0.994*	2000	0.994*		
250	0.718	0.716	1.004*	2045	1.004*		
273.2	0.717						
298.2	0.716						
300	0.716						
323.2	0.716						

* Extrapolated.

REMARKS

The recommended values are for well-annealed high-purity platinum and are considered accurate to within ±3% of the true values near room temperature, ±6% at about 100 K and 1200 K, and ±10% below 100 K and at 2000 K. The thermal conductivity at temperatures near and below the corresponding temperature, T_m, of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens, and the recommended values below 200 K are applicable only to platinum having residual electrical resistivity ρ₀ = 0.0106 μΩ cm. Values at temperatures below about 1.5 T_m are calculated to fit experimental data by using equation (7) and using n = 2.10, α' = 0.000301, and the parameter β = 0.433.

THERMAL CONDUCTIVITY OF PLUTONIUM

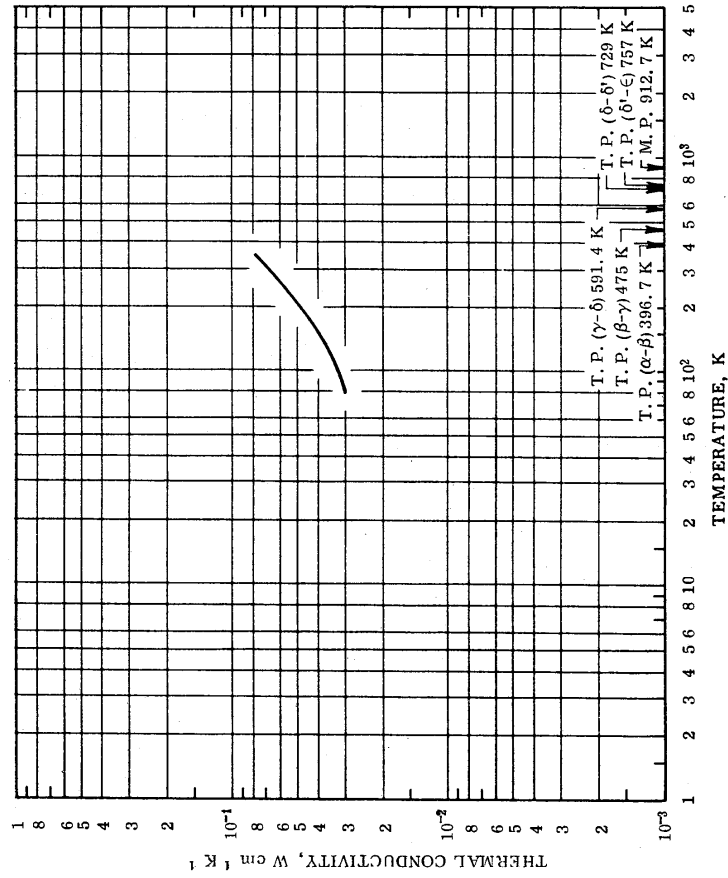

PROVISIONAL VALUES


[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]

SOLID	
Polycrystalline	
T	k
80	0.0306
90	0.0318
100	0.0332
123.2	0.0361
150	0.0399
173.2	0.0432
200	0.0476
223.2	0.0516
250	0.0568
273.2	0.0616
298.2	0.0670
300	0.0674
323.2	0.0726
350	0.0790

REMARKS

The provisional values are for well-annealed high-purity polycrystalline plutonium. The uncertainty of the values is of the order of ±25%.

THERMAL CONDUCTIVITY OF POTASSIUM

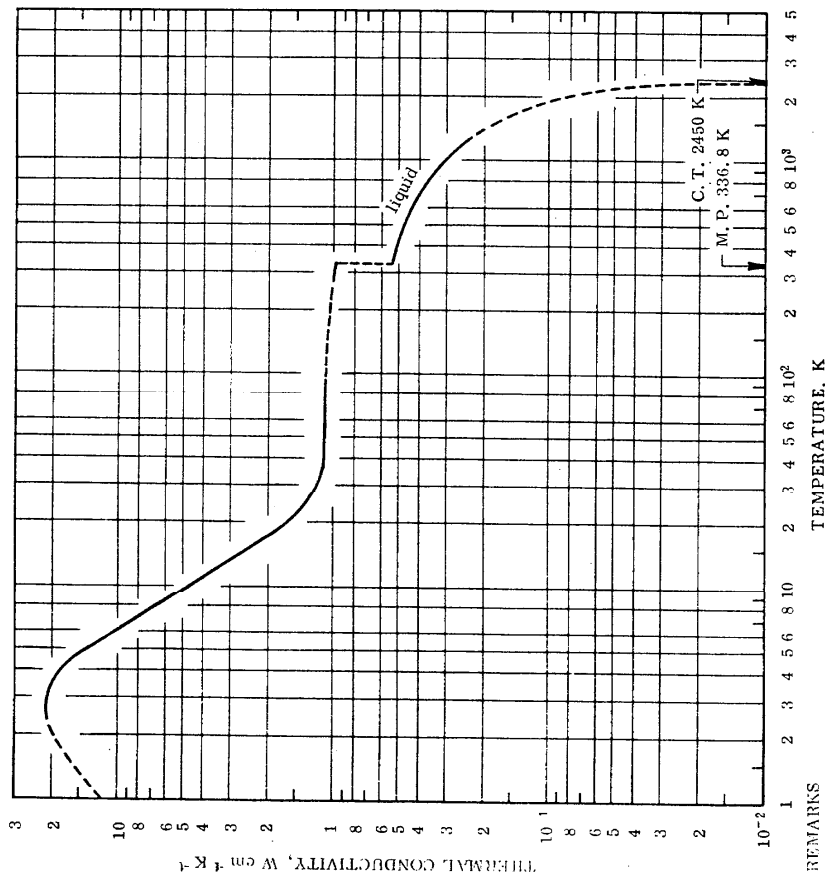

RECOMMENDED VALUES †
[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]


T	SOLID		LIQUID	
	T	k	T	k
0	0	1.10	336.8	0.548
1	11.9*	1.09	350	0.542
2	20.4*	1.08	373.2	0.532
3	22.1	1.075	400	0.520
4	19.1	1.070*	473.2	0.490
5	14.4	1.058*	500	0.479
6	10.8	1.050*	573.2	0.449
7	8.33	1.046*	600	0.439
8	6.62	1.043*	673.2	0.413
9	5.42	1.042*	700	0.404
10	4.58	1.040*	773.2	0.380
11	3.97	1.036*	800	0.371
12	3.47	1.025	873.2	0.348
13	3.06	1.024	900	0.340
14	2.74	1.003	973.2	0.320
15	2.48	0.985	1000	0.313
16	2.26		1073.2	0.294
18	1.91		1100	0.287
20	1.67		1173.2	0.269
25	1.33		1200	0.263
30	1.23		1273.2	0.245
35	1.18		1300	0.239
40	1.15		1373.2	0.222
45	1.13		1400	0.215
50	1.12		1473.2	0.199
				C.T.=2450

REMARKS

The recommended values are for high-purity potassium and are considered accurate to within $\pm 10\%$ of the true values for the solid state, $\pm 5\%$ for the liquid state below 1000 K, and $\pm 10\%$ from 1000 to 1500 K. The uncertainty increases at higher temperatures. The thermal conductivity at temperatures near and below the corresponding temperature, T_m , of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens, and the recommended values below 50 K are applicable only to potassium having residual electrical resistivity $\rho_0 = 0.00220 \mu\Omega \text{ cm}$. Values at temperatures below about 1.5 T_m are calculated to fit experimental data by using equation (7) and using the constants m , n , and α' given for potassium in Table 1 and the parameter $\beta = 0.0820$.

* Extrapolated, interpolated, or estimated.
† Values above 1500 K are provisional.

THERMAL CONDUCTIVITY OF PRASEODYMIUM

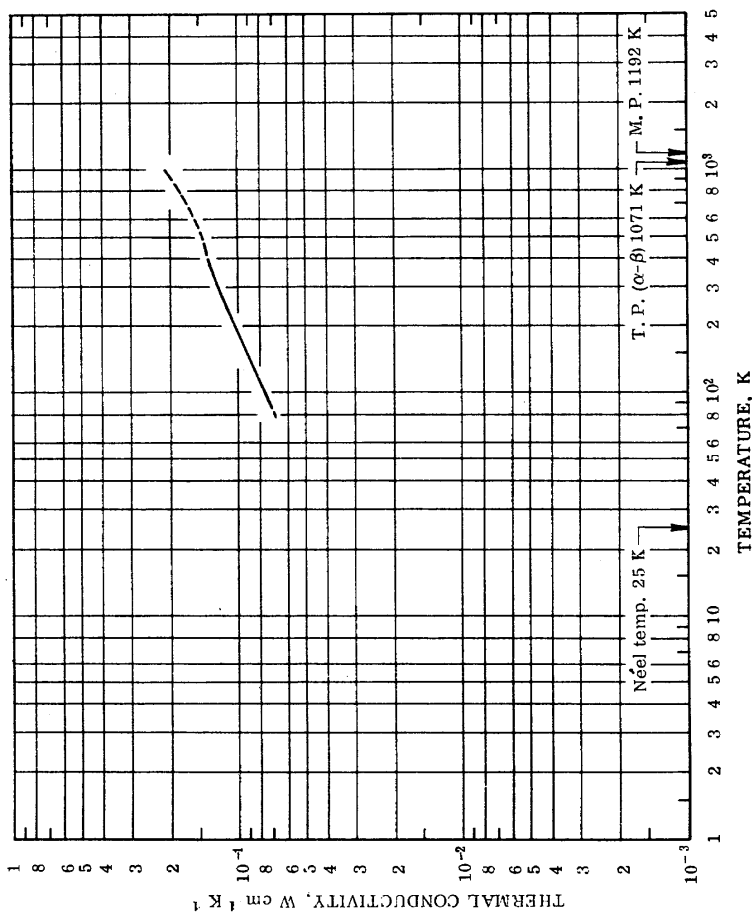

RECOMMENDED VALUES

[Temperature, T, K; Thermal Conductivity, k , $\text{W cm}^{-1} \text{K}^{-1}$]

SOLID

Polycrystalline


T k	k
80	0.0692*
90	0.0732
100	0.0769
123.2	0.0844
150	0.0926
173.2	0.0987
200	0.105
223.2	0.110
250	0.116
273.2	0.120
298.2	0.125
300	0.125
323.2	0.128
350	0.131
373.2	0.134
400	0.136*
473.2	0.144*
500	0.147*
573.2	0.154*
600	0.157*
673.2	0.166*
700	0.169*
773.2	0.180*
800	0.184*
873.2	0.195*
900	0.200*
973.2	0.212*
1000	0.216*

REMARKS

The recommended values are for well-annealed high-purity polycrystalline praseodymium and are thought to be accurate to within $\pm 5\%$ of the true values near room temperature and ± 10 to $\pm 15\%$ at other temperatures.

* Extrapolated.

THERMAL CONDUCTIVITY OF PROMETHIUM

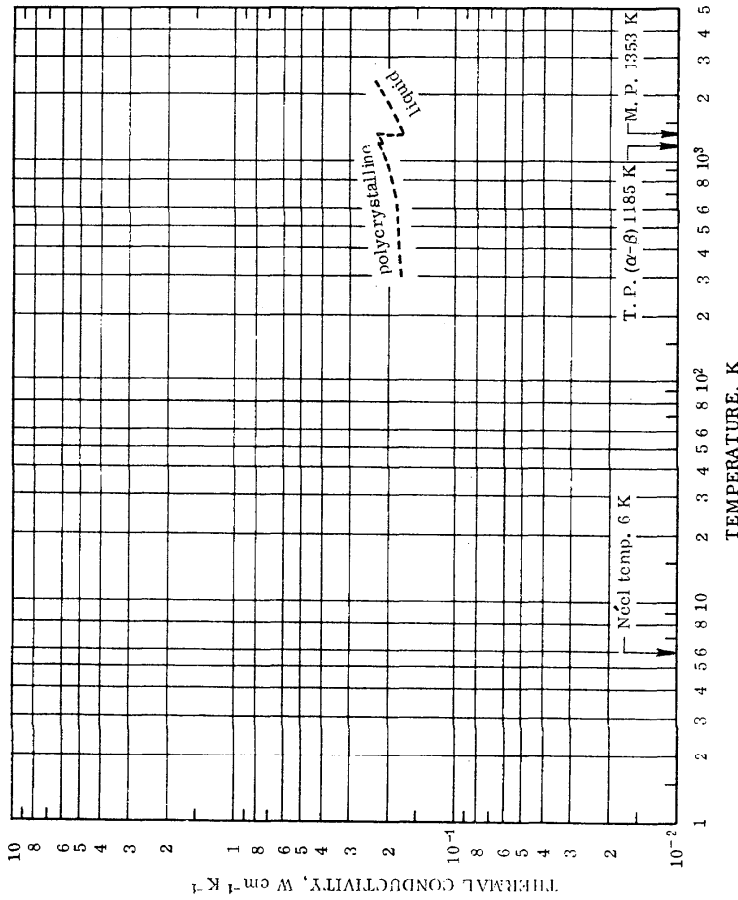

PROVISIONAL VALUES
[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]


SOLID		LIQUID	
Polycrystalline		T	k
T	k	T	k
300	0.179*	1353	0.175*
323.2	0.181*	1373.2	0.177*
330	0.182*	1400	0.178*
373.2	0.184*	1473.2	0.182*
400	0.184*	1500	0.184*
473.2	0.185*	1573.2	0.188*
500	0.185*	1600	0.190*
573.2	0.186*	1673.2	0.194*
600	0.187*	1700	0.196*
673.2	0.190*	1773.2	0.200*
700	0.191*	1800	0.202*
773.2	0.194*	1873.2	0.206*
800	0.195*	1900	0.208*
873.2	0.198*	1973.2	0.212*
900	0.201*	2000	0.214*
973.2	0.205*	2073.2	0.212*
1000	0.207*	2173.2	0.225*
1073.2	0.213*	2200	0.226*
1100	0.215*	2253	0.229*
1173.2	0.221*		
1135	0.222*		
1135	0.213*		
1200	0.214*		
1273.2	0.220*		
1300	0.223*		
1333	0.230*		

REMARKS

The provisional values are for high-purity promethium and those for solid promethium are for polycrystalline samples. They are probably accurate to within ±25% for solid and ±40% for molten promethium.

* Estimated.

THERMAL CONDUCTIVITY OF RADIUM

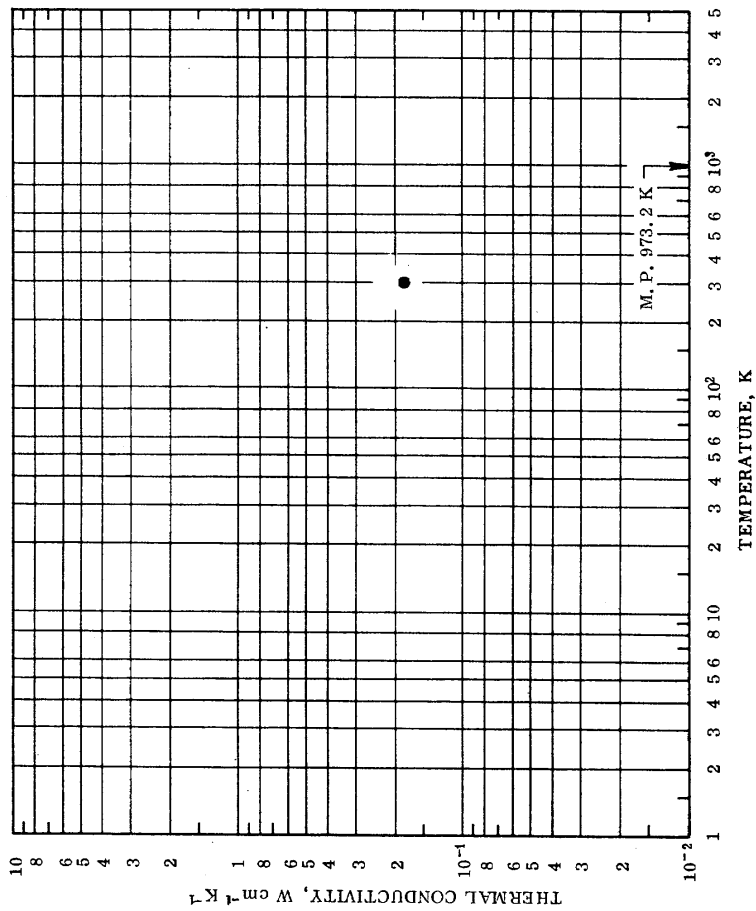

PROVISIONAL VALUES
 [Temperature, T, K; Thermal Conductivity, k, $\text{W cm}^{-1} \text{K}^{-1}$]


SOLID

T	k
298.2	0.186

REMARKS

This thermal conductivity value is provisional and its uncertainty may be as much as $\pm 50\%$.

THERMAL CONDUCTIVITY OF RADON

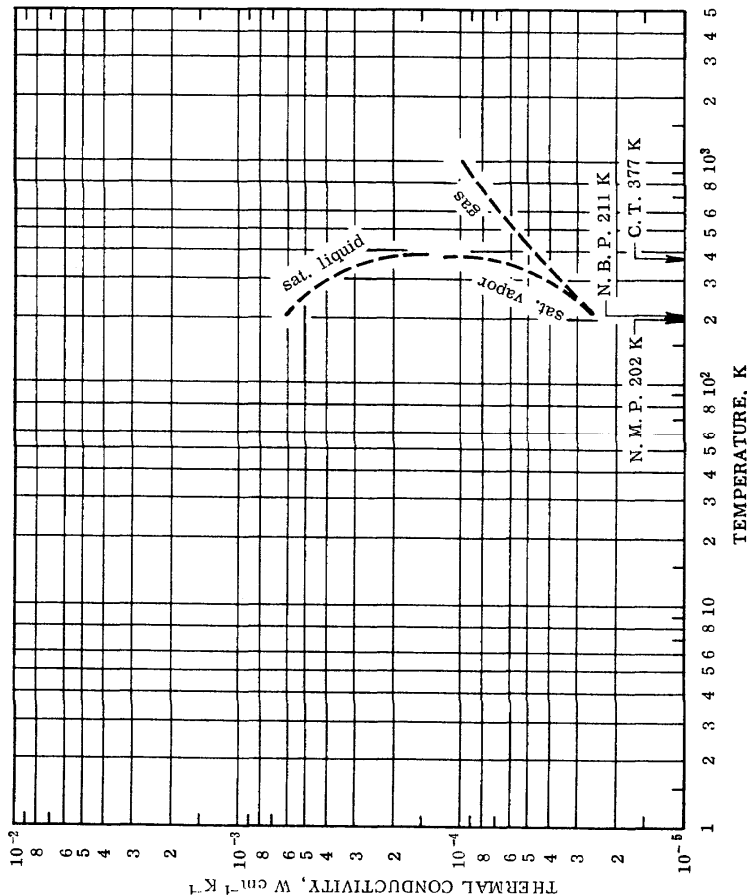

REMARKS


Values for the liquid and vapor were based on a generalized correlation together with estimated critical parameters and are thus considered tentative. The gas values, while likewise lacking experimental corroboration, could possibly be accurate to within 5% below 500 K and 10% at higher temperatures.

SATURATED LIQUID		SATURATED VAPOR		PROVISIONAL VALUES	
T	k x 10 ³	T	k x 10 ³	[Temperature, T, K; Thermal Conductivity, k, W cm ⁻¹ K ⁻¹]	GAS (At 1 atm)
202	0.604*			211	0.0256*
210	0.586*	211	0.026*	220	0.0266*
220	0.562*	220	0.028*	230	0.0279*
230	0.540*	230	0.030*	240	0.0291*
240	0.518*	240	0.032*	250	0.0303*
250	0.498*	250	0.034*	260	0.0315*
260	0.477*	260	0.035*	270	0.0327*
270	0.456*	270	0.038*	280	0.0339*
280	0.437*	280	0.040*	290	0.0351*
290	0.417*	290	0.042*	300	0.0364*
300	0.396*	300	0.045*	310	0.0376*
310	0.375*	310	0.047*	320	0.0387*
320	0.353*	320	0.051*	330	0.0398*
330	0.330*	330	0.055*	340	0.0410*
340	0.305*	340	0.060*	350	0.0422*
350	0.278*	350	0.065*	360	0.0433*
360	0.249*	360	0.073*	370	0.0445*
370	0.213*	370	0.089*†	380	0.0457*
377	0.136*†	377	0.138*†	390	0.0468*
				400	0.0480*
				410	0.0490*
				420	0.0501*
				430	0.0512*
				440	0.0523*
				450	0.0534*
				460	0.0544*
				470	0.0555*
				480	0.0566*
				490	0.0576*
				500	0.0586*
				550	0.0643*
				600	0.0690*
				650	0.0740*
				700	0.0789*
				750	0.0832*
				800	0.0874*
				850	0.0915*
				900	0.0964*
				950	0.0997*
				1000	0.1042*

* Estimated or extrapolated.

† Pseudo-critical value.

THERMAL CONDUCTIVITY OF RHENIUM

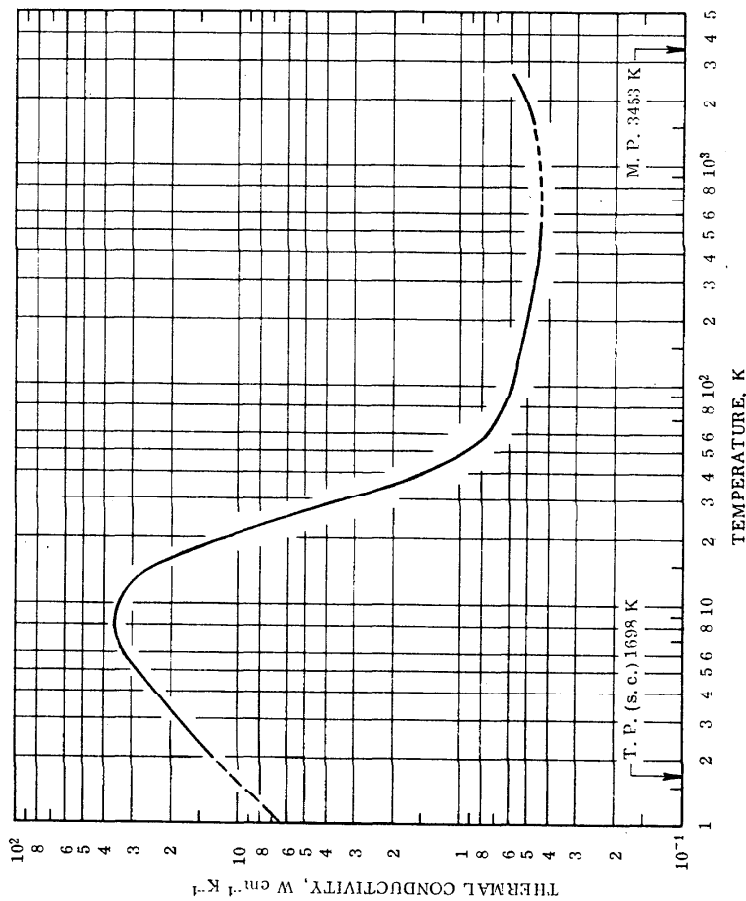

REMARKS

The recommended values are for well-annealed high-purity polycrystalline rhenium and are considered accurate to within $\pm 10\%$ of the true values at temperatures below 100 K, $\pm 5\%$ from 100 to 500 K, and $\pm 15\%$ above 500 K. The thermal conductivity at temperatures near and below the corresponding temperature, T_m , of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens, and the recommended values below 100 K are applicable only to rhenium having residual electrical resistivity $\rho_0 = 0.00366 \mu\Omega \text{ cm}$. Values at temperatures below about $1.5 T_m$ are calculated to fit experimental data by using equation (10) and using the values $n = 2.2$, $\alpha = 0.0000648$, $\beta = 0.150$, and $\gamma = 0.000282$. However, for specimens of lower purity (higher ρ_0), equation (7) and the constants given in Table 1 should be used.


RECOMMENDED VALUES

[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]

T		k	
0	0	0	0.470
1	6.65*	350	0.466
2	13.2*	373.2	0.461
3	19.4	400	0.451
4	25.0	473.2	0.449
5	29.7	500	0.444*
6	33.3	573.2	0.442*
7	35.6	600	0.441*
8	36.6	673.2	0.440*
9	36.6	773.2	0.440*
10	35.6	800	0.441*
11	34.0	873.2	0.442*
12	31.7	900	0.443*
13	28.9	973.2	0.445*
14	26.0	1000	0.446*
15	23.1	1073.2	0.450*
16	20.3	1100	0.451*
18	15.4	1173.2	0.455*
20	11.6	1200	0.457*
25	6.02	1273.2	0.462*
30	3.39	1300	0.464*
35	2.19	1373.2	0.469*
40	1.56	1400	0.471*
45	1.21	1473.2	0.476*
50	0.986	1500	0.478*
60	0.774	1573.2	0.483
70	0.678	1600	0.485
80	0.629	1673.2	0.490
90	0.606	1700	0.492
100	0.589	1773.2	0.498
123.2	0.561	1800	0.500
150	0.538	1873.2	0.507
173.2	0.524	1900	0.509
200	0.510	1973.2	0.516
223.2	0.501	2000	0.519
250	0.492	2073.2	0.526
273.2	0.486	2173.2	0.536
298.2	0.480	2200	0.539
300	0.479	2273.2	0.547
323.2	0.475	2400	0.563
		2473.2	0.573
		2600	0.592

* Extrapolated or interpolated.

THERMAL CONDUCTIVITY OF RHODIUM

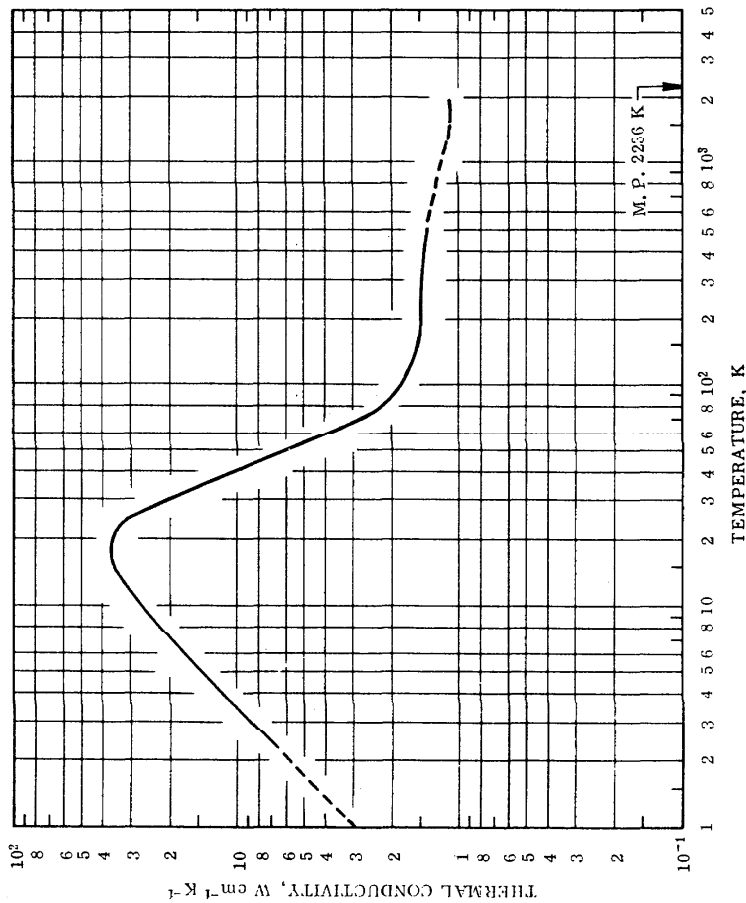

RECOMMENDED VALUES
[Temperature, T, K; Thermal Conductivity, k, $W\ cm^{-1}\ K^{-1}$]

SOLID


T	k	T	k
0	0	250	1.52
1	2.91*	273.2	1.51
2	5.81	298.2	1.50
3	8.69	300	1.50
4	11.6	323.2	1.49
5	14.5	350	1.48
6	17.3	373.2	1.47
7	20.1	400	1.46
8	22.8	473.2	1.42
9	25.4	500	1.41
10	27.8	573.2	1.37
11	29.9	600	1.36*
12	32.1	673.2	1.32*
13	33.8	700	1.31*
14	35.3	773.2	1.28*
15	36.3	800	1.27*
16	37.0	873.2	1.25*
18	37.3	900	1.24*
20	36.4	973.2	1.21*
25	30.5	1000	1.21*
30	21.6	1073.2	1.19*
35	14.5	1100	1.18*
40	10.2	1173.2	1.17*
45	7.47	1200	1.16*
50	5.70	1273.2	1.15*
60	3.78	1300	1.14*
70	2.89	1373.2	1.13*
80	2.38	1400	1.12*
90	2.06	1473.2	1.11*
100	1.86	1500	1.10
123.2	1.63	1573.2	1.10
150	1.58	1600	1.10
173.2	1.56	1673.2	1.10
200	1.54	1700	1.10
223.2	1.53	1773.2	1.10
		1800	1.10
		1873.2	1.11
		1900	1.11
		1973.2	1.12
		2000	1.12

* Extrapolated or interpolated.

REMARKS

The recommended values are for well-annealed high-purity rhodium and are considered accurate to within $\pm 5\%$ of the true values at moderate temperatures and $\pm 10\%$ at low and high temperatures. The thermal conductivity at temperatures near and below the corresponding temperature, T_m , of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens, and the recommended values below 150 K are applicable only to rhodium having residual electrical resistivity $\rho_0 = 0.0840\ \mu\Omega\ cm$. Values at temperatures below about 1.5 T_m are calculated to fit experimental data by using equation (7) and using the constants m , n , and α' given for rhodium in Table 1 and the parameter $\beta = 0.344$.

THERMAL CONDUCTIVITY OF RUBIDIUM

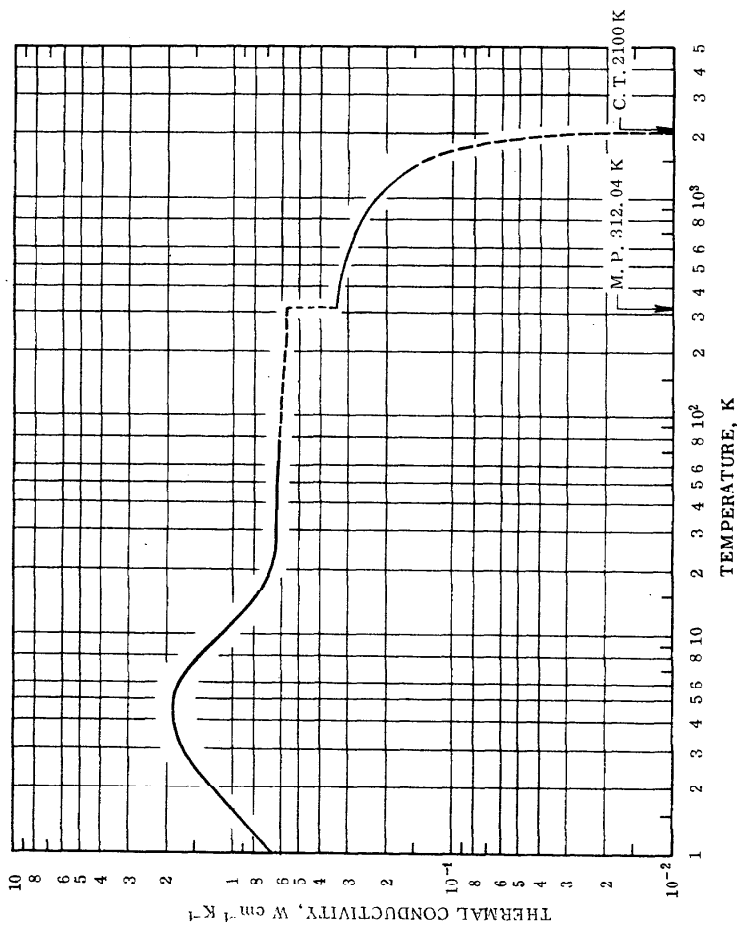

REMARKS

The recommended values are for high-purity rubidium and are considered accurate to within $\pm 10\%$ of the true values at temperatures below 1000 K. The uncertainty increases at higher temperatures. The thermal conductivity at temperatures near and below the corresponding temperature, T_m , of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens, and the recommended values below 40 K are applicable only to rubidium having residual electrical resistivity $\rho_0 = 0.0384 \mu\Omega \text{ cm}$. Values at temperatures below about 1.5 T_m are calculated to fit experimental data by using equation (7) and using $n = 2.00$, $\alpha' = 0.00930$, and the parameter $\beta = 1.50$.

RECOMMENDED VALUES †


[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]

SOLID		LIQUID	
T	k	T	k
0	0	312.04	0.333
1	0.663*	323.2	0.331
2	1.27	350	0.325
3	1.71	373.2	0.321
4	1.91	400	0.318
5	1.88	473.2	0.306
6	1.73	500	0.302
7	1.56	573.2	0.289
8	1.38	600	0.285
9	1.22	673.2	0.273
10	1.09	700	0.268
11	0.991	773.2	0.256
12	0.919	800	0.251
13	0.859	873.2	0.239
14	0.810	900	0.234
15	0.772	973.2	0.222
16	0.746	1000	0.218
18	0.710	1073.2	0.205
20	0.685	1100	0.201
25	0.657	1173.2	0.188
30	0.647	1200	0.184
35	0.640	1273.2	0.172
40	0.635	1300	0.167
45	0.630	1373.2	0.155*
50	0.627	1400	0.150*
60	0.620	1473.2	0.137*
70	0.615	1500	0.132*
80	0.611*	1573.2	0.118*
90	0.607*	1600	0.113*
100	0.603*	1673.2	0.0987*
123.2	0.599*	1700	0.0933*
150	0.594*	1773.2	0.0787*
173.2	0.592*	1800	0.0730*
200	0.589*	1873.2	0.0580*
223.2	0.587*	1900	0.0516*
250	0.586*	1973.2	0.0339*
273.2	0.583*	2000	0.0272*
298.2	0.582	2073.2	0.0079*
300	0.582		
312.04	0.581		

* Extrapolated, interpolated, or estimated.

† Values above 1300 K are provisional.

THERMAL CONDUCTIVITY OF RUTHENIUM

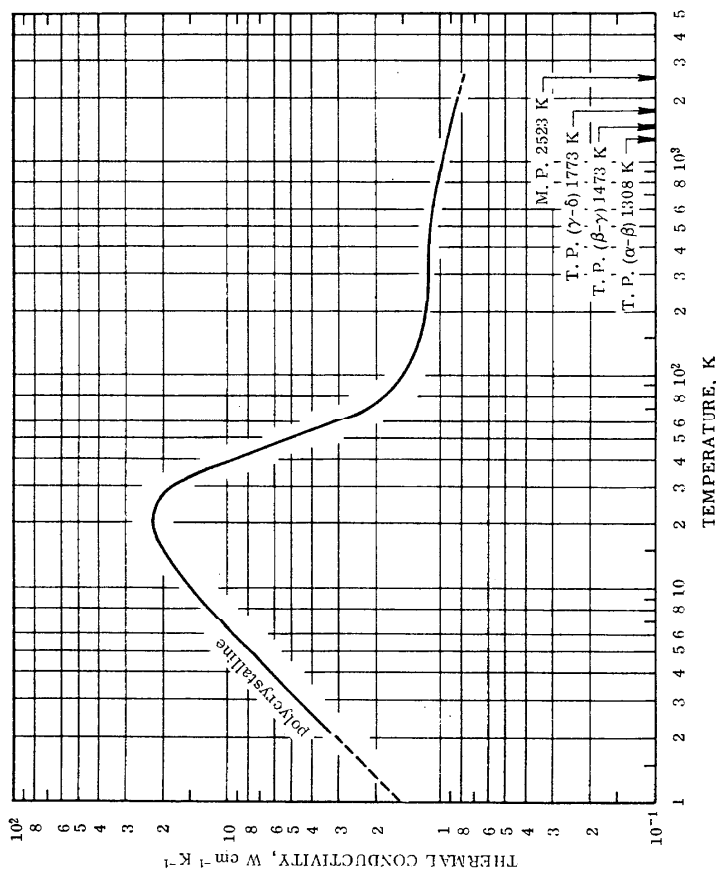

REMARKS


The recommended values are for well-annealed high-purity polycrystalline ruthenium and are considered accurate to within $\pm 5\%$ of the true values at temperatures below 500 K and $\pm 15\%$ at the highest temperatures. The thermal conductivity at temperatures near and below the corresponding temperature, T_m , of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens, and the conductivity values below 250 K are applicable only to ruthenium having residual electrical resistivity $\rho_0 = 0.0158 \mu\Omega \text{ cm}$. Values at temperatures below about 1.5 T_m are calculated to fit experimental data by using equation (7) and using the constants m , n , and σ'' given for ruthenium in Table I and the parameter $\beta = 0.647$.

RECOMMENDED VALUES
[Temperature, T, K; Thermal Conductivity, k , $\text{W cm}^{-1} \text{K}^{-1}$]

T		k	
SOLID			
Polycrystalline			
T	k	T	k
0	0	350	1.15
1	1.55*	373.2	1.15
2	3.09*	400	1.14
3	4.64	473.2	1.12
4	6.18	500	1.11
5	7.71	573.2	1.08
6	9.23	600	1.08
7	10.7	673.2	1.06
8	12.2	700	1.05
9	13.6	773.2	1.03
10	15.0	800	1.02
11	16.3	873.2	1.01
12	17.5	900	0.997
13	18.7	973.2	0.982
14	19.7	1000	0.976
15	20.5	1073.2	0.962
16	21.3	1100	0.957
18	22.3	1173.2	0.944
20	22.6	1200	0.939
25	21.3	1273.2	0.928
30	17.8	1300	0.923
35	13.3	1373.2	0.913
40	9.53	1400	0.909
45	6.88	1473.2	0.899
50	5.10	1500	0.895
60	3.10	1573.2	0.885
70	2.26	1600	0.882
80	1.86	1673.2	0.873
90	1.65	1700	0.870
100	1.54	1773.2	0.862
123.2	1.38	1800	0.859
150	1.28	1873.2	0.851
173.2	1.23	1900	0.848
200	1.18	1973.2	0.841
223.2	1.17	2000	0.838
250	1.17	2073.2	0.831*
273.2	1.17	2173.2	0.822*
298.2	1.17	2200	0.820*
300	1.17	2273.2	0.813*
323.2	1.16	2400	0.803*
		2473.2	0.798*
		2500	0.796*

* Extrapolated.

THERMAL CONDUCTIVITY OF SAMARIUM

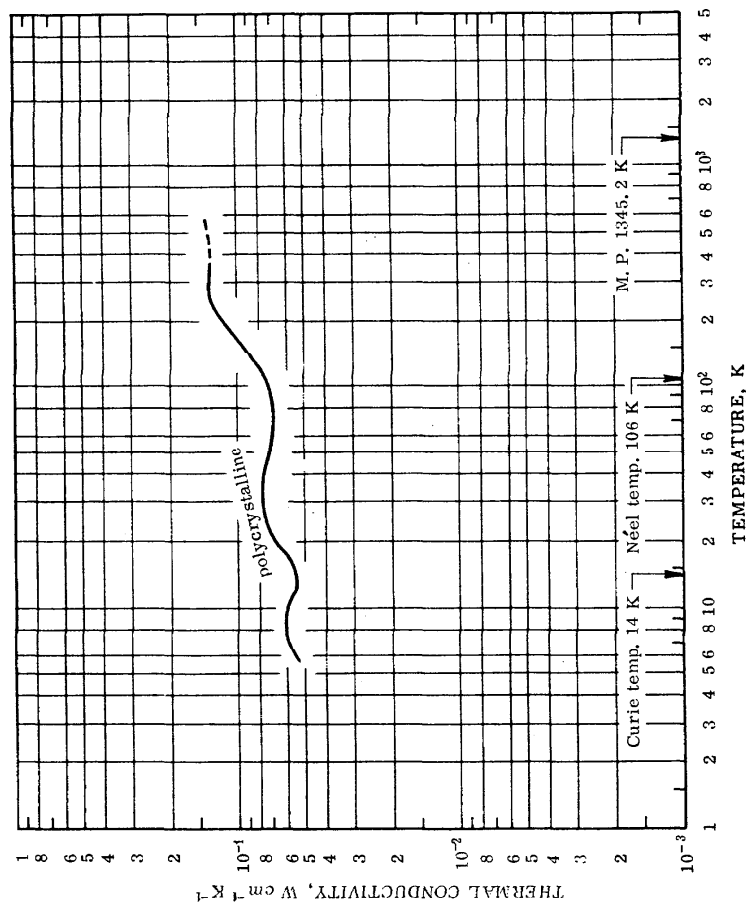

PROVISIONAL VALUES
[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]

SOLID
Polycrystalline


T	k	T	k
6	0.0555	100	0.0735
7	0.0591	123.2	0.0820
8	0.0611	150	0.0924
9	0.0618	173.2	0.101
10	0.0607	200	0.113
11	0.0586	220	0.123
12	0.0557	223.2	0.124
13	0.0542	250	0.132
14	0.0551	273.2	0.133
15	0.0566	298.2	0.133
16	0.0580	300	0.133
17	0.0598	323.2	0.133
18	0.0623	350	0.133
19	0.0659	373.2	0.133
20	0.0692	400	0.133
25	0.0754	473.2	0.134*
30	0.0770	500	0.135*
35	0.0768	573.2	0.139*
40	0.0754	600	0.141*
45	0.0742		
50	0.0732		
60	0.0714		
70	0.0708		
80	0.0709		
90	0.0714		

REMARKS

The provisional values are for well-annealed high-purity polycrystalline samarium and are thought to be accurate to within ±15% of the true values near room temperature, ±20% at higher temperatures, and ±25% at lower temperatures. Values below room temperature are applicable only to samarium having electrical resistivity $\rho_0 = 6.73 \mu\Omega \text{ cm}$ at 4.2 K.

* Extrapolated.

THERMAL CONDUCTIVITY OF SCANDIUM

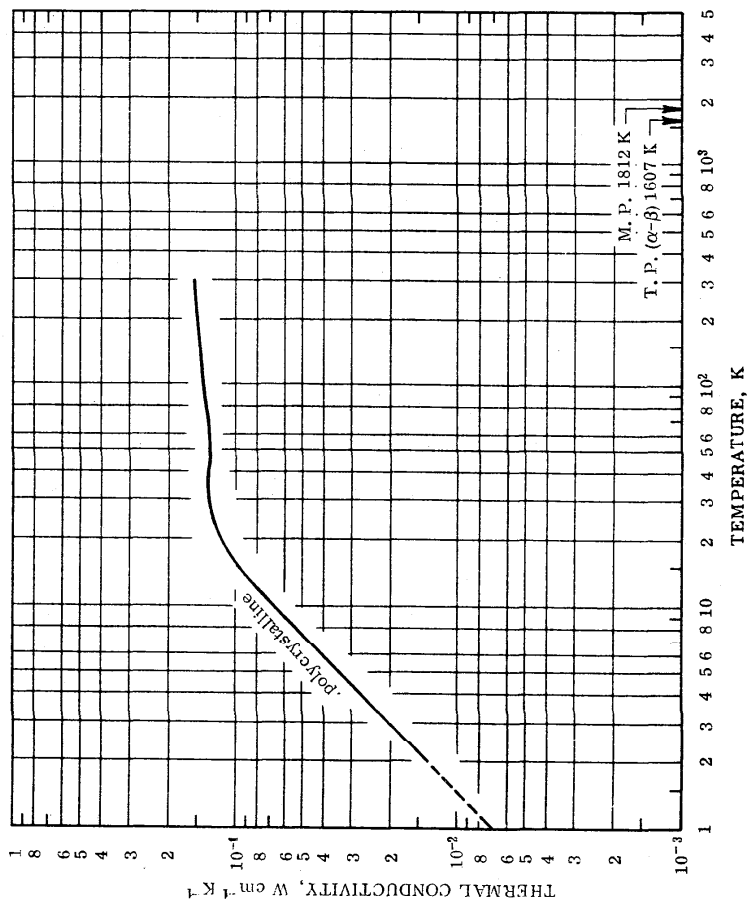

RECOMMENDED VALUES
 [Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]


T	k
0	0
1	0.00706*
2	0.0140
3	0.0208
4	0.0276
5	0.0344
6	0.0412
7	0.0479
8	0.0545
9	0.0612
10	0.0678
11	0.0738
12	0.0797
13	0.0855
14	0.0910
15	0.0960
16	0.101
18	0.109
20	0.117
25	0.130
30	0.137
35	0.138
40	0.138
45	0.136
50	0.135
60	0.136
70	0.138
80	0.139
90	0.141
100	0.143
123.2	0.146
150	0.149
173.2	0.151
200	0.153
223.2	0.154
250	0.156
273.2	0.157
298.2	0.158
300	0.158

REMARKS

The recommended values are for well-annealed high-purity polycrystalline scandium and are considered accurate to within ±5% of the true values near room temperature and ±15% below 200 K. The values below 200 K are applicable only to scandium having residual electrical resistivity $\rho_0 = 10.6 \mu\Omega \text{ cm}$.

* Extrapolated.

THERMAL CONDUCTIVITY OF SELENIUM

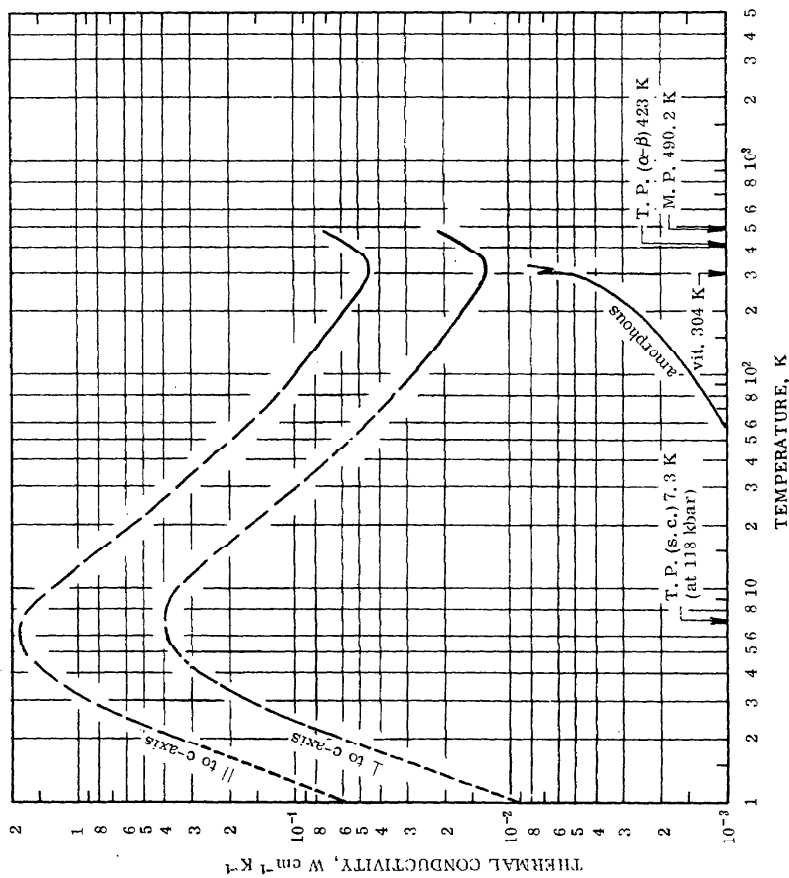

REMARKS

The values are for high-purity selenium. Those for selenium single crystal at temperatures above 80 K are recommended values and are thought to be accurate to within ± 10 to $\pm 20\%$. The values below 80 K are merely typical values and represent a typical curve serving only to indicate the general trend of the thermal conductivity of selenium single crystal at low temperatures. The values for amorphous selenium are recommended values and are considered accurate to within $\pm 10\%$ except for those values around the vitrification temperature, which are provisional and their uncertainty may be as much as $\pm 25\%$.

RECOMMENDED VALUES †
[Temperature, T, K; Thermal Conductivity, k , $W\ cm^{-1}\ K^{-1}$]

SOLID		// to c-axis		T		// to c-axis		⊥ to c-axis	
T	k	k	k	T	k	k	k	k	k
0	0	0	0	60	0.168	0.144	0.0480	0.0480	0.0480
1	0.0563*	0.00865*	0.00865*	70	0.144	0.126	0.0411	0.0411	0.0411
2	0.353	0.0600	0.0600	80	0.126	0.112	0.0360	0.0360	0.0360
3	0.855	0.160	0.160	90	0.112	0.103	0.0320	0.0320	0.0320
4	1.41	0.268	0.268	100	0.103		0.0294	0.0294	0.0294
5	1.75	0.348	0.348	123.2	0.0880		0.0253	0.0253	0.0253
6	1.92	0.395	0.395	150	0.0762		0.0218	0.0218	0.0218
7	1.90	0.410	0.410	173.2	0.0681		0.0195	0.0195	0.0195
8	1.78	0.407	0.407	200	0.0608		0.0174	0.0174	0.0174
9	1.61	0.390	0.390	223.2	0.0555		0.0161	0.0161	0.0161
10	1.42	0.359	0.359	250	0.0513		0.0147	0.0147	0.0147
11	1.26	0.329	0.329	273.2	0.0481		0.0137	0.0137	0.0137
12	1.12	0.301	0.301	298.2	0.0452		0.0131	0.0131	0.0131
13	1.01	0.276	0.276	300	0.0452		0.0130	0.0130	0.0130
14	0.919	0.253	0.253	323.2	0.0448		0.0127	0.0127	0.0127
15	0.844	0.234	0.234	350	0.0461		0.0132	0.0132	0.0132
16	0.778	0.217	0.217	373.2	0.0483		0.0139	0.0139	0.0139
18	0.672	0.189	0.189	400	0.0538		0.0154	0.0154	0.0154
20	0.588	0.166	0.166	473.2	0.0696		0.0198	0.0198	0.0198
25	0.448	0.127	0.127	490.2	0.0747		0.0213	0.0213	0.0213
30	0.362	0.103	0.103						
35	0.303	0.0866	0.0866						
40	0.260	0.0743	0.0743						
45	0.228	0.0651	0.0651						
50	0.203	0.0580	0.0580						

* Extrapolated.

† Values below 80 K are merely typical values.

THERMAL CONDUCTIVITY OF SELENIUM (continued)


RECOMMENDED VALUES †

SOLID			
Amorphous			
T	k	T	k
0	0	250	0.00360
1	0.000130*	273.2	0.00428
2	0.000236	290	0.00484
3	0.000290	295	0.00504
4	0.000323	298.2	0.00519
5	0.000342	299.2	0.00524
6	0.000358	300	0.00528
7	0.000374	300.2	0.00529
8	0.000390	301	0.00533
9	0.000405	301.2	0.00534
10	0.000420	302	0.00538
11	0.000435	302.2	0.00539
12	0.000450	303	0.00544
13	0.000465	303.2	0.00545
14	0.000480	303.5	0.00547
15	0.000494	304	0.00732
16	0.000508	304.5	0.00681
18	0.000532	304.7	0.00671
20	0.000560	305	0.00657
25	0.000619	305.2	0.00650
30	0.000675	305.5	0.00640
35	0.000730	305.7	0.00635
40	0.000788	306	0.00627
45	0.000843	306.2	0.00623
50	0.000900	306.5	0.00619
60	0.00102	306.7	0.00619
70	0.00113	307	0.00619
80	0.00125	307.2	0.00621
90	0.00136	307.5	0.00625
100	0.00148	308	0.00631
123.2	0.00173	309	0.00644
150	0.00204	310	0.00656
173.2	0.00230	313.2	0.00696
200	0.00263	320	0.00782
223.2	0.00299	323.2	0.00818

* Extrapolated.

† Values at temperatures from 301 to 300 K are provisional.

THERMAL CONDUCTIVITY OF SILICON

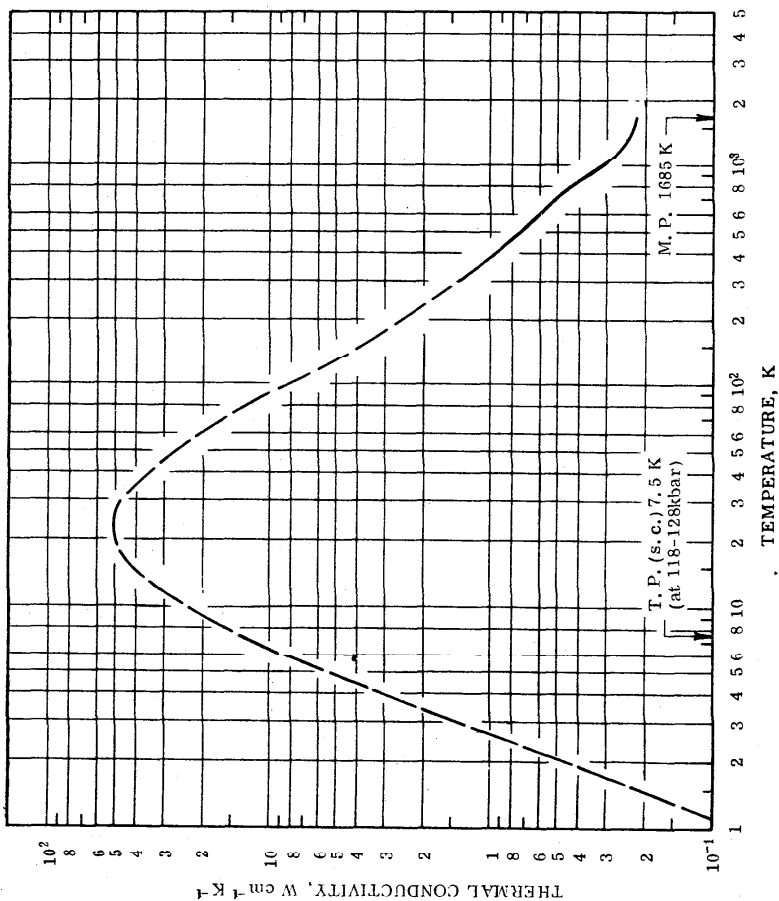

REMARKS

The values are for high-purity silicon. Those at temperatures 300 K and above are recommended values and are considered accurate to within ±5% of the true values at temperatures from 300 to 1000 K and ±10% at the highest temperatures. The values below 300 K are merely typical values and represent a typical curve serving to indicate the general trend of the thermal conductivity of silicon at moderate and low temperatures.


RECOMMENDED VALUES †

[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]

SOLID			
T	k	T	k
0	0	250	1.91
1	0.0693*	273.2	1.68
2	0.454	298.2	1.49
3	1.38	300	1.48
4	2.97	323.2	1.33
5	5.27	350	1.19
6	8.23	373.2	1.08
7	11.7	400	0.989
8	15.5	473.2	0.814
9	19.5	500	0.762
10	23.3	573.2	0.651
11	27.0	600	0.619
12	30.9	673.2	0.536
13	34.8	700	0.508
14	38.4	773.2	0.442
15	41.6	800	0.422
16	44.1	873.2	0.374
18	47.7	900	0.359
20	49.8	973.2	0.323
25	51.3	1000	0.312
30	48.1	1073.2	0.286
35	41.3	1100	0.279
40	35.3	1173.2	0.262
45	30.6	1200	0.257
50	26.8	1273.2	0.247
60	21.1	1300	0.244
70	16.8	1373.2	0.237
80	13.4	1400	0.235
90	10.8	1473.2	0.229
100	8.84	1500	0.227
123.2	5.99	1573.2	0.223
150	4.09	1600	0.221
173.2	3.30	1673.2	0.220
200	2.64	1685	0.220
223.2	2.25		

* Extrapolated.
 † Values below 300 K are merely typical values.

THERMAL CONDUCTIVITY OF SILVER

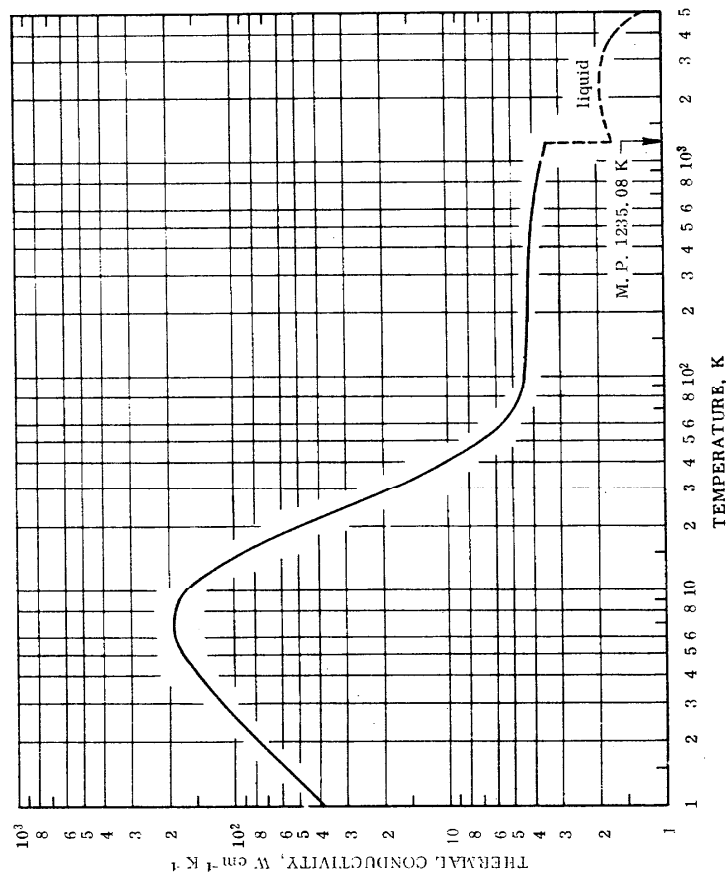

REMARKS

The recommended values are for well-annealed high-purity silver and are considered accurate to within $\pm 2\%$ of the true values near room temperature and $\pm 5\%$ below 100 K and above 1000 K. The thermal conductivity at temperatures near and below the corresponding temperature, T_m , of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens, and the recommended values below 150 K are applicable only to silver having residual electrical resistivity $\rho_0 = 0.000621 \mu\Omega \text{ cm}$. Values at temperatures below about $1.5 T_m$ are calculated by using equation (7) and using the constants m , n , and α' given for silver in Table 1 and the parameter $\beta = 0.0254$. No experimental data are available for molten silver and the values given here are estimated and are provisional values. They are probably good to $\pm 20\%$ from melting point to 2000 K.


RECOMMENDED VALUES †

[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]

SOLID		LIQUID	
T	k	T	k
0	0	1235.08	1.75*
1	39.4	1273.2	1.77*
2	78.3	1300	1.78*
3	115	1373.2	1.82*
4	147	1400	1.83*
5	172	1473.2	1.86*
6	187	1500	1.87*
7	193	1573.2	1.89*
8	190	1600	1.90*
9	181	1673.2	1.92*
10	168	1700	1.93*
11	154	1773.2	1.94*
12	139	1800	1.95*
13	124	1873.2	1.96*
14	109	1900	1.96*
15	96	1973.2	1.97*
16	85	2000	1.97*
18	66	2073.2	1.98*
20	51	2173.2	1.98*
25	29.5	2200	1.98*
30	19.3	2273.2	1.99*
35	13.7	2300	1.98*
40	10.5	2400	1.98*
45	8.4	2473.2	1.98*
50	7.0	2600	1.97*
60	5.5	2673.2	1.96*
70	4.97	2800	1.95*
80	4.71	2873.2	1.94*
90	4.60	3000	1.91*
100	4.50	3073	1.90*
		3200	1.87*
		1235.08	

* Extrapolated or estimated.
 † Values for molten silver are provisional.

THERMAL CONDUCTIVITY OF SODIUM

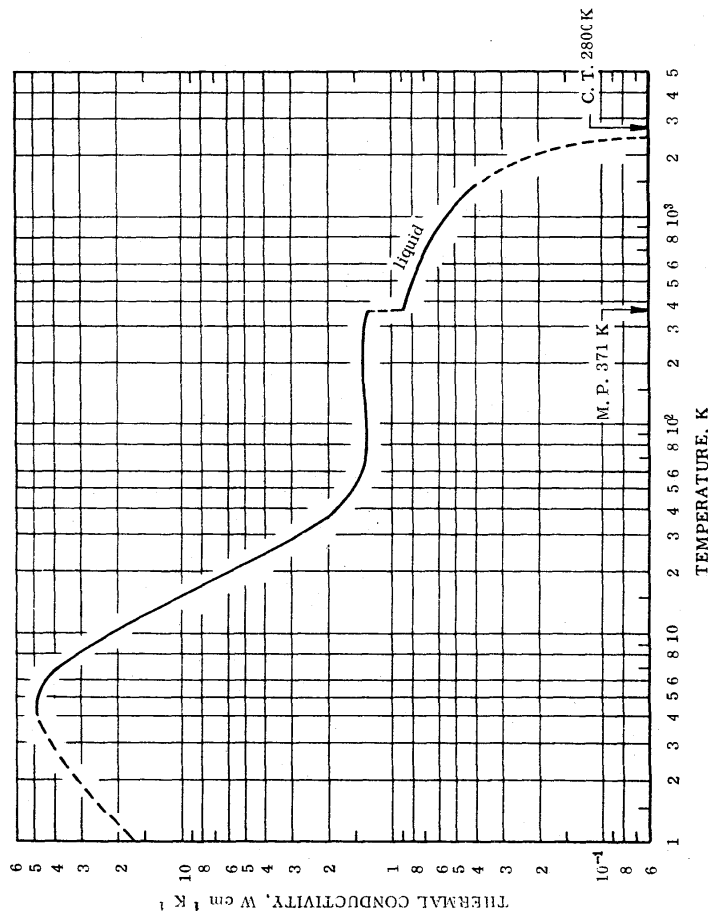

REMARKS


The recommended values are for high-purity sodium and are considered accurate to within $\pm 6\%$ of the true values at temperatures below 60 K, $\pm 10\%$ from 60 K to the melting point, $\pm 5\%$ for the liquid state below 1000 K, and $\pm 10\%$ from 1000 to 1600 K. The thermal conductivity at temperatures near and below the corresponding temperature, T_m , of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens, and the recommended values below 80 K are applicable only to sodium having residual electrical resistivity $\rho_0 = 0.00147 \mu\Omega \text{ cm}$. Values at temperatures below about $1.5 T_m$ are calculated to fit experimental data by using equation (7) and using the constants m , n , and α' given for sodium in Table 1 and the parameter $\beta = 3.0600$.

RECOMMENDED VALUES†
[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]

SOLID		LIQUID	
T	k	T	k
0	0	371	0.883
1	16.6*	373.2	0.882
2	31.8*	400	0.868
3	43.2	473.2	0.827
4	48.5	500	0.815
5	48.2	573.2	0.778
6	44.2	600	0.764
7	38.4	673.2	0.728
8	31.7	700	0.715
9	26.3	773.2	0.681
10	22.0	800	0.668
11	18.8	873.2	0.638
12	16.1	900	0.625
13	14.0	973.2	0.596
14	12.2	1000	0.583
15	10.7	1073.2	0.553
16	9.40	1100	0.543
18	7.48	1173.2	0.513
20	6.09	1200	0.503
25	3.94	1273.2	0.476
30	2.83	1300	0.465
35	2.22	1373.2	0.438
40	1.89	1400	0.428*
45	1.71	1473.2	0.402*
50	1.58	1500	0.393*
50	1.45	1573.2	0.367*
70	1.38	1600	0.358*
80	1.35	1673.2	0.334*
90	1.36	1700	0.325*
100	1.36	1773.2	0.301*
123.2	1.38		
130	1.40		
173.2	1.41		
200	1.42		
223.2	1.42		
250	1.43		
273.2	1.42		
298.2	1.42		
300	1.41		
323.2	1.39		
350	1.35		
371	1.32		

* Extrapolated or estimated.
† Values above 1600 K are provisional.

THERMAL CONDUCTIVITY OF STRONTIUM

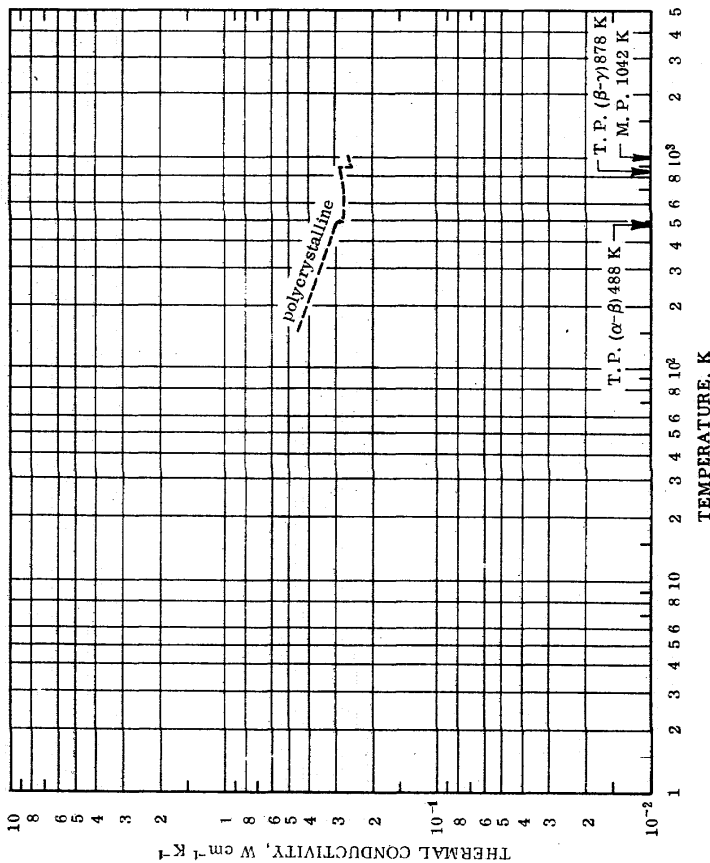

PROVISIONAL VALUES
 [Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]


SOLID	
Polycrystalline	
T	k
150	0.446*
173.2	0.424*
200	0.403*
223.2	0.390*
250	0.375*
273.2	0.364*
298.2	0.354*
300	0.353*
323.2	0.344*
350	0.333*
373.2	0.325*
400	0.317*
473.2	0.301*
488	0.300*
488	0.281*
500	0.280*
573.2	0.277*
600	0.276*
673.2	0.277*
700	0.278*
773.2	0.282*
800	0.284*
873.2	0.289*
878	0.290*
878	0.248*
900	0.250*
973.2	0.257*
1000	0.260*

REMARKS

The provisional values are for high-purity strontium and are probably good to ±20% below 450 K. The uncertainty increases above 500 K due to the effect of the phase transformations. No values appear to have been reported for the thermal conductivity of strontium, and these provisional values are derived from electrical resistivity data.

* Estimated.

THERMAL CONDUCTIVITY OF SULFUR

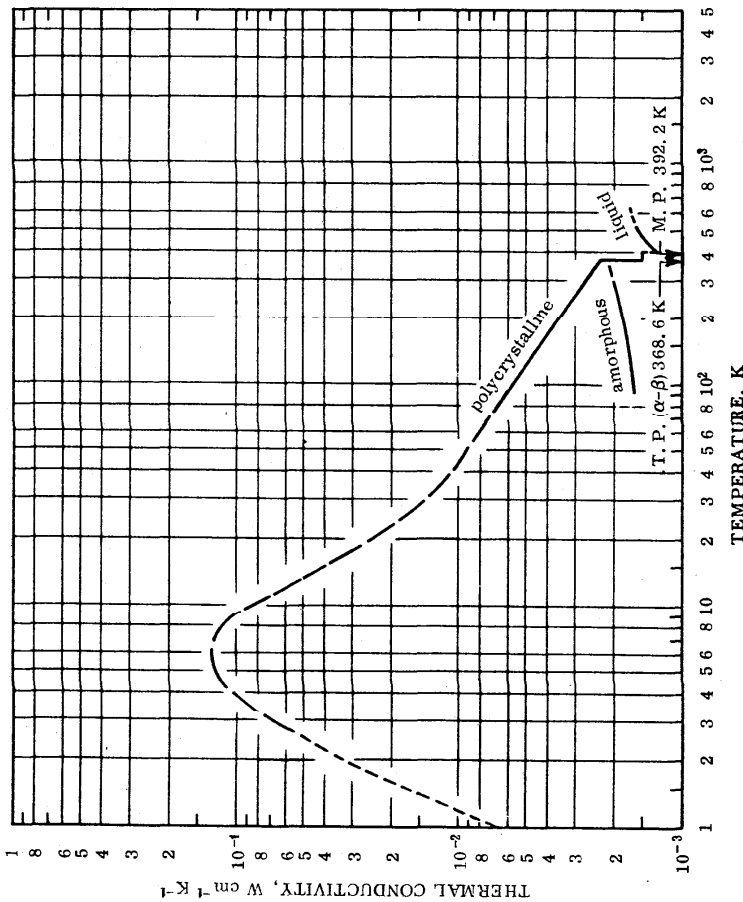

RECOMMENDED VALUES †
[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]

SOLID		Amorphous	
Polycrystalline		T	k
T	k	T	k
0	0	60	0.00799
1	0.00662*	70	0.00717
2	0.0320*	80	0.00654
3	0.0694	90	0.00602
4	0.106	100	0.00562
5	0.124	123.2	0.00490
6	0.128	150	0.00430
7	0.123	173.2	0.00389
8	0.112	200	0.00355
9	0.0970	223.2	0.00330
10	0.0817	250	0.00305
11	0.0688	273.2	0.00287
12	0.0581	298.2	0.00270
13	0.0499	300	0.00269
14	0.0435	323.2	0.00256
15	0.0384	350	0.00242
16	0.0343	368.6	0.00233
18	0.0280	368.6	0.00154
20	0.0235	373.2	0.00154
25	0.0169	392.2	0.00150
30	0.0140		
35	0.0122		
40	0.0109		
45	0.00993		
50	0.00917		

LIQUID	
T	k
392.2	0.00129
400	0.00132
473.2	0.00153
500	0.00160
573.2	0.00169
600	0.00170*


REMARKS

The values are for high-purity sulfur. Those for polycrystalline sulfur at temperatures above 70 K are recommended values and are considered accurate to within $\pm 10\%$ of the true values from 70 K to room temperature and $\pm 5\%$ from room temperature to the melting point. The values below 70 K are merely typical values and represent a typical curve serving to indicate the general trend of the thermal conductivity of sulfur at low temperatures. The values for amorphous sulfur are recommended values and are probably good to $\pm 15\%$. The recommended values for liquid sulfur are considered accurate to within $\pm 5\%$.

* Extrapolated.

† Values below 70 K are merely typical values.

THERMAL CONDUCTIVITY OF TANTALUM

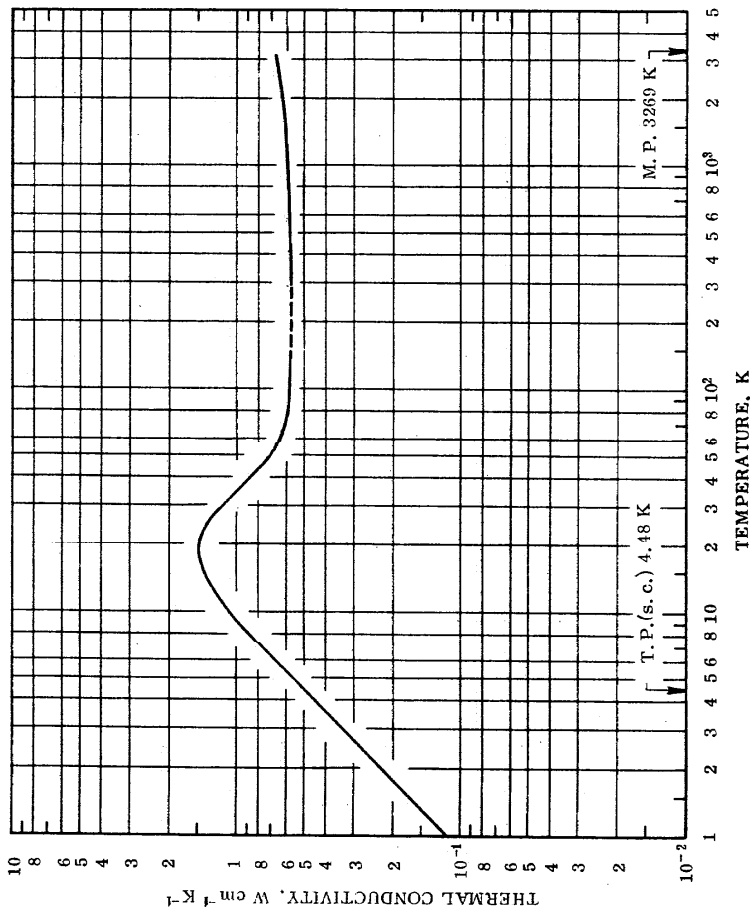

RECOMMENDED VALUES
Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹


T	k	T	k	T	k
0	0	123.2	0.586*	1300	0.614
1	0.115	150	0.580*	1373.2	0.617
2	0.230	173.2	0.578*	1400	0.618
3	0.344	200	0.575*	1473.2	0.622
4	0.458	223.2	0.574*	1500	0.622
5	0.569	250	0.574*	1573.2	0.625
6	0.678	273.2	0.574	1600	0.626
7	0.784	298.2	0.575	1673.2	0.629
8	0.884	300	0.575	1700	0.630
9	0.979	323.2	0.576	1773.2	0.633
10	1.07	350	0.576	1800	0.634
11	1.15	373.2	0.577	1873.2	0.637
12	1.22	400	0.578	1900	0.638
13	1.28	473.2	0.582	1973.2	0.640
14	1.33	500	0.582	2000	0.641
15	1.37	573.2	0.585	2073.2	0.644
16	1.40	600	0.586	2173.2	0.647
18	1.43	673.2	0.588	2200	0.648
20	1.42	700	0.590	2273.2	0.650
25	1.30	773.2	0.593	2400	0.654
30	1.15	800	0.594	2473.2	0.656
35	0.99	873.2	0.597	2600	0.659
40	0.87	900	0.598	2673.2	0.661
45	0.78	973.2	0.602	2800	0.664
50	0.72	1000	0.602	2873.2	0.665
60	0.651	1073.2	0.605	3000	0.666
70	0.616	1100	0.606	3073	0.666
80	0.603	1173.2	0.609	3200	0.666
90	0.596	1200	0.610		
100	0.592	1273.2	0.613		

REMARKS

The recommended values are for well-annealed high-purity tantalum and are considered accurate to within ±5% of the true values at moderate temperatures and ±10% at low and high temperatures. The thermal conductivity at temperatures near and below the corresponding temperature, T_m, of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens, and the recommended values below 100 K are applicable only to tantalum having residual electrical resistivity ρ₀ = 0.214 μΩ cm. Values at temperatures below about 1.5 T_m are calculated to fit experimental data by using equation (7) and using the constants m, n, and α' given for tantalum in Table I and the parameter β = 8.70.

* Interpolated.

THERMAL CONDUCTIVITY OF TECHNETIUM

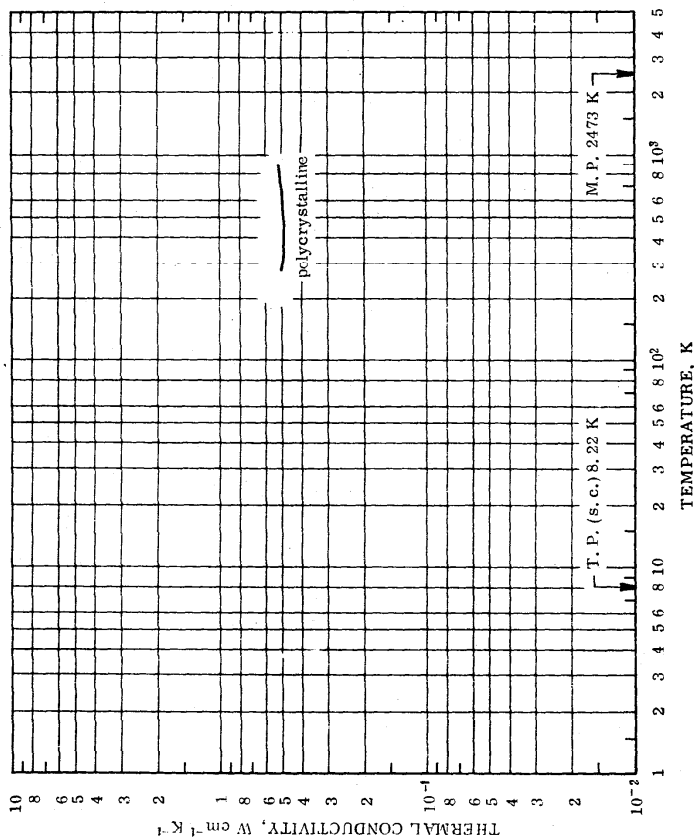

RECOMMENDED VALUES
 [Temperature, T, K; Thermal Conductivity, k, $\text{W cm}^{-1} \text{K}^{-1}$]


SOLID	
Polycrystalline	
T	k
273.2	0.509*
298.2	0.506
300	0.506
323.2	0.504
350	0.502
373.2	0.501
400	0.500
473.2	0.498
500	0.498
573.2	0.499
600	0.499
673.2	0.504
700	0.507
773.2	0.515
800	0.519
873.2	0.530*
900	0.534*

REMARKS

The recommended values are for well-annealed high-purity polycrystalline technetium and are thought to be accurate to within $\pm 1\%$ near room temperature and $\pm 20\%$ at the highest temperatures.

* Extrapolated.

THERMAL CONDUCTIVITY OF TELLURIUM

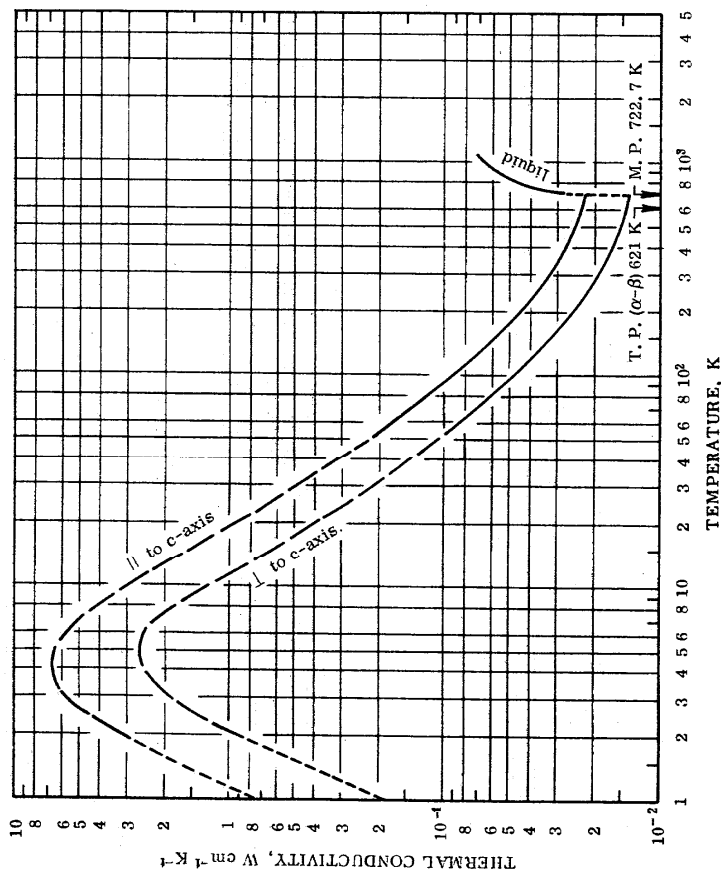

RECOMMENDED VALUES†
[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]

T	SOLID		T	// to c-axis		T	// to c-axis	
	// to c-axis	k		k	k		k	k
0	0	0	60	0.180	0.0870	60	0.180	0.0870
1	0.710*	0.198*	70	0.146	0.0723	70	0.146	0.0723
2	3.14	0.906	80	0.122	0.0618	80	0.122	0.0618
3	5.75	1.87	90	0.104	0.0542	90	0.104	0.0542
4	6.72	2.50	100	0.0912	0.0484	100	0.0912	0.0484
5	6.59	2.67	123.2	0.0716	0.0396	123.2	0.0716	0.0396
6	5.92	2.56	150	0.0585	0.0328	150	0.0585	0.0328
7	5.04	2.28	173.2	0.0513	0.0291	173.2	0.0513	0.0291
8	4.33	1.91	200	0.0455	0.0259	200	0.0455	0.0259
9	3.66	1.57	223.2	0.0417	0.0239	223.2	0.0417	0.0239
10	3.09	1.30	250	0.0383	0.0221	250	0.0383	0.0221
11	2.67	1.10	273.2	0.0360	0.0208	273.2	0.0360	0.0208
12	2.31	0.943	298.2	0.0338	0.0197	298.2	0.0338	0.0197
13	2.01	0.823	300	0.0337	0.0196	300	0.0337	0.0196
14	1.77	0.728	323.2	0.0320	0.0188	323.2	0.0320	0.0188
15	1.57	0.649	350	0.0304	0.0180	350	0.0304	0.0180
16	1.40	0.583	373.2	0.0292	0.0173	373.2	0.0292	0.0173
18	1.14	0.482	400	0.0280	0.0168	400	0.0280	0.0168
20	0.950	0.407	473.2	0.0256	0.0156	473.2	0.0256	0.0156
25	0.660	0.289	500	0.0250	0.0152	500	0.0250	0.0152
30	0.491	0.221	573.2	0.0236	0.0146	573.2	0.0236	0.0146
35	0.391	0.178	600	0.0234	0.0144	600	0.0234	0.0144
40	0.321	0.148	673.2	0.0230	0.0141	673.2	0.0230	0.0141
45	0.271	0.127	700	0.0229	0.0141	700	0.0229	0.0141
50	0.233	0.110	722.7	0.0229	0.0140	722.7	0.0229	0.0140

LIQUID


T	k
722.7	0.0280
773.2	0.0381
800	0.0424
873.2	0.0522
900	0.0554
973.2	0.0630
1000	0.0651
1073.2	0.0686
1100	0.0709*

* Extrapolated.
† Values below 50 K are merely typical values.

REMARKS

The values are for well-annealed high-purity tellurium. Those at temperatures above 50 K are recommended values and are considered accurate to within ±10 to ±15% of the true values for the solid and ±10 to ±20% for the liquid. The values below 50 K are merely typical values and represent two typical curves serving to indicate the general trend of the thermal conductivity of tellurium at low temperatures.

THERMAL CONDUCTIVITY OF TERBIUM

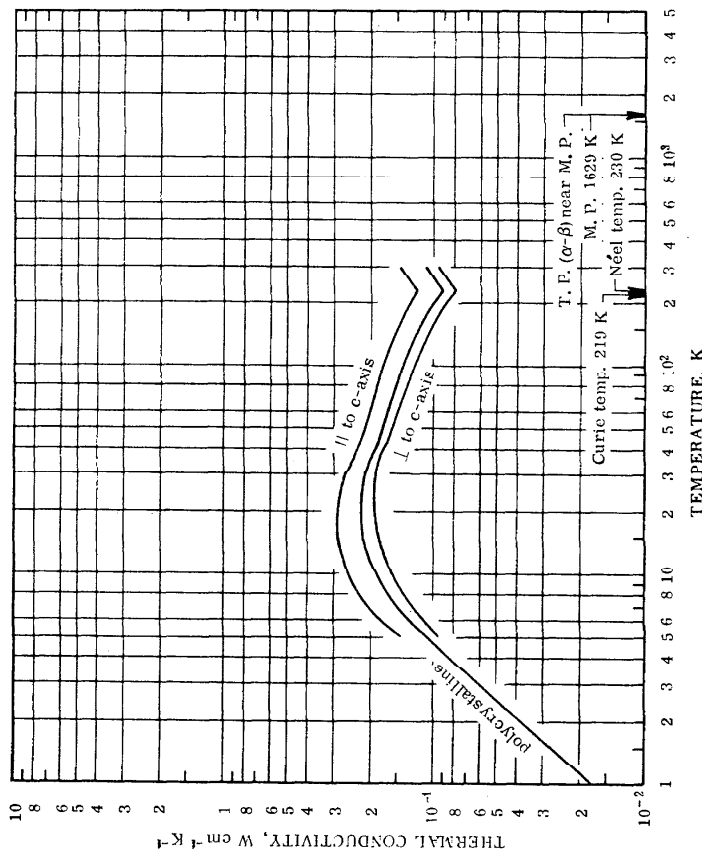

REMARKS


The provisional values are for well-annealed high-purity terbium and are considered accurate to within $\pm 1.5\%$ of the true values near room temperature and $\pm 20\%$ down to 50 K. The values below 50 K are very uncertain. The values below 150 K for $k_{||}$, k_{\perp} , and k poly are applicable only to samples having residual electrical resistivities of 1.87, 2.37, and 2.19 $\mu\Omega$ cm, respectively.

PROVISIONAL VALUES

[Temperature, T, K; Thermal Conductivity, k, $W\ cm^{-1}\ K^{-1}$]

T	POLYCRYSTALLINE		SOLID		T	// to c-axis		⊥ to c-axis		T	// to c-axis		⊥ to c-axis	
	k	k	k	k		k	k	k	k		k	k	k	k
0	0	0	0	0	30	0.262	0.192	0.262	0.192	30	0.262	0.192	0.213	
1	0	0	0.0180	0	35	0.245	0.184	0.245	0.184	35	0.245	0.184	0.202	
2	0	0	0.0383	0	40	0.231	0.174	0.231	0.174	40	0.231	0.174	0.191	
3	0	0	0.0602	0	45	0.221	0.166	0.221	0.166	45	0.221	0.166	0.183	
4	0	0	0.0842	0	50	0.214	0.160	0.214	0.160	50	0.214	0.160	0.176	
5	0.146	0.0939	0.109	0.109	60	0.205	0.151	0.205	0.151	60	0.205	0.151	0.168	
6	0.179	0.112	0.131	0.131	70	0.198	0.144	0.198	0.144	70	0.198	0.144	0.160	
7	0.208	0.127	0.150	0.150	80	0.190	0.138	0.190	0.138	80	0.190	0.138	0.153	
8	0.231	0.140	0.166	0.166	90	0.183	0.132	0.183	0.132	90	0.183	0.132	0.147	
9	0.249	0.151	0.179	0.179	100	0.177	0.127	0.177	0.127	100	0.177	0.127	0.142	
10	0.263	0.160	0.189	0.189	123.2	0.164	0.117	0.164	0.117	123.2	0.164	0.117	0.131	
11	0.273	0.168	0.198	0.198	150	0.152	0.106	0.152	0.106	150	0.152	0.106	0.120	
12	0.281	0.173	0.204	0.204	173.2	0.143	0.0988	0.143	0.0988	173.2	0.143	0.0988	0.112	
13	0.288	0.178	0.209	0.209	200	0.132	0.0902	0.132	0.0902	200	0.132	0.0902	0.103	
14	0.292	0.182	0.213	0.213	223.2	0.124	0.0828	0.124	0.0828	223.2	0.124	0.0828	0.0948	
15	0.295	0.186	0.217	0.217	230	0.122	0.0800	0.122	0.0800	230	0.122	0.0800	0.0922	
16	0.296	0.189	0.220	0.220	250	0.131	0.0846	0.131	0.0846	250	0.131	0.0846	0.0980	
18	0.296	0.193	0.223	0.223	273.2	0.138	0.0900	0.138	0.0900	273.2	0.138	0.0900	0.104	
20	0.294	0.196	0.225	0.225	298.2	0.147	0.0956	0.147	0.0956	298.2	0.147	0.0956	0.111	
25	0.279	0.196	0.221	0.221	300	0.148	0.0959	0.148	0.0959	300	0.148	0.0959	0.111	

THERMAL CONDUCTIVITY OF THALLIUM

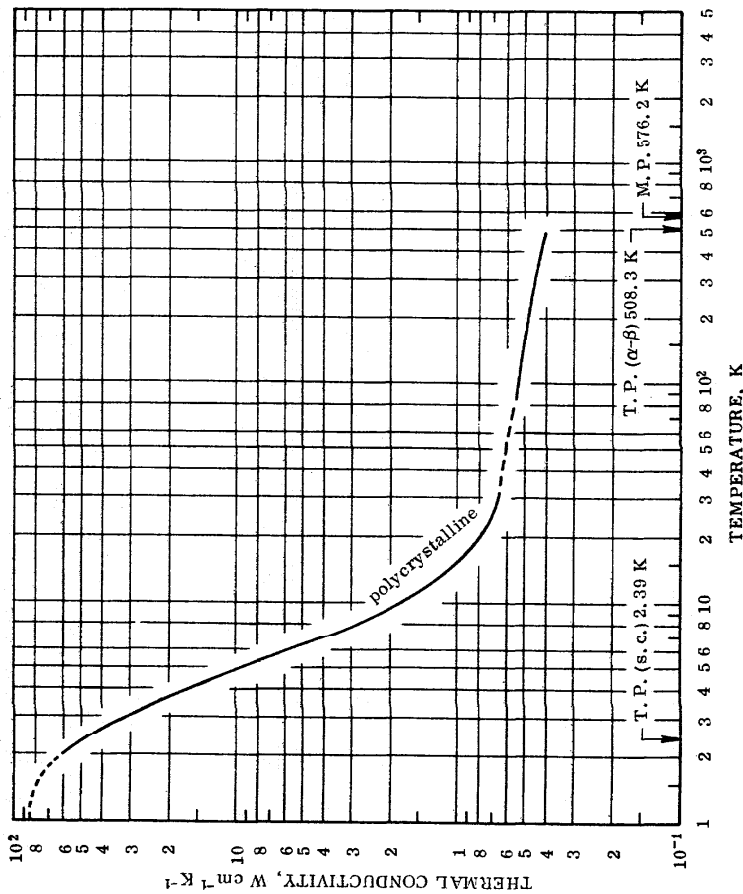

RECOMMENDED VALUES †
[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]

SOLID		Polycrystalline	
T	k	T	k
0	0	60	0.607*
1	82.7*	70	0.590*
2	63.4*	80	0.578
3	33.2	90	0.567
4	17.6	100	0.556
5	10.2	123.2	0.538
6	6.19	150	0.519
7	4.04	173.2	0.506
8	2.95	200	0.494
9	2.30	223.2	0.485
10	1.87	250	0.476
11	1.60	273.2	0.469
12	1.40	298.2	0.461
13	1.27	300	0.461
14	1.16	323.2	0.455
15	1.07	373.2	0.443
16	1.00	400	0.438
18	0.889	473.2	0.425
20	0.811	500	0.421*
25	0.718		
30	0.682		
35	0.663*		
40	0.650*		
45	0.637*		
50	0.626*		


REMARKS

The values are for well-annealed high-purity polycrystalline thallium. Those at temperatures above 30 K are recommended values and are considered accurate to within ±15% of the true values from 30 to 100 K and ±10% above 100 K. The values below 30 K are provisional and furthermore they are applicable only to a sample having residual resistivity $\rho_0 = 0.000240 \mu\Omega\text{cm}$. These provisional values are probably good to within ±20%. Values at temperatures below about 1.5 m are calculated by using equation (7) and using the constants m, n, and α' given for thallium in Table I and the parameter $\beta = 0.00982$.

* Extrapolated or interpolated.

† Values below 30 K are provisional.

THERMAL CONDUCTIVITY OF THORIUM

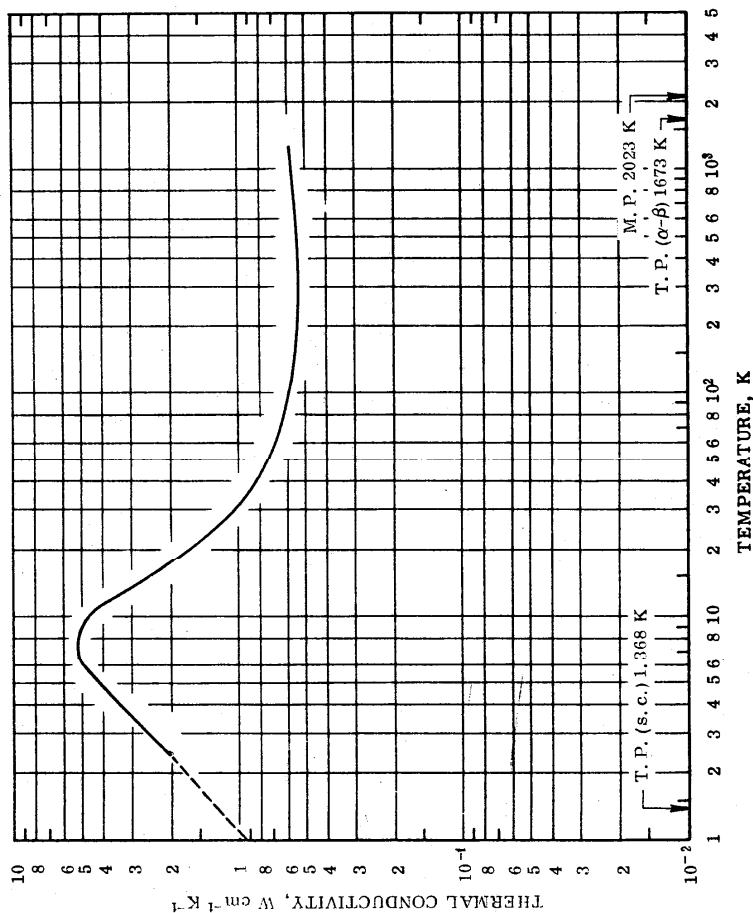

PROVISIONAL VALUES
[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]


T	k	T	k
0	0	123.2	0.578
1	0.938*	150	0.563
2	1.87	173.2	0.554
3	2.78	200	0.546
4	3.64	223.2	0.543
5	4.37	250	0.541
6	4.91	273.2	0.540
7	5.20	298.2	0.540
8	5.23	300	0.540
9	5.02	323.2	0.541
10	4.66	350	0.542
11	4.20	373.2	0.543
12	3.72	400	0.545
13	3.30	473.2	0.549
14	2.96	500	0.551
15	2.66	573.2	0.556
16	2.41	600	0.558
18	2.01	673.2	0.563
20	1.70	700	0.564
25	1.26	773.2	0.568
30	1.04	800	0.569
35	0.917	873.2	0.572
40	0.841	900	0.573
45	0.788	973.2	0.577
50	0.747	1000	0.578
60	0.690	1073.2	0.581
70	0.655	1100	0.583
80	0.630	1173.2	0.586
90	0.612	1200	0.587
100	0.598	1273.2	0.589
		1300	0.590

* Extrapolated.

REMARKS

The provisional values are for well-annealed high-purity thorium and their uncertainty is probably of the order of ±15% below 100K, ±20% from 100 to 500K, and ±25% above 500K. The thermal conductivity at temperatures near and below the corresponding temperature, T_m, of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens, and the values below 150K are applicable only to thorium having residual electrical resistivity ρ₀ = 0.0268 μΩ cm. Values at temperatures below about 1.5 T_m are calculated to fit experimental data by using equation (7) and using the constants m, n, and α' given for thorium in Table I and the parameter β = 1.07.

THERMAL CONDUCTIVITY OF THULIUM

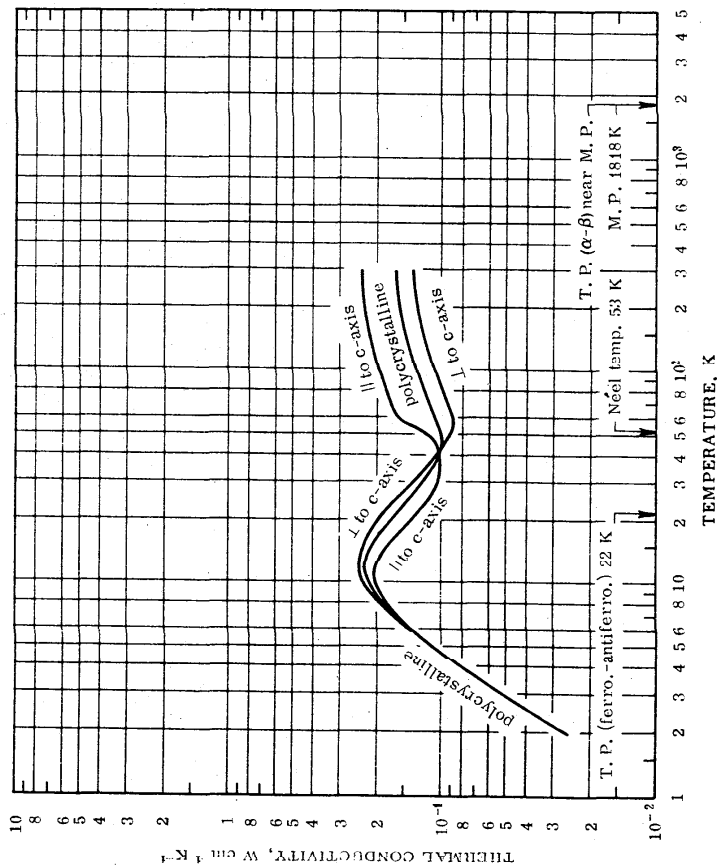

PROVISIONAL VALUES
[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]


T	# to c-axis		POLY- crystalline		T	# to c-axis		# to Poly- crystalline	
	k	κ	k	κ		k	κ	k	κ
2	0.139	0.142	0.0269*	0.105	40	0.105	0.110	0.108	0.108
3	0.162	0.170	0.0517	0.106	42.4	0.106	0.106	0.106	0.106
4	0.180	0.197	0.0815	0.109	45	0.109	0.102	0.104	0.104
5	0.196	0.221	0.113	0.119	50	0.119	0.0948	0.102	0.102
6	0.207	0.236	0.141	0.141	55	0.141	0.0912	0.106	0.106
7	0.210	0.244	0.167	0.160	58	0.160	0.0911	0.110	0.110
8	0.207	0.246	0.191	0.164	60	0.164	0.0920	0.112	0.112
9	0.193	0.243	0.212	0.175	70	0.175	0.0997	0.120	0.120
10	0.183	0.238	0.226	0.185	80	0.185	0.105	0.127	0.127
11	0.173	0.232	0.246	0.193	90	0.193	0.108	0.131	0.131
12	0.207	0.246	0.230	0.200	100	0.200	0.111	0.135	0.135
13	0.202	0.245	0.230	0.214	123.2	0.214	0.117	0.144	0.144
14	0.193	0.243	0.225	0.224	150	0.224	0.126	0.153	0.153
15	0.183	0.238	0.218	0.230	173.2	0.230	0.130	0.158	0.158
16	0.173	0.232	0.211	0.235	200	0.235	0.134	0.162	0.162
18	0.158	0.218	0.196	0.238	223.2	0.238	0.136	0.164	0.164
20	0.144	0.202	0.180	0.241	250	0.241	0.138	0.167	0.167
25	0.120	0.167	0.150	0.242	273.2	0.242	0.140	0.168	0.168
30	0.106	0.141	0.128	0.242	298.2	0.242	0.141	0.169	0.169
35	0.105	0.123	0.117	0.242	300	0.242	0.141	0.169	0.169

REMARKS

The provisional values are for well-annealed high-purity thulium and are considered accurate to within ±1% of the true values at temperatures above 150K. The values below 150K are very uncertain. Values below 100K for k_{\parallel} , k_{\perp} , and k_{poly} are applicable only to samples having residual electrical resistivities of 3, 5, 1, 7, and 18 $\mu\Omega$ cm respectively.

* Extrapolated.

THERMAL CONDUCTIVITY OF TIN

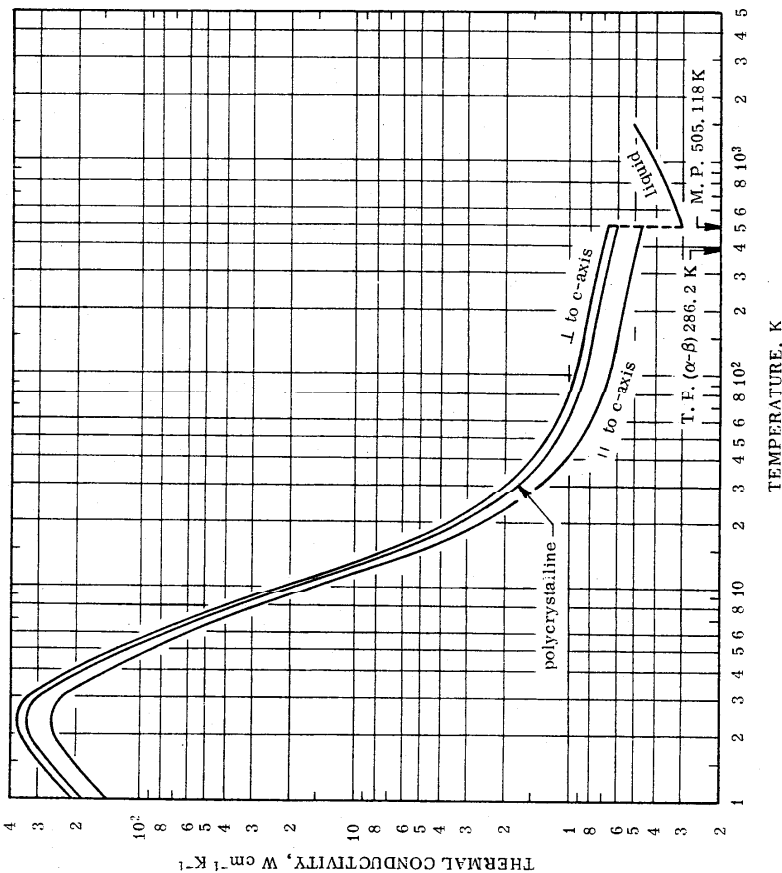

REMARKS

The recommended values are for well-annealed high-purity tin. The values for polycrystalline tin are thought to be accurate to within $\pm 3\%$ of the true values at moderate temperatures, $\pm 5\%$ at high temperatures, and $\pm 15\%$ at low temperatures. Those for $k_{//}$ and k_{\perp} of tin single crystal should be accurate to within $\pm 6\%$ at moderate temperatures, $\pm 10\%$ at high temperatures, and $\pm 15\%$ at low temperatures. For molten tin the values are probably good to $\pm 5\%$ near the melting point, but an increasing uncertainty remains to be resolved at higher temperatures. At temperatures below 100 K the values for $k_{//}$, k_{\perp} , and k_{poly} are applicable only to samples having $\rho_0 = 0.000170$, 0.000116 , and 0.0003213 cm, respectively. Values for $k_{//}$ and k_{\perp} at temperatures below about $1.5 T_m$ are calculated by using equation (7) and using $n = 2.6$, $\sigma' = 0.0030861$ and 0.0000588 , and $\beta = 0.00696$ and 0.00484 , respectively.


RECOMMENDED VALUES †

[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]

T	// to c-axis		⊥ to c-axis		Poly-crystalline		T	// to c-axis		⊥ to c-axis		T	Poly-crystalline	
	k	k	k	k	k	k		k	k	k	k			
0	0	0	0	0	0	0	60	0.797	1.16	1.04	1.04	60	0.797	1.16
1	142	204	204	204	183	183	70	0.740	1.07	0.960	0.960	70	0.740	1.07
2	250	360	360	360	323	323	80	0.705	1.02	0.915	0.915	80	0.705	1.02
3	230	331	331	331	297	297	90	0.679	0.980	0.880	0.880	90	0.679	0.980
4	140	202	202	202	181	181	100	0.660	0.950	0.853	0.853	100	0.660	0.950
5	90	130	130	130	117	117	123.2	0.630	0.906	0.814	0.814	123.2	0.630	0.906
6	59	85.0	85.0	85.0	76	76	150	0.602	0.867	0.779	0.779	150	0.602	0.867
7	40	58.0	58.0	58.0	52	52	173.2	0.585	0.842	0.757	0.757	173.2	0.585	0.842
8	28	40.0	40.0	40.0	36	36	200	0.567	0.816	0.733	0.733	200	0.567	0.816
9	20.1	29.0	29.0	29.0	26	26	223.2	0.553	0.796	0.715	0.715	223.2	0.553	0.796
10	14.9	21.5	21.5	21.5	19.3	19.3	250	0.538	0.775	0.696	0.696	250	0.538	0.775
11	11.4	16.5	16.5	16.5	14.8	14.8	273.2	0.527	0.759	0.682	0.682	273.2	0.527	0.759
12	9.0	12.9	12.9	12.9	11.6	11.6	298.2	0.516	0.743	0.668	0.668	298.2	0.516	0.743
13	7.2	10.4	10.4	10.4	9.3	9.3	300	0.515	0.742	0.666	0.666	300	0.515	0.742
14	5.9	8.5	8.5	8.5	7.6	7.6	323.2	0.506	0.729	0.655	0.655	323.2	0.506	0.729
15	4.9	7.0	7.0	7.0	6.3	6.3	350	0.496	0.715	0.642	0.642	350	0.496	0.715
16	4.1	5.9	5.9	5.9	5.3	5.3	373.2	0.489	0.704	0.632	0.632	373.2	0.489	0.704
18	3.1	4.5	4.5	4.5	4.0	4.0	400	0.481	0.693	0.622	0.622	400	0.481	0.693
20	2.5	3.6	3.6	3.6	3.2	3.2	473.2	0.466	0.670	0.602	0.602	473.2	0.466	0.670
25	1.72	2.5	2.5	2.5	2.24	2.24	500	0.461	0.664	0.596	0.596	500	0.461	0.664
30	1.36	2.0	2.0	2.0	1.79	1.79	505.118	0.460	0.662	0.595	0.595	505.118	0.460	0.662
35	1.16	1.67	1.67	1.67	1.50	1.50	505.118	0.303	1.000	0.405	0.405	505.118	0.303	1.000
40	1.04	1.50	1.50	1.50	1.33	1.33	573.2	0.317	1.073.2	0.420	0.420	573.2	0.317	1.073.2
45	0.950	1.37	1.37	1.37	1.23	1.23	600	0.323	1.100	0.425	0.425	600	0.323	1.100
50	0.886	1.28	1.28	1.28	1.15	1.15	673.2	0.338	1.173.2	0.440	0.440	673.2	0.338	1.173.2
							700	0.344	1.200	0.446	0.446	700	0.344	1.200
							773.2	0.358	1.273.2	0.460	0.460	773.2	0.358	1.273.2
							800	0.364	1.300	0.466	0.466	800	0.364	1.300
							873.2	0.378	1.373.2	0.481	0.481	873.2	0.378	1.373.2
							900	0.384	1.400	0.487	0.487	900	0.384	1.400
							973.2	0.399	1.473.2	0.501	0.501	973.2	0.399	1.473.2
							1500			0.507	0.507	1500		

† Values above 373 K are provisional.

THERMAL CONDUCTIVITY OF TITANIUM

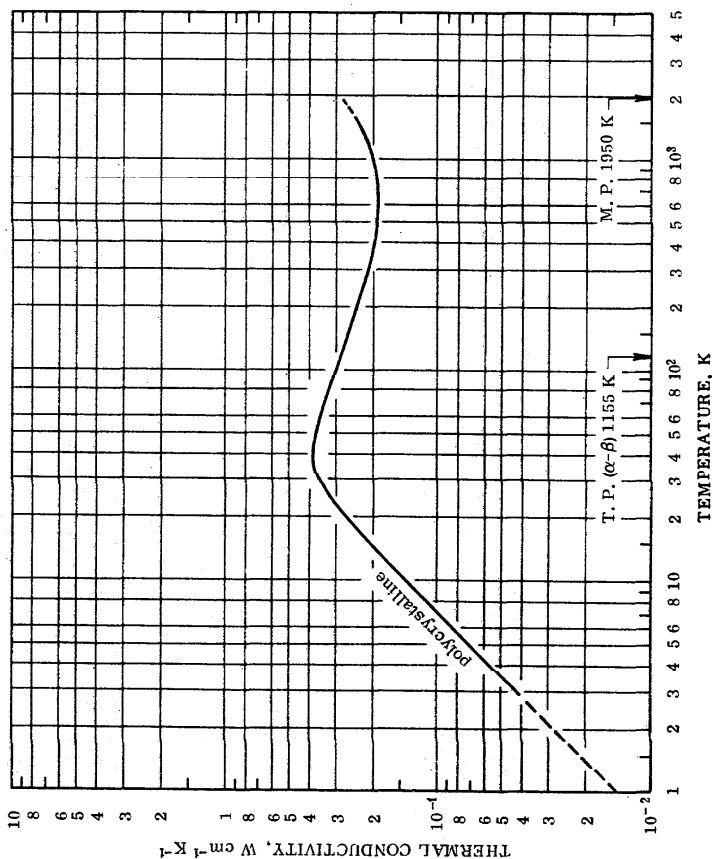

REMARKS

The recommended values are for well-annealed high-purity polycrystalline titanium and are considered accurate to within $\pm 10\%$ of the true values at moderate temperatures and $\pm 15\%$ at low and high temperatures. The thermal conductivity at temperatures near and below the corresponding temperature, T_m , of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens, and the recommended values below room temperature are applicable only to titanium having residual electrical resistivity $\rho_0 = 1.90 \mu\Omega \text{ cm}$. Values at temperatures below about $1.5 T_m$ are calculated to fit experimental data by using equation (7) and using the constants m , n , and α'' as listed in table 1 and the parameter $\beta = 63.5$.


RECOMMENDED VALUES

[Temperature, T, K; Thermal Conductivity, k, $\text{W cm}^{-1} \text{K}^{-1}$]

SOLID		
Polycrystalline		
T	k	T
0	0	250
1	0.0144*	273.2
2	0.0288*	298.2
3	0.0432	300
4	0.0575	323.2
5	0.0719	350
6	0.0863	373.2
7	0.101	400
8	0.115	473.2
9	0.129	500
10	0.143	573.2
11	0.157	600
12	0.171	673.2
13	0.185	700
14	0.189	773.2
15	0.212	800
16	0.225	873.2
18	0.250	900
20	0.275	973.2
25	0.327	1000
30	0.365	1073.2
35	0.386	1100
40	0.390	1173.2
45	0.385	1200
50	0.374	1273.2
60	0.355	1300
70	0.340	1373.2
80	0.326	1400
90	0.315	1473.2
100	0.305	1500
123.2	0.286	1573.2
150	0.270	1600
173.2	0.257	1673.2
200	0.245	1700
223.2	0.237	1773.2
1800	0.270*	1800
1873.2	0.277*	1873.2
1900	0.279*	1900
1950	0.283*	1950

* Extrapolated.

THERMAL CONDUCTIVITY OF TUNGSTEN

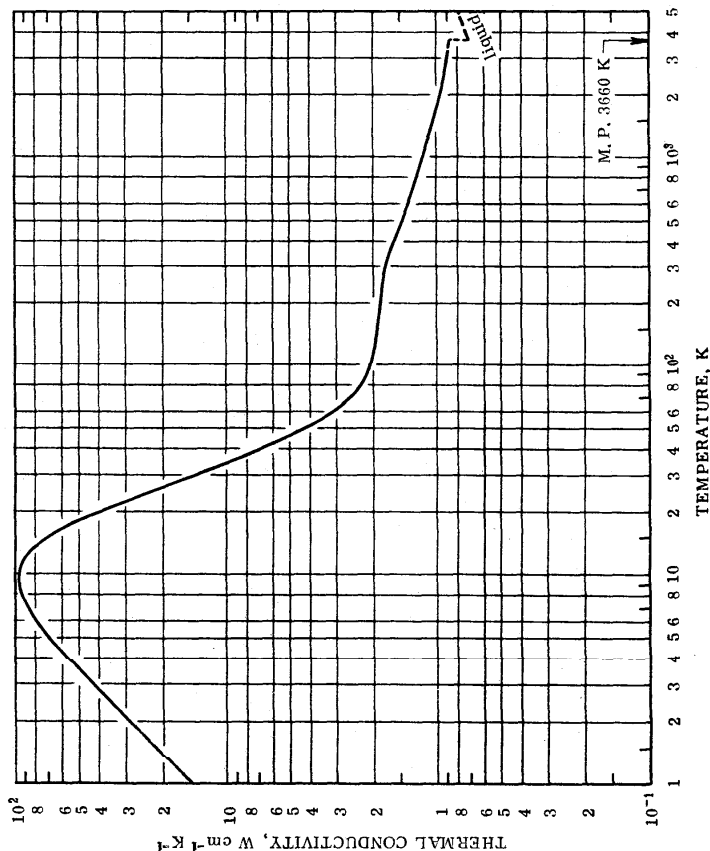

REMARKS

The recommended values are for well-annealed high-purity tungsten and are considered accurate to within $\pm 3\%$ of the true values at temperatures from 300 to 1500 K, $\pm 5\%$ from 100 to 300 K and 1500 to 3000 K, and $\pm 10\%$ below 100 K and above 3000 K. The provisional values for molten tungsten are estimated and very uncertain. The thermal conductivity at temperatures near and below the corresponding temperature, T_m , of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens, and the conductivity values below 200 K are applicable only to tungsten having residual electrical resistivity $\rho_0 = 0.00170 \mu\Omega$ cm. Values at temperatures below about 1.5 T_m are calculated by using equation (7) and using the constants m , n , and α' as listed in Table I and the parameter $\beta = 0.0698$.

RECOMMENDED VALUES
[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]

SOLID

T	k	T	k	T	k
0	0	123.2	1.98	1300	1.10
1	14.4	150	1.92	1373.2	1.08
2	28.7	173.2	1.88	1400	1.08
3	42.8	200	1.85	1473.2	1.06
4	56.3	223.2	1.82	1500	1.06
5	68.7	250	1.80	1573.2	1.04
6	79.5	273.2	1.77	1600	1.04
7	88.0	298.2	1.73	1673.2	1.03
8	93.8	300	1.74	1700	1.02
9	96.8	323.2	1.71	1773.2	1.01
10	97.1	350	1.67	1800	1.01
11	95.0	373.2	1.63	1873.2	0.997
12	91.1	400	1.59	1900	0.994
13	86.0	473.2	1.50	1973.2	0.984
14	79.4	500	1.46	2000	0.980
15	72.0	573.2	1.39	2073.2	0.971
16	64.5	600	1.37	2173.2	0.960
18	51.2	673.2	1.32	2200	0.957
20	40.5	700	1.30	2273.2	0.950
25	23.2	773.2	1.27	2400	0.937
30	14.4	800	1.25	2473.2	0.931
35	9.61	873.2	1.22	2600	0.920
40	6.92	900	1.21	2673.2	0.914
45	5.27	973.2	1.19	2800	0.906
50	4.27	1000	1.18	2873.2	0.902
60	3.14	1073.2	1.16	3000	0.895
70	2.58	1100	1.15	3073	0.892
80	2.29	1173.2	1.13	3200	0.887
90	2.17	1200	1.12	3273	0.885
100	2.08	1273.2	1.11	3400	0.882
				3600	0.878*
				3660	0.877*

* Extrapolated.


THERMAL CONDUCTIVITY OF TUNGSTEN (continued)

PROVISIONAL VALUES

LIQUID			
T	k	T	k
3660	0.705*	11000	0.732*
3673	0.704*	11273	0.721*
3800	0.723*	12000	0.693*
3873	0.721*	12273	0.681*
4000	0.730*	13000	0.646*
4073	0.735*	13273	0.632*
4273	0.748*	14000	0.594*
4300	0.761*	14273	0.579*
4773	0.780*	15000	0.538*
5000	0.785*	15273	0.521*
5273	0.795*	16000	0.478*
5500	0.801*	16273	0.461*
5773	0.809*	17000	0.416*
6000	0.811*	17273	0.398*
6273	0.817*	18000	0.352*
6773	0.818*	18273	0.334*
7000	0.819*	19000	0.286*
7273	0.819*	19273	0.267*
7500	0.819*	20000	0.217*
7773	0.818*	20273	0.198*
8000	0.816*	21000	0.146*
8273	0.813*	21273	0.127*
8500	0.810*	22000	0.0736*
8773	0.805*	22273	0.054*
9000	0.799*		
9273	0.791*		
9500	0.784*		
9773	0.776*		
10000	0.768*		
10273	0.758*		

* Estimated.

THERMAL CONDUCTIVITY OF URANIUM

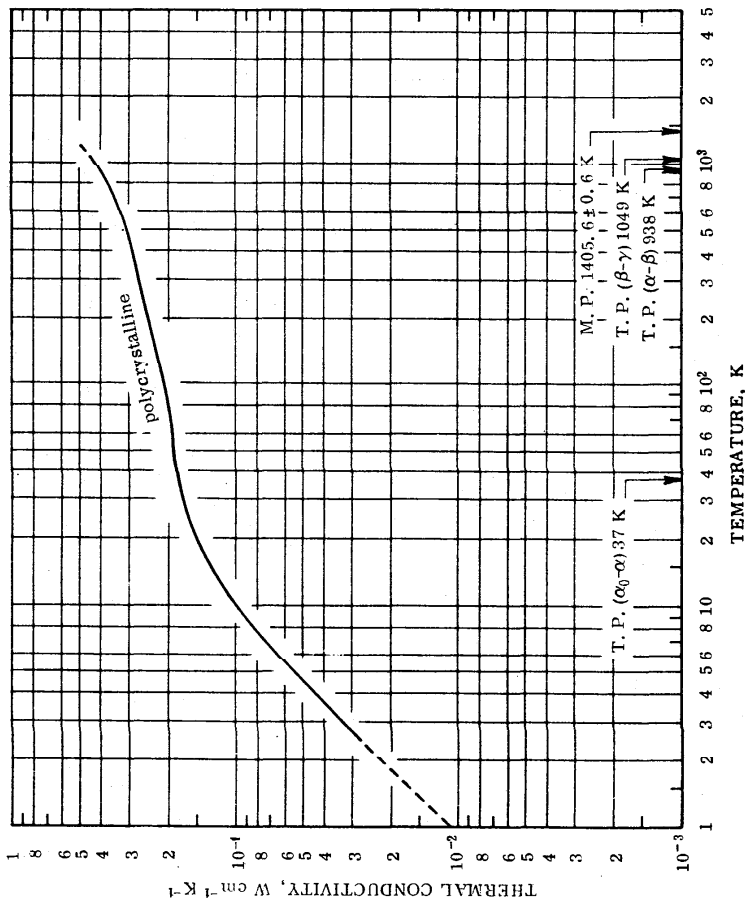

REMARKS

The recommended values are for well-annealed high-purity polycrystalline uranium and are considered accurate to within $\pm 10\%$ of the true values at temperatures from 300 to 900 K and ± 15 to $\pm 20\%$ at other temperatures. The values below room temperature are applicable only to uranium having residual electrical resistivity $\rho_0 = 2.14 \mu\Omega$ cm.

RECOMMENDED VALUES


[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]

SOLID

Polycrystalline	
T	k
0	0
1	0.0114*
2	0.0228*
3	0.0338
4	0.0442
5	0.0541
6	0.0638
7	0.0731
8	0.0818
9	0.0898
10	0.0980
11	0.106
12	0.113
13	0.120
14	0.126
15	0.132
16	0.138
18	0.149
20	0.158
25	0.167
30	0.173
35	0.178
40	0.182
45	0.186
50	0.189
60	0.196
70	0.202
80	0.208
90	0.212
100	0.217
123.2	0.226
150	0.236
173.2	0.243
200	0.251
223.2	0.257
250	0.264
273.2	0.270
298.2	0.275
300	0.276
323.2	0.281
350	0.286
373.2	0.291
400	0.296
473.2	0.311
500	0.317
573.2	0.334
600	0.340
673.2	0.357
700	0.364
773.2	0.381
800	0.388
873.2	0.405
900	0.413
973.2	0.431
1000	0.439
1073.2	0.456
1100	0.463
1173.2	0.483
1200	0.490*

* Extrapolated.

THERMAL CONDUCTIVITY OF VANADIUM

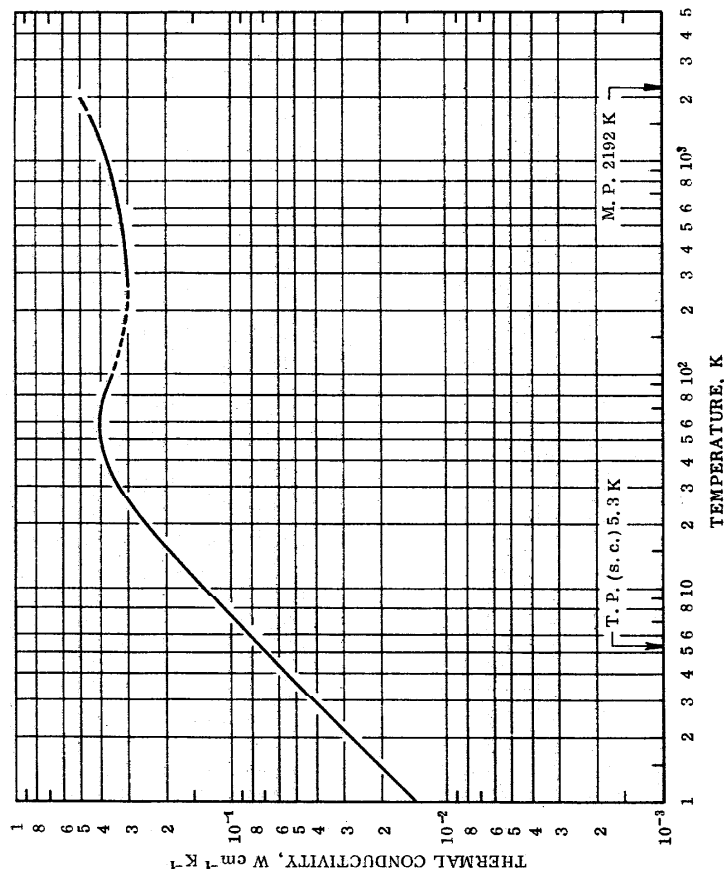

REMARKS

The recommended values are for well-annealed high-purity vanadium and are considered accurate to within ±10% of the true values at room temperature and above and ±15% below 30 K. Values between 30 K and room temperature are conjectured and very uncertain. The values below 200 K are applicable only to vanadium having residual electrical resistivity $\rho_0 = 1.72 \mu\Omega \text{ cm}$.

RECOMMENDED VALUES


[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]

SOLID

T	k	T	k
0	0	350	0.309
1	0.0142	373.2	0.310
2	0.0282	400	0.313
3	0.0422	473.2	0.319
4	0.0561	500	0.322
5	0.0697	573.2	0.330
6	0.0835	600	0.333
7	0.0971	673.2	0.342
8	0.111	700	0.345
9	0.125	773.2	0.354
10	0.138	800	0.357
11	0.151		0.366
12	0.165	900	0.369
13	0.177	973.2	0.379
14	0.190	1000	0.382
15	0.202	1073.2	0.392
16	0.214	1100	0.395
18	0.237	1173.2	0.405
20	0.258	1200	0.408
25	0.305	1273.2	0.417
30	0.342	1300	0.421
35	0.369	1373.2	0.430
40	0.389	1400	0.434
45	0.401	1473.2	0.443
50	0.405	1500	0.446
60	0.406	1573.2	0.455
70	0.402	1600	0.459
80	0.390	1673.2	0.468
90	0.373	1700	0.472
100	0.358*	1773.2	0.481
123.2	0.336*	1800	0.484
150	0.324*	1873.2	0.494
173.2	0.318*	1900	0.497*
200	0.313*	1973.2	0.506*
223.2	0.310*	2000	0.509*
250	0.308*		
273.2	0.307*		
298.2	0.307		
300	0.307		
323.2	0.308		

* Extrapolated or interpolated.

THERMAL CONDUCTIVITY OF XENON

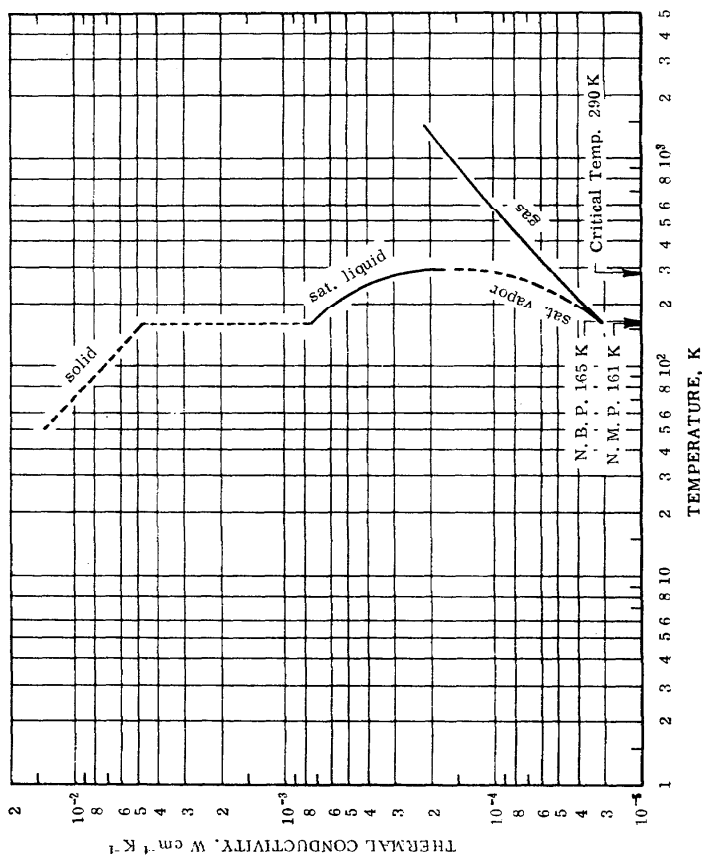

REMARKS

Difficulties in sample characterization limit the accuracy of the recommended values to possibly within 20% for the solid material. The liquid values should be reliable to within 5% except possibly in the immediate vicinity of the critical point. The vapor values are felt to have a similar accuracy below 250 K. The gas values should be accurate to a few percent below 500 K, the uncertainty then increasing to at least 5% at 1000 K and 10% at 1500 K.

SOLID			RECOMMENDED VALUES [Temperature, T, K; Thermal Conductivity, k , $W\ cm^{-1}\ K^{-1}$]			SATURATED LIQUID			SATURATED VAPOR		
T	$k \times 10^3$		T	$k \times 10^3$		T	$k \times 10^3$		T	$k \times 10^3$	
50	14.4*		161	0.74		165	0.032*		165	0.032*	
60	12.0*		170	0.70		170	0.034*		170	0.034*	
70	10.5*		180	0.66		180	0.037*		180	0.037*	
80	9.2*		190	0.62		190	0.041*		190	0.041*	
90	8.2*		200	0.58		200	0.044*		200	0.044*	
100	7.5*		210	0.54		210	0.048*		210	0.048*	
110	6.8*		220	0.50		220	0.051*		220	0.051*	
120	6.3*		230	0.46		230	0.055*		230	0.055*	
130	5.8*		240	0.42		240	0.060*		240	0.060*	
140	5.4*		250	0.38		250	0.066*		250	0.066*	
150	5.1*		260	0.34		260	0.073*		260	0.073*	
160	4.8*		270	0.31		270	0.084*		270	0.084*	
161	4.8*		280	0.27		280	0.098*		280	0.098*	
			290	0.16**†		290	0.16**†		290	0.16**†	

* Estimated or extrapolated, hence provisional.

† Pseudo-critical value.


THERMAL CONDUCTIVITY OF XENON (continued)

RECOMMENDED VALUES

GAS
(At 1 atm)

T	k x 10 ³	T	k x 10 ³	T	k x 10 ³
165	0.0325	500	0.0905	850	0.142
170	0.0334	510	0.0920	860	0.143
180	0.0352	520	0.0935	870	0.145
190	0.0370	530	0.0950	880	0.146
200	0.0388	540	0.0965	890	0.147
210	0.0406	550	0.0980	900	0.149
220	0.0424	560	0.0995	910	0.150
230	0.0442	570	0.1010	920	0.151
240	0.0460	580	0.1025	930	0.152
250	0.0478	590	0.1040	940	0.154
260	0.0496	600	0.1055	950	0.155
270	0.0514	610	0.1070	960	0.156
280	0.0532	620	0.1085	970	0.157
290	0.0550	630	0.1100	980	0.159
300	0.0569	640	0.1115	990	0.160
310	0.0587	650	0.1130	1000	0.161
320	0.0605	660	0.1145	1050	0.167
330	0.0623	670	0.1160	1100	0.173
340	0.0641	680	0.1175	1150	0.179
350	0.0659	690	0.1190	1200	0.185
360	0.0677	700	0.1205	1250	0.190
370	0.0695	710	0.1220	1300	0.196
380	0.0713	720	0.1234	1350	0.202
390	0.0731	730	0.1249	1400	0.208
400	0.0745	740	0.1263	1450	0.213
410	0.0761	750	0.1278	1500	0.219
420	0.0777	760	0.129		
430	0.0793	770	0.131		
440	0.0809	780	0.132		
450	0.0825	790	0.134		
460	0.0841	800	0.135		
470	0.0857	810	0.136		
480	0.0873	820	0.138		
490	0.0889	830	0.139		
		840	0.140		

THERMAL CONDUCTIVITY OF YTTERBIUM

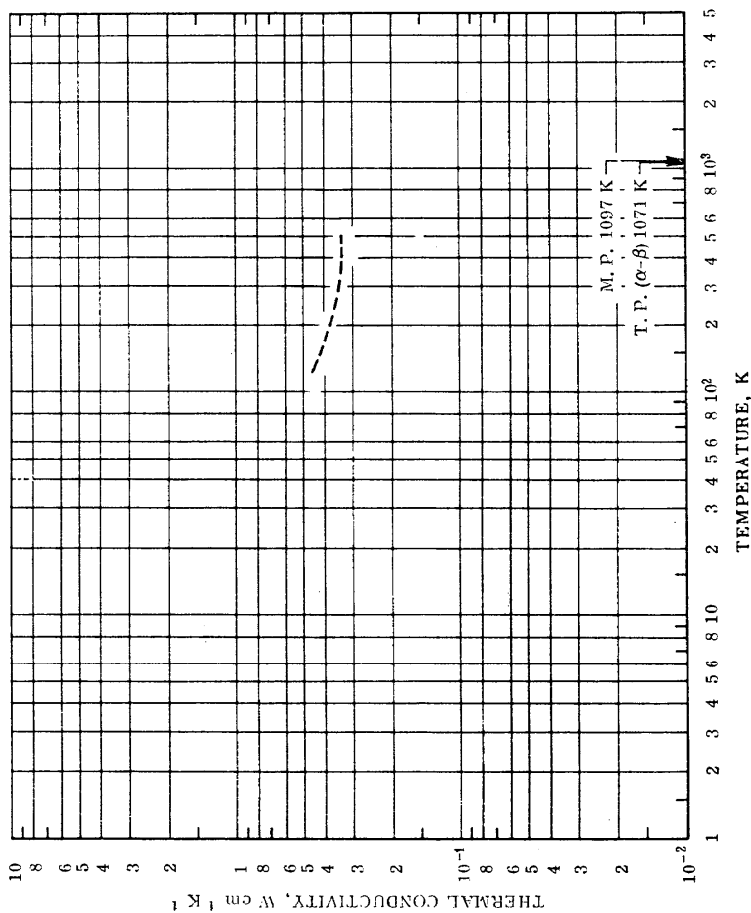

PROVISIONAL VALUES

[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]

SOLID


T, K	k
123.2	0.456*
150	0.423*
173.2	0.402*
200	0.384*
223.2	0.372*
250	0.361*
273.2	0.354*
298.2	0.349*
300	0.349*
323.2	0.347*
350	0.345*
373.2	0.343*
400	0.341*
473.2	0.338*
500	0.337*

REMARKS

The provisional values are for high-purity ytterbium and are probably good to $\pm 20\%$ near room temperature and $\pm 30\%$ at extreme temperatures.

* Estimated

THERMAL CONDUCTIVITY OF YTTRIUM

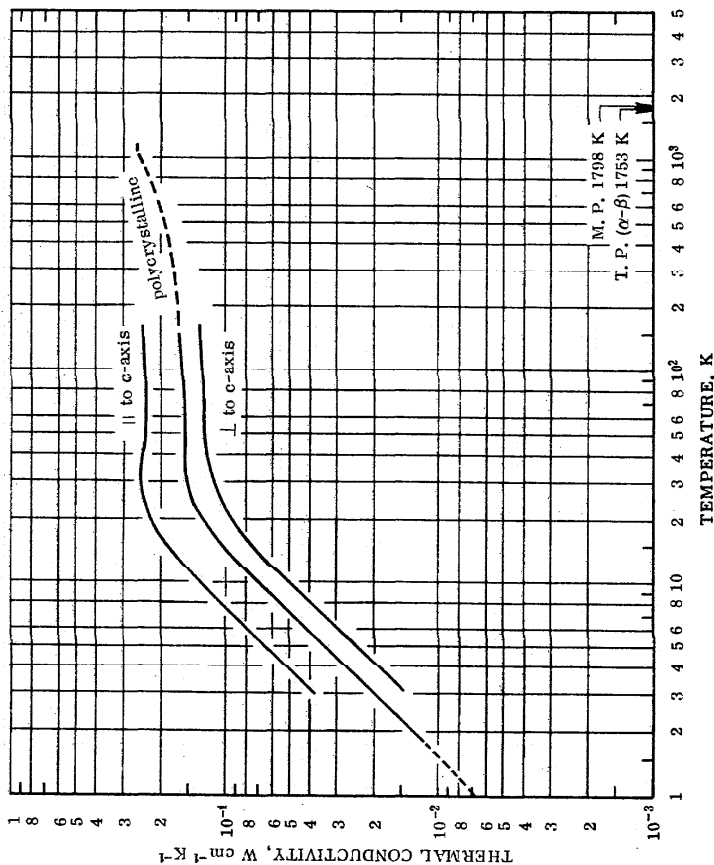

REMARKS

The provisional values are for well-annealed high-purity yttrium and are probably good to $\pm 10\%$ near room temperature and ± 15 to $\pm 20\%$ at other temperatures. The values below 100 K for $k_{||}$, k_{\perp} , and k_{poly} are applicable only to yttrium having residual electrical resistivity $\rho_{300} = 2.30, 8.70,$ and $5.54 \mu\Omega$ cm, respectively.

PROVISIONAL VALUES


[Temperature, T, K; Thermal Conductivity, k, W cm⁻¹ K⁻¹]

SOLID

T	// to c-axis		Polycrystalline	
	k	T	k	T
3	0.0389	0.0138	0	123.2
4	0.0526	0.0189	0	150
5	0.0662	0.0240	0.00648*	173.2
6	0.0795	0.0292	0.0133	200
7	0.0927	0.0343	0.0166*	223.2
8	0.106	0.0395	0.0271	250
8	0.119	0.0445	0.0343	273.2
9	0.132	0.0497	0.0415	298.2
10	0.144	0.0545	0.0486	300
11	0.156	0.0594	0.0558	300
12	0.167	0.0646	0.0628	323.2
13	0.178	0.0695	0.0699	350
14	0.188	0.0742	0.0765	373.2
15	0.198	0.0787	0.0832	400
16	0.214	0.0870	0.0900	473.2
18	0.228	0.0943	0.0964	500
20	0.245	0.107	0.102	573.2
25	0.248	0.115	0.106	600
30	0.244	0.118	0.119	673.2
35	0.238	0.121	0.128	700
40	0.236	0.122	0.142	773.2
45	0.236	0.124	0.150	800
50	0.236	0.125	0.151	873.2
60	0.237	0.126	0.152	900
70	0.238	0.127	0.153	973.2
80	0.240	0.128	0.154	1000
90	0.241	0.128	0.155	1073.2
100	0.245	0.130	0.156	1100
123.2	0.247	0.133	0.157	1173.2
150	0.248	0.133	0.158	
160			0.159	

* Extrapolated or estimated.

THERMAL CONDUCTIVITY OF ZINC

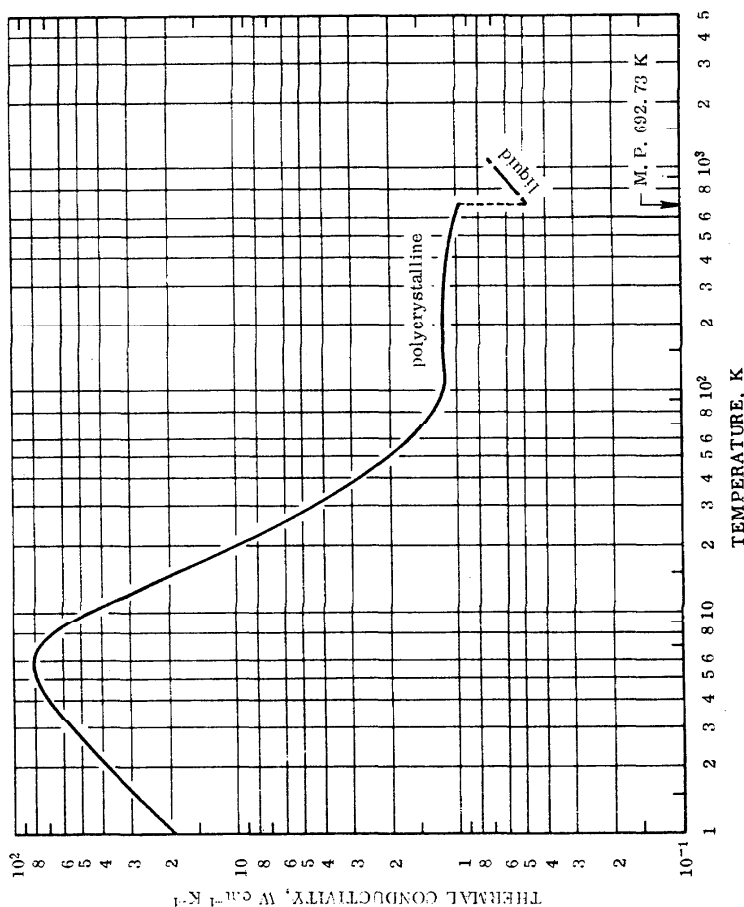

RECOMMENDED VALUES †
[Temperature, T, K; Thermal Conductivity, k, $\text{W cm}^{-1} \text{K}^{-1}$]


POLYCRYSTALLINE		LIQUID	
T	k	T	k
0	0	692.73	0.495*
1	19.0	700	0.499*
2	37.9	773.2	0.542
3	55.8	800	0.557
4	70.9	873.2	0.599
5	80.7	900	0.615
6	83.1	973.2	0.657
7	78.7	1000	0.673
8	69.7	1073.2	0.715*
9	58.0	1100	0.730*
10	47.3		
11	38.8		
12	31.9		
13	26.5		
14	22.4		
15	19.2		
16	16.6		
18	12.7		
20	9.98		
25	6.26		
30	4.42		
35	3.42		
40	2.80		
45	2.36		
50	2.05		

REMARKS

The recommended values are for well-annealed high-purity polycrystalline zinc and are considered accurate to within $\pm 3\%$ of the true values at moderate temperatures, $\pm 5\%$ at high temperatures, $\pm 10\%$ from 20 to 100 K, and $\pm 15\%$ below 20 K. The thermal conductivity at temperatures near and below the corresponding temperature, T_m , of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens, and the recommended values below 150 K are applicable only to zinc having residual electrical resistivity $\rho_0 = 0.00128 \mu\Omega \text{ cm}$. Values at temperatures below about 1.5 T are calculated by using equation (7) and the constants m, n, and α'' as listed in Table 1 and the parameter $\beta = 0.0525$. Values for molten zinc are provisional and they are probably good to $\pm 15\%$.

* Extrapolated.
† Values for molten zinc are provisional.

THERMAL CONDUCTIVITY OF ZIRCONIUM

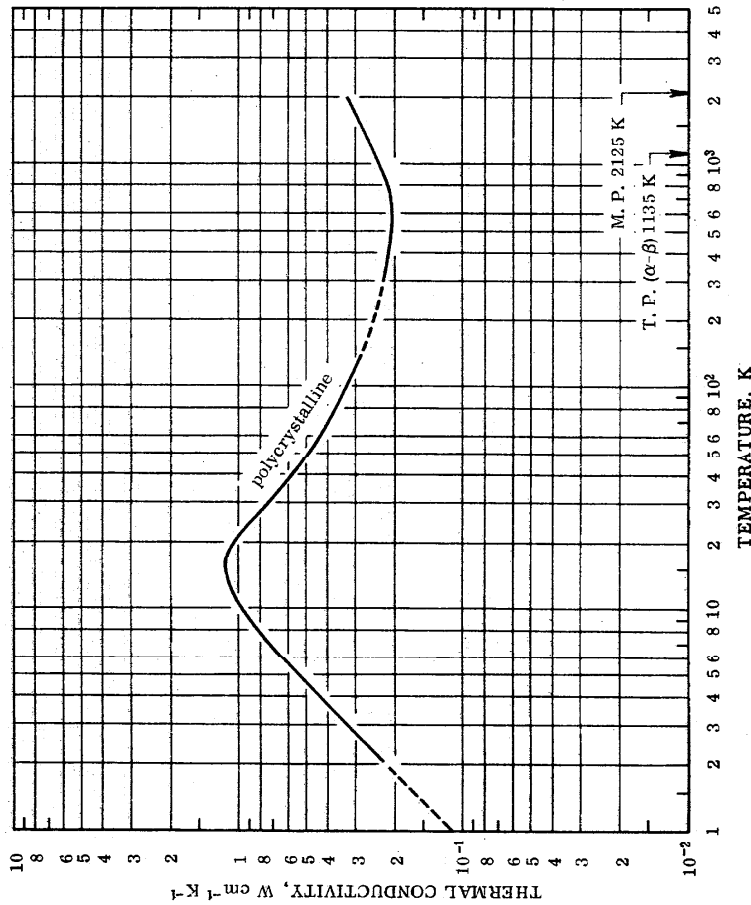

REMARKS

The recommended values are for well-annealed high-purity polycrystalline zirconium and are considered accurate to within $\pm 10\%$ of the true values at temperatures below 800 K , the uncertainty increasing to ± 20 to $\pm 25\%$ as the melting point is approached. The thermal conductivity at temperatures near and below the corresponding temperature, T_m , of the conductivity maximum is highly sensitive to small physical and chemical variations among different specimens, and the recommended values below room temperature are applicable only to zirconium having residual electrical resistivity $\rho_0 = 0.218 \mu\Omega \text{ cm}$. Values at temperatures below about $1.5 T_m$ are calculated to fit experimental data by using equation (7) and using the constants m , n , and α'' as listed in Table I and the parameter $\beta = 8.93$.

RECOMMENDED VALUES

[Temperature, T, K; Thermal Conductivity, k, $\text{W cm}^{-1} \text{K}^{-1}$]

SOLID

Polycrystalline

T	k	T	k
0	0	373.2	0.218
1	0.112*	400	0.216
2	0.224*	473.2	0.211
3	0.335	500	0.210
4	0.444	573.2	0.207
5	0.551	600	0.207
6	0.653	673.2	0.208
7	0.750	700	0.209
8	0.839	773.2	0.213
9	0.918	800	0.216
10	0.988	873.2	0.223
11	1.05	900	0.226
12	1.09	973.2	0.234
13	1.13	1000	0.237
14	1.15	1073.2	0.246
15	1.16	1100	0.249
16	1.16	1173.2	0.257
18	1.13	1200	0.260
20	1.08	1273.2	0.267
25	0.906	1300	0.270
30	0.761	1373.2	0.277
35	0.663	1400	0.279
40	0.590	1473.2	0.286
45	0.538	1500	0.288
50	0.497	1573.2	0.295
60	0.442	1600	0.297
70	0.402	1673.2	0.303
80	0.374	1700	0.306
90	0.350	1773.2	0.312
100	0.332	1800	0.314
123.2	0.302	1873.2	0.320
150	0.278*	1900	0.322
173.2	0.265*	1973.2	0.328
200	0.252*	2000	0.330
223.2	0.245*		
250	0.237*		
273.2	0.232*		
300	0.227		
323.2	0.224		
350	0.221		

* Extrapolated or interpolated.

THERMAL CONDUCTIVITY OF ACTINIUM, AMERICIUM, ASTATINE, BERKELIUM,
CALIFORNIUM, CURIUM, EINSTEINIUM, FERMIUM, FRANCIUM, LAWRENCIUM,
MENDELEVIUM, NOBELIUM, POLONIUM, PROTACTINIUM, ELEMENT 104,
ELEMENT 105, ELEMENT 106, AND ELEMENT 118

No information is available in the literature for the thermal conductivity of these elements. Very rough estimations of their thermal conductivity values at 300 K have been made and they are given below. For details of the estimations, the reader is referred to the comprehensive volume [1]. The values are very uncertain and are probably good to $\pm 50\%$.

Thermal Conductivity at 300 K
(W cm⁻¹ K⁻¹)

Actinium	0.12
Americium	0.1
Astatine	0.017
Berkelium	0.1
Californium	0.1
Curium	0.1
Einsteinium	0.1
Fermium	0.1
Francium	0.15
Lawrencium	0.1
Mendelevium	0.1
Nobelium	0.1
Polonium	0.20
Protactinium	0.47
Element 104	0.23
Element 105	0.58
Element 106	1.9
Element 118	2.3 x 10 ⁻⁵ (in the gaseous state; N. B. P. 262.5 K)

4. Acknowledgments

This work is primarily the result of financial support and interest of the Office of Standard Reference Data of the National Bureau of Standards. The support of the extensive documentary work necessary for its preparation was made possible through the support received from the Air Force Materials Laboratory of the Air Force Systems Command.

While the preparation and continued maintenance of his work is the responsibility of TPRC's Data Tables Division, the work would not have been possible without the direct input of TPRC's Scientific Documentation Division and, to a lesser degree, the Theoretical and Experimental Research Divisions. It should also be clearly understood, however, that many have contributed over the years within and outside of TPRC, and their contributions are hereby acknowledged.

In order to give a greater degree of confidence to the recommendations set forth in this work, preliminary sections of the comprehensive volume have been submitted to some 70 international experts in this field for their comments and critique. The authors wish to express their appreciation and gratitude to all who responded. Particular acknowledgment is made for the valuable contributions made by the following individuals:

- Dr. A. R. Adams, University of Surrey, London, England.
- Dr. N. Bäcklund, The Royal Institute of Technology, Stockholm, Sweden.
- Dr. R. Berman, University of Oxford, Oxford, England.
- Prof. C. F. Bonilla, Columbia University, New York, New York.
- Dr. R. I. Boughton, The Ohio State University, Columbus Ohio.
- Dr. A. Cezairliyan, National Bureau of Standards, Washington, D. C.
- Dr. L. J. Challis, University of Nottingham, Nottingham, England.
- Dr. J. G. Cook, National Research Council, Ottawa, Canada.
- Dr. M. J. Duggin, CSIRO, National Standards Laboratory, Chippendale, N.S.W., Australia.
- Prof. L. P. Filippov, Moscow State University, Moscow, U.S.S.R.
- Mr. D. R. Flynn, National Bureau of Standards, Washington, D.C.
- Prof. A. V. Grosse, Research Institute of Temple University, Philadelphia, Pennsylvania.
- Dr. H. J. Hanley, National Bureau of Standards, Boulder, Colorado.
- Dr. M. G. Holland, Raytheon Company, Waltham, Massachusetts.
- Prof. J. J. Jackson, Howard University, Washington, D.C.
- Dr. D. T. Jamieson, National Engineering Laboratory, Glasgow, Scotland.
- Dr. J. Kaspar, Aerospace Corporation, El Segundo, California.
- Dr. B. T. Kelly, United Kingdom Atomic Energy Authority, Reactor Materials Laboratory, Warrington, Lancs, England.
- Prof. J. Kestin, Brown University, Providence, Rhode Island.
- Dr. P. G. Klemens, The University of Connecticut, Storrs, Connecticut.
- Dr. M. J. Laubitz, National Research Council, Ottawa, Canada.
- Prof. S. Legvold, Iowa State University, Ames, Iowa.
- Dr. W. W. Lozier, Union Carbide Corporation, Cleveland, Ohio.
- Prof. A. V. Luikov, Heat and Mass Transfer Institute, Minsk, U.S.S.R.
- Mr. I. B. Mason, Atomic Energy Research Establishment, Harwell, England.
- Mr. J. D. McClelland, Aerospace Corporation, El Segundo, California.
- Dr. D. L. McElroy, Oak Ridge National Laboratory, Oak Ridge, Tennessee.
- Dr. E. McLaughlin, Imperial College, London, England (now at Louisiana State University, Baton Rouge, Louisiana).
- Prof. G. T. Meaden, Dalhousie University, Halifax, Nova Scotia, Canada.
- Prof. A. Missenard, Société Française des Thermiciens, Paris, France.
- Mr. J. P. Moore, Oak Ridge National Laboratory, Oak Ridge, Tennessee.
- Dr. Ya. M. Naziev, Esman Baku Institute of Power Engineering, Baku, Azerbaidzhan S.S.R., U.S.S.R.
- Dr. H. Poltz, Physikalisch-Technische Bundesanstalt, Braunschweig, West Germany.
- Dr. R. L. Powell, National Bureau of Standards, Boulder, Colorado.
- Dr. F. Richter, Thyssen Röhrenwerke Aktiengesellschaft, Düsseldorf, West Germany.
- Prof. B. H. Sage, California Institute of Technology, Pasadena, California.
- Prof. G. Samsonov, Institute of Problems of Material Science, Kiev, U.S.S.R.
- Dr. N. H. Saunders, University College of Swansea, Swansea, Wales.
- Dr. J. T. Schriempf, Naval Research Laboratory, Washington, D.C.
- Prof. A. E. Sheindlin, Institute of High Temperature, Moscow, U.S.S.R.
- Prof. E. E. Shpil'rain, Institute of High Temperature, Moscow, U.S.S.R.
- Dr. G. A. Slack, General Electric Research Laboratory, Schenectady, New York.
- Dr. I. A. Smirnov, Institute of Semiconductors, Leningrad, U.S.S.R.

Prof. N. B. Vargaftik, Moskovskii Aviatsionnyi Institut, Moscow, U.S.S.R.

Dr. P. Wagner, University of California, Los Alamos Scientific Laboratory, Los Alamos, New Mexico.

Dr. G. K. White, CSIRO, National Standards Laboratory, Chippendale, N.S.W., Australia.

Prof. S. B. Woods, University of Alberta, Edmonton, Alberta, Canada.

Prof. M. Yaqub, The Ohio State University, Columbus, Ohio.

It goes without saying that while the individuals

mentioned above have read selected parts of the preliminary version of this work and have given helpful comments and criticisms, this in no way commits them to the views and judgments expressed in this work for which the authors assume complete responsibility. In this connection, C. Y. Ho and R. W. Powell have jointly performed the analysis of the data for the elements which are solid at normal temperature and pressure (N.T.P.) and P. E. Liley has performed the analysis for those elements which are in the liquid or gaseous state at N.T.P.

5. References

- [1] Ho, C. Y., Powell, R. W., and Liley, P. E., Thermal Conductivity of the Elements, Supplementary Volume of the Journal of Physical and Chemical Reference Data (to be published in 1972).
- [2] Bloch, F., On the Quantum Mechanics of Electrons in Crystal-line Lattice, *Z. Physik*, **52**, 555-600, 1928.
- [3] Wilson, A. H., The Second Order Electrical Effects in Metals, *Proc. Camb. Phil. Soc.*, **33**(2), 371-9, 1937.
- [4] Makinson, R. E. B., The Thermal Conductivity of Metals, *Proc. Camb. Phil. Soc.*, **34**(3), 474-97, 1938.
- [5] Kroll, W., On the Theory of Heat Conduction, *Sci. Papers Inst. Phys. Chem. Res. Tokyo*, **34**(756), 194-6, 1938.
- [6] Kohler, M., Treatment of the Nonequilibrium Process with the Aid of Extreme Principle, *Z. Physik*, **124**, 772-89, 1948.
- [7] Kohler, M., Transport Phenomena in Electron Gas, *Z. Physik*, **125**, 679-93, 1949.
- [8] Umeda, K. and Yamamoto, T., Kroll's Expression for the Heat Resistance of the Monovalent Metals, *J. Fac. Sci. Hokkaido Univ.*, **2**, 3, 249-54, 1949.
- [9] Sondheimer, E. H., The Theory of the Transport Phenomena in Metals, *Proc. Roy. Soc. (London)*, **A203**(1072), 75-98, 1950.
- [10] Sondheimer, E. H., A Note on the Theory of Conduction in Metals, *Proc. Phys. Soc. (London)*, **A65**, 561-2, 1952.
- [11] Sondheimer, E. H., The Thermal Conductivity of Metals at Low Temperatures, *Proc. Phys. Soc. (London)*, **A65**, 562-4, 1952.
- [12] Ziman, J. M., The Electrical and Thermal Conductivities of Monovalent Metals, *Proc. Roy. Soc. (London)*, **A226**, 436-54, 1954.
- [13] Klemens, P. G., The Thermal Conductivity of Monovalent Metals, *Proc. Phys. Soc. (London)*, **A67**, 194-6, 1954.
- [14] Cezairliyan, A., Prediction of Thermal Conductivity of Metallic Elements and Their Dilute Alloys at Cryogenic Temperatures, *Purdue Univ., TPRC Rept. 14*, 1-140, 1962; U.S. Air Force Rept. ASD-TDR-63-291, 1-140, 1963.
- [15] Cezairliyan, A. and Touloukian, Y. S., Generalization and Calculation of the Thermal Conductivity of Metals by Means of the Law of Corresponding States, *Teplofiz. Vys. Temp.*, **3**(1), 75-85, 1965; English Translation: *High Temperature*, **3**(1), 63-75, 1965.
- [16] Cezairliyan, A. and Touloukian, Y. S., Correlation and Prediction of Thermal Conductivity of Metals through the Application of the Principle of Corresponding States, in *Advances in Thermophysical Properties at Extreme Temperatures and Pressures*, 3rd Symposium on Thermophysical Properties, A.S.M.E., 301-13, 1965.
- [17] Herring, C., Simple Property of Electron-Electron Collisions in Transition Metals, *Phys. Rev. Letters*, **19**(4), 167-8, 1967; Errata, **19**(11), 684, 1967.
- [18] Rice, M. J., Itinerant Electron Correlation and the Ideal Lorenz Number of Transition Metals, *Phys. Letters*, **26A**(2), 86-7, 1967.
- [19] Schriempf, J. T., Three-term Analysis of the Ideal Thermal and Electrical Resistivities of Transition Metals, *Phys. Rev. Lett.*, **20**(19), 1034-6, 1968.
- [20] Casimir, H. B. G., Note on the Conduction of Heat in Crystals, *Physica*, **5**(6), 495-500, 1938.
- [21] Olsen, J. L. and Wyder, P., A Direct Comparison of the Mean Free Paths for Electrical and Thermal Conduction in Indium at Low Temperatures, in *Proceedings of the Seventh International Conference on Low Temperature Physics (Toronto, 1960)*, 266-7, 1961.
- [22] Boughton, R. I. and Yaqub, M., Size Effect in the Electronic Thermal Conductivity of Gallium Single Crystals, *Phys. Rev. Letters*, **20**(3), 108-10, 1968.
- [23] Geballe, T. H. and Hull, G. W., Isotopic and Other Types of Thermal Resistance in Germanium, *Phys. Rev.*, **2**, **110**(3), 773-5, 1958.
- [24] Oskotskii, V. S., Pogarskii, A. M., Timchenko, I. N., and Shalyt, S. S., Effect of Isotope Content on Lattice Thermal Conductivity and Thermoelectromotive Force of Tellurium, *Fiz. Tverd. Tela*, **10**(11), 3247-53, 1968; English Translation: *Soviet Physics-Solid State*, **10**(11), 2569-73, 1969.
- [25] Berman, R., Bounds, C. L., and Rogers, S. J., The Effect of Isotopes on Lattice Heat Conduction. II. Solid Helium, *Proc. Roy. Soc. (London)*, **A289**(1416), 66-80, 1965.
- [26] Berman, R., Foster, E. L., and Ziman, J. M., The Thermal Conductivity of Dielectric Crystals: The Effect of Isotopes, *Proc. Roy. Soc. (London)*, **A237**, 344-54, 1956.
- [27] Wilson, A. H., *The Theory of Metals*, 2nd Edition (Cambridge University Press, London, 1953).
- [28] Voigt, W., *Lehrbuch der Kristallphysik* (Teubner, Leipzig, 1928).
- [29] Hall, P. M., Legvold, S., and Spedding, F. H., Electrical Resistivity of Yttrium Single Crystals, *Phys. Rev.*, **116**(6), 1446-7, 1959.
- [30] Hashin, Z. and Shtrikman, S., Conductivity of Polycrystals, *Phys. Rev.*, **130**(1), 129-33, 1963.
- [31] Grosse, A. V., Thermal Conductivity of Liquid Metals over the Entire Liquid Range, i.e., from the Melting Point to Critical Point, in *Relation to Their Electrical Conductivities and the Fallacy of Dividing Metals into "Normal" and "Abnormal" Thermally Conducting Ones*, The Research Institute of Temple University, Philadelphia, Pa., 1-71, 1965.
- [32] Grosse, A. V., Electrical and Thermal Conductivities of Metals over Their Entire Liquid Range, i.e., from Melting Point to Critical Point and the Containment of Metallic Substances

- up to 5000 K for Substantial Periods of Time, *Rev. Intern. Hautes Temp. Réfractaires*, **3**(2), 115-46, 1966.
- [33] Grosse, A. V., Simple Relationship between Electrical Conductivity of Liquid Metals and Temperature over Their Entire Liquid Temperature Range, i.e., from the Melting Point to the Critical Point, The Research Institute of Temple University, Philadelphia, Pa., 1-40, 1964.
- [34] Powell, R. W., Correlations of Metallic Thermal and Electrical Conductivities for both Solid and Liquid Phases, *Intern. J. Heat Mass Transfer*, **8**(7), 1033-45, 1965.
- [35] Filippov, L. P., Liquid Thermal Conductivity Research at Moscow University, *Intern. J. Heat Mass Transfer*, **11**(2), 331-45, 1968.
- [36] Mardykin, I. P. and Filippov, L. P., Thermal Properties of Liquid Metals. I. Copper, Antimony, *Fiz. Khim. Obrab. Mater.*, **1**, 110-2, 1968.
- [37] Yurchak, R. P. and Smirnov, B. P., Thermal Conductivity and Lorenz Number of Solid and Liquid Gallium, *Fiz. Tverd. Tela*, **10**(5), 1340-2, 1968; English Translation: *Soviet Phys.-Solid State*, **10**(5), 1065-6, 1968.
- [38] Owens, E. J. and Thodos, G., Thermal-Conductivity-Reduced-State Correlation for the Inert Gases, *AIChE Journal*, **3**, 454-61, 1957.
- [39] Samsonov, G. V. (Editor), *Handbook of the Physicochemical Properties of the Elements* (IFI/Plenum Data Corp., New York, 1968).
- [40] Chirkin, V. S., *Thermal Conductivity of Industrial Materials*, Mashgiz, 1962; see Ref. 39, p. 277.