

RI 9557

REPORT OF INVESTIGATIONS/1995

Extraction of Titanium and Iron From Ilmenite With Fluosilicic Acid

UNITED STATES DEPARTMENT OF THE INTERIOR



UNITED STATES BUREAU OF MINES



U.S. Department of the Interior
Mission Statement

As the Nation's principal conservation agency, the Department of the Interior has responsibility for most of our nationally-owned public lands and natural resources. This includes fostering sound use of our land and water resources; protecting our fish, wildlife, and biological diversity; preserving the environmental and cultural values of our national parks and historical places; and providing for the enjoyment of life through outdoor recreation. The Department assesses our energy and mineral resources and works to ensure that their development is in the best interests of all our people by encouraging stewardship and citizen participation in their care. The Department also has a major responsibility for American Indian reservation communities and for people who live in island territories under U.S. administration.

Report of Investigations 9557

Extraction of Titanium and Iron From Ilmenite With Fluosilicic Acid

By Dennis A. Hansen, Davis E. Traut, and G. Tim Fisher II

**UNITED STATES DEPARTMENT OF THE INTERIOR
Bruce Babbitt, Secretary**

**BUREAU OF MINES
Rhea Lydia Graham, Director**

International Standard Serial Number
ISSN 1066-5552

CONTENTS

	<i>Page</i>
Abstract	1
Introduction	2
Materials	2
Equipment	2
Procedure	3
Results	3
Effect of temperature	3
Effect of H_2SiF_6 concentration	4
Effect of particle size	4
Conclusions	5
References	5

ILLUSTRATIONS

1. Titanium extraction as a function of time and temperature at 2.6M H_2SiF_6 concentration	4
2. Effect of temperature on leach rate using ash diffusion model for Ti	4
3. Titanium extraction as a function of time and H_2SiF_6 concentration at 85 °C	4
4. Effect of H_2SiF_6 concentration on leach rate using ash diffusion model for Ti	4
5. Titanium extraction as a function of time and particle size at 2.6M H_2SiF_6 concentration at 65 °C	5
6. Effect of particle size on leach rate using ash diffusion model for Ti	5

TABLES

1. Chemical analysis of New York rock ilmenite.	2
2. Chemical analysis of as-received 2.6M H_2SiF_6	2

UNIT OF MEASURE ABBREVIATIONS USED IN THIS REPORT

g/L gram per liter

mL milliliter

h hour

Mt million metric tons

K kelvin

wt % weight percent

L liter

μm micrometer

M molar concentration

$^{\circ}\text{C}$ degree Celsius

min minute

Extraction of Titanium and Iron From Ilmenite With Fluosilicic Acid

By Dennis A. Hansen,¹ Davis E. Traut,² and G. Tim Fisher II³

ABSTRACT

As part of a U.S. Bureau of Mines program to develop a more continuous titanium metal extraction process that uses domestic resources, a study was made to determine the extraction of titanium (Ti) and iron (Fe) from New York rock ilmenite using fluosilicic acid (H_2SiF_6). The effects of leach temperature, acid concentration, and particle size were investigated for the rate at which Ti and Fe are extracted from the ilmenite. Within the leach time studied, the extraction data fit a shrinking-core model; the rate-controlling step was diffusion of H_2SiF_6 through an ash layer resulting from a heterogeneous leaching reaction. The rate is linearly dependent on the H_2SiF_6 concentration and is inversely proportional to the square of the particle diameter. Using 2.6M H_2SiF_6 at 85 °C, 49% of the Ti and 53% of the Fe in 44- to 74- μm New York rock ilmenite were extracted in 3 h.

¹Chemical engineer.

²Supervisory chemical engineer.

³Métallurgist.

Albany Research Center, U.S. Bureau of Mines, Albany OR.

INTRODUCTION

In support of its mission to help ensure that an appropriate share of the Nation's domestic resources are being used in the production of minerals, the U.S. Bureau of Mines (USBM) has investigated a fluoride leaching route to produce Ti metal starting with ilmenite (FeTiO_3) as a raw material (1-2).⁴ Part of that investigation is the study of Ti extraction by acid leaching from ilmenite. Of the major Ti-bearing ores in the United States (ilmenite, rutile, and perovskite), ilmenite represents the largest resource of Ti, an estimated 7.2 Mt of contained Ti in reserves with an additional 14.1 Mt of contained Ti in the reserve base (3). A process to manufacture pure Ti metal that would utilize lower grade, less costly, and more readily available raw materials, such as ilmenite, has long been sought.

A number of methods have been proposed for extracting Ti values from ilmenite or other Ti ores with various fluoride compounds.

These fluoride compounds include hydrofluoric acid (HF) (4-13), fluosilicic acid (H_2SiF_6) (13), HF gas (14-15), alkali fluosilicates (16-23), ammonium fluoride (NH_4F) (8, 24-25), ammonium bifluoride (NH_4HF_2) (26), alkali double fluorides (8, 16, 18, 27), calcium fluoride (CaF_2) with sulfuric acid (H_2SO_4) (18, 28), CaF_2 with ferric chloride (FeCl_3) or hydrochloric acid (HCl) (29), and ferric fluoride (FeF_3) (30). Fluosilicic acid (H_2SiF_6) was chosen for study because it is a relatively low-cost byproduct of fertilizer manufacture and thus may offer an economic advantage over other fluorides. Previous H_2SiF_6 studies (13) do not provide information concerning the effects of various leaching conditions on Ti and Fe extraction. Therefore, the objective of this research was to correlate Ti and Fe extraction data with a kinetic model such that equipment and conditions might be designed to maximize the extraction of Ti and Fe from ilmenite using H_2SiF_6 .

MATERIALS

A rock-type ilmenite from Tahawus, NY, was used for all leaching tests. About 34% (2.4 Mt of contained Ti) of the U.S. Ti reserves are of this type, and the remainder are ancient beach sand deposits (3). This material was an ilmenite concentrate obtained from a massive deposit of primary ilmenite-magnetite minerals in rock containing anorthosite and gabbro (31). A mineralogical examination indicated the presence of approximately 96% FeTiO_3 , 2% spinel, 1% garnet, and 1% miscellaneous minerals, including quartz and feldspar. The chemical analysis of the rock ilmenite is shown in table 1 and indicates 27.7 wt% Ti and 35.2 wt% Fe.

The H_2SiF_6 used was reagent grade, and the chemical analysis is shown in table 2. The maximum concentration of H_2SiF_6 used in this study was 2.6M since that concentration is the commercially available reagent grade and is greater than the 2.0M H_2SiF_6 available as byproduct.

Table 1.—Chemical analysis of New York rock ilmenite

Element	Wt %
Fe	35.2
Ti	27.7
Mg	1.4
Si	0.6
F	0.3
Mn	0.3
C	0.2
Ca	0.2

Table 2.—Chemical analysis of as-received
2.6M H_2SiF_6

Element	g/L
F	261
Si	70.0
Cl	0.20
Ti	0.02
Fe	0.02

EQUIPMENT

A 400-mL tetrafluoroethylene (TFE) beaker placed in a 2-L water bath was used as the batch reactor to avoid possible problems with leaching of silica from glass by the H_2SiF_6 . The beaker was partially covered by a TFE watchglass during the experiment. The water bath was heated by a hotplate to reach

and maintain the desired temperature ($\pm 1^\circ\text{C}$). The temperatures of the H_2SiF_6 -ilmenite slurry and the surrounding water bath were monitored using a digital thermometer. Other equipment was either polyethylene or polypropylene to avoid corrosion and contamination problems.

⁴Italic numbers in parentheses refer to items in the list of references at the end of this report.

PROCEDURE

Three test series were used to independently investigate the effects of the three leach variables chosen. One series investigated temperatures of 45, 65, and 85 °C. Another series determined the effects of H₂SiF₆ concentrations using 0.65M, 1.30M, and 2.60M H₂SiF₆. The last series investigated the effect of initial ilmenite particle size using 20- to 38- μ m- and 44- to 74- μ m-diameter particles. A low pulp density (1.6%) was used during the experiments for three reasons: (1) to maintain a constant H₂SiF₆ concentration during leaching, (2) to act as a heat sink, which would minimize any temperature rise from this exothermic leach and maintain isothermal conditions, and (3) to maximize Ti and Fe extraction and solubility. The slurry was stirred vigorously throughout the test. After the


ilmenite was added, 5-mL liquid samples were taken at specified time intervals. Each test was replicated. Sampling schedules were varied for the otherwise identical tests to check the reliability of test data and to add additional data points.

Leaching progress was followed by analysis for Ti and Fe in the extracted samples. Titanium was analyzed by inductively coupled plasma spectrophotometry, and Fe was analyzed by atomic absorption spectrophotometry. Initial material and final residue analyses for both Ti and Fe were done by a volumetric method. Scanning electron microscope (SEM) photographs were obtained by first coating the cross-sectioned leached ilmenite with gold to enhance the surface deformation.

]

RESULTS

The reaction of ilmenite with H₂SiF₆ is a heterogeneous reaction; therefore the shrinking-core model (32) was assumed. The shrinking-core model states that the reaction rate is controlled by one of three steps that occur in series: diffusion of H₂SiF₆ through a film surrounding the particle, diffusion of H₂SiF₆ through an "ash" layer, and chemical reaction on the surface of the unreacted core. Indication of the diffusion control was provided by the SEM, which showed a rough surface on the particle after a H₂SiF₆ leach. Analysis of the rinsed particles showed an Si-containing substance, probably silica (SiO₂), present in this ash layer. A possible chemical equation for the reaction is



The ash layer slows the reaction because the diffusion-rate-controlling step is slower than the chemical reaction step. An earlier study indicated that HF leaching of ilmenite was controlled by the chemical reaction step (12). SEM photographs of those rinsed particles showed a smooth surface after an HF leach of the particles. The equation for the ash diffusion model (32, p. 51.2) is

$$1 - 3(1 - \alpha)^{2/3} + 2(1 - \alpha) = Kt \quad (2)$$

where α = fractional amount of element leached,

$$K = \text{overall rate constant, min}^{-1},$$

and t = time, min.

K is linearly dependent on acid concentration and inversely dependent on the square of the particle diameter:


$$K \propto C/(D^2). \quad (3)$$

EFFECT OF TEMPERATURE

The effect of temperature on Ti and Fe extraction was investigated using 2.60M H₂SiF₆ solution with the 44- to 74- μ m size fraction of New York rock ilmenite. The temperatures used were 45, 65, and 85 °C. Preliminary tests showed that 25 °C was too low to obtain usable data, and at temperatures greater than 85 °C, the test results were affected by loss of H₂SiF₆ vapor.


Figure 1 shows that when the concentration of extractant remains constant, the rate of leaching of Ti increases with temperature. At 45 °C, the leach took 180 min to extract 2% of the Ti. At 85 °C, the Ti extracted increased to 49%. The rates of Ti extraction are shown in figure 2 using equation 2. Similar results were observed for Fe. Within the leach time studied, the ash diffusion does not control the reaction kinetics in the beginning stages, when some other resistance or combination of resistances must be controlling. Eventually though, the controlling mechanism shifts to ash diffusion (32). The reason for this is that the particle starts with no ash layer, hence no resistance to ash diffusion. The straight lines in figure 2 were drawn from the method of least squares using the linear range of the data. The slope of the lines is K (the overall rate constant).

Figure 1

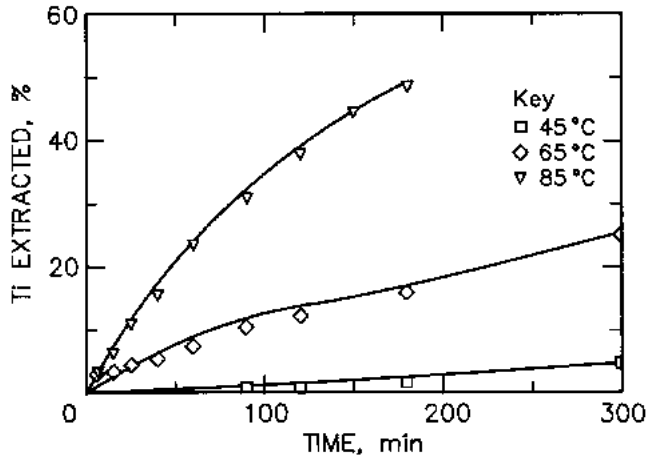

Titanium extraction as a function of time and temperature at 2.6M H_2SiF_6 concentration.

Figure 2

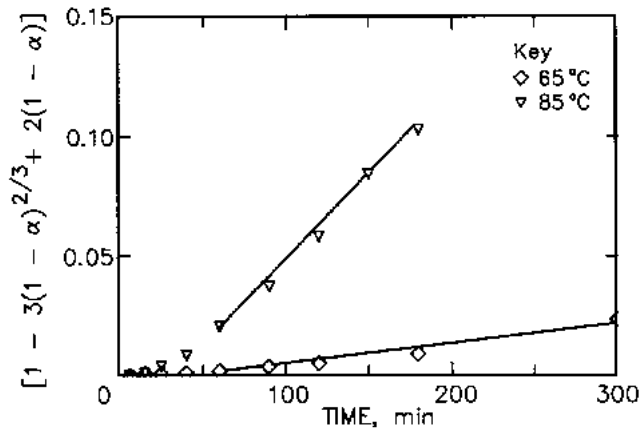


Effect of temperature on leach rate using ash diffusion model for Ti.

EFFECT OF H_2SiF_6 CONCENTRATION


The effect of H_2SiF_6 concentration on Ti and Fe extraction was investigated using constant conditions of 85 °C with the 44- to 74- μm size fraction New York ilmenite. The H_2SiF_6 concentrations used were 0.65M, 1.30M, and 2.60M. The percent of Ti extracted is shown in figure 3. The effect of H_2SiF_6 concentration on Ti extraction is apparent. Using 0.65M H_2SiF_6 , the leach took 180 min to extract just 23% of the Ti. Using 2.60M H_2SiF_6 , the extraction increased to 49% during the same contact time. In each of the three curves, extraction increased over time and did not level off at the end of the sampling times. Figure 4 shows the rates of Ti extraction using equation 2. Similar results were observed for Fe. Within the

Figure 3

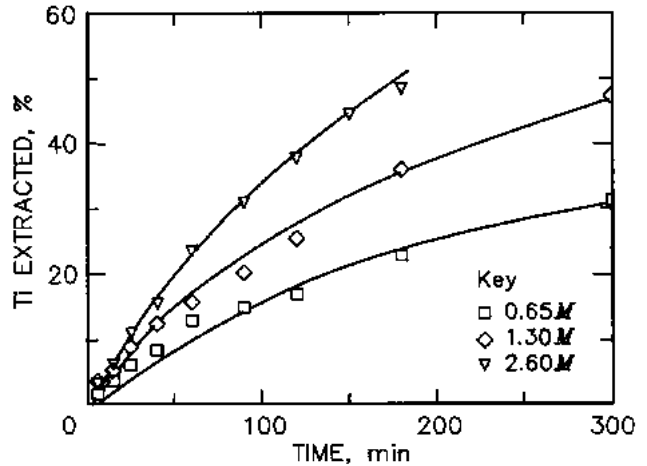

Titanium extraction as a function of time and H_2SiF_6 concentration at 85 °C.

Figure 4

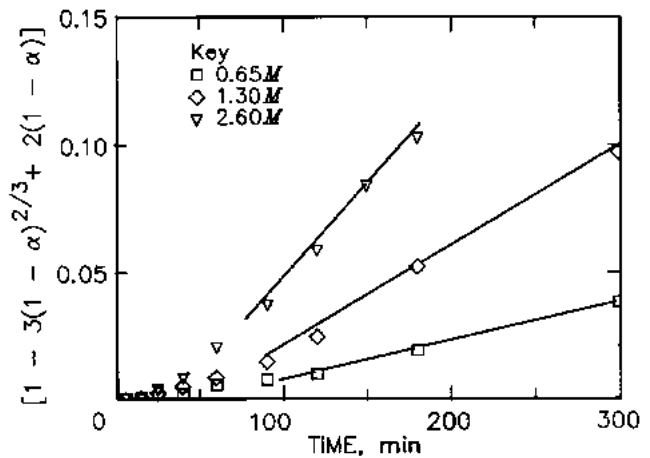


Effect of H_2SiF_6 concentration on leach rate using ash diffusion model for Ti.

leach time studied, the reaction kinetics were similar to those of the temperature data because ash diffusion does not control the reaction kinetics until a later stage. Equation 3 states that K should be linearly dependent on the H_2SiF_6 concentration. A simple plot showed this to be true for both Ti and Fe using the experimental data.

EFFECT OF PARTICLE SIZE

The effect of ilmenite particle size on Ti and Fe extraction was investigated using 2.6M H_2SiF_6 solutions at 65 °C. Two discrete initial particle size ranges were used, 20 to 38 μm and 44 to 74 μm , as they represented most of the ilmenite material.


Figure 5

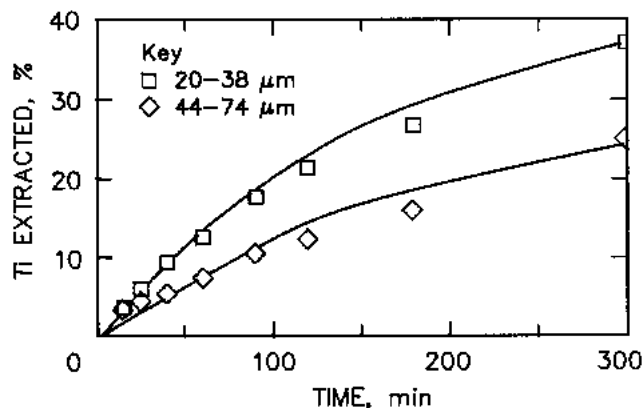

Titanium extraction as a function of time and particle size at 2.6M H_2SiF_6 concentration at 65 °C.

The percent of Ti extracted is shown in figure 5. The effect of particle size on Ti extraction is apparent. With the 44- to 74- μm particle size, 25% of the Ti was extracted in 300 min, and with the smaller, 20- to 38- μm particle size, 37% of the Ti was extracted. Using equation 2, the rates of Ti extraction are shown in figure 6. Similar results were observed for Fe.

Figure 6

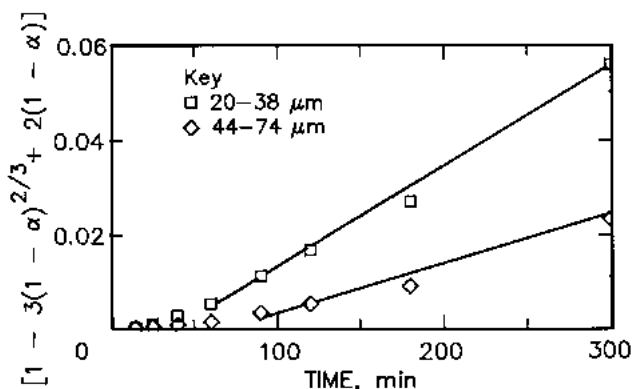

Effect of particle size on leach rate using ash diffusion model for Ti.

Within the leach time studied, ash diffusion control did not begin right away but the ash diffusion step did eventually control the extraction rate. The overall rate constant K should be dependent on the inverse of the square of the particle size according to equation 3. A simple plot shows this relationship to be true for both Ti and Fe using the experimental data.

CONCLUSIONS

The USBM has investigated the effects of leach temperature, acid concentration, and particle size on the extraction of Ti and Fe from New York rock ilmenite using H_2SiF_6 . Within the leach time studied, the data fit a shrinking-core model, with the rate eventually controlled by the ash diffusion step. The diffusion is a result of an ash layer developing around the unreacted core. This diffusion control rate is slower than the

chemical reaction control rate. The reaction might proceed faster, therefore, if the ash layer could be continually removed from the reacting particle by leaching in an apparatus such as an attrition mill. The rate is linearly dependent on the H_2SiF_6 concentration and is inversely proportional to the square of the particle diameter.

REFERENCES⁵

1. Traut, D. E. Induction Slag Reduction Process for Making Titanium. U.S. Pat. 4,985,069, Jan. 15, 1991.
2. Traut, D. E., D. A. Hansen, and J. I. Paige. Calcium Fluorotitanate-Induction-Slag Furnace Route to Titanium Metal. Paper in Sixth World Conference on Titanium, ed. by Lacombe, P., Tricot, R., and Beranger, G. (Proc. Conf. Cannes, France, June 6-9, 1988). Societe Francaise de Metallurgie, Les Ulis Ceclax, France, 1988, pp. 679-684.
3. Lynd, L. E. Titanium. Ch. in Mineral Facts and Problems, 1985 Edition. USBM Bull. 675, 1985, pp. 859-879.
4. Kawecki, H. C., and E. J. Bielecki. Production of Potassium Titanium Fluoride. U.S. Pat. 2,568,341, Sept. 18, 1951.
5. Kamlet, J. Titanium-Aluminum Alloys. U.S. Pat. 2,781,261, Feb. 12, 1957.
6. Jackson, R. B., D. H. Kelley, and R. V. Townsend. Anhydrous Titanium Tetrafluoride. U.S. Pat. 2,900,234, Aug. 18, 1959.
7. Peskin, B., G. Neshor, Z. Pessachovitz, K. M. Michael, H. Bernstein, S. Havel, and H. Klein. Verfahren zur Herstellung von Fluotitansaure und Hexafluotitanaten (Method for the Manufacture of Fluorotitanic Acid and Hexafluorotitanates). Ger. Pat. 1,222,026, Aug. 4, 1966.
8. Chemical and Phosphates, Ltd. Process for the Production of Fluotitanic Acid and of Fluotitanates. Brit. Pat. 1,044,025, Sept. 28, 1966.
9. Nagasubramanian, K., and K. J. Liu. Recovery of TiO_2 From Ilmenite-Type Ore Using an Organophosphoric Acid Extractant for Impurity Iron Removal. U.S. Pat. 4,168,297, Sept. 18, 1979.
10. Plakhotnik, V. N., I. L. Gulivets, and N. V. Krivenko. Sposob Polucheniya Geksaftortitanata Kaliya (Potassium Hexafluorotitanate). U.S.S.R. Pat. 819,062, Apr. 7, 1981.

⁵A title enclosed in parentheses is a translation from the language in which the work was published.

11. Biswas, R. K., and M. G. K. Mondal. A Study on the Dissolution of Ilmenite Sand. *Hydrometallurgy*, v. 17, No. 3, Mar. 1987, pp. 385-390.
12. Hansen, D. A., and D. E. Traut. The Kinetics of Leaching Rock Ilmenite With Hydrofluoric Acid. *JOM*, v. 41, No. 5, May 1989, pp. 34-36.
13. Spijker, R. Low-Temperature Process for the Preparation of Alkali Metal Fluorotitanates. *Eur. Pat. Appl. EP 209,760*, Jan. 28, 1987.
14. Lapin, P. V., K. Y. Mukhamedzhanov, A. I. Solov'ev, V. V. Bordunov, and V. V. Khmelev. *Fiziko-Tekhnicheskii Fakul'tet: Issledovanie Protsessa Ftorirovaniya Il'menita (Study of the Fluorination of Ilmenite)*. *Sb. Annot. Nauchno-Issled. Rab.-Tomsk. Politekh. Inst.*, v. 6, 1975, p. 40.
15. Lapin, P. V., K. Y. Mukhamedzhanov, and V. N. Gofman. *Fiziko Tekhnicheskii Fakul'tet: Issledovanie Protsessa Ftorirovaniya Il'menitovogo Kontsentrata Elementarnym Ftorom (Study of the Fluorination of an Ilmenite Concentrate With Elemental Fluorine)*. *Sb. Annot. Nauchno-Issled. Rab.-Tomsk. Politekh. Inst.*, v. 6, 1975, p. 41.
16. Kawecki, H. C. Ore Treatment Process. U.S. Pat. 2,418,074, Mar. 25, 1947.
17. _____. Production of Alkali Metal Fluorotitanates and Fluorozirconates. U.S. Pat. 2,653,855, Sept. 29, 1953.
18. Horizons Titanium Corp. Improved Preparation of Double Alkali Metal Titanium Fluorides. *Brit. Pat. 729,845*, May 11, 1982.
19. Aotani, K. (Preparation of Sodium Fluorotitanate). *Kogyo Kagaku Zasshi*, v. 62, 1959, pp. 1368-1370.
20. Hard, R. A., and M. A. Prieto. Process To Make Titanium Oxide From Titanium Ore. U.S. Pat. 4,359,449, Nov. 16, 1982.
21. Hard, R. A., and M. A. Prieto. Process To Make Titanium Oxide From Titanium Ore. U.S. Pat. 4,390,365, June 28, 1983.
22. Megy, J. A. Process To Make Titanium From Titanium Ore. U.S. Pat. 4,468,248, Aug. 28, 1984.
23. Hard, R. A., and J. A. Megy. Process To Make Titanium, Zirconium, and Hafnium Based Metal Particles for Powder Metallurgy. U.S. Pat. 4,470,847, Sept. 11, 1984.
24. Mayer, P. E. Treatment of Titanium-Bearing Materials. U.S. Pat. 2,288,727, July 7, 1943.
25. Mathew, P. M. Recovering Titanium Values From Ores. *Indian Pat. 120,269*, Apr. 24, 1971.
26. Kawecki, H. C. Production of Potassium Titanium Fluoride. U.S. Pat. 2,577,130, Dec. 4, 1951.
27. _____. Ore Treatment Process. U.S. Pat. 2,418,073, Mar. 25, 1947.
28. _____. Production of Potassium Titanium Fluoride. U.S. Pat. 2,375,287, July 5, 1949.
29. McLaughlin, R. J. W. Mineral Treatment. *Aust. Pat. 501,893*, July 5, 1979.
30. Moss, J. H., and B. Leng. Production of Titanium Tetrahalide. U.S. Pat. 3,395,531, Dec. 9, 1975.
31. Elger, G. W., J. B. Wright, J. E. Tress, H. E. Bell, and R. R. Jordon. Producing Chlorination-Grade Feedstock From Domestic Ilmenite—Laboratory and Pilot Plant Studies. *USBM RI 9002*, 1986, pp. 4-5.
32. Levenspiel, O. *The Chemical Reactor Omnibook* *. OR State Univ., Corvallis, OR, 1984, ch. 51, 55.